

Exploiting the Efficacy of Tyro3 and Folate Receptors to Enhance the Delivery of Gold Nanoparticles into Colorectal Cancer Cells *In Vitro*

Nakul Nautam Patel (✉ Nakulpatel90@yahoo.com)

"Middlesex University" <https://orcid.org/0000-0002-0846-661X>

Lucy Ghali

"Middlesex University"

Ivan Roitt

Chelsea and Westminster Hospital NHS Foundation Trust

Leonardo Pantoja Munoz

"Middlesex University"

Richard Bayford

"Middlesex University"

Nano Express

Keywords: Folate, Tyro3, Colorectal cancer, Gold nanoparticles, internalisation, efficiency

Posted Date: November 5th, 2020

DOI: <https://doi.org/10.21203/rs.3.rs-101290/v1>

License:  This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

Version of Record: A version of this preprint was published at *Nanoscale Advances* on January 1st, 2021.
See the published version at <https://doi.org/10.1039/D1NA00318F>.

Abstract

Colorectal cancer (CRC) is the fourth most common cancer in the world. Due to its asymptomatic nature, CRC is diagnosed at an advanced stage where the survival rate is <5%. Besides, prognosis from CRC treatment using chemotherapy, radiotherapy and surgery often causes undesirable side-effects. As such, gold nanoparticles (GNPs) are envisaged in the field for the diagnosis and treatment of CRC. GNPs have unique physical, chemical and electrical properties at nanoscale which makes them suitable for application in biomedicine. However, for GNPs to become clinically effective, its internalisation efficiency in the cancer cells must be enhanced. Folate receptor- α (FR) are overexpressed in CRC wherein FR helps in uptake of folic acid within the cell. Tyro3, a novel tyrosine kinase receptor, drives cell proliferation and its overexpression is correlated with poor prognosis in CRC. Their upregulated expression in CRC cells relative to normal cells makes them an ideal target for GNPs using active targeting. Therefore, in this study receptors FR and Tyro3 were simultaneously targeted using specific antibody-coated GNPs in order to enhance uptake and internalisation of GNPs in CRC cells *in vitro*. Four different types of coated-GNPs were synthesised GNPs-PEG, GNPs-anti-FR, GNPs-anti-Tyro3 and GNPs-anti-(FR+Tyro3) and incubated (0ng – 50ng) with three CRC cell lines including CRL1790, CRL2159 and HCT116. Simultaneous targeting of these receptors by GNPs-anti-(FR+Tyro3) was found to be the most effective in internalisation in CRC cells compared with GNPs targeted singly to FR or Tyro3 ($p<0.05$). Besides this, results show that Tyro3 mediated similar internalisation efficacy as FR ($p<0.05$) in CRC using ICP-OES.

1. Introduction

Colorectal Cancer (CRC) ranks fourth in mortality and morbidity worldwide and is characterised by the formation of malignant neoplasms in the mucosa of the colon and rectum (1, 2). In CRC, early diagnosis and treatment is key to treating the disease as CRC remains asymptomatic and develops over the span of 10 years (3). Adjuvant chemo-radiotherapy and surgery are the only alternatives to treating CRC, but due to late diagnosis, not all patients respond to therapeutic regimes properly and, therefore, no one magic bullet can target CRC. Also, toxic side-effects associated with the treatment such as vomiting, diarrhoea, blood and hair loss, proteinuria etc. can have an overwhelming effect on a patient's routine life (4). Additionally, the results of the surgery too are not noteworthy as it relies on radiotherapy and chemotherapy for its success. Hence, the need to develop a personalised tailor-made therapy specific for CRC remains indispensable (5). To that end, nanotechnology is utilised in order to circumvent the above mentioned drawbacks.

Nanotechnology is evolving as a novel area in scientific research and has led to advances in the field of cancer therapy, drug delivery, biological sensors, microbiology, heart disease etc. (6). Gold Nanoparticles (GNPs) refers to particles constituted of gold (Au) atoms with sizes ranging between 2 nm to 100 nm that are derived by reducing gold-based compounds such as HAuCl₄ (7, 8). GNPs have a unique physicochemical feature of readily forming thiol and amine bonds as well as intrinsic surface plasmon

resonance (SPR), a property which makes them versatile in biological applications. SPR refers to the collective oscillation of the electrons by absorbing photons from light at a specific wavelength and emitting the energy dependent upon the size and shape of the GNPs. SPR of GNPs can be tuned to resonate with the specific wavelength of light in the visible or infrared spectrum. Hence, monitoring the therapy, imaging, drug delivery and biomedical imaging as a contrast agent, diagnosing and hyperthermia therapy could be possible (5). Additionally, GNPs are shown to be non-toxic to the cells as the core of the GNPs is inert (9).

GNPs have a wide spectrum of applications in genomics, biosensors, immunoassays, clinical studies, drug discovery, detection, imaging and microbiology (6). Amongst all these, its application in cancer diagnosis and therapy is most promising (10). GNPs can be delivered by linking molecules that can recognise the protein/molecules on the CRC cell's surface in a process called 'active targeting'. In contrast, in passive targeting, due to leaky and poorly developed blood vessels with enlarged pores (100 nm – 600 nm), GNPs can preferentially accumulate in the tumour (11). Also, with underdeveloped lymphatic vessels, GNPs are improperly drained from the tumour. As such, they targets the CRC tumour passively in a process called the enhanced permeability effect (EPR) (12). As a result, GNPs (10 nm – 200 nm) penetrate the tumour and accumulate prior to reaching the cell cytoplasm (13). Consequently, this results in increased delivery of drug's ferrying GNPs into the tumour (14).

Currently, applications of nanomedicine can be hindered by problems of toxicity and delivery (15). Nanomaterials administered *in vivo* spread throughout the body and can reach off-target sites and damage healthy cells and tissues. Consequently, this lowers their efficacy in reaching the target site leading to non-specific accumulation and unwanted side-effects (16). For GNPs application *in vivo*, they need to reach directly the tumour site to enhance its subsequent uptake by the tumour cells (17). These obstacles must be addressed in order to improve the efficacy of using GNPs for delivery and, therefore, efficient delivery of GNPs which must be attained for its biomedical application such as imaging, detection/diagnosis and therapy (18–20). To overcome these drawbacks and in order to increase the GNP's internalisation and delivery efficacy, two different receptors folate receptor-a (FR) and Tyro3 receptors on CRC cells were selected simultaneously for active targeting.

FR are overexpressed in various malignancies such as breast, colon, ovarian, endometrium, kidney, brain and myeloid cells (21). These folate receptors are limited or absent in non-proliferating normal cells which helps to distinguish tumour cells from normal healthy cells (22). FR are membrane-bound receptors and participate in the transport of folate into the cells (23). FR is present in four different isoforms (α , β , γ and δ) and different tissues express different isoforms. In cancer, folate receptor- α is overexpressed in colon, ovary, breast and head and neck cancers constituting up to 40% in human cancers (24). FR- β is upregulated in brain, liver, thyroid, uterus, stomach, prostate, testis and colon (24). Therefore, due to folate receptor- α 's overexpression in different cancers, especially in CRC, we selected it as a targeting moiety (25).

Tyro3, together with Axl and Mer, constitutes the TAM receptor family and is a subfamily receptor of tyrosine kinases discovered in 1991 (26). In 1993, Tyro3 receptor, also known as Tif, Sky, BYK and Dtk (27), was discovered to have a role in embryonic differentiation (28). In 1995, Gas6/protein S (Pros1) were identified as ligands for these TAM receptors (29). TAM mediates signal transduction through the binding of Gas6/Protein S followed by homodimerisation or heterodimerisation of its receptors and autophosphorylation of the tyrosine residue in the kinase domain (30). Tyro3's oncogenic potential first emerged when murine models were shown to have mammary tumours due to the upregulation of TAM receptors (31). Tyro3 can also be activated in ligand-independent activation when expressed in high concentrations (32). Similar to FR, Tyro3 receptors are also upregulated in various human cancers including CRC and its overexpression is correlated with poor prognosis and advanced tumour stage (33). For example, in a study conducted in CRC patients, it was found that Tyro3 was overexpressed in CRC tumour patients compared with healthy colon mucosa ($p < 0.0001$). It was also shown that overexpression of Tyro3 led to CRC and metastasis in the liver, making Tyro3 a potential target in CRC (30). In another study comparing 76 polyps and 265 pairs of normal and cancer samples, overexpression of Tyro3 was found to greatly enhance cell motility, invasion, anchorage-independent growth and metastatic ability in CRC and induces Endothelial to Mesenchymal Transition (EMT) (27). Moreover, no clinical trials so far have been shown to have targeted Tyro3 receptors, making Tyro3 a novel target in CRC (30, 34). Besides CRC, Tyro3 as a novel target, was also demonstrated in Hepatocellular Carcinoma (HCC) wherein sample from 55 patients showed two-fold expression of Tyro3 in the cancerous tissue compared to normal tissue (35). Therefore, the aim of the current study was to target FR and Tyro3 receptors simultaneously in order to increase the efficacy of GNPs delivery and internalisation in CRC tumour cells. Figure 1 shows a schematic representation of the entire research.

Figure 1: Schematic representation shows the synthesis of FR and Tyro3 antibodies-coated GNPs, incubation with all three cell lines and subsequent assessment via ICP-OES.

2. Results And Discussion

2.1 Gold Nanoparticles Characterisation by UV-Vis spectroscopy and DLS

Ultraviolet visible (UV-Vis) spectroscopy is a vital technique in determining the GNP's size distribution, concentration and aggregation levels. Hence, UV-Vis spectra were used to determine the characteristics and attachment of the FR and Tyro3 antibodies to the GNPs. For GNPs-PEG, the SPR peak was found at 513 nm but after conjugation the peak shifted towards a longer wavelength (36). Newly synthesised GNPs-anti-FR and GNPs-anti-Tyro3 had respective λ_{max} at 517 nm (Fig. 2b and Fig. 2c) whereas for GNPs-anti-(FR + Tyro3) the λ_{max} was at 516 nm (Fig. 2d). These newly formed SPR peaks were associated with red shifts (4 nm and 3 nm) due to the change in local refractive index indicating the addition of antibody layers around the GNPs (37). Table 1 provides an overview of all the 4 GNPs and

their respective UV-Vis spectra. A similar red-shift (< 10 nm) was also reported when Epidermal Growth Factor Receptor (C225) antibody was conjugated to GNPs with an alkane-thiol linker (38).

Stability of GNPs was also determined via inducing aggregation. Aggregation of GNPs will induce a red shift towards the infrared region of the spectrum and broadening of the SPR peak (39). As such, GNPs-anti-FR (Fig. 3a), GNPs-anti-Tyro3 (Fig. 3b) and GNPs-anti-(FR + Tyro3) (Fig. 3c) were tested with different concentrations of NaCl for 1 hour to determine the stability in the solution. For all three types of GNPs constructs, no observable red shift or broadening of the peaks were seen indicating all three constructs were highly stable.

Dynamic light scattering (DLS) is also commonly used to determine the hydrodynamic size of the nanoparticles in suspension in the nanometer range. The size of GNPs-PEG was measured to be 22.97 nm (Fig. 4a). However, after the addition of the FR and Tyro3 antibodies, the overall size of the GNPs-anti-FR and GNPs-anti-Tyro3 increased to 30.78 nm and 31.76 nm, respectively (Fig. 6). The molecular mass of the antibodies used is ~ 150 kDa and their corresponding size is around 7–10 nm (40). Therefore, the overall increase in the GNPs hydrodynamic size of approximately 8 nm – 10 nm is attributed to the attachment of the antibodies to GNPs. Similarly, the hydrodynamic diameter of GNPs-anti-(FR + Tyro3) was 31.64 nm (Fig. 4d) confirming the attachment of both FR and Tyro3 antibodies to GNPs. Additionally, the polydispersity index (PDI) for all types of GNPs was < 0.3 indicating a narrow monodispersed GNPs suspension (Fig. 4). Taken together, UV-Vis and DLS study shows that GNPs conjugates are highly stable, monodispersed and bonded with respective antibodies (Table 1).

Table 1

Table summarises the characteristics of all 4 GNPs constructs using UV-Visible Spectroscopy and Dynamic Light Scattering (DLS).

Types of GNPs constructs	UV-Vis Spectrophotometry	DLS (nm)	PDI
GNPs-PEG	513 nm	22.97 nm ± 2.1	0.204
GNPs-anti-FR	517 nm	30.78 nm ± 1.8	0.231
GNPs-anti-Tyro3	517 nm	31.76 nm ± 2.9	0.225
GNPs-anti-(FR + Tyro3)	516 nm	31.64 nm ± 2.3	0.252

2.2 Bradford Assay to quantify antibodies attachment

A modified Bradford assay was used to quantify the antibody conjugation to GNPs. The assay involves the use of the dye Coomassie Brilliant Blue G-250 for the quantification of proteins. First, the Bradford assay was performed to determine the amount of antibodies in the supernatant obtained after the centrifugation and incubation of GNPs with respective antibodies. A standard solution of IgG was used to generate a calibration curve to quantify the unbound antibodies in the supernatant. Thereafter, the number of antibodies conjugated to GNPs was calculated via the difference between the initial concentration used and concentration found in the supernatant (Fig. 5). Consequently, the number of antibodies (IgG) bound to one GNP was calculated to be ~ 7 antibodies (41). Table 2 summarises the

calculation of antibody molecules attached to each type of GNP construct. The number of antibody attached to single GNPs is consistent as quantified in two separate studies (37) and (42).

Table 2

Table illustrates amount of IgG (anti-FR and anti-Tyro3) antibodies bound to different types of GNP constructs

Type pf Gold Nanoparticles	Initial amount 200 µg	Supernatant using Bradford assay	Antibody attached	Antibody coated to one Gold Nanoparticle
GNPs-anti-FR	200 µg	1.7 µg	198.3 µg ± 1.2	7.23 ± 0.3
GNPs-anti-Tyro3	200 µg	2.1 µg	197.9 µg ± 1.4	7.19 ± 0.2
GNPs-anti-(FR + Tyro3)	200 µg	0.4 µg	199.6 µg ± 0.9	7.26 ± 0.5

2.3 Matrix Associated Laser Desorption/Ionisation Time-of-Flight (TOF) Mass Spectroscopy (MALDI-TOF)

MALDI-TOF was implemented to further confirm the attachment of the IgG (anti-FR and anti-Tyro3) to all the antibody-coated GNPs constructs. Intensity peaks were confirmed using IgG as standard. Three intensity peaks were observed $[M + H]^+$, $[M + 2H]^{2+}$ and $[M + 3H]^{3+}$ (Fig. 6a) generated from the IgG as shown previously (45) and (46). Out of three, IgG is mainly denoted by two main peaks $[M + H]^+$ and $[M + 2H]^{2+}$ corresponding to single protonated ($m/z = 148,286$) and double protonated ($m/z = 74,478$) IgG molecules (47) and (48). For all the antibody-coated GNPs (Fig. 6c), (Fig. 6d) and (Fig. 7), similar peaks were also shown which confirmed the attachment of the antibodies to GNPs-PEG (Fig. 6b). As a proof of principle, GNPs-PEG was also analysed using MALDI-TOF and showed no similar IgG peaks in the sample due to the absence of the antibodies. This further confirmed those peaks were emanating from IgG only and not generated from either the GNPs, polyethyleneglycol chain or the matrix used to analyse the GNPs.

2.4 FR and Tyro3 expression levels in different cell lines

For targeting and testing of GNPs, FR and Tyro3 were assayed for their expression levels in colon epithelial cell line (CRL1790) vs. CRC cell lines (CRL2159 and HCT116). FR are membrane bound receptors and were found to be overexpressed in CRL2159 and HCT116 CRC cell lines whereas they were absent in CRL1790 in ICC experiments (Fig. 8). FR are upregulated in many cancers such as brain, kidney, breast and ovaries including colon (22). Due to the fact that FR are absent or minimally expressed in normal colonic tissue, it makes them a potential target for GNPs application in biomedicine (43). Tyro3 is another subtype of tyrosine kinase and a membrane bound receptor along with others such as EGFR, VEGFR, PDGFR, IFF1R and MET (35). Tyro3 had been found to be overexpressed in various cancers including CRC (44). In ICC experiments, their expression patterns too were concomitant with the literature

and were not expressed in CRL1790 compared to CRL2159 and HCT116 (30) and (27) (Fig. 8). Thus, FR and Tyro3 receptors are overexpressed in CRC compared to colon epithelial cells making them a feasible target for GNPs. Hence, they were used simultaneously to target the cells by exploiting their upregulation in CRC cells in order to increase the efficiency of GNPs delivery to the targeted tumour cells.

2.5 Inductively Coupled Plasma-Optical Emission Spectroscopy (ICP-OES)

To study the internalisation and efficacy of all GNPs constructs, elemental analysis was conducted using the ICP-OES technique. After binding with the receptors on the plasma membrane of the cells, GNPs become internalised via receptor-mediated endocytosis (RME) (49). Different amount of all types of GNPs (0 ng – 50 ng) were aliquoted in wells for each of the three cell lines. After 4 hours of incubation, cells were thoroughly washed, then digested in *aqua regia* before being subjected to ICP-OES. CRL1790 has shown the least internalisation with less than 10 ng for all the GNPs concentrations (Fig. 10). In CRL1790, uptake of antibody-coated GNPs were greater than that observed for GNPs-PEG alone ($p < 0.05$). An important observation was also made that there was no difference in internalisation in single antibody-coated GNPs (GNPs-anti-FR & GNPs-anti-Tyro3) vs. double antibody-coated GNPs (GNPs-anti-(FR + Tyro3)) ($p > 0.05$). Both of these observations can be attributed to the low number of FR and Tyro3 receptors in CRL1790.

In CRL2159, there was an increase in GNPs uptake for single antibody-coated GNPs ($p < 0.05$) and double antibody-coated GNPs ($p < 0.05$) compared to GNPs-PEG (Fig. 11). Also, compared to GNPs-PEG, GNPs-anti-FR, GNPs-anti-Tyro3 and GNPs-anti-(FR + Tyro3) had more internalisation for each and every concentration of the incubated GNPs. At 20 ng, GNPs-anti-FR and GNPs-anti-Tyro3 were internalised more than 10 ng in CRL2159 compared to below 10 ng in CRL1790 ($p < 0.05$). This could be explained by the overexpression of FR and Tyro3 receptors in CRL2159, as a result of which there was a two-fold increase in RME and internalisation compared to CRL1790. Additionally, double antibody-coated GNPs were highly efficient in targeting CRL2159 cells compared to single antibody-coated GNPs ($p < 0.05$). Most importantly, no significant difference in internalisation efficiency was observed between FR and Tyro3 targeted single antibody-coated GNPs ($p > 0.05$). This means that GNPs-anti-Tyro3 had the same internalisation capability as GNPs-anti-FR. This observation that Tyro3 receptors can be equally capable as FR in targeting CRC using GNPs is a novel finding. The graph also demonstrates there was a very low uptake of GNPs-PEG in CRL2159 (Fig. 11) particularly when compared to single and double antibody-coated GNPs.

A similar pattern was also seen with the HCT116 colorectal carcinoma cell line (Fig. 12). For every concentration of all single and double-antibody coated GNPs, there was an increased internalisation efficiency compared to GNPs-PEG. However, at 50 ng there was a non-specific uptake that could be explained by the high number of non-targeted GNPs. This set of results also show that HCT116 had a high number of internalised GNPs compared to CRL1790 and CRL2159 which can be attributed to overexpression of FR and Tyro3 receptors and a different method of endocytosis mechanism pertaining

to an individual cell line (50). Such results also indicate that double antibody-coated GNPs had a higher internalisation efficiency compared to single antibody-coated GNPs ($p < 0.05$). Moreover, the GNPs-anti-Tyro3 had similar internalisation efficacy as GNPs-anti-Tyro3 since there was no significant difference in their uptake ($p > 0.05$) showing that Tyro3 receptors had an equal potential for the uptake of GNPs as FR receptors.

2.6 Cell uptake studies using confocal microscopy

Conjugation of FITC antibody-coated GNPs has enabled confocal microscopy imaging to determine cellular uptake and localisation (Fig. 13). A concentration of 50 ng was chosen for the experiment since the fluorescent signals were constant compared to other concentrations used and also were the most internalised concentration as determined using ICP-OES. In the present experiment, GNPs-anti-FR, GNPs-anti-Tyro3 and GNPs-anti-(FR + Tyro3) were successfully used to target cancer cells using FR and Tyro3 receptors as quantified by ICP-OES. CRL1790 gave reduced non-specific binding or no signal due to low expression of FR or Tyro3 receptors on these CRC cells. On the other hand, CRL2159 and HCT116 had overexpressed FR & Tyro3 receptors and, therefore, had more internalisation of GNPs which was also supported by ICP-OES (Fig. 11) and (Fig. 12). Similar results can also be seen with strong green fluorescence associated with GNPs uptake (Fig. 13). As a comparison, cells from all three cell lines without GNPs are also shown in Fig. 14. In a separate study, electron microscopy had demonstrated 4 nm and 6 nm internalisation by HeLa cells and were sub-localised in endosomes and lysosomes (51). In another experiment to demonstrate the uptake, HeLa cells were incubated with folate-conjugated GNPs. GNPs were shown via confocal and electron microscopy to be localised in the cytoplasm due to overexpressed folate receptors (44). These results strongly suggests the presence of GNPs in the cytoplasm was due to receptor mediated endocytosis (RME) via invagination of the plasma membrane in the cytoplasm. Results as shown in Fig. 13 are also in line with the experiments conducted here and previous literature as stated above confirming the hypothesis that simultaneous targeting of FR and Tyro3 receptors has led to an increase in cellular uptake of GNPs.

Figure 13: Figure shows internalisation of GNPs-anti-FR, GNPs-anti-Tyro3 and GNPs-anti-(FR+Tyro3) (red arrows) at 50ng in all three cell lines. Nuclei were stained in blue and GNPs in green. Experiments were repeated in triplicates ($n=3$). Scale bar = 50 μ m. Magnification 40X.

3. Conclusion

CRC ranks fourth in mortality and morbidity worldwide whereas diagnosis and treatment have shortcomings making CRC's survival rate < 5%. Therefore, targeting CRC using GNPs could result in diagnosis and better treatment by delivering contrast agents and drugs, respectively, in a selective manner with minimum side-effects. To that end, this work demonstrates targeting novel receptor Tyro3 and FR on CRC cells simultaneously to enhance GNPs delivery *in vitro*. The minimum threshold levels of GNPs in CRC cells were higher via targeting these receptors simultaneously compared to when targeted individually. RME mediated localisation of GNPs was also shown using confocal microscopy and

concomitantly quantified using ICP-OES. Similarly, depending on the cancer types overexpressing specific receptors, GNPs can be exploited for targeting using similar principle to efficiently and specifically deliver nanoparticles into cancer cells. Furthermore, the work has also elucidated the internalisation of GNPs via the novel receptor Tyro3 wherein it is equally effective as FR in delivering GNPs in cancer cells. Therefore, by increasing cellular delivery and internalisation, hyperthermia based molecular imaging and treatments using GNPs can be made feasible (52).

4. Materials And Methods

4.1 Cell culture

Human Colon Epithelium Cell Line CRL1790 (ATCC no. CCD841), Human Colorectal Cancer Duke's B CRL2159 (ATCC no. LS411N) and Colorectal Carcinoma HCT116 (ATCC no. CCL-247) were used to grow and test the efficiency of Gold Nanoparticles. CRL1790 was cultured using Sigma's Minimum Essential Medium (MEM) Eagle (product no. M4655) supplemented with 10% (v/v) Foetal Bovine Serum (FBS) and 1% Penicillin/Streptomycin (v/v) antibiotic solution. CRL2159 was cultured using Sigma's RPMI1640 (product no. R8758) supplemented with 10% FBS and 1% antibiotic solution. HCT116 was cultured using Gibco's Dulbecco's Modified Eagle Medium (DMEM) solution (product no. 61965-026) and supplemented with 10% FBS and 1% antibiotic solution. Cells were passaged at 80%-90% confluence, once or twice a week. Approximately, 10,000 cells/well were aliquoted in 6-well plates and allowed to reach 80%-90% confluency before aliquoting GNPs with different targeting moieties for the purpose of testing the efficiency.

4.2 Synthesis of different types of GNPs.

Schematic representation of the study is shown in Fig. 1. To test the hypothesis that targeting FR and Tyro3 simultaneously leads to higher concentration of GNPs in the cell, pegylated GNPs (GNPs-PEG), folate receptor- α antibody bound GNPs (GNPs-anti-FR), Tyro3 receptor antibody bound GNPs (GNPs-anti-Tyro3) and both antibodies specific for FR and Tyro3 receptors (1:1) attached GNPs (GNPs-anti-(Tyro3 + FR)) were tested in Colon Epithelium (CRL1790), Duke's Carcinoma (CRL2159) and Colorectal Carcinoma (HCT116) cell lines to investigate the uptake of these constructs. To synthesise the above mentioned GNPs, lyophilised GNPs with a polyethylene glycol (PEG) (5 kDa) linker, NHS ester-activated kit were purchased from Cytodiagnostics (product no. CGN5K-5-2) and protocol followed as given (Fig. 15). Briefly, 5 mg/ml FR (product no. MA-23917) or Tyro3 antibodies (product no. ab235078) were reacted with NHS-activated GNPs for 2 hours to yield GNPs-anti-FR and GNPs-anti-Tyro3 conjugates. For GNPs-anti-(FR + Tyro3), a 1:1 ratio was used whilst reacting respective antibodies with NHS-activated GNPs. The solution was then centrifuged at 15,000 g for 1 hour using 100 kDa membrane filters (product no. VS0152) to remove the unbound antibodies from the antibody-conjugated GNPs. GNPs-PEG were synthesised by activating the GNPs first without any antibodies resulting into pegylated GNPs. Synthesised conjugates were then stored in gold nanoparticles buffer at 4 °C where they were stable for 3

months. The final volume had approximately 1.1×10^{14} GNPs in accordance with the information provided by the company.

Due to the fact that fluorescein isothiocyanate (FITC) recognises and binds to primary amine residues found on monoclonal antibodies, all antibody-coated GNPs were reacted with 0.1 mol/L FITC for 24 hours in the dark on an orbital shaker to enable visualisation using confocal microscopy (Zhang *et al.*, 2010). FITC labelled GNPs conjugates were then centrifuged using 10,000 MW Amicon® centrifugal filter tubes to remove excess FITC from the suspension. GNPs-PEG was the only exception since it does not provide a supporting amino group to bind FITC and, thus, was not included in the confocal imaging experiment. Since confocal imaging is used to qualitatively and solely assess the localisation of single- and double-antibody-coated GNPs in the cytoplasm, inclusion of GNPs-PEG would be an irrelevant experiment. ICP-OES was used to quantify the uptake of GNPs-PEG in all three cell lines as a control.

Figure 15: Figure shows the attachment of antibodies to GNPs-PEG

4.3 Ultraviolet Visible (UV-Vis) Spectroscopy.

All UV-spectra were recorded using the BMG FLUstar Omega software to read the absorbance at room temperature. Briefly, 300 μ l of GNPs-PEG, GNPs-anti-FR, GNPs-anti-Tyro3 and GNPs-anti-(FR + Tyro3) were aliquoted into the 96-well plate (96NUN) and readings recorded between 400–800 nm. Colloidal stability of nanoparticles in biological media is equally crucial to preserve their utility as aggregation often leads to undesirable biological response. A quantitative measurement of nanoparticle aggregation in solution would provide a valuable assessment of colloidal stability of bio-nano interfaces after surface functionalization. As such, 1 ml GNPs-PEG, GNPs-anti-FR, GNPs-anti-Tyro3 and GNPs-anti-(FR + Tyro3) were incubated with 100 μ l of varied NaCl concentrations (0.01M, 0.1M, 0.5M and 1M) for 1 hour at room temperature. This provided a check for aggregation via a red-spectral shift in SPR peak of all the GNPs constructs using a UV-Vis spectrophotometer.

4.4 Dynamic Light Scattering (DLS)

The Dynamic light scattering apparatus (DLS) (Malvern Nano-ZS) was used to record the distribution of the size of the nanoparticles in the suspension. Disposable cuvettes were used to determine the size of the respective GNPs. 1.5 ml GNPs solution was loaded into the DLS and measurements were taken. Readings were taken in triplicates for every GNPs conjugate.

4.5 Bradford Assay

To quantify the antibodies attached to all the GNPs construct, the Bradford assay was performed. A calibration curve was plotted in the range of 0 to 50 μ g/ml using IgG antibody (product no. 56834-25MG) in 1X PBS buffer (pH 7.4) as standard ($R^2 = 0.997$) (Fig. 5). Briefly, in a 96-well plate, 100 μ l of supernatant from GNPs-anti-FR, GNPs-anti-Tyro3 and GNPs-anti-(FR + Tyro3) were aliquoted and incubated with 150 μ l of Bradford reagent (catalog no. 23200). The samples were incubated with Bradford reagent (lot no. SLBW5151) in the dark for 10 minutes. Subsequently, the absorbance readings were taken at 450 nm and 595 nm to estimate the amount of antibodies attached to each GNPs construct.

by subtracting from the total amount added. GNPs-PEG were not aliquoted since there was no antibody associated with this construct.

4.6 FR and Tyro3 expression levels in different cell lines

CRL1790, CRL2159 and HCT116 were cultured and passaged as mentioned above. For detecting differential expression of FR and Tyro3 receptors in normal vs. CRC cell lines, cells cultured on sterilised coverslips were fixed using 4% paraformaldehyde (PFA) for 30 minutes. After fixation, residual PFA was washed away by washing twice with 1X PBS buffer after which all three cell lines were subjected to ICC experiments. Fixed cells, after being washed 3 times with 1X PBS, were treated with citrate buffer at pH 6 for FR antigen retrieval for 10 minutes whereas it remained untreated for Tyro3 receptors. The citrate treated cells are washed thoroughly with 1X PBS. Subsequently, 50% horse serum in 1X PBS (1:1) was aliquoted to inhibit any unwanted signals and non-specific binding of primary antibodies to the antigen receptors. Thereafter, FR receptor alpha rabbit polyclonal antibody (no. PA5-42004) at a concentration of 1:100 and Tyro3 mouse monoclonal antibody (no. MA5-11171) at a concentration 1:50 were incubated with all three types of cell line for 90 minutes followed by washing with 1X PBS. Next, using the VECTASTATIN ABC kit (catalog no. AK-6100), a biotinylated-secondary antibody was incubated with the cell to facilitate binding with the primary antibodies for 30 minutes. Again, the residual unbound secondary antibody was washed away using 1X PBS. Avidin-bound tertiary antibody was then aliquoted for 20 minutes to bind to the biotinylated-secondary antibodies at room temperature. Cells were washed with 1X PBS again. A tertiary peroxidase-labelled avidin was applied at room temperature for 20 min before developing with a tyramide signal amplification (TSA) fluorescein system (NEN Life Science Products, Boston, MA, USA) to enable the visualisation of the receptors. Excess FITC was washed away using 1X PBS, and the cover-slips were counter-stained using DAPI (4',6-diamidino-2-phenylindole) (Product no. H-1200) based mounting media. Confocal microscopy was used for obtaining pictures of FR and Tyro3 expression.

4.7 Matrix Associated Laser Desorption/Ionisation Time-of-Flight (TOF) Mass Spectroscopy (MALDI-TOF)

The MALDI-TOF instrument (Bruker) was calibrated using IgG antibodies as standard (product no. 56834-25MG). Thereafter, 1 µl GNPs-PEG, GNPs-anti-FR, GNPs-anti-Tyro3 and GNPs-anti-(FR + Tyro3) conjugates were deposited on the target plate to detect the presence of attached antibody. The samples were left to air-dry at room temperature. Subsequently, 1 µl of sinapinic acid in acetonitrile and water (1:1) with 0.1% trifluoroacetate (TFA) (70:30 v/v) was pipetted onto the dried sample and left to form a thin layer over the sample at room temperature. The mass spectra were acquired in a positive linear mode with the laser beam at 60% intensity and 5000 shots on an average were fired upon the sample to generate protonated ions within the 20,000-200,000 m/z range. Spectra were reviewed in FlexAnalysis Software (Bruker) and visually inspected for the presence of monoclonal peaks.

4.8 Cell uptake studies using confocal microscopy

All 3 fluorescently-labelled GNP constructs GNPs-anti-FR, GNPs-anti-Tyro3 and GNPs-anti-(FR + Tyro3) were subjected to confocal microscopy. Normal Colon Epithelium (CRL1790), Duke's B Colorectal Cancer (CRL2159) and colorectal carcinoma (HCT116) were grown and cultured as mentioned above. After trypsinisation, 10,000 cells were pipetted onto the sterilised covers-slips in the 6-well plates and placed in the incubator at 37°C at 5% CO₂ to reach 80%-90% confluence. Later, FITC bound antibody-coated GNPs (10 ng – 50 ng) were aliquoted in all three cell lines and incubated for 4 hours. For a control, one well of each cell line were incubated without GNPs. Thereafter, the media were discarded and the non-bound GNPs was washed away by using 1X PBS repeatedly over 4 times. 4% PFA was later pipetted to fix the cells for 30 minutes. The cells were again washed using 1X PBS twice and cover-slips were mounted onto the slides using DAP-based mounting media. Internalisation of FITC bound GNPs was then visualised using Leica confocal microscopy.

4.9 ICP-OES

Quantification of GNPs in nanograms (ng) was carried out using ICP-OES (iCAP 6000 Series). The conditions ICP-OES being operated upon are listed in Table 3. A gold standard calibration curve ($R^2 = 0.9946$) was plotted using gold standard solution (product no. 170321) in the range of 0–10ug/L. All three cells lines were grown and passaged as mentioned above and later aliquoted in the 6-well plates at approximately 10,000 cells/well. Cells were allowed to grow until they were 80%-90% confluent. GNPs-PEG and the antibody-coated GNP were incubated for 4 hours with all the three cell lines. After incubation with relevant GNPs, cells were washed 4 times with 1X PBS to remove free and loosely bound GNPs. Later, the cells were digested using freshly prepared 1 ml *aqua regia* (3:1 HCl:HNO₃) for 1 hour. Each digested sample with *aqua regia* was later brought upto 10 ml by adding de-ionised water in 15 ml centrifuged tubes. Respective samples were then run through ICP-OES to measure the uptake of GNPs in nanograms. Concentrations (μg/L) obtained from ICP-OES were used to determine the amount internalised by the cells in 10 ml suspension using a C1V1 = C2V2 formula.

Table 3
Operating condition of ICP-OES

Nebuliser	Cross-Flow
Spray Chamber	Glass-Scott type
Power (Watts)	1150 Watts
Coolant gas (L min^{-1})	12 L min^{-1}
Auxillary gas (L min^{-1})	0.5 L min^{-1}
Nebuliser gas (L min^{-1})	0.7 L min^{-1}
Viewing	Axial
Sample Uptake (ml)	1 ml
Analyte wavelength	242.795 nm
Measurement time per replicate (seconds)	30 s
R^2	0.9946

4.10 Statistics

Analysis of variance (ANOVA) was carried out where two or more groups of means were involved and student's unpaired *t*-test where only two groups were compared. $P \leq 0.05$ was considered to be statistically significant.

5. Abbreviations

Colorectal Cancer (CRC), Gold nanoparticles (GNPs), Folate receptor-a (FR), Surface Plasmon Resonance (SPR), Enhanced Permeability Effect (EPR), Ultraviolet Visible (UV-Vis), Dynamic Light Scattering (DLS), Polydispersity Index (PDI), Immunocytochemistry (ICC), Matrix Associated Laser Desorption/Ionisation - Time of Flight (MALDI-TOF) mass spectrometry, Inductively Coupled Plasma-Optical Emission (ICP-OES) mass spectrometry, Fluorescein isothiocyanate (FITC), Minimum Essential Medium (MEM), Foetal Bovine Serum (FBS), Dulbecco's Modified Eagle Medium (DMEM), Tyramide signal amplification (TSA), 4',6-diamidino-2-phenylindole (DAPI),

6. Declarations

6.2 Competing interest

There was no competing interest amongst the authors.

6.3 Funding

This research was partly funded by Engineering and Physical Sciences Research Council (EPSRC) under grant number EP/R04192X/1.

6.5 Acknowledgement

We are also extremely grateful to our colleagues Fahimullah Hayat and Nirusha Chandima Weerasinghe for their support during the time.

7. References

1. Siegel RL, Miller KD, Jemal A. Cancer statistics (2018) CA Cancer J Clin. 2018;68(6):394–424
2. Cisterna BA, Kamaly N, Choi W, II, Tavakkoli A, Farokhzad OC, Vilos C (2016) Targeted nanoparticles for colorectal cancer. Nanomedicine 11(8):2443–2456
3. Gonzalez-Pons M, Cruz-Corra M. Colorectal Cancer Biomarkers: Where Are We Now? Biomed Res Int [Internet]. 2015;2015:149014. Available from: <http://europepmc.org/articles/PMC4461726>
4. Kaliberov SA, Buchsbaum DJ (2012) Cancer treatment with gene therapy and radiation therapy. Adv Cancer Res [Internet]. [cited 2018 Nov 28];115:221–63. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/23021246>
5. Singh M, Harris-Birtill DC, Markar SR, Hanna GB, Elson DS (2015 Nov) Application of gold nanoparticles for gastrointestinal cancer theranostics: A systematic review. Nanomedicine 11(8):2083–2098
6. Shah M, Badwaik VD, Dakshinamurthy R (2014) Biological applications of gold nanoparticles. J Nanosci Nanotechnol 37(9):1896–1908
7. Turkevich J, Stevenson PC, Hillier J. A study of the nucleation and growth processes in the synthesis of colloidal gold. Discuss Faraday Soc [Internet]. 1951;11(0):55–75. Available from: <http://dx.doi.org/10.1039/DF9511100055>
8. Grobmyer SR, Iwakuma N, Sharma P, Moudgil BM. What Is Cancer Nanotechnology? In: Grobmyer SR, Moudgil BM, editors. Cancer Nanotechnology: Methods and Protocols [Internet]. Totowa, NJ: Humana Press; 2010. p. 1–9. Available from: https://doi.org/10.1007/978-1-60761-609-2_1
9. Lévy R, Shaheen U, Cesbron Y, Sée V (2010) Gold nanoparticles delivery in mammalian live cells: a critical review. Nano Rev [Internet]. [cited 2018 Oct 22];1(1):4889. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/22110850>
10. Cai W, Gao T, Hong H, Sun J. Applications of gold nanoparticles in cancer nanotechnology. Nanotechnol Sci Appl. 2008 Sep 19;1:17–32
11. Obaid G, Chambrier I, Cook MJ, Russell DA. Cancer targeting with biomolecules: a comparative study of photodynamic therapy efficacy using antibody or lectin conjugated phthalocyanine-PEG gold

- nanoparticles. *Photochem Photobiol Sci* [Internet]. 2015;14(4):737–47. Available from: <http://dx.doi.org/10.1039/C4PP00312H>
12. Hong Y, Rao Y. Current status of nanoscale drug delivery systems for colorectal cancer liver metastasis. *Biomed Pharmacother*. 2019;114.
 13. Holback H, Yeo Y (2011) Intratumoral drug delivery with nanoparticulate carriers. *Pharm Res* 28(8):1819–1830
 14. Her S, Jaffray DA, Allen C (2017) Gold nanoparticles for applications in cancer radiotherapy: Mechanisms and recent advancements. *Adv Drug Deliv Rev* [Internet] 109:84–101. file://www.sciencedirect.com/science/article/pii/S0169409X15300144 Available from:
 15. Albanese A, Tang PS, Chan WCW (2012) The Effect of Nanoparticle Size, Shape, and Surface Chemistry on Biological Systems. *Annu Rev Biomed Eng* 14:1–16
 16. Gou N, Onnis-Hayden A, Gu AZ (2010) Mechanistic toxicity assessment of nanomaterials by whole-cell-array stress genes expression analysis. *Environ Sci Technol* 44(15):5964–5970
 17. Lévy R, Shaheen U, Cesbron Y, Séé V (2010) Gold nanoparticles delivery in mammalian live cells: a critical review. *Nano Rev* 1(1):4889
 18. Giljohann DA, Mirkin CA (2009) Drivers of biodiagnostic development. *Nature* 462(7272):461–464
 19. Alivisatos P (2004) The use of nanocrystals in biological detection. *Nat Biotechnol* 22(1):47–52
 20. Chou LYT, Chan WCW (2012) Fluorescence-Tagged Gold Nanoparticles for Rapidly Characterizing the Size-Dependent Biodistribution in Tumor Models. *Adv Healthc Mater* 1(6):714–721
 21. Cheung A, Bax HJ, Josephs DH, Ilieva KM, Pellizzari G, Opzoomer J et al (2016) Targeting folate receptor alpha for cancer treatment. *Oncotarget* 7(32):52553–52574
 22. Sega EI, Low PS. Tumor detection using folate receptor-targeted imaging agents. *Cancer Metastasis Rev* [Internet]. 2008 Dec 4 [cited 2018 Dec 6];27(4):655–64. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/18523731>
 23. Antony AC (1996) Folate Receptors. *Annu Rev Nutr* [Internet]. Jul [cited 2018 Dec 6];16(1):501–21. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/8839936>
 24. Shen J, Putt KS, Visscher DW, Murphy L, Cohen C, Singhal S et al (2015) Assessment of folate receptor-beta expression in human neoplastic tissues. *Oncotarget* 6(16):14700–14709
 25. Bhattacharya R, Patra CR, Earl A, Wang S, Katarya A, Lu L et al (2007) Attaching folic acid on gold nanoparticles using noncovalent interaction via different polyethylene glycol backbones and targeting of cancer cells. *Nanomedicine Nanotechnology, Biol Med*. Sep 1;3(3):224–38
 26. Schmidt T, Ben-Batalla I, Schultze A, Loges S (2012) Macrophage-tumor crosstalk: Role of TAMR tyrosine kinase receptors and of their ligands. *Cell Mol Life Sci* 69(9):1391–1414
 27. Chien CW, Hou PC, Wu HC, Chang YL, Lin SC, Lin SC et al (2016) Targeting TYRO3 inhibits epithelial-mesenchymal transition and increases drug sensitivity in colon cancer. *Oncogene* 35(45):5872–5881
 28. Biesecker LG, Gottschalk LR, Emerson SG (1993) Identification of four murine cDNAs encoding putative protein kinases from primitive embryonic stem cells differentiated in vitro. *Proc Natl Acad*

Sci U S A [Internet]. Aug 1 [cited 2019 Jan 6];90(15):7044–8. Available from:

<http://www.ncbi.nlm.nih.gov/pubmed/8346215>

29. Stitt TN, Conn G, Gore M, Lai C, Bruno J, Radziejewski C et al (1995) The anticoagulation factor protein S and its relative, Gas6, are ligands for the Tyro 3/Axl family of receptor tyrosine kinases. *Cell* [Internet]. Feb 24 [cited 2019 Jan 6];80(4):661–70. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/7867073>
30. Schmitz R, Valls AF, Yerbes R, Richter S von, Kahlert C, Loges S et al (2016) TAM receptors Tyro3 and Mer as novel targets in colorectal cancer. *Oncotarget* [Internet]. [cited 2020 Jul 30];7(35):56355–70. Available from: <https://pubmed.ncbi.nlm.nih.gov/27486820/>
31. Taylor ICA, Roy S, Yaswen P, Stampfer MR, Varmus HE (1995) Mouse mammary tumors express elevated levels of RNA encoding the murine homolog of SKY, a putative receptor tyrosine kinase. *J Biol Chem* 270(12):6872–6880
32. Taylor IC, Roy S, Varmus HE (1995) Overexpression of the Sky receptor tyrosine kinase at the cell surface or in the cytoplasm results in ligand-independent activation. *Oncogene* [Internet]. Dec 21 [cited 2019 Jan 6];11(12):2619–26. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/8545119>
33. Graham DK, Deryckere D, Davies KD, Earp HS (2014) The TAM family: Phosphatidylserine-sensing receptor tyrosine kinases gone awry in cancer. *Nat Rev Cancer* 14(12):769–785
34. Hojjat-Farsangi M. Small-molecule inhibitors of the receptor tyrosine kinases: Promising tools for targeted cancer therapies [Internet]. Vol. 15, International Journal of Molecular Sciences. Int J Mol Sci; 2014 [cited 2020 Jul 30]. p. 13768–801. Available from: <https://pubmed.ncbi.nlm.nih.gov/25110867/>
35. Duan Y, Wong W, Chua SC, Wee HL, Lim SG, Chua BT et al (2016) Overexpression of Tyro3 and its implications on hepatocellular carcinoma progression. *Int J Oncol* 48(1):358–366
36. Haiss W, Thanh NTK, Aveyard J, Fernig DG, Haiss (2007) Wolfgang and Thanh, Nguyen and Fernig D. Determination of Size and Concentration of Gold Nanoparticles from UV/vis Spectra - Supporting Information. *Anal Chem* 79(11):4215–4221
37. Kumar S, Aaron J, Sokolov K (2008) Directional conjugation of antibodies to nanoparticles for synthesis of multiplexed optical contrast agents with both delivery and targeting moieties. *Nat Protoc* 3(2):314–320
38. Raoof M, Corr SJ, Kaluarachchi WD, Massey KL, Briggs K, Zhu C et al (2012) Stability of antibody-conjugated gold nanoparticles in the endolysosomal nanoenvironment: Implications for noninvasive radiofrequency-based cancer therapy. *Nanomedicine Nanotechnology Biol Med* 8(7):1096–1105
39. Fang C, Bhattacharai N, Sun C, Zhang M (2009) Functionalized nanoparticles with long-term stability in biological media. *Small* 5(14):1637–1641
40. Jans H, Liu X, Austin L, Maes G, Huo Q (2009) Dynamic light scattering as a powerful tool for gold nanoparticle bioconjugation and biomolecular binding studies. *Anal Chem* 81(22):9425–9432
41. Tripathi K, Driskell JD (2018) Quantifying Bound and Active Antibodies Conjugated to Gold Nanoparticles: A Comprehensive and Robust Approach to Evaluate Immobilization Chemistry. *ACS*

42. Eck W, Craig G, Sigdel A, Ritter G, Old LJ, Tang L et al (2008) PEGylated gold nanoparticles conjugated to monoclonal F19 antibodies as targeted labeling agents for human pancreatic carcinoma tissue. *ACS Nano* 2(11):2263–2272
43. Samadian H, Hosseini-Nami S, Kamrava SK, Ghaznavi H, Shakeri-Zadeh A. Folate-conjugated gold nanoparticle as a new nanoplatform for targeted cancer therapy. *J Cancer Res Clin Oncol* [Internet]. 2016 Nov 21 [cited 2019 Feb 9];142(11):2217–29. Available from: <http://link.springer.com/10.1007/s00432-016-2179-3>
44. Zhang Z, Jia J, Lai Y, Ma Y, Weng J, Sun L (2010) Conjugating folic acid to gold nanoparticles through glutathione for targeting and detecting cancer cells. *Bioorganic Med Chem* 18(15):5528–5534
45. Bian J, Olesik SV (2017) Surface-assisted laser desorption/ionization time-of-flight mass spectrometry of small drug molecules and high molecular weight synthetic/biological polymers using electrospun composite nanofibers. *Analyst* 142(7):1125–1132
46. Signor L, Erba EB (2013) Matrix-assisted laser desorption/ionization time of flight (MALDI-TOF) mass spectrometric analysis of intact proteins larger than 100 kDa. *J Vis Exp* [Internet]. [cited 2020 Jul 30];(79). Available from: <https://pubmed.ncbi.nlm.nih.gov/24056304/>
47. Lapolla A, Fedele D, Garbeglio M, Martano L, Tonani R, Seraglia R et al (2000) Matrix-assisted laser desorption/ionization mass spectrometry, enzymatic digestion, and molecular modeling in the study of nonenzymatic glycation of IgG. *J Am Soc Mass Spectrom*. Feb 1;11(2):153–9
48. Lapolla A, Fedele D, Aronica R, Garbeglio M, D'Alpaos M, Seraglia R et al (1997) Evaluation of IgG glycation levels by matrix-assisted laser desorption/ionization mass spectrometry. *Rapid Commun Mass Spectrom* [Internet]. [cited 2020 Jul 30];11(12):1342–6. Available from: <https://pubmed.ncbi.nlm.nih.gov/9276978/>
49. Gao H, Shi W, Freund LB (2005) Mechanics of receptor-mediated endocytosis. *Proc Natl Acad Sci U S A* 102(27):9469–9474
50. Bhattacharyya S, Bhattacharya R, Curley S, McNiven MA, Mukherjee P (2010) Nanoconjugation modulates the trafficking and mechanism of antibody induced receptor endocytosis. *Proc Natl Acad Sci U S A* [Internet]. Aug 17 [cited 2020 Apr 9];107(33):14541–6. Available from: <http://www.ncbi.nlm.nih.gov/pubmed/20679244>
51. Kim CS, Li X, Jiang Y, Yan B, Tonga GY, Ray M et al. Cellular imaging of endosome entrapped small gold nanoparticles. *MethodsX* [Internet]. 2015 Jun 25 [cited 2020 Jul 30];2(6):306–15. Available from: <https://pubmed.ncbi.nlm.nih.gov/26151001/>
52. Huang X, El-Sayed IH, Qian W, El-Sayed MA (2006) Cancer cell imaging and photothermal therapy in the near-infrared region by using gold nanorods. *J Am Chem Soc* [Internet]. Feb 15 [cited 2020 Jul 30];128(6):2115–20. Available from: <https://pubmed.ncbi.nlm.nih.gov/16464114/>

Figures

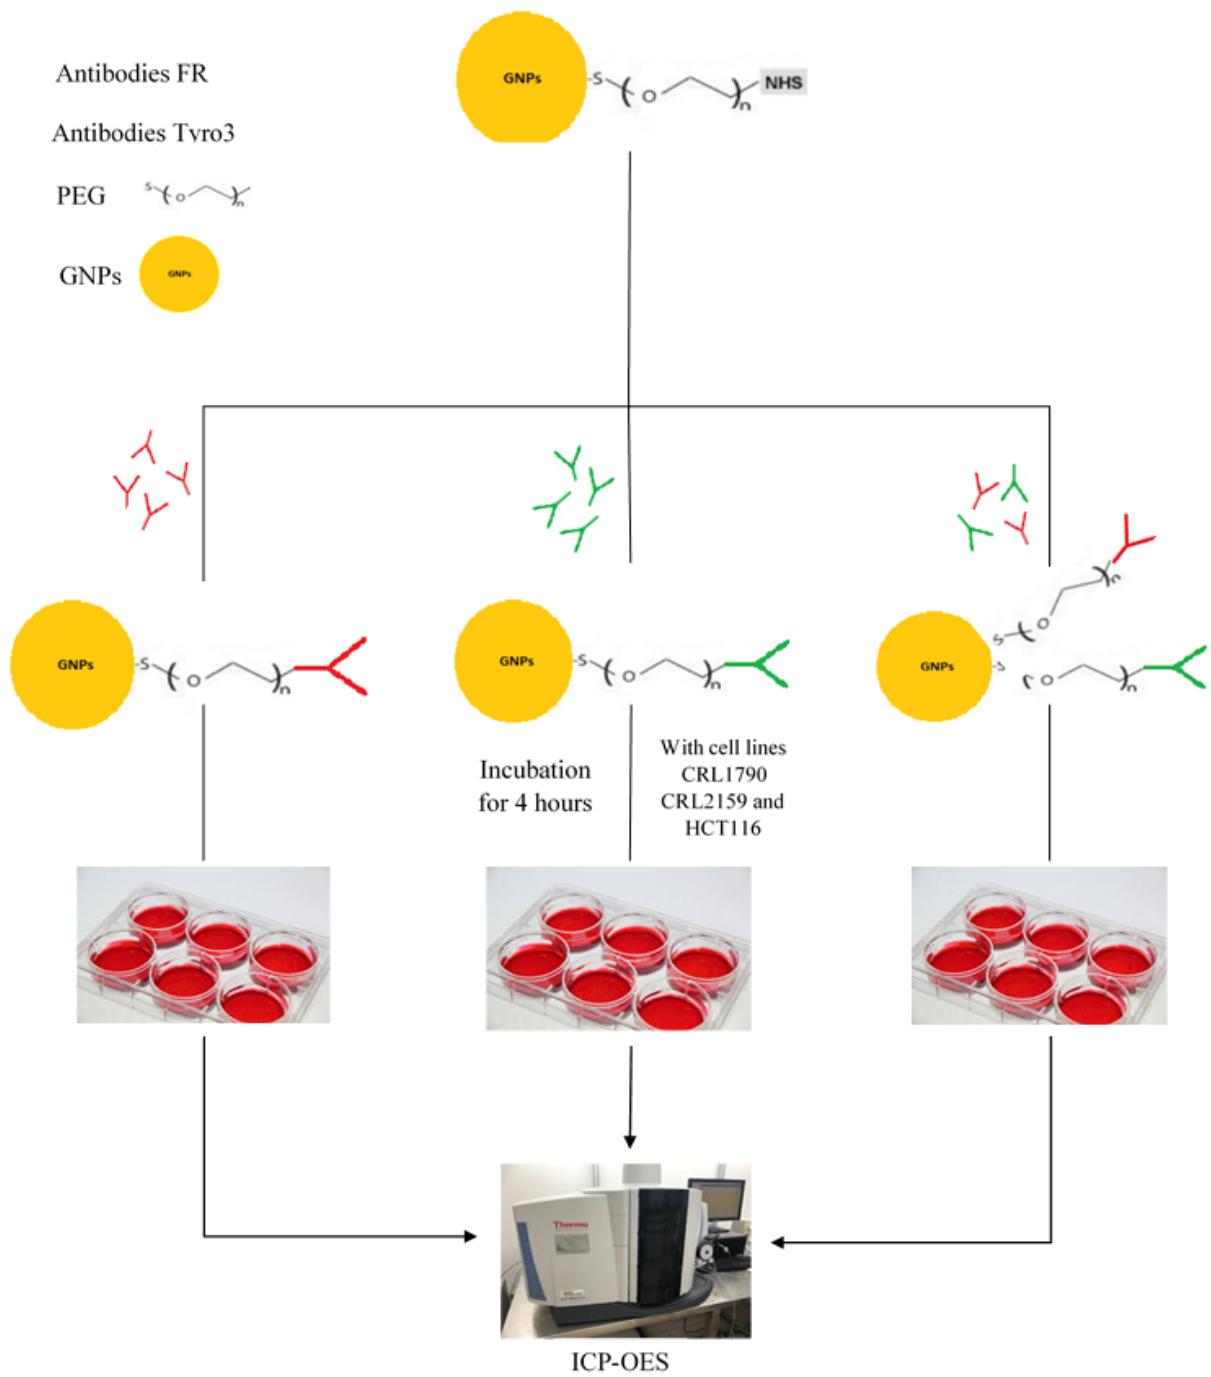


Figure 1

Schematic representation shows the synthesis of FR and Tyro3 antibodies-coated GNPs, incubation with all three cell lines and subsequent assessment via ICP-OES.

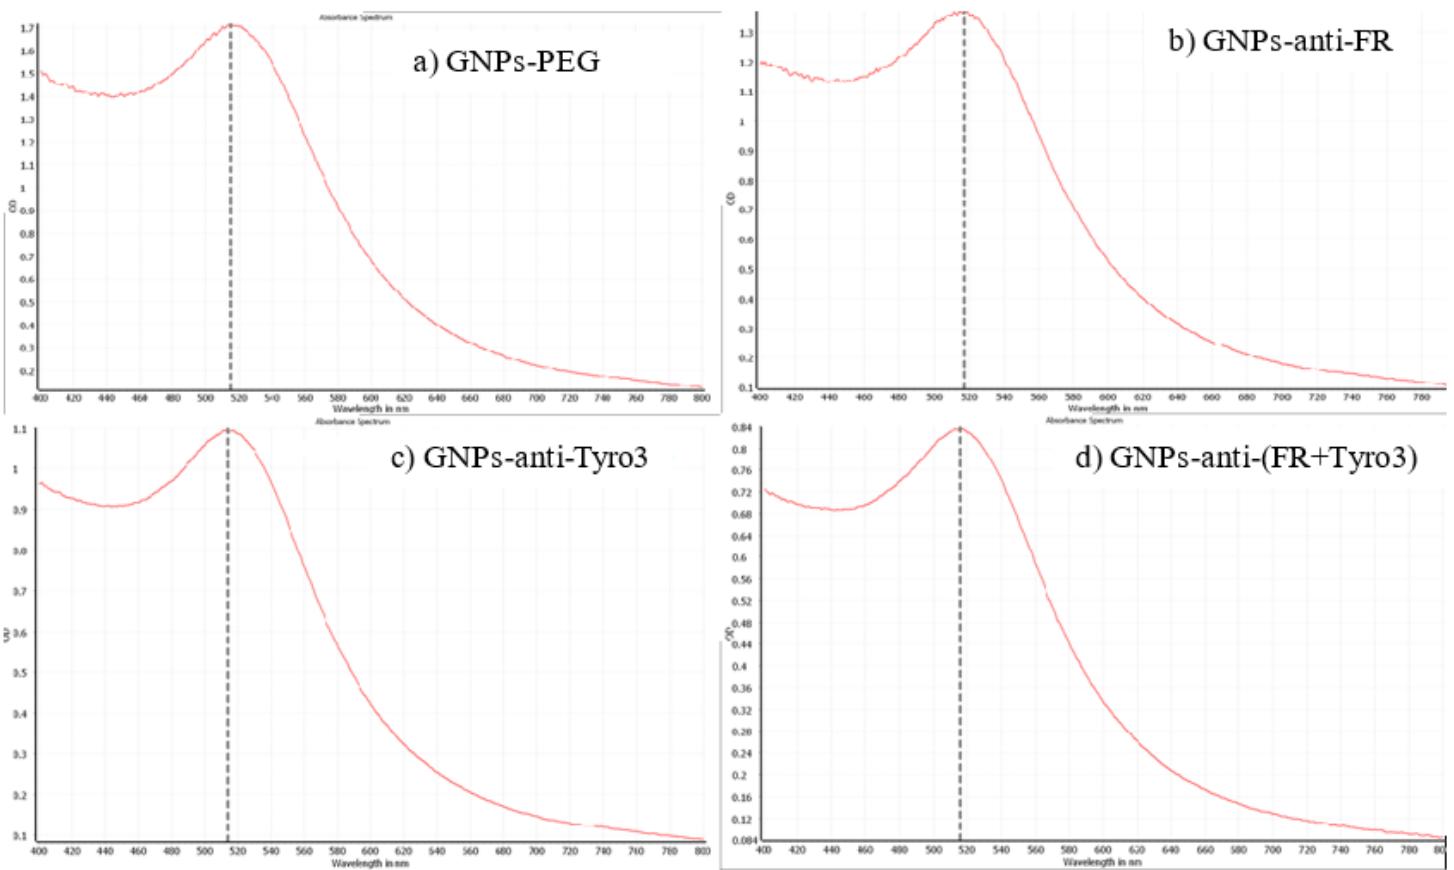


Figure 2

UV-Vis spectra of all 4 GNPs constructs a) GNPs-PEG b) GNPs-anti-FR c) GNPs-anti-Tyro3 d) GNPs-anti-(FR+Tyro3).

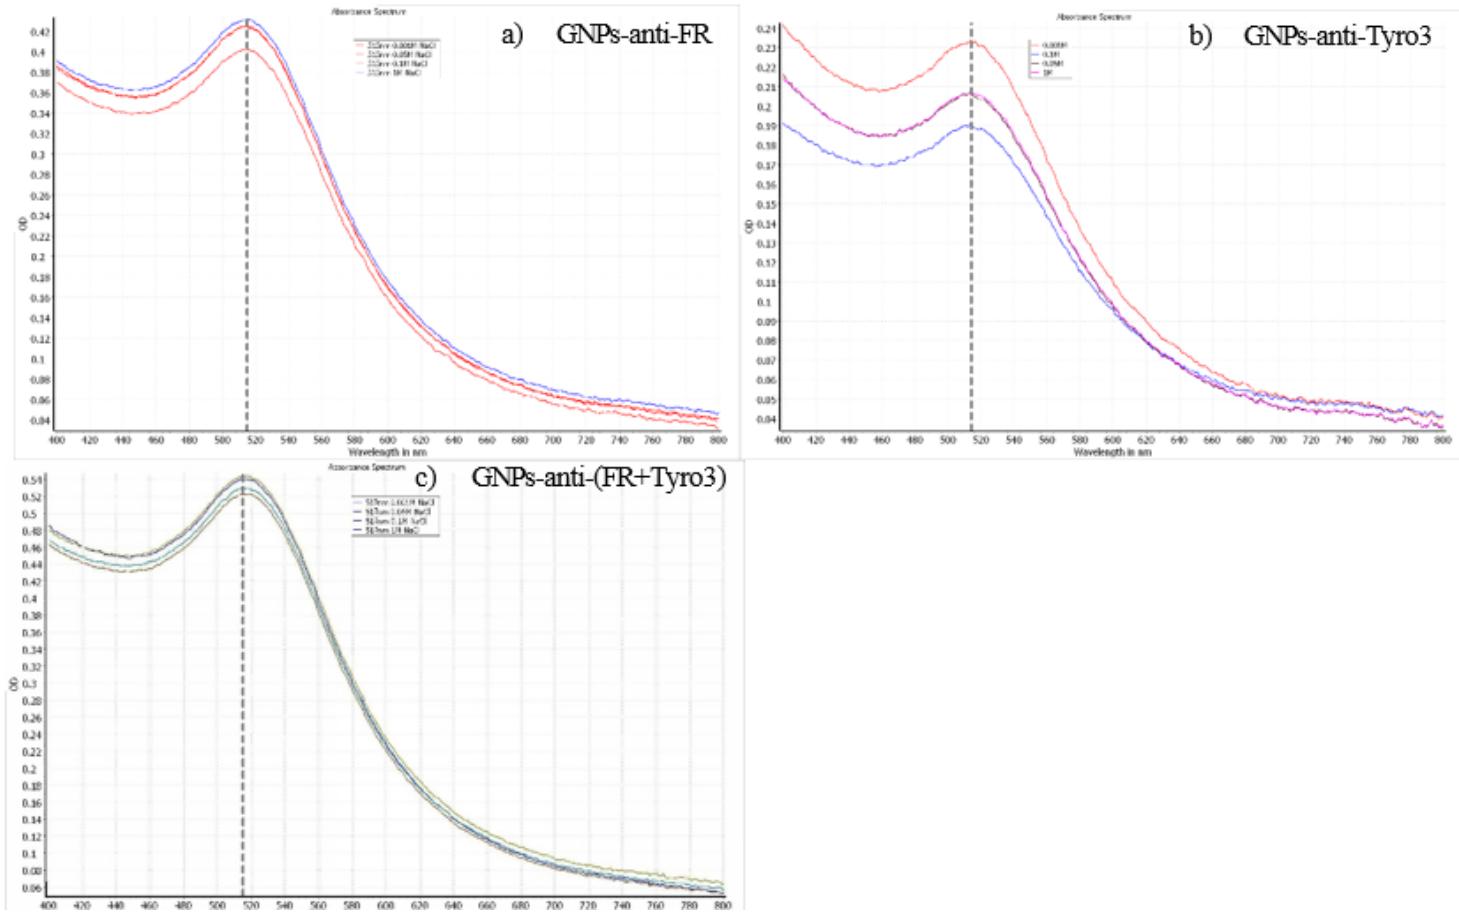


Figure 3

The stability of 5a) GNPs-anti-FR 5b) GNPs-anti-Tyro3 and 5c) GNPs-anti-(FR+Tyro3) at different NaCl concentration solutions (0.001M – 1M). UV-Vis peak show no red-shift or broadening of the peak.

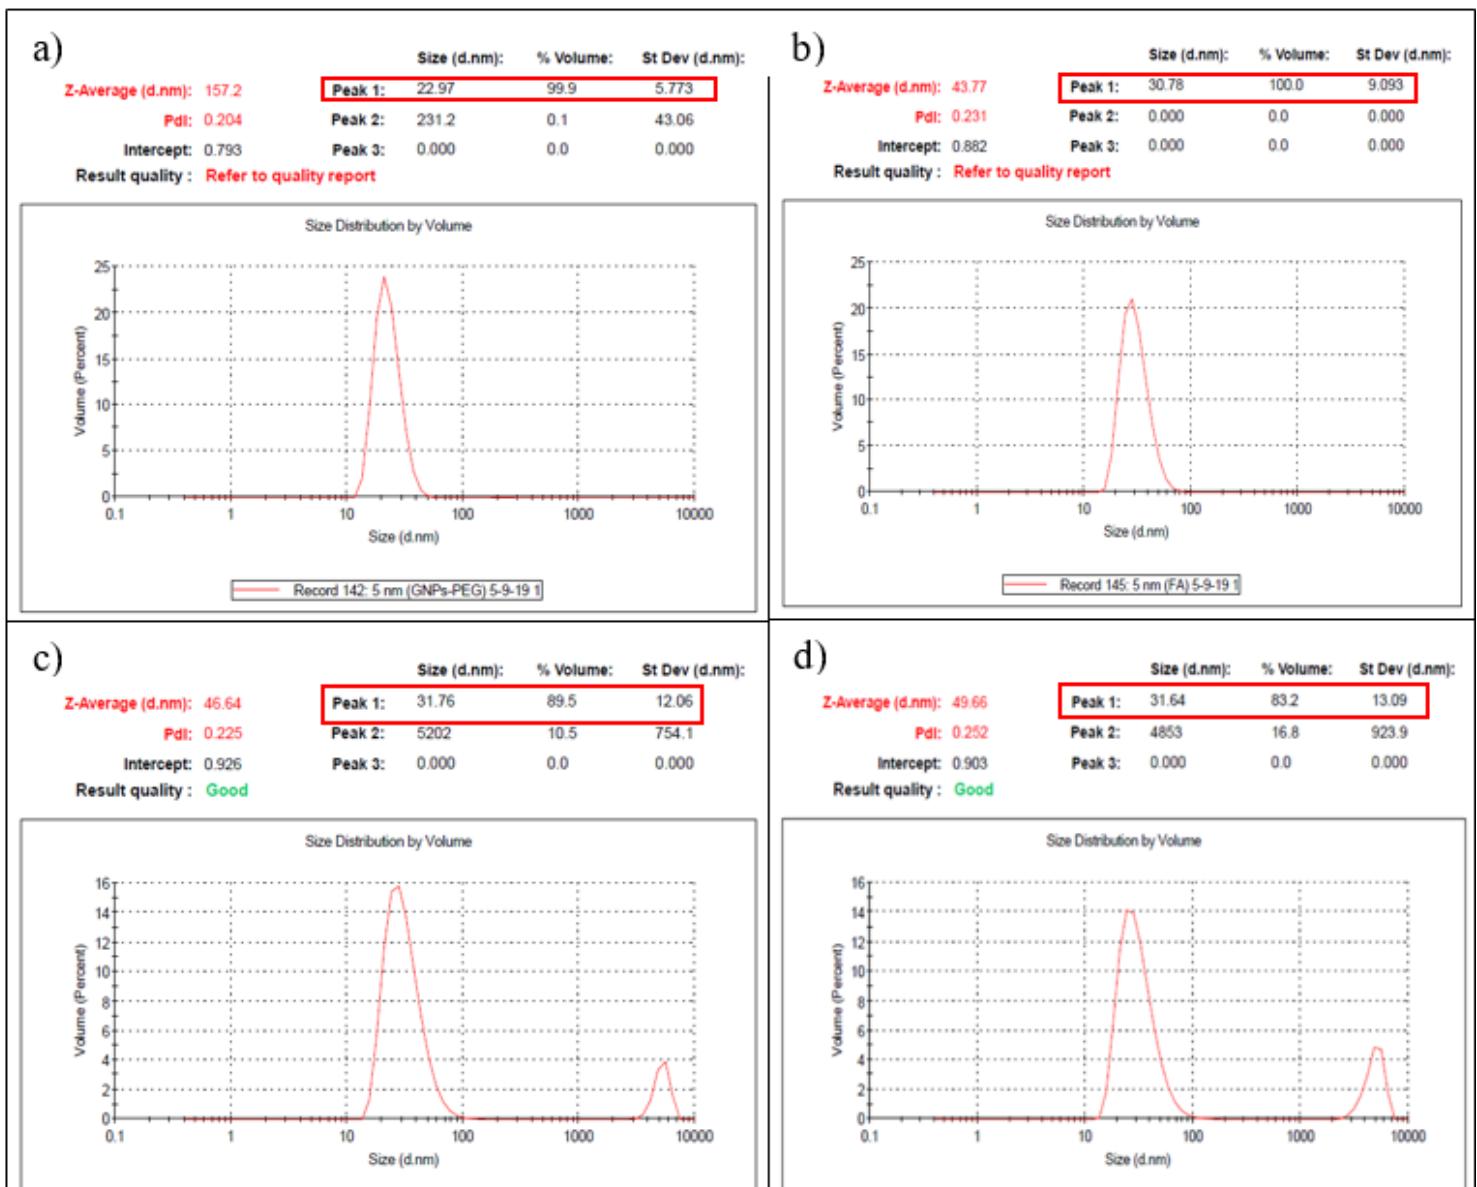


Figure 4

Hydrodynamic size of GNPs are shown in figure 4a, 4b, 4c and 4d of GNPs-PEG, GNPs-anti-FR, GNPs-anti-Tyro3 and GNPs-anti-(FR+Tyro3), respectively. PDI <0.03. The corresponding molecular weights are shown in Figure 6 and Figure 7

Bradford Standard IgG Curve

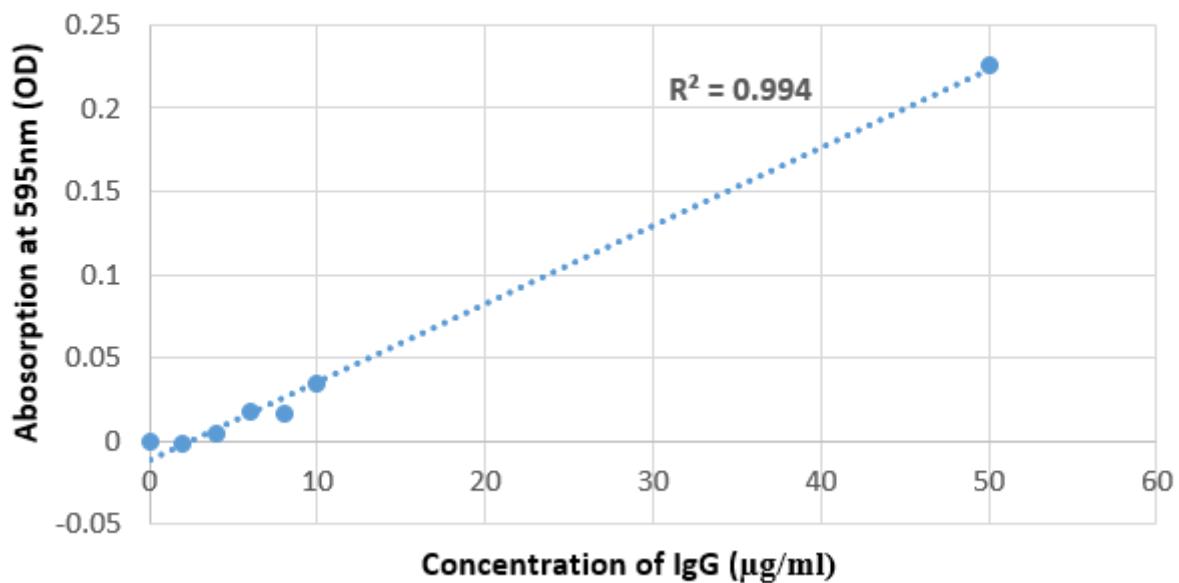


Figure 5

Calibration curve using IgG antibody in Bradford assay.

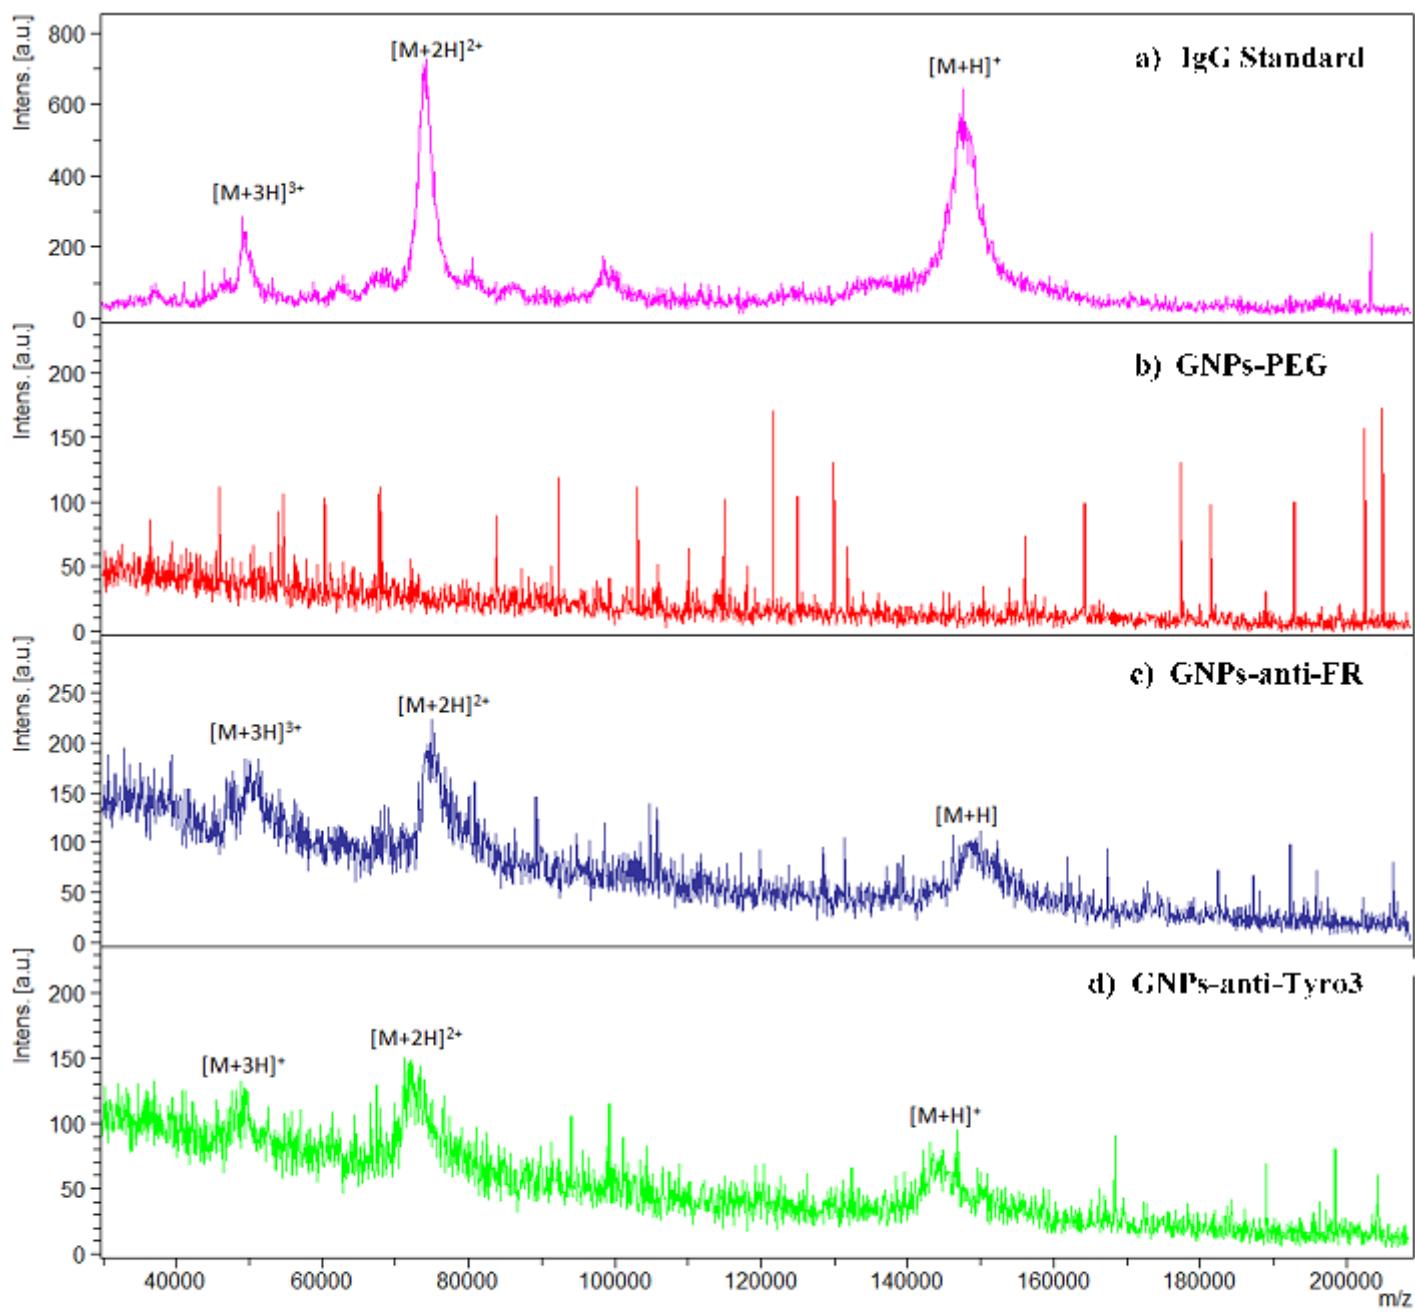


Figure 6

MALDI-TOF spectra for a) IgG as standard, b) GNPs-PEG, c) GNPs-anti-FR and d) GNPs-anti-Tyro3 is shown. High intensity peaks for IgG $[M+H]^+ = m/z$ 148,286, $[M+2H]^{2+} = 74,478$ and $[M+3H]^{3+}$ is seen. Spectra in c) and d) shows the same peaks, however, they are absent in GNPs-PEG.

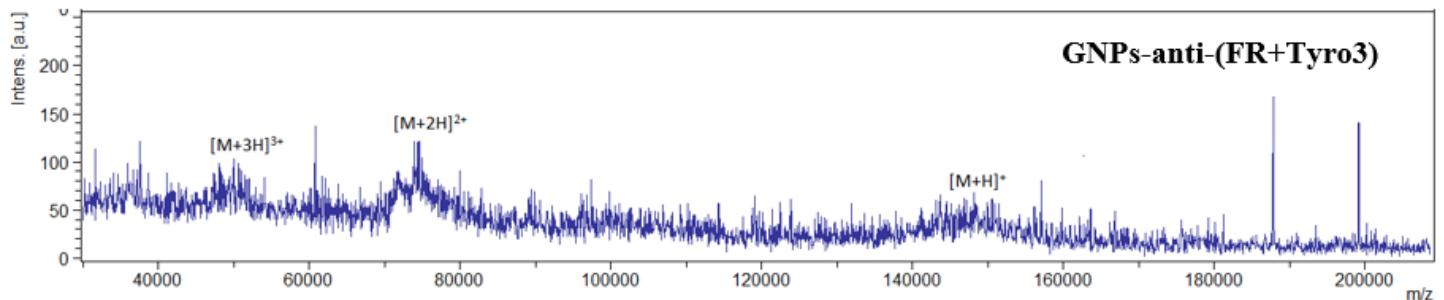


Figure 7

MALDI-TOF spectrum for GNPs-anti-(FR+Tyro3) also shows all three intensity peaks representative of IgG antibody.

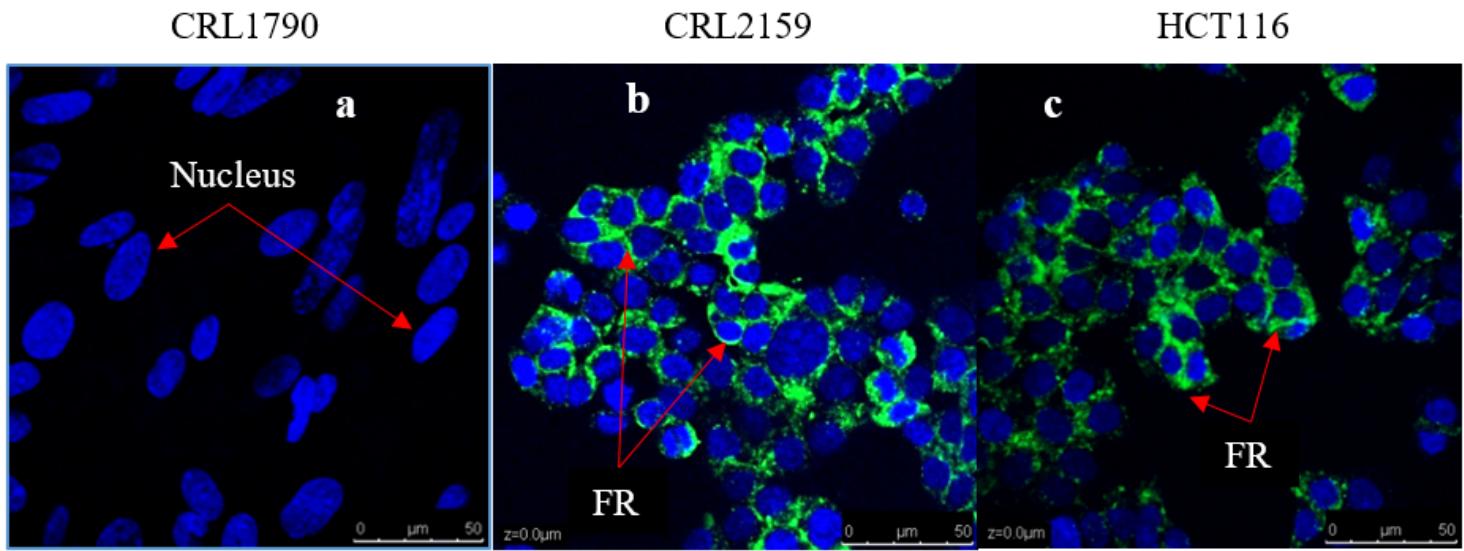


Figure 8

Figure shows the relative expression of FR in all three cell lines. DAPI stains the nucleus blue while FITC stains the FR membranous receptors in green. a) Colon Epithelium (CRL1790), b) Duke' B carcinoma (CRL2159) and c) Colorectal carcinoma (HCT116). Clear expression patterns can be seen of FR receptors being upregulated in CRL2159 and HCT116 compared to CRL1790. Scale bar = 50 μ m. Magnification 40X.

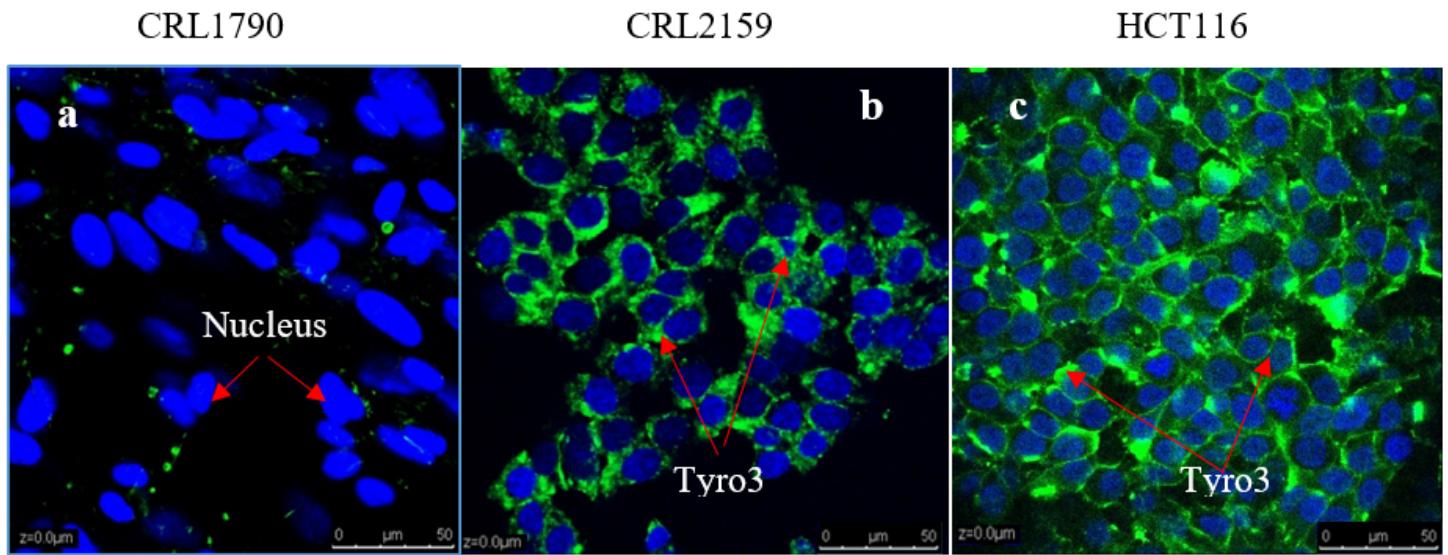


Figure 9

Figure shows the relative expression of Tyro3 receptors in three types of cell lines. DAPI stains the nucleus blue while FITC stains the Tyro3 membranous receptors in green. a) Colon Epithelium (CRL1790), b) Duke' B carcinoma (CRL2159) and c) Colorectal carcinoma (HCT116). Clear expression patterns can be seen of Tyro3 receptors being upregulated in CRL2159 and HCT116 compared to CRL1790. Scale bar = 50 μ m. Magnification 40X.

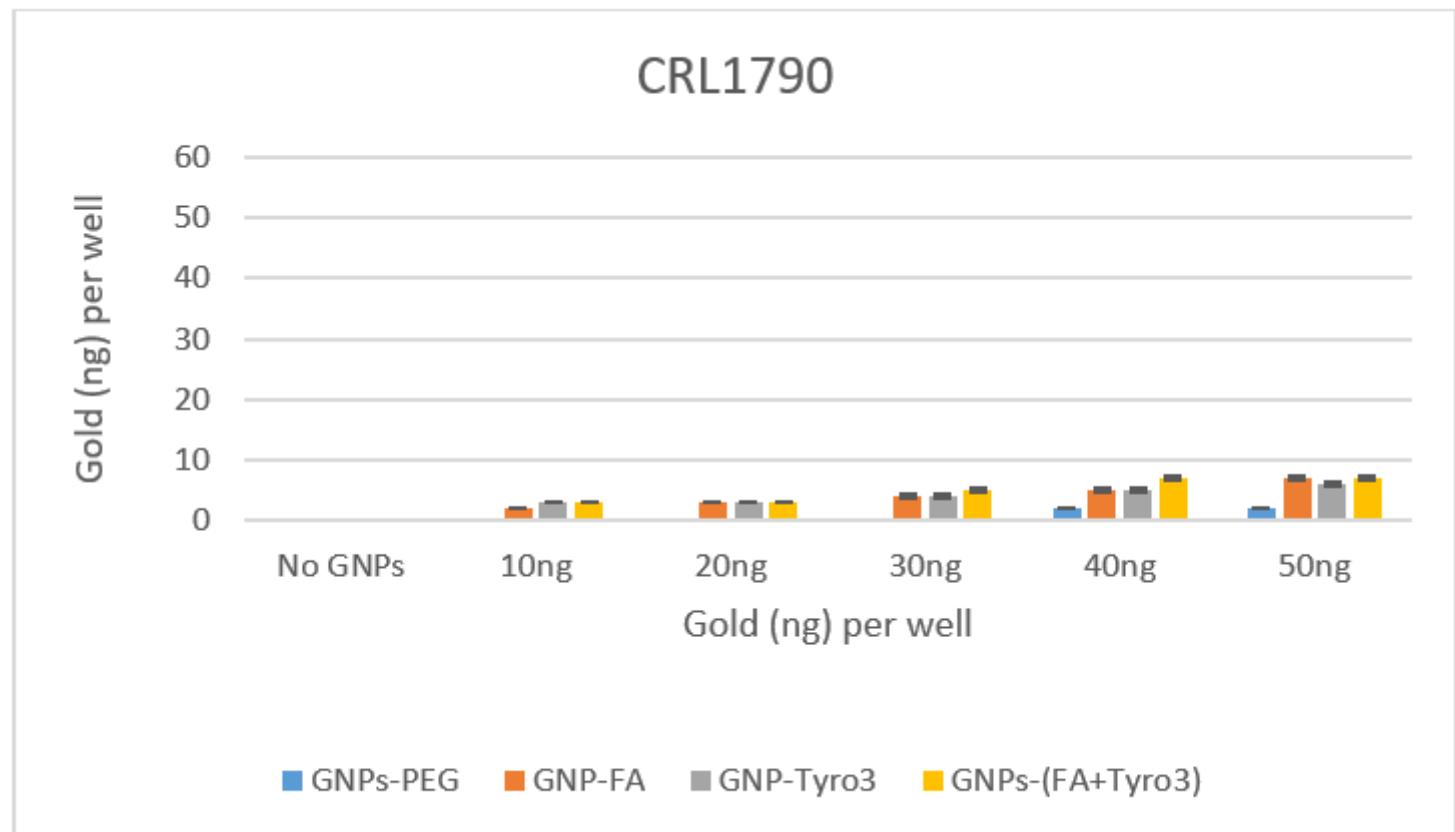


Figure 10

Internalisation all 4 GNP constructs in CRL1790 cell lines. Internalisation is shown for each well. Experiments were done in triplicates ($n=3$). ANOVA = $p<0.05$. Standard error of mean represents three or more replicates.

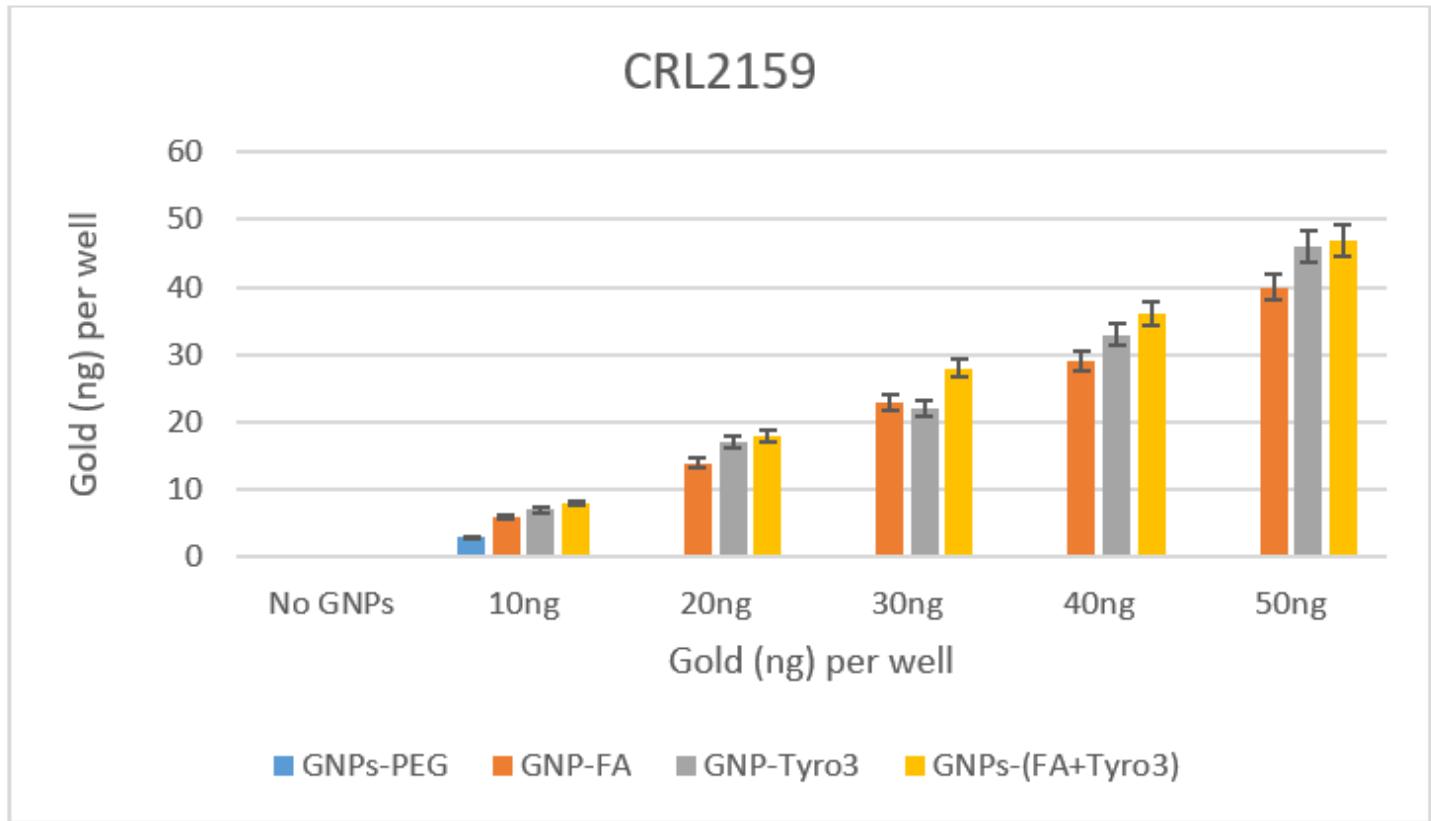


Figure 11

Internalisation all 4 GNP constructs in CRL2159 cell lines Internalisation is shown for each well. Experiments were done in triplicates ($n=3$). ANOVA = $p<0.05$. Standard error of mean represents three or more replicates.

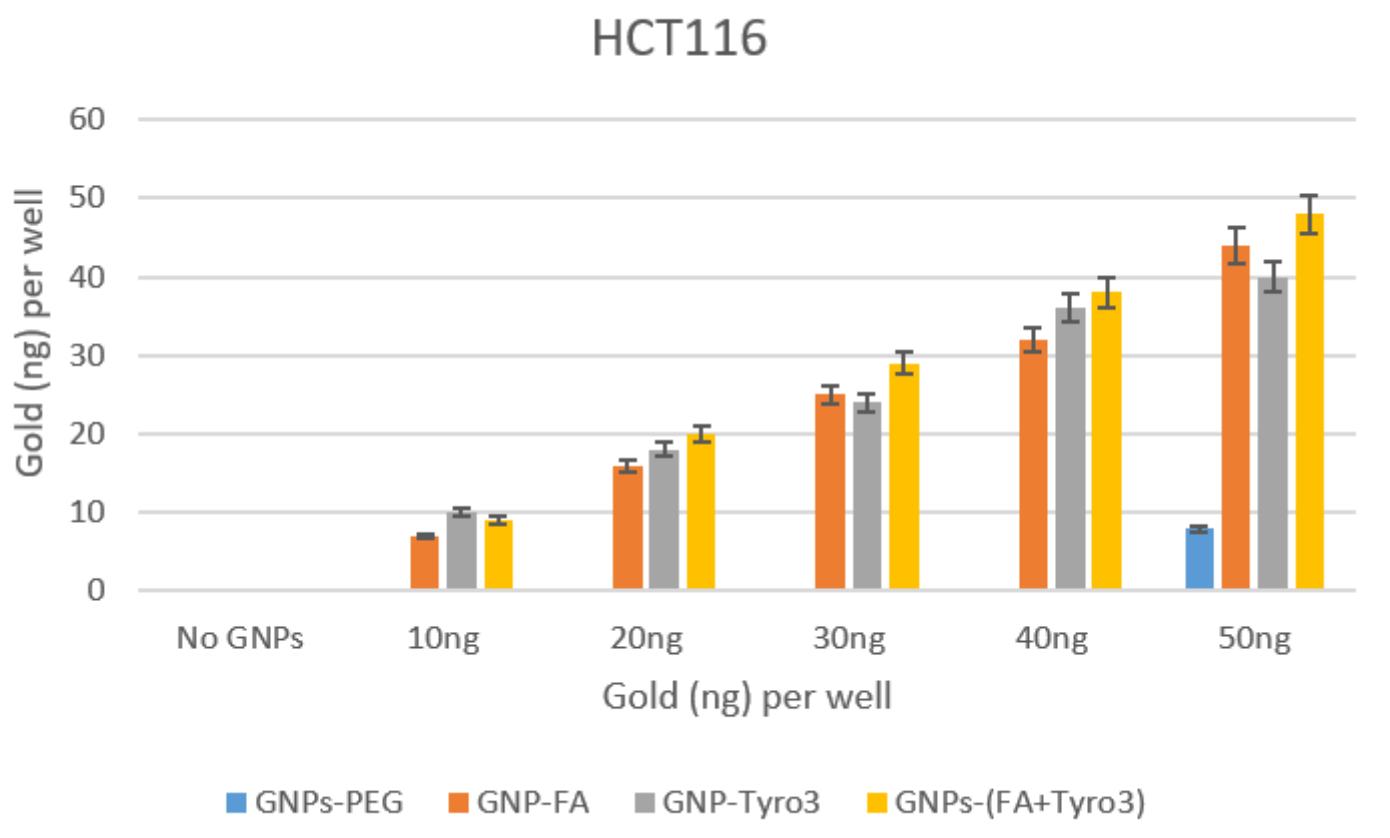


Figure 12

Internalisation all 4 GNP constructs in HCT116 cell lines Internalisation is shown for each well. Experiments were done in triplicates ($n=3$). ANOVA = $p<0.05$. Standard error of mean represents three or more replicates.

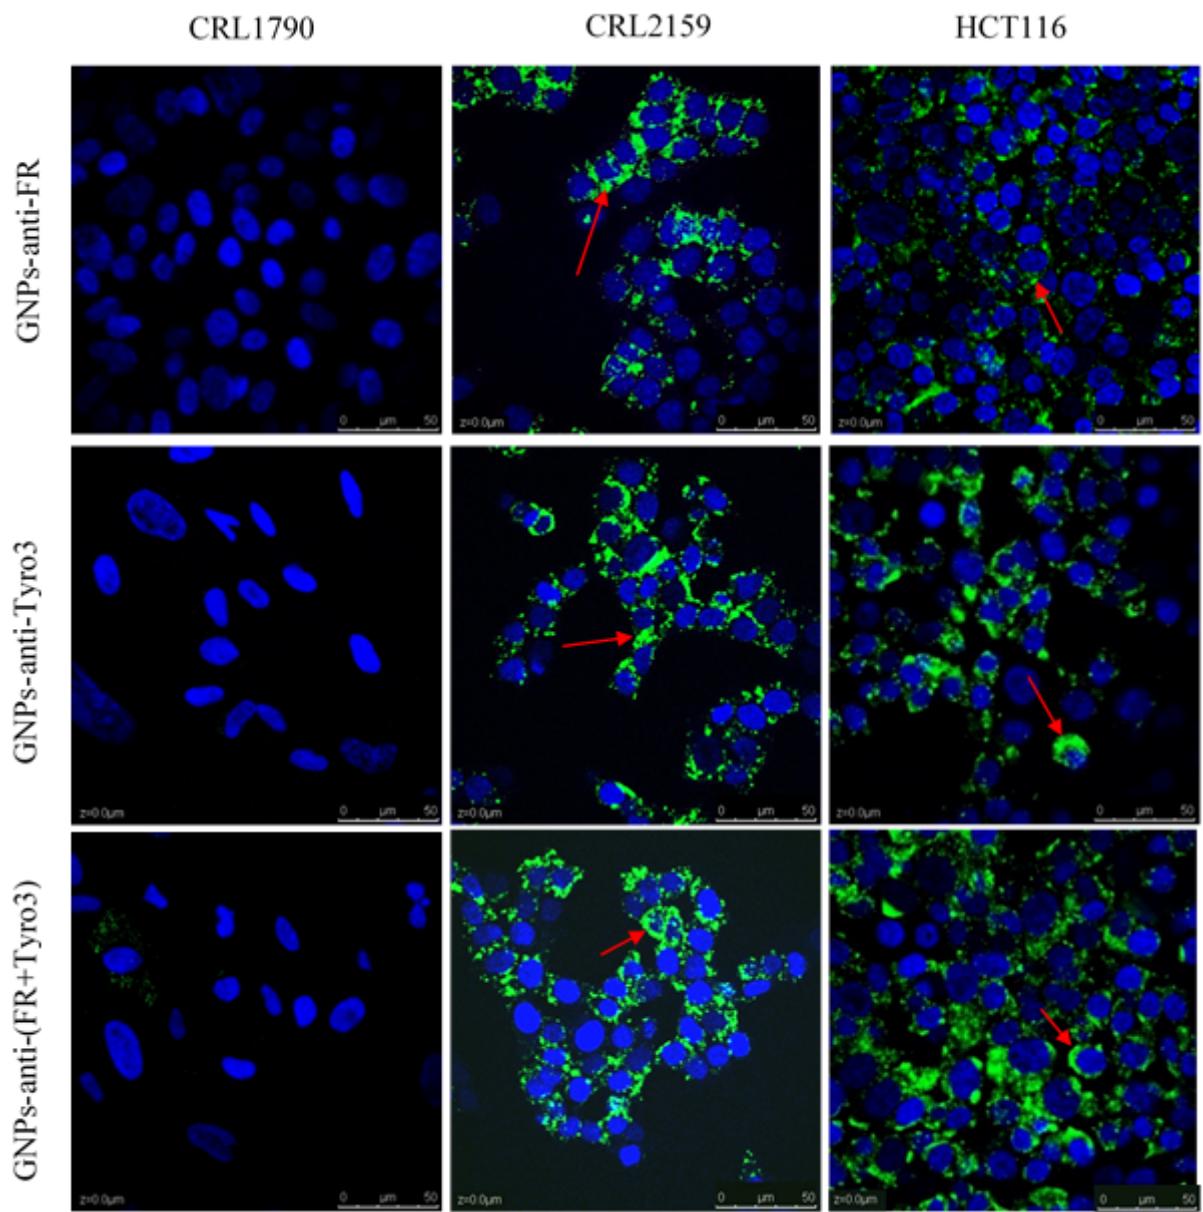


Figure 13

Figure shows internalisation of GNPs-anti-FR, GNPs-anti-Tyro3 and GNPs-anti-(FR+Tyro3) (red arrows) at 50ng in all three cell lines. Nuclei were stained in blue and GNPs in green. Experiments were repeated in triplicates (n=3). Scale bar = 50μm. Magnification 40X.

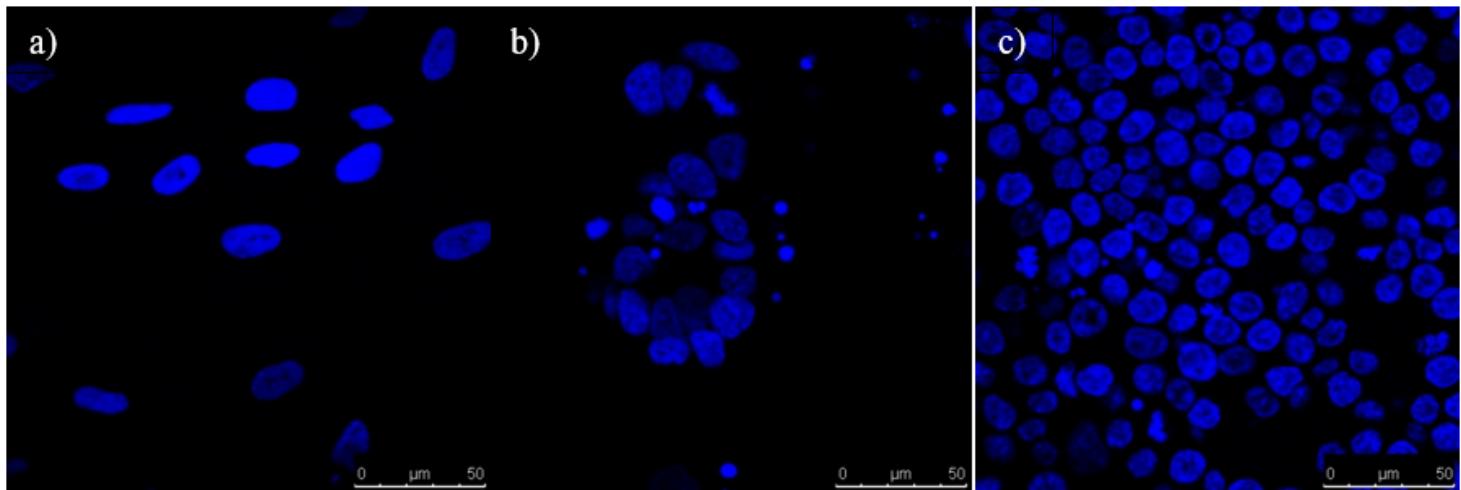


Figure 14

All three cell lines A) CRL1790, B) CRL2159 and C) HCT116 from confocal microscopy are shown. The images are represented as control for each cell line without any antibody-coated GNPs. The nuclei of the cell is represented in blue. (Scale bar = 50 μ m). Magnification 40X.

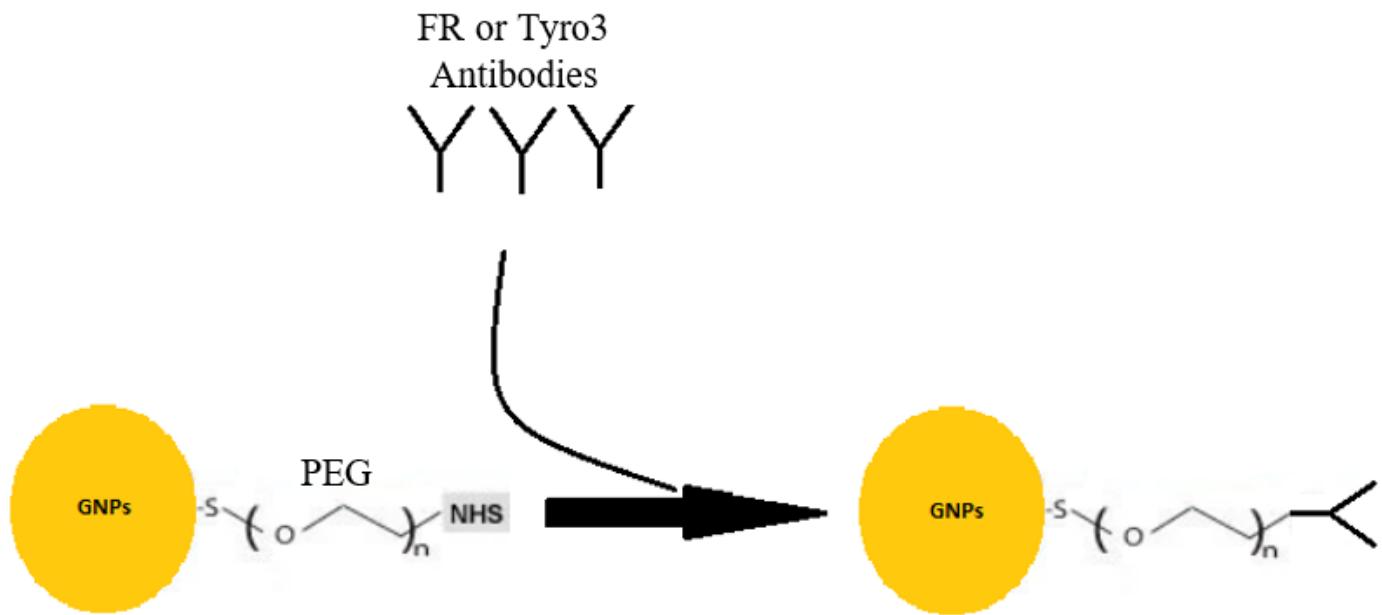


Figure 15

Figure shows the attachment of antibodies to GNPs-PEG