

Theoretical prediction of two-dimensional BC₂X (X=N, P, As) monolayers: Ab initio investigations

A. Bafekry (✉ bafekry.asad@gmail.com)

Department of Physics, University of Antwerp, Groenenborgerlaan 171, B-2020 Antwerp, Belgium

N. Naseri

Department of Physics, Kermanshah Branch, Islamic Azad University, 6718997551, Kermanshah, Iran

F. Faraji

Micro and Nanotechnology Graduate Program, TOBB University of Economics and Technology, Sogutozu Caddesi No 43 Sogutozu, 06560, Ankara, Turkey

M. M. Fadlallah

Department of Physics, Faculty of Science, Benha University, 13518 Benha

D. M. Hoat

Institute of Theoretical and Applied Research, Duy Tan University, Ha Noi 100000

H. R. Jappor

Department of Physics, College of Education for Pure Sciences, University of Babylon, Hilla

M. Ghergherehchi

Department of Electrical and Computer Engineering, Sungkyunkwan University, 16419 Suwon

D. Gogova

Department of Physics, Chemistry and Biology, Linkoping University, 58183 Linkoping

Research Article

Keywords:

Posted Date: April 4th, 2022

DOI: <https://doi.org/10.21203/rs.3.rs-1418447/v1>

License:  This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

Theoretical prediction of two-dimensional BC₂X (X=N, P, As) monolayers: Ab initio investigations

A. Bafekry,^{1,*} M. Naseri,^{2,3} M. Faraji,⁴ M. M. Fadlallah,⁵ D. M. Hoat,^{6,7} H. R. Jappor,⁸ M. Ghergherechi,^{9,†} and D. Gogova¹⁰

¹*Department of Physics, University of Antwerp, Groenenborgerlaan 171, B-2020 Antwerp, Belgium*

²*Department of Physics, Kermanshah Branch, Islamic Azad University, 6718997551, Kermanshah, Iran*

³*Department of Chemistry, Department of Physics and Astronomy,*

CMS - Center for Molecular Simulation, Institute for Quantum Science and Technology, Quantum Alberta, University of Calgary, 2500 University Drive NW, Calgary, Alberta, Canada, T2N 1N4

⁴*Micro and Nanotechnology Graduate Program, TOBB University of Economics and Technology, Sogutozu Caddesi No 43 Sogutozu, 06560, Ankara, Turkey*

⁵*Department of Physics, Faculty of Science, Benha University, 13518 Benha, Egypt*

⁶*Institute of Theoretical and Applied Research, Duy Tan University, Ha Noi 100000, Viet Nam*

⁷*Faculty of Natural Sciences, Duy Tan University, Da Nang 550000, Viet Nam*

⁸*Department of Physics, College of Education for Pure Sciences, University of Babylon, Hilla, Iraq*

⁹*Department of Electrical and Computer Engineering, Sungkyunkwan University, 16419 Suwon, Korea*

¹⁰*Department of Physics, Chemistry and Biology, Linköping University, 58183 Linköping, Sweden*

In this work, novel two-dimensional BC₂X (X=N, P, As) monolayers with X atoms out of the B-C plane, are predicted by means of the density functional theory. The structural, electronic, optical, photocatalytic and thermoelectric properties of the BC₂X monolayers have been investigated. Stability evaluation of the BC₂X single-layers is carried out by phonon dispersion, ab-initio molecular dynamics (AIMD) simulation, elastic stability, and cohesive energies study. The mechanical properties reveal all monolayers considered are stable and have brittle nature. The band structure calculations using the HSE06 functional reveal that the BC₂N, BC₂P and BC₂As are semiconducting monolayers with indirect bandgaps of 2.68 eV, 1.77 eV and 1.21 eV, respectively. The absorption spectra demonstrate large absorption coefficients of the BC₂X monolayers in the ultraviolet range of electromagnetic spectrum. Furthermore, we disclose the BC₂N and BC₂P monolayers are potentially good candidates for photocatalytic water splitting. The electrical conductivity of BC₂X is very small and slightly increases by raising the temperature. Electron doping may yield greater electric productivity of the studied monolayers than hole doping, as indicated by the larger power factor in the n-doped region compared to the p-type region. These results suggest that BC₂X (X=N, P, As) monolayers represent a new promising class of 2DMs for electronic, optical and energy conversion systems.

I. INTRODUCTION

The discovery of graphene has motivated enormous theoretical and experimental endeavors in two-dimensional (2D), van der Waals (vdW) materials study,¹ for attaining new properties and designing of innovative devices. A large number of 2D materials have been tested including elemental semiconductors (phosphorene, stanene, silicene, borophene, antimonene, germanene),² carbon nitrides,³ indium and gallium chalcogenide (GaS, InSe, GaSe),⁴ transition metal chalcogenide (FeSe, FeTe, CdS, CdSe, MoSe₂),⁵⁻⁷ pnictogens-based monolayer (Sb₂X₃ (X= S, Se, Te)),⁸ transition metal oxides (ZnO₂, CdO₂, HgO₂),⁹ and Janus materials.¹⁰

Potential applications in almost all fields of modern technology, such as energy storage sensors, field-effect transistors, spintronics, photocatalytic hydrogen production, catalysis, and supercapacitors¹¹⁻¹³ have been demonstrated. In latest years, 2D materials based on boron element have drawn a lot of interest due to its exceptional layer structure and excellent electronic, optical and mechanical properties. Prompted by such fascinating properties, the boron-based 2D materials poten-

tial can be used in thermoelectric applications,¹⁴ battery applications,¹⁵ clean energy storage,¹⁶ water cleaning,¹⁷ sensing,¹⁸ photovoltaic,¹⁹ and many more. In particular, as the front runner in boron-carbon materials family, a compound of BC shows a large surface-to-volume ratio, tunable bandgap, high thermal stability, numerous active sites, and multilateral bonding of both carbon and boron atoms, making it an excellent candidate for optoelectronics applications. Besides, carbon and boron can indeed be mixed to produce a variety of 2D materials, however, some of them have stable and strong covalent bonds.^{20,21}

Among the number of detailed investigations, both experimental and theoretical, studies focused mainly on BCN monolayer, composed of boron, carbon, and nitrogen atoms.²²⁻²⁴ The proposed new type of semiconductor monolayer (BCN) exhibited a range of band structures from semiconducting to insulating, based on their geometry and composition²⁵ as well as high carrier mobility and absorption in the visible range.²⁶ Thus, it proffers a variety of applications in catalysis, hydrogen evolution reaction, electrochemical sensors, transistors, electrochemical energy storage devices, and nanoelectronics.²⁷⁻³¹ On the other hand, 2D BCN monolayer has been experimentally fabricated.³² Furthermore, other authors expected

that free-standing monolayers can be produced by peeling because of the extreme intermolecular bonding between the atoms within the monolayer.³³ Zhang Li et al. have found by MD simulations that the hexagonal graphene-like BCN monolayer exhibits a lower thermal conductivity than graphene.³⁴ However, as has been exposed in the work of Zhang et al., BCN monolayer has a fracture strength value (81.4-93.5 GPa) lower than that of graphene and the temperature has a sturdy impact on its mechanical properties.³⁵ In this context, Thomas and Lee predicted that the BCN monolayer has perfect mechanical properties with higher directional anisotropy, higher flexibility and Young's modulus lesser than that of graphene.³⁶ Furthermore, the 2D BC₂N monolayer, with all atoms in one plane, has been synthesized. The experimental results show that BC₂N monolayer is a semiconductor with a direct bandgap of ~ 2 eV.⁴⁰ Its electronic and thermal properties have been studied. The final conclusion was that BC₂N monolayer is a good candidate for thermoelectric devices.^{37,38} Also, the BC₂N monolayer can be a suitable anode in Li- and Na-ion batteries.³⁹ Considering the fact that nitrogen can enhance the electronic, thermal, optical, and mechanical properties, it is interesting to study the impact of phosphorus (P) and arsenic (As) neighboring N in the nitrogen (pnictogen) group on these properties.

In line with the ongoing efforts made in the field of hexagonal 2D structures, in the present study, we propose and systematically investigate for the first time the structural, electronic structure, optical and thermoelectric properties of three kinds of a graphene-like BC₂X (X=N, P, As) monolayers, with X atoms out of the plane of the C and B atoms. Remarkably, the intermixture of BC and N, P, and As atoms can dramatically change the electronic structure, enhance the dynamic stability of various 2D materials, and may lead to BC₂X with bandgaps in the visible range. Our simulation results provide some guidelines for future experimental studies on graphene-like BC₂X monolayers.

II. METHOD

The density-functional theory calculations were performed by using the plane-wave basis projector augmented wave and the generalized gradient approximation of Perdew-Burke-Ernzerhof (PBE)^{42,43} as implemented in the VASP package.^{44,45} The band structure calculations were obtained by the screened-nonlocal-exchange functional (HSE06)⁴⁶ for a more accurate description. The kinetic energy cut-off was 520 eV, the variation in the energies was below 10^{-5} eV and the total Hellmann-Feynman forces were less than 0.05 eV/Å for the optimized structures. The distance between two neighboring sheet, in z direction, was 20 Å, which was sufficient to avoid any image interaction. The \mathbf{k} -point mesh was $20 \times 20 \times 1$ Monkhorst-Pack scheme⁴⁷ for the primitive unit cell and the charge transfer analysis was performed

using the Bader technique.⁴⁸ The vibrational properties were calculated as implemented in the PHONOPY code.⁴⁹ The optical properties such as dielectric constants, absorption spectra, and reflectivity were studied on the basis of the HSE06 functional. The training set is prepared by conducting ab-initio molecular dynamics (AIMD) simulations over $4 \times 4 \times 1$ supercells with $9 \times 9 \times 1$ k-point grids. AIMD simulations are carried out at 300 K.

III. STRUCTURAL PROPERTIES

The top and side figures of the structure of the BC₂X (X=N, P, As) monolayers are shown in Fig. 1(a). The hexagonal primitive unit cell with $P3m1$ space group is formed by four atoms and indicated by a parallelogram. The structural parameters are also defined in the Fig. 1(a). We found that the lattice parameters of the BC₂N, BC₂P and BC₂As sheets are 2.56 Å, 2.82 Å and 2.91 Å, respectively. The calculated bond lengths of B-C (d_1), C-C (d_2) and C-X (d_3) are respectively: 1.49, 1.65 and 1.56 Å (BC₂N), 1.63 Å, 1.65 Å and 1.86 Å (BC₂P) and in the case of BC₂As they are 1.68 Å, 1.62 Å, 1.95 Å. The bond lengths and angles, and thickness are tabulated (see Table I). The two angles of B-C-B and C-X-C are determined to be 117°, 109° (BC₂N), 118°, 119° (BC₂P) and 118°, 120° (BC₂As). Notice that the studied monolayers are high anisotropic lattice, while the thickness of the BC₂N, BC₂P and BC₂As are 2.41 Å, 2.73 Å and 2.79 Å, respectively. We found that the bond lengths, bond angles and thickness increase as the atomic radius of X atom increases (see table I).

The electron localization function (ELF) considered monolayers is illustrated in Fig. 1(b). The red (blue) color indicates high (low) electron density in the ELF. Obtained results demonstrate that there is a charge transfer from B/C to X atoms in BC₂X with a corresponding amount of 0.702e, 0.80e, and 1.10e for N, P, and As, respectively. The B/C atoms are positively charged ions that surround the N, P and As negatively charged ions.

IV. DYNAMICAL AND THERMAL STABILITY

The phonon dispersion of BC₂X (X=N, P, As) monolayers are also calculated to evaluate their dynamical stability. The phonon bands of the considered monolayers is illustrated in Fig. 1(c). Obviously, the phonon branches do not contain imaginary frequencies which confirms the dynamical stability of the studied monolayers. It is shown that each monolayer material exhibits a quadratic dispersion for the ZA phonon branch around the Γ point as a direct consequence of the 2D nature of the structure. The highest optical phonon branches are found to be at frequencies approximately 1600, 1150, and 1000^{-1} for BC₂N, BC₂P, and BC₂As, respectively. This

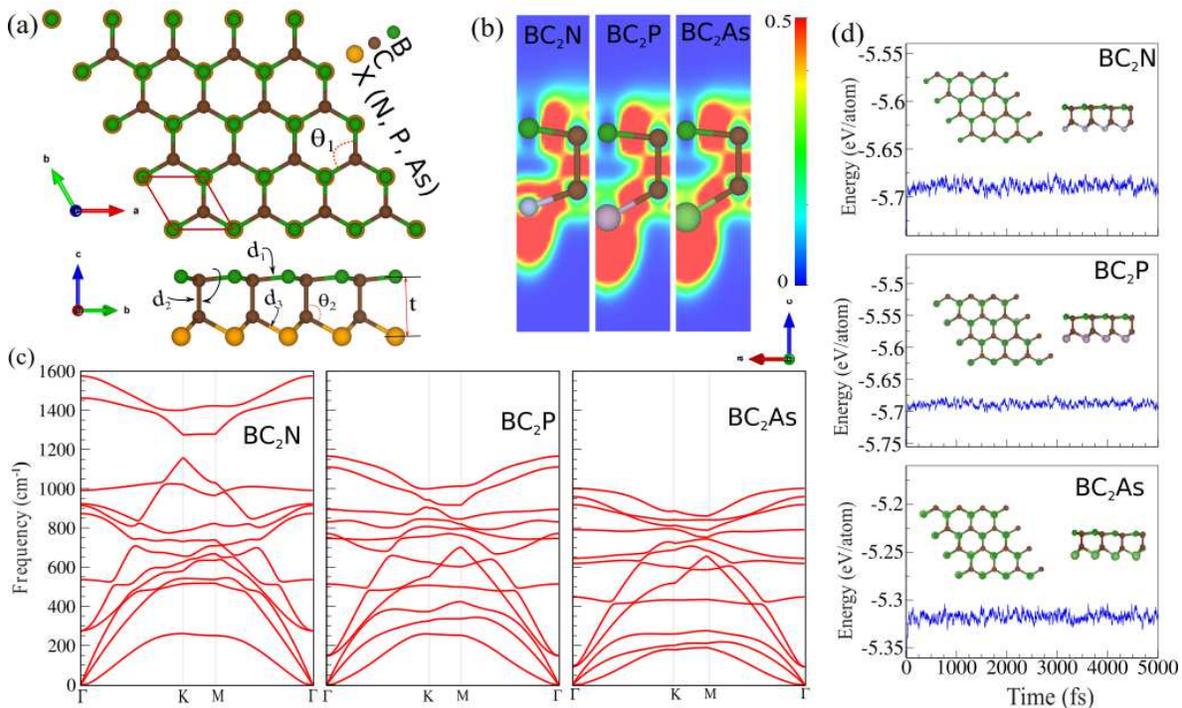


Figure 1. (a) Top and side views of monolayer structure, (b) contour plot of the electron localization function (ELF), (c) phonon dispersions and (d) Ab initio molecular dynamics (AIMD) 300 K temperature for the BC_2X ($X=N, P, As$) monolayers. The primitive unit cell (red parallelogram) and the structural parameters are illustrated. Red (blue) color refers to the high (low) electron density in the ELF. The structure after 5 ps of simulation demonstrated as insets in the AIMD.

Table I. Structural and electronic parameters of BC_2X ($X=N, P, As$) monolayers as shown in Figs. 1(a,b). including lattice constants a ; bond lengths between B-C, C-C and C-X atoms ($d_{1,2,3}$); thickness defined by the difference between the largest and smallest z coordinates of B and X atoms (t); bond angles between B-C-B and C-X-C atoms $\theta_{1,2}$; cohesive energy per atom, (E_{coh}); charge transfer (ΔQ) between atoms B and X atoms; work function (Φ) bandgap (E_g) of PBE (HSE06); bulk modulus (B); shear modulus (S); Young's modulus (Y); Poisson's ratio (ν); and bulk/shear ratio (B/S), respectively.

	a (Å)	$d_{1,2,3}$ (Å)	t (Å)	$\theta_{1,2}$ (°)	E_{coh} (Å)	ΔQ (eV/atom)	Φ (e)	E_g (eV)	B (GPa)	S (GPa)	Y (GPa)	ν	BS
BC_2N	2.56	1.49, 1.65, 1.56	2.41	117, 109	-6.40	0.70	4.32	1.51 (2.68)	14.63	9.20	22.81	0.24	1.59
BC_2P	2.82	1.63, 1.65, 1.86	2.73	118, 119	-6.16	0.80	4.00	0.78 (1.77)	4.16	3.11	7.42	0.20	1.35
BC_2As	2.91	1.68, 1.62, 1.95	2.79	118, 120	-5.77	1.10	3.50	0.39 (1.21)	3.54	2.77	6.60	0.19	1.28

indicates that as the atomic mass increases from N to As, the frequency of vibrations decreases and the material gets quite softer. Moreover, the phonon gap between the highest two optical branches and the other phonons decreases as going from N to As. We then examine the thermal stability of BC_2X monolayers by evaluating ab initio molecular dynamics (AIMD) trajectories at 300 K. The AIMD simulations of BC_2X monolayers at 300 K temperature are shown in Figs. 1(d). The different views of the optimized structure after 5 ps of simulation demonstrated in the insets. Analysis of the AIMD trajectories also reveals that all the structures could stay intact at 300 K with very stable temperature and energy profiles, proving the thermal stability of the BC_2X monolayers. This finding will definitely stimulate efforts in experimental synthesis of 2D BC_2X monolayers.

V. MECHANICAL PROPERTIES

The cohesive energy per atom was calculated as following:

$$E_{coh} = (E_{tot} - E_B - 2E_C - E_X)/4, \quad (1)$$

where E_{tot} represents the total energy of the BC_2X monolayers. E_B , E_C and E_X represent the total energies of isolated single B, C and X (N, P and As) atoms, respectively, and 4 represents the total number of atoms in the primitive cell. Our results show that the cohesive energies are -6.40 eV/atom (BC_2N), -6.16 eV/atom (BC_2P) and -5.77 eV/atom (BC_2As). The more negative value of the cohesive energies suggests the more energetically stable monolayer is BC_2N . It can be seen that the structure

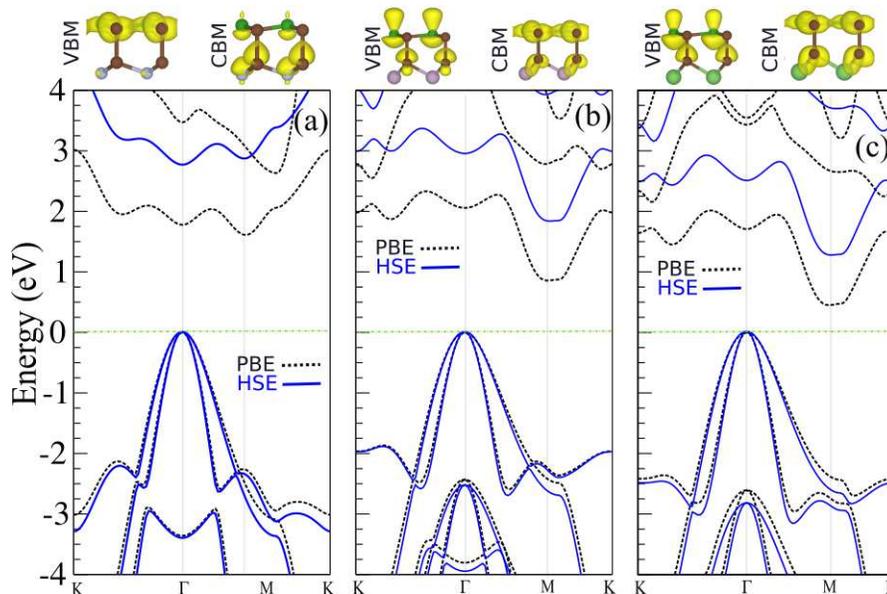


Figure 2. Electronic band structure calculated using the PBE and HSE06 functionals for (a) BC_2N , (b) BC_2P and (c) BC_2As monolayers. Charge densities of the valence band maximum (VBM) and conduction band minimum (CBM) orbitals are indicated on the top of the panel. Zero energy is set to the Fermi energy.

with a smaller atomic mass or atomic radius, and high electronegativity has the greater magnitude of cohesive energy, specifically, BC_2N has a higher electronegativity with that of N (3.04) as compared to the electronegativity of P (2.19) and As (2.18).

And last but not least the mechanical stability of BC_2X ($\text{X}=\text{N}, \text{P}, \text{As}$) monolayers has been studied using the harmonic approximation method. Thus, we found out that all BC_2X considered are mechanically stable. The computations prove that BC_2X monolayers satisfy the elastic stability criteria.⁵⁰ The elastic constants are used to determine the other mechanical parameters such as: the bulk (B), shear (S), and Young's (Y) moduli, Poisson's ratio (ν), and B/S ratio using the Voigt Reuss-Hill approximation⁵¹ (see Table I). The bulk modulus refers to the ability of the monolayer to withstand compressing under applied force. The bulk modulus are determined to be: 14.63, 4.16, and 3.54 GPa for the BC_2N , BC_2P , and BC_2As , respectively. It is evident that the BC_2N monolayer can withstand greater compression as compared with the other monolayers. This result is supported by the calculation of the Young's modulus, which is 22.81, 7.42, and 6.60 GPa for the BC_2N , BC_2P , and BC_2As , respectively. The shear modulus measures the resistance of the change to the structure, where the shear modulus increases as the material rigidity increases. The calculated S values are 9.20, 3.11, 2.77 GPa for $\text{X}=\text{N}, \text{P}$, and As respectively, which indicates that BC_2N monolayer has the highest rigidity within the members of this family. The B/S ratio measures the ductile or brittle nature of the material. We have determined the B/S is 1.59 (BC_2N), 1.35 (BC_2P) and 1.28 (BC_2As). Notice, that all BC_2X monolayers are brittle structures since the

B/S value is less than 1.75.⁵² Also, the calculation of the Poisson's ratio, ν , confirms the brittle behavior of the BC_2X sheets. We found out the values of ν to be: 0.24, 0.20, and 0.19 for $\text{X}=\text{N}, \text{P}$, and As , respectively, i.e., all of them are less than 0.33.⁵³

VI. ELECTRONIC PROPERTIES

The calculated electronic band structures of the BC_2X ($\text{X}=\text{N}, \text{P}, \text{As}$) monolayers are shown in Figs. 2(a-c). The charge densities of the valence band maximum (VBM) and conduction band minimum (CBM) orbitals are depicted in Figs. 2(a-c) (top parts). Our results demonstrate that BC_2N is an indirect semiconductor and has a bandgap of 1.51 eV using the PBE functional. However, the plane BC_2N has a direct experimental bandgap of ~ 2 eV and a theoretical PBE-based bandgap of 1.6 eV, which is larger than the value of our BC_2N monolayer.^{37,40} The VBM and CBM are located at the Γ and M point, respectively. Similarly, BC_2N , BC_2P and BC_2As are semiconductors with indirect bandgaps of 0.78 eV and 0.39 eV, respectively according to the PBE method. Due to the underestimated bandgap values by the PBE-calculations, the HSE06⁴⁶ hybrid functional was also utilized to evaluate the electronic band structure. The results obtained are depicted in Figs. 2(a-c) (blue curves). The bandgap value is calculated to be 2.68 eV using the HSE06 hybrid functional and the VBM and CBM are located at the Γ -point, resulting in a direct bandgap, which means the HSE06 approach changes the value and type of the bandgap of the BC_2N monolayer as compared with the PBE-based results. It is found out the HSE06 approach

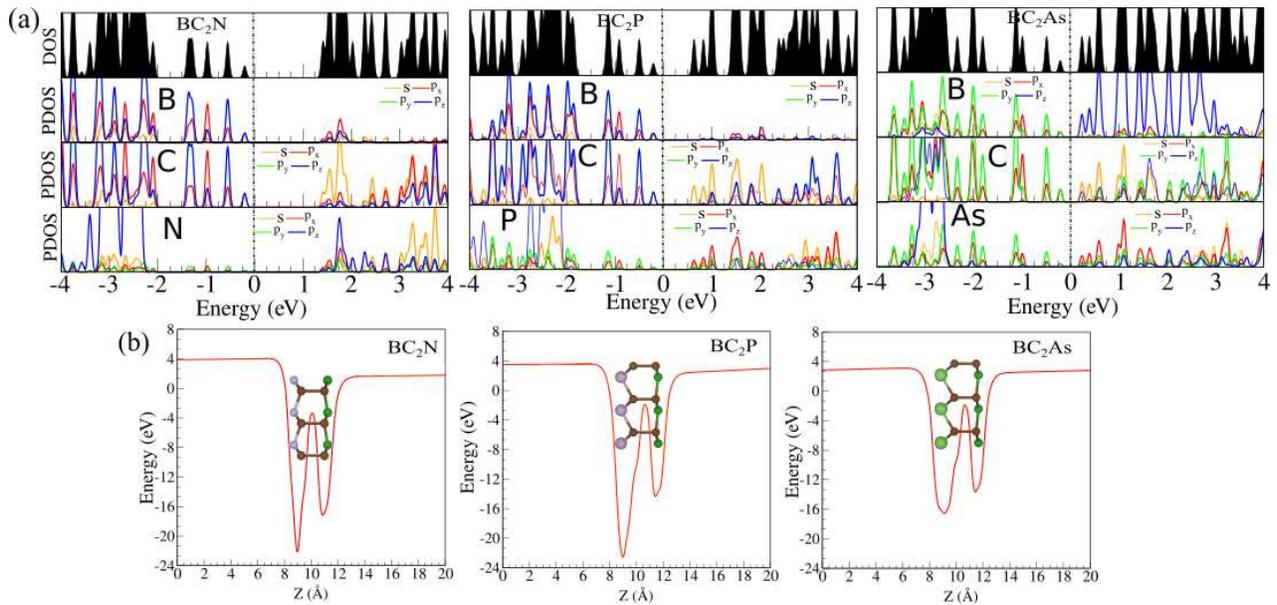


Figure 3. Density of states (DOS) and partial DOS (PDOS) of (a) BC_2N , (b) BC_2P and (c) BC_2As monolayers. (d) Planar average electrostatic potential energy. The atomic structures are shown in the inset.

does not change the nature of the bandgaps of the BC_2P and BC_2As monolayers. The HSE06 values for the indirect bandgaps of BC_2P and BC_2As are 1.77 and 1.21 eV, respectively. The density of states (DOS) and partial DOS (PDOS) of the BC_2X monolayers are exhibited in Figs. 3(a). From the DOS and PDOS of the BC_2N and BC_2P monolayers, the VBM is composed of the p_z orbitals of B and C atoms, while the CBM comes from C-s orbital and p_x orbital states of B (BC_2N) and P (BC_2P) atoms. In the case of the BC_2As monolayer, the VBM consists from p_y of B and P orbitals states, while the CBM consists of B/C- p_z and As- p_x orbital. The average electrostatic potential energy of the BC_2X sheets is illustrated in Fig. 3(b). From this, the work function was calculated using the following relation: $\Phi = E_{\text{vacuum}} - E_F$, where E_{vacuum} is the vacuum energy (extracted from the electrostatic potential) and E_F is the Fermi energy. The work function of the BC_2N , BC_2P and BC_2As monolayers is calculated as 4.32 eV, 4.00 eV and 3.50 eV, respectively, i.e., it decreases with the decrease of the X atom electronegativity (see Table 1).

VII. OPTICAL PROPERTIES

To evaluate the possible optical applications of the discussed monolayer semiconductors, we calculated their most important optical parameters, namely, the complex dielectric functions of the monolayer materials which can be represented by: $\varepsilon(\omega) = \varepsilon_1(\omega) + i\varepsilon_2(\omega)$ where ε_1 and ε_2 are the real and imaginary terms, respectively. The imaginary part can be identified by using the random phase approximation (RPA), which counts the matrix elements of interband optical transitions between occupied

and unoccupied states.⁵⁴ Once the imaginary part is obtained, by using the Kramers-Kronig relations,⁵⁴ the real part can be computed too. From the real and imaginary components, all other optical parameters of a material such as the absorption and reflectivity spectra can be calculated. Figs. 4(a-d) illustrates the optical characteristics of the BC_2N , BC_2P and BC_2As monolayers. The real and imaginary parts are plotted in Figures 4 (a) and (b). When looking at the complex dielectric function of a material, the static dielectric function $\varepsilon_1(0)$ and the high frequency dielectric function $\varepsilon_1(\infty)$ are important since these parameters describe the dielectric response to static and high energy electromagnetic fields, respectively. As seen in Fig. 4 (a), based on our computations, the values of 2.21, 2.50, 2.55 are obtained for the static dielectric functions of BC_2N , BC_2P and BC_2As monolayers, respectively. The high frequency dielectric function is calculated to be 3.85 (BC_2N), 4.12 (BC_2P) and 4.41 (BC_2As), meaning that these monolayers show a similar response to high energy electromagnetic field. Furthermore, as displayed in Figs. 4 (a,b), by increasing the energy of incident photons, both components of the dielectric function increase and exhibit the first peaks at 4.00 eV, 4.75 eV for BC_2N , 4.50 eV, 5.00 eV for BC_2P and 4.75 eV, 5.20 eV for BC_2As , respectively. The calculated absorption and reflectivity spectra are illustrated in Figs. 4 (c,d). Notably, the first main peaks of absorption appear at the energies of 5.00 eV, 5.75, 6.25 eV for the BC_2N , BC_2P and BC_2As monolayers respectively, while all monolayers show almost insignificant absorption properties in the low energy region of the electromagnetic spectrum. The first main absorption peak appears at approximately 5.00 eV for BC_2N , 6.00 eV for BC_2P and 7.50 eV for BC_2As . Finally, the first major reflectivity

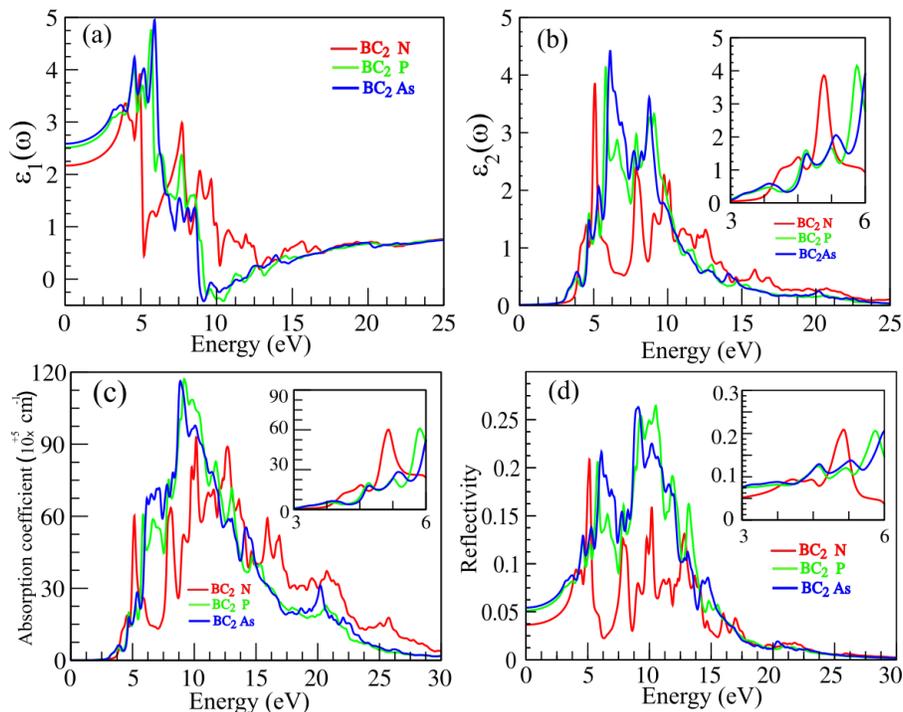


Figure 4. (a) Real and (b) imaginary parts of the complex dielectric constant, (c) absorption coefficient and (d) reflectivity of BC_2N , BC_2P and BC_2As monolayers.

ity peaks occur at 5.00 eV for BC_2N , 6.00 eV for BC_2P and 7.00 eV for BC_2As with a reflectivity of about 21.5 %, 21 %, and 22 %, respectively. These results indicate that the 2D BC_2X materials proposed are transparent for visible light, however, are highly absorbing UV light.

A. Band alignment

Figure. 5 illustrates the band alignment of the oxidation potentials for water splitting with respect to the band edges of the BC_2N , BC_2P and BC_2As monolayers, obtained using the HSE06 with reference to the normal hydrogen electrode potential. Most importantly, BC_2N and BC_2P monolayers exhibit suitable bandgap values of ~ 2.66 eV and 1.77 eV, respectively. The CB edge (CBE) and the VB edge (VBE) must be higher (more negative) and lower (more positive) than the hydrogen reduction potential of H^+/H_2 and the water oxidation potential of $\text{H}_2\text{O}/\text{O}_2$, respectively. The CBE is computed from the relation: $E_{\text{CBE}} = X - 0.5E_g - 4.5$ eV,⁵⁵⁻⁵⁷ and the VBE is $E_{\text{VBE}} = E_{\text{CBE}} + E_g$, where X is the geometric mean⁵⁸ and 4.5 eV is the free electron energy with respect to the vacuum level. Obviously, the BC_2N and BC_2P monolayers would be advantageous photocatalysts for water splitting due to their suitable bandgaps and band edge alignments.

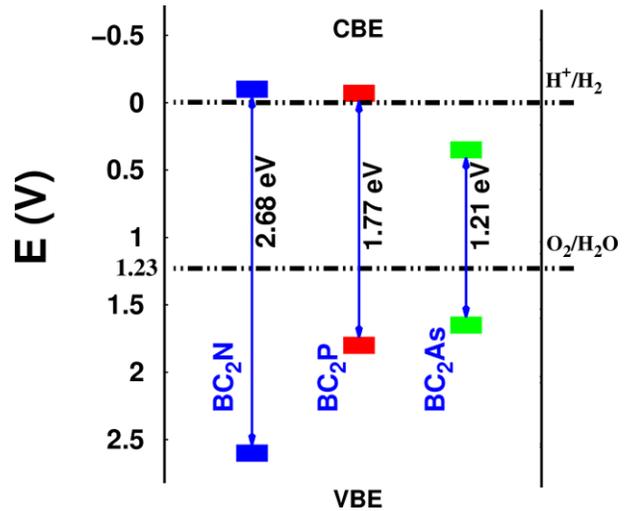


Figure 5. Band alignments of BC_2N , BC_2P and BC_2As monolayers, with respect to the normal hydrogen electrode potential (in Volts), for photocatalytic water splitting at $\text{pH}=0$.

VIII. THERMOELECTRIC PROPERTIES

Herein, the thermoelectric properties of the BC_2X ($X = \text{A}, \text{P}, \text{As}$) monolayers have been calculated using the semiclassical Boltzmann transport theory within the framework of the rigid band approximation. Electrical conductivity σ , Seebeck coefficient S and electronic thermal conductivity κ are calculated using the following for-

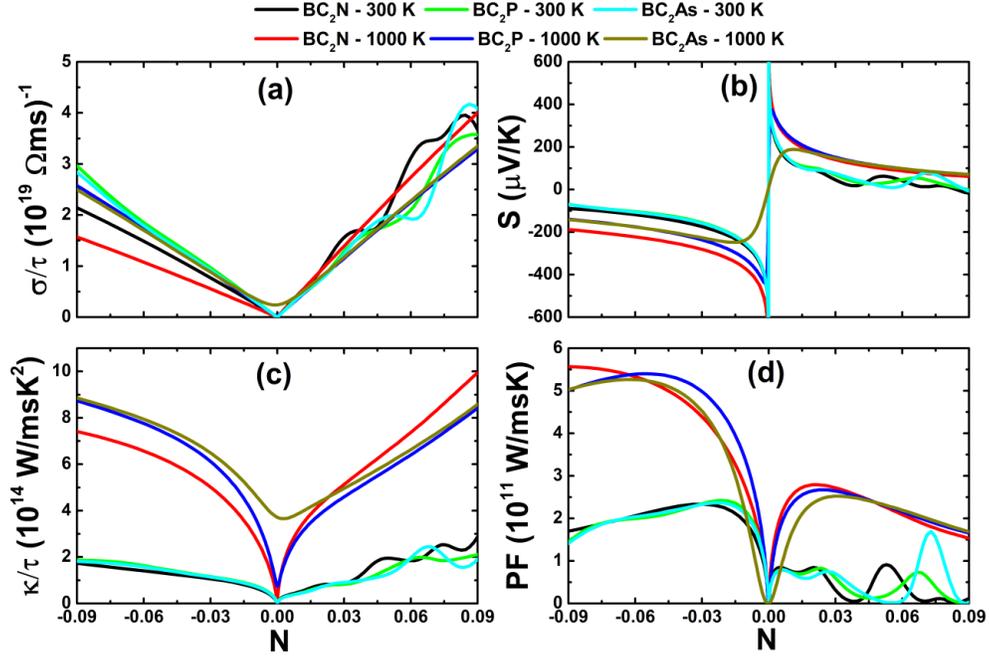


Figure 6. (a) Electrical conductivity, (b) Seebeck coefficient, (c) electronic thermal conductivity and (d) Power factor of the BC_2X ($\text{X} = \text{N}, \text{P}$ and As) monolayers at 300 and 1000 K.

mula:

$$\sigma_{\alpha\beta}(T, \mu) = \frac{1}{\Omega} \int \sigma_{\alpha\beta}(\epsilon) \left[-\frac{\partial f_0(T, \epsilon, \mu)}{\partial \epsilon} \right] d\epsilon \quad (2)$$

$$S_{\alpha\beta}(T, \mu) = \frac{1}{eT\Omega\sigma_{\alpha\beta}(T, \mu)} \int \sigma_{\alpha\beta}(\epsilon)(\epsilon - \mu) \left[-\frac{\partial f_0(T, \epsilon, \mu)}{\partial \epsilon} \right] d\epsilon \quad (3)$$

$$\kappa_{\alpha\beta}^0(T, \mu) = \frac{1}{e^2 T \Omega} \int \sigma_{\alpha\beta}(\epsilon)(\epsilon - \mu)^2 \left[-\frac{\partial f_0(T, \epsilon, \mu)}{\partial \epsilon} \right] d\epsilon \quad (4)$$

where $\sigma_{\alpha\beta}(\epsilon)$ refer to the transport distribution tensor elements, which are calculated via Fourier interpolation of the band structure; Ω , μ and T denote the cell volume, chemical potential and absolute temperature, respectively.

Figure 6(a) depicts the electrical conductivity as a function of the doping level for the BC_2X monolayers at temperatures of 300 and 1000 K. Thermoelectric materi-

als should have large electrical conductivity, which facilitates the movement of charge carriers. Without doping, the electrical conductivity is quite small and it can be increased slightly by raising the temperature. The most notable increase is observed in the case of the BC_2As single-layer, for which a value of $0.24 (10^{-19}\Omega\text{m.s})^{-1}$ is $d\epsilon$ reached. This transport parameter increases almost linearly with the doping level, however, at room temperature the slight fluctuation may be caused by the hole doping with a concentration larger than 0.038. For most of the considered doping levels, the BC_2P and BC_2As monolayers exhibit quite similar electrical conductivity values, which are larger (smaller) than that of the BC_2N monolayer in the n -region (p -region). Note, that the temperature increase may give rise to the reduction of this important parameter in the case of electron doping. When the systems are p -type doped, the temperature influences significantly only at high concentrations. It appears that the hole doping may be more favorable to create the charge carriers flow provided that the electrical conductivity is larger in the p -region than in the n -region at the same concentration of holes and electrons.

The Seebeck coefficient (thermopower) of the BC_2X monolayers is plotted in Fig.6(b). In thermoelectric materials, the temperature difference creates a potential that generates the electric force to push charge carriers. From the figure, one can see that large Seebeck coefficients are obtained for extremely small doping levels, with the largest values of 2555 (-2636), 1329 (-1429) and 632 (-732) ($\mu\text{V}/\text{K}$) in p -region(n -region) for the BC_2N , BC_2P and BC_2As monolayer, respectively. By increas-

Table II. Largest power factor (10^{11} W/m.s.K) of the BC_2X monolayers in the considered doping range from -0.09 to 0.09.

	n -type		p -type	
	300 K	1000 K	300 K	1000 K
BC_2N	2.335	2.573	0.915	2.792
BC_2P	2.424	5.401	0.827	2.671
BC_2As	2.368	5.266	1.690	2.522

ing the doping concentration, the thermopower decreases rapidly in the concentration range from -0.03 to 0.03. Beyond this, the reduction rate becomes considerably smaller. Obviously, all three considered single-layers exhibit quite similar thermopower values at room temperature. Increasing the temperature to 1000 K may favor the electric potential evolution provided that the Seebeck coefficient increases notably, where the BC₂N shows the largest values. It is worth mentioning that at high temperature the thermopower of the BC₂As monolayer shows interesting behavior in the doping range from -0.015 to 0.015, where it reaches maximum values of 188 $\mu\text{V}/\text{K}$ (for N = 0.011) and -249 ($\mu\text{V}/\text{K}$) (for N = -0.015) in the *p*-region and *n*-region, respectively.

The doping level dependence of the electronic thermal conductivity for the BC₂X monolayers is illustrated in Fig.6(c) for temperatures of 300 and 1000 K. In general, one can expect a similar variation of the electronic thermal conductivity κ_{el} and electrical conductivity σ , provided by the proportional relation established by the Wiedemann-Franz law: $\kappa_{el} = LT\sigma$, where the Lorenz number and the absolute temperature are denoted by *L* and *T*, respectively. For good thermoelectric performance, low thermal conductivity is desired. Our simulations indicate that at room temperature the studied 2D materials exhibit quite similar electronic thermal conductivity values. This parameter is strongly dependent on temperature. For example, at extremely low doping level it increases from negligible values to 0.026 (BC₂N), 0.742 (BC₂P) and 3.715 (BC₂As) ($10^{14}\text{W}/\text{msK}^2$) when increasing the temperature from 300 to 1000 K. At a high temperature and high doping levels, the BC₂N monolayer exhibits the smallest (largest) electronic thermal conductivity in the *n*-region (*p*-region), while those of the BC₂P and BC₂As monolayers show notable similarity.

Now we examine the electric power generation of the studied monolayers through the power factor parameter, which is deduced from the Seebeck coefficient and electrical conductivity as follows: $PF = S^2\sigma$. Larger power factors imply good ability for producing electricity from the temperature difference across a material. Fig. 6(d) displays the power factor of the BC₂X monolayers. Note that for small charge carrier concentrations, this parameter is quite small, indicating poor electric production due to the low electrical conductivity. On increasing the doping level, this parameter shows a fast rapid increasing trend to reach its maximum before decreasing, with the exception of the hole doping at room temperature for which a significant fluctuation is observed. In Table.II the largest power factor values for the considered doping levels are given. It appears that electron doping may favor more the electric productivity of the studied 2D materials than the hole doping.

IX. CONCLUSION

On the basis of first-principles investigation, we introduced BC₂N, BC₂P and BC₂As monolayers as novel 2D structures. The monolayers are proved to be stable as indicated by the calculations of the cohesive energy, phonon dispersion, AIMD simulation and elastic stability criteria. The mechanical study shows that all BC₂X monolayers have brittle nature. Also we found out the BC₂P monolayer can resist compression more than the other monolayers. The cohesive energy, the work function, and the bandgap values of BC₂X (*X*=N, P, and As) decrease as we move down the 5A group (in the periodic table), i.e., from N, P and As. The calculated bandgaps using the PBE (HSE06) for BC₂N, BC₂P and BC₂As monolayers are 1.51 (2.68) eV, 0.78 (1.77) eV and 0.39 (1.21) eV, respectively, which are appealing for applications in nanoelectronic devices. For optical applications, the BC₂X monolayers are 2D materials active in the ultraviolet spectral region. BC₂N and BC₂P can be good photocatalysts for water splitting. Our study further shows that the electrical conductivity of the BC₂X monolayers is very small at any temperature. Regarding the thermal conductivity, BC₂N has a small (large) electronic thermal conductivity in the *n*-region (*p*-region) with increasing temperature. Electron doping of the considered single-layers may be more favorable regarding electric power generation than hole doping, providing a larger power factor in the *n*-region than in the *p*-region. The novel BC₂N, BC₂P and BC₂As monolayers are promising materials for electronic, optical and energy conversion applications.

X. ACKNOWLEDGEMENTS

This work was supported by the National Research Foundation of Korea under grant number NRF-2015M2B2A4033123. Moreover, computational resources were provided by TUBITAK ULAK-BIM, at the High Performance and Grid Computing Center (TR-Grid e-Infrastructure).

XI. AUTHOR CONTRIBUTIONS

A.B.: Conceptualization, Methodology, Software, Writing - original draft, Formal analysis, Visualization, Investigation, Supervision, Project administration. M.N.: Methodology, Software, Writing - original draft. M.F.: Methodology, Software, Writing - original draft. M.M.F.: Methodology, Software, Writing - original draft. D.M.H.: Methodology, Software, Writing. H.R.J.: Writing - review editing. M.G.: Writing - review editing, Supervision, Project administration. D.G.: Writing - original draft, Writing - review editing.

XII. COMPETING INTERESTS

The authors declare no competing interests.

-
- * Correspondence to bafekry.asad@gmail.com
 † Correspondence to mitragh@skku.edu
- ¹ Novoselov, K.S., Geim, A.K., Morozov, S. V., Jiang, D.A., Zhang, Y.Y., Dubonos, S. V., Firsov, A.A., Grigorieva, I. V. & Firsov, A.A. Electric Field Effect in Atomically Thin Carbon Films. *Sci.* **306** 666-669 (2004).
 - ² Cahangirov, S., Topsakal, M., Akturk, E., Sahin, H. & Ciraci, S. Two- and one-dimensional honeycomb structures of silicon and germanium. *Phys. Rev. Lett.* **102** 1-4 (2009).
 - ³ Bafekry, A., Shahrokhi, M., Jappor, H.R., Shafique, A., Shojaei, F., Feghhi, S.A.H., Ghergherehchi, M. & Gogova, D. Two-dimensional carbon nitride C₆N nanosheet with egg-comb-like structure and electronic properties of a semimetal. *Nanotechnol.* **32** 215702 (2020).
 - ⁴ Ayadi, T., Debbichi, L., Said, M. & Lebegue, S. An ab initio study of the electronic structure of indium and gallium chalcogenide bilayers. *J. Chem. Phys.* **147** 114701 (2017).
 - ⁵ Almayyali, A.O.M., Kadhim, B.B. & Jappor, H.R. Stacking impact on the optical and electronic properties of two-dimensional MoSe₂/PtS₂ heterostructures formed by PtS₂ and MoSe₂ monolayers. *Chem. Phys.* **532** 110679 (2020).
 - ⁶ Bafekry, A., Abdolhosseini Sarsari, I., Faraji, M., Fadlallah, M.M., Jappor, H.R., Karbasizadeh, S., Nguyen, C. V. & Ghergherehchi, M. Electronic and magnetic properties of two-dimensional of FeX (X = S, Se, Te) monolayers crystallize in the orthorhombic structures. *Appl. Phys. Lett.* **118** 143102 (2021).
 - ⁷ Naseri, M., Bafekry, A., Faraji, M., Hoat, D.M., Fadlallah, M.M., Ghergherehchi, M., Sabbaghi, N. & Gogova, D. Two-dimensional buckled tetragonal cadmium chalcogenides including CdS, CdSe, and CdTe monolayers as photo-catalysts for water splitting. *Phys. Chem. Chem. Phys.* **23** 12226-12232 (2021).
 - ⁸ Bafekry, A., Mortazavi, B., Faraji, M., Shahrokhi, M., Shafique, A., Jappor, H.R., Nguyen, C., Ghergherehchi, M. & Feghhi, S.A.H. Ab initio prediction of semiconductivity in a novel two-dimensional Sb₂X₃ (X = S, Se, Te) monolayers with orthorhombic structure. *Sci. Rep.* **11** 10366 (2021).
 - ⁹ Faraji, M., Bafekry, A., Gogova, D., Hoat, D.M., Ghergherehchi, M., Chuong, N. V. & Feghhi, S.A.H. Novel two-dimensional ZnO₂, CdO₂ and HgO₂ monolayers: a first-principles-based prediction. *New J. Chem.* **45** 9368-9374 (2021).
 - ¹⁰ Vo, D.D., Vu, T. V., Al-Qaisi, S., Tong, H.D., Le, T.S., Nguyen, C. V., Phuc, H. V., Luong, H.L., Jappor, H.R., Obeid, M.M. & Hieu, N.N. Janus monolayer PtSSe under external electric field and strain: A first principles study on electronic structure and optical properties. *Superlattices Microstruct.* **147** 106683 (2020).
 - ¹¹ Chen, W., Qu, Y., Yao, L., Hou, X., Shi, X. & Pan, H. Electronic, magnetic, catalytic, and electrochemical properties of two-dimensional Janus transition metal chalcogenides. *J. Mater. Chem. A* **6** 8021-8029 (2018).
 - ¹² Wu, C.Y., Sun, L., Han, J.C. & Gong, H.R. Band structure, phonon spectrum, and thermoelectric properties of β -BiAs and β -BiSb monolayers. *J. Mater. Chem. C* **8** 581-590 (2020).
 - ¹³ Chaurasiya, R. & Dixit, A. Ultrahigh sensitivity with excellent recovery time for NH₃ and NO₂ in pristine and defect mediated Janus WSSe monolayers. *Phys. Chem. Chem. Phys.* **22** 13903-13922 (2020).
 - ¹⁴ Mishra, P., Singh, D., Sonvane, Y. & Ahuja, R. Two-dimensional boron monochalcogenide monolayer for thermoelectric material, Sustain. *Energy Fuels* **4** 2363-2369 (2020).
 - ¹⁵ Zhang, X., Hu, J., Cheng, Y., Yang, H.Y., Yao, Y. & Yang, S.A. Borophene as an extremely high capacity electrode material for Li-ion and Na-ion batteries. *Nanoscale* **8** 15340-15347 (2016).
 - ¹⁶ Alhameedi, K., Karton, A., Jayatilaka, D. & Hussain, T. Metal functionalized inorganic nano-sheets as promising materials for clean energy storage. *Appl. Surf. Sci.* **471** 887-892 (2019).
 - ¹⁷ Lei, W., Portehault, D., Liu, D., Qin, S. & Chen, Y. Porous boron nitride nanosheets for effective water cleaning. *Nat. Commun.* **4** 1777 (2013).
 - ¹⁸ Shukla, V., Warna, J., Jena, N.K., Grigoriev, A. & Ahuja, R. Toward the Realization of 2D Borophene Based Gas Sensor. *J. Phys. Chem. C* **121** 26869-26876 (2017).
 - ¹⁹ Peng, B., Zhang, H., Shao, H., Xu, Y., Zhang, R. & Zhu, H. The electronic, optical, and thermodynamic properties of borophene from first-principles calculations. *J. Mater. Chem. C* **4** 3592-3598 (2016).
 - ²⁰ Mishra, P., Singh, D., Sonvane, Y. & Ahuja, R. Excitonic effects in the optoelectronic properties of graphene-like BC monolayer. *Opt. Mater.* **110** 110476 (2020).
 - ²¹ Cao, Y., Yu, H., Tan, J., Peng, F., Wang, H., Li, J., Zheng, W. & Wong, N.B. Nitrogen-, phosphorous- and boron-doped carbon nanotubes as catalysts for the aerobic oxidation of cyclohexane. *Carbon* **57** 433-442 (2013).
 - ²² Chakraborty, H., Mogurampelly, S., Yadav, V.K., Waghmare, U. V. & Klein, M.L. Phonons and thermal conducting properties of borocarbonitride (BCN) nanosheets. *Nanoscale* **10** 22148-22154 (2018).
 - ²³ Zhang, M., Gao, G., Kutana, A., Wang, Y., Zou, X., Tse, J.S., Yakobson, B.I., Li, H., Liu, H. & Ma, Y. Two-dimensional boron-nitrogen-carbon monolayers with tunable direct bandgaps. *Nanoscale* **7** 12023-12029 (2015).
 - ²⁴ Thomas, S., Manju, M.S., Ajith, K.M., Lee, S.U. & Asle Zaeem, M. Strain-induced work function in h-BN and BCN monolayers. *Phys. E Low-Dimensional Syst. Nanostruct.* **123** 114180 (2020).
 - ²⁵ Lu, J., Zhang, K., Liu, X.F., Zhang, H., Sum, T.C., Neto, A.H.C. & Loh, K.P. Order-disorder transition in a two-dimensional boron-carbon-nitride alloy. *Nat. Commun.* **4** 1-7 (2013).
 - ²⁶ Zhang, H., Li, X., Meng, X., Zhou, S., Yang, G. & Zhou, X. Isoelectronic analogues of graphene: The BCN monolayers with visible-light absorption and high carrier mobility. *J. Phys. Condens. Matter.* **31** 125301 (2019).
 - ²⁷ Sreedhara, M.B., Gopalakrishnan, K., Bharath, B., Kumar, R., Kulkarni, G.U. & Rao, C.N.R. Properties of

- nanosheets of 2D-borocarbonitrides related to energy devices, transistors and other areas. *Chem. Phys. Lett.* **657** 124-130 (2016).
- ²⁸ Chhetri, M., Maitra, S., Chakraborty, H., Waghmare, U. V. & Rao, C.N.R. Superior performance of borocarbonitrides, $B_xC_yN_z$, as stable, low-cost metal-free electrocatalysts for the hydrogen evolution reaction, *Energy Environ. Sci.* **9** 95-101 (2016).
- ²⁹ Rao, C.N.R. & Gopalakrishnan, K. Borocarbonitrides, $B_xC_yN_z$: synthesis, characterization, and properties with potential applications. *ACS Appl. Mater. Interfaces* **9** 19478-19494 (2017).
- ³⁰ Manna, A.K. & Pati, S.K. Tunable electronic and magnetic properties in $B_xN_yC_z$ nanohybrids: Effect of domain segregation. *J. Phys. Chem. C* **115** 10842-10850 (2011).
- ³¹ Saini, H., Das, S. & Pathak, B. BCN monolayer for high capacity Al-based dual-ion batteries. *Mater. Adv.* **1** 2418-2425 (2020).
- ³² Kumar, N., Moses, K., Pramoda, K., Shirodkar, S.N., Mishra, A.K., Waghmare, U. V., Sundaresan, A. & Rao, C.N.R. Borocarbonitrides, $B_xN_yC_z$. *J. Mater. Chem. A* **1** 5806-5821 (2013).
- ³³ Beniwal, S., Hooper, H. J., Miller, D.P., Costa, P.S., Chen, G., Liu, S.Y., Dowben, P.A., Sykes, E.C.H., Zurek, E. & Enders, A. Graphene-like Boron-Carbon-Nitrogen Monolayers. *ACS Nano* **11** 2486-2493 (2017).
- ³⁴ Zhang, Y.Y., Pei, Q.X., Liu, H.Y. & Wei, N. Thermal conductivity of a h-BCN monolayer. *Phys. Chem. Chem. Phys.* **19** 27326-27331 (2017).
- ³⁵ Zhang, Y.Y., Pei, Q.X., Sha, Z.D. & Zhang, Y.W. A molecular dynamics study of the mechanical properties of h-BCN monolayer using a modified Tersoff interatomic potential. *Phys. Lett. Sect. A Gen. At. Solid State Phys.* **383** 2821-2827 (2019).
- ³⁶ Thomas, S. & Lee, S.U. Atomistic insights into the anisotropic mechanical properties and role of ripples on the thermal expansion of h-BCN monolayers. *RSC Adv.* **9** 1238-1246 (2019).
- ³⁷ Barbosa, R.C., Guimaraes, P.S. & Baierle, R.J. First principles study of native defects in a graphitic BC_2N monolayer. *Thin Solid Films* **518** 4356 (2010).
- ³⁸ Lin, C., Zhang, X. & Rao, Z. Theoretical prediction of thermal transport in BC_2N monolayer. *Nano Energy* **38** 249 (2017).
- ³⁹ Li, H., Duan, Q., Jiang, D., Hou, J. & Guo, X. A first-principles study of boron-doped BC_2N sheet as potential anode material for Li/Na-Ion batteries. *ChemElectroChem* **6** 3797 (2019).
- ⁴⁰ Watanabe, M. O., Itoh, S., Sasaki, T. & Mizushima, K. Visible-Light-Emitting Layered BC_2N Semiconductor. *Phys. Rev. Lett.* **77** 187 (1996).
- ⁴¹ Wang, G., Pandey, R. & Karna, S.P. Carbon phosphide monolayers with superior carrier mobility. *Nanoscale* **8** 8819-8825 (2016).
- ⁴² Perdew, J. P., Burke, K. & Ernzerhof, M. Generalized gradient approximation made simple. *Phys. Rev. Lett.* **77** 3865 (1996).
- ⁴³ Perdew, J. P., Burke, K. & Ernzerhof, M. Generalized gradient approximation made simple, *Phys. Rev. Lett.* **78** 1396 (1997).
- ⁴⁴ Kresse, G. & Hafner, J. Ab initio molecular dynamics for liquid metals. *Phys. Rev. B* **47** 558 (1993).
- ⁴⁵ Kresse, G. & Hafner, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **49** 14251 (1994).
- ⁴⁶ Heyd, J., Scuseria, G. E. & Ernzerhof, M. Screened hybrid density functionals applied to solids. *J. Chem. Phys.* **118** 8207 (2003).
- ⁴⁷ Monkhorst, H.J. & Pack, J.D. Special points for Brillouin-zone integrations. *Phys. Rev. B* **13** 12, (1976).
- ⁴⁸ Henkelman, G., Arnaldsson, A. & Jonsson, H. A fast and robust algorithm for Bader decomposition of charge density. *Comput. Mater. Sci.* **36** 354 (2006).
- ⁴⁹ Alfe, D. PHON: A program to calculate phonons using the small displacement method. *Comput. Phys. Commun.* **180** 2622 (2009).
- ⁵⁰ Rojas-Chavez, H., Cruz-Martinez, H., Flores-Rojas, E., Juarez-Garcia, J.M., Gonzalez-Dominguez, J.L., Daneu, N. & Santoyo-Salazar, J. The mechanochemical synthesis of PbTe nanostructures: following the Ostwald ripening effect during milling. *Phys. Chem. Chem. Phys.* **20** 27082 (2018).
- ⁵¹ Hill, R. The Elastic Behaviour of a Crystalline Aggregate. *Proc. Phys. Soc., London, Sect. A* **65** 349 (1952).
- ⁵² Pugh, S. F. Relations between the elastic moduli and the plastic properties of polycrystalline pure metals. *Philos. Mag.* **45** 823 (1954).
- ⁵³ Hu, W. C., Liu, Y., Li, D. J., Zeng, X. Q. & Xu, C. S. *Comput. Mater. Sci.* **83** 27 (2014).
- ⁵⁴ Bass, M., Stryland, E.W.V., Williams, D.R. & Woffe, W.L. Handbook of Optics, Second Edition, vol. 1. *McGraw-Hill, New York* (1995).
- ⁵⁵ Fadlallah, M. M., Shibl, M. F., Vlugt, T. J. H. & Schwingschlogl, U. Theoretical study on cation codoped $SrTiO_3$ photocatalysts for water splitting. *J. Mater. Chem. A* **6** 24342 (2018).
- ⁵⁶ Fadlallah, M. M. & Eckern, U. Electronic and optical properties of metal-doped TiO_2 nanotubes: spintronic and photocatalytic applications. *NJPhys.* **22** 093028 (2020).
- ⁵⁷ Fadlallah, M. M. & Eckern, U. Cation Mono- and Co-Doped Anatase TiO_2 Nanotubes: An Ab Initio Investigation of Electronic and Optical Properties. *physica status solidi (b)* **257** 1900217 (2020).
- ⁵⁸ Bartolotti, L. J., Gadre, Sh. R. & Parr, R. G. Electronegativities of the elements from simple. *JACS* **102** 2945 (1980).