

Discrimination of Skyrmion Chirality Via Spin-Orbit and -Transfer Torques for Logic Operation

Yoshinobu Nakatani (✉ nakatani@cs.uec.ac.jp)

University of Electro-Communications

Keisuke Yamada

Gifu University

Atsufumi Hirohata

University of York

Research Article

Keywords: Magnetic skyrmion, micromagnetically simulated, spin-orbit torque (SOT), spin-transfer torque (STT)

Posted Date: January 14th, 2021

DOI: <https://doi.org/10.21203/rs.3.rs-143134/v1>

License:   This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

Version of Record: A version of this preprint was published at Scientific Reports on April 16th, 2021. See the published version at <https://doi.org/10.1038/s41598-021-87742-6>.

Discrimination of skyrmion chirality via spin-orbit and -transfer torques for logic operation

*Yoshinobu Nakatani¹, Keisuke Yamada², Atsufumi Hirohata³

1. Graduate school of Informatics and Engineering, University of Electro-Communications, Chohu, Tokyo, Japan.
2. Department of Chemistry and Biomolecular Science, Faculty of Engineering, Gifu University, Gifu-shi, Gifu, Japan
3. Department of Electronic Engineering, University of York, York, United Kingdom

corresponding author Y. Nakatani E-mail nakatani@cs.uec.ac.jp

abstract

Recently many works on magnetic memories and logic circuits, which use a magnetic skyrmion have been reported. Previously we micromagnetically simulated a method to switch a chirality of a magnetic skyrmion formed in a magnetic thin film by introducing a pulsed heat spot. In this paper, we propose a method to discriminate the chirality of a skyrmion in a branched nanowire by using spin-orbit torque (SOT) and spin-transfer torque (STT), and confirm the validity of the method by using simulation. The simulated results show that the motion changes depending on the chirality when additional SOT is applied on a skyrmion moving in a branch by STT. This method can be used as a fundamental building block for electrical detection in memory and logic devices using the chirality of skyrmions as a data bit in addition to the presence (and polarity) of the skyrmions as conventionally used, which can be lead to multiple-valued operation.

Introduction

Magnetic skyrmion [1,2] is a chiral structure appearing in a magnetic thin film by the Dzyaloshinskii-Moriya exchange interaction [3,4]. Because of the small size (~ 10 nm) [5,6] and the small current density required for the motion ($\sim 10^6$ A/m²) [7-10], a skyrmion is expected to become an ideal information carrier for next generation memory and logic devices such as a racetrack memory. Many works have accordingly been reported [9-22]. Among them, however, some works use the presence [9-12,14-19] polarity [20] or chirality [13,21] of a skyrmion as a data bit, which are the other characteristics of the skyrmion [22].

Previously we demonstrated by simulation that skyrmions with opposite chiralities can be formed in the same magnetic thin film, and their chiralities can be switched by introducing a single heat pulse [21]. These results show the possibility of the multiple-valued memory operation with skyrmions using their chirality. To date the chirality has been measured by imaging a skyrmion using magnetic force microscopy (MFM) [23,24] and X-ray photoemission electron microscopy (XPEEM) [25]. However to realize such a memory, an electrical method to discriminate the chiralities is required.

Recently, it was reported that a skyrmion can be moved [26,27] by using spin-orbit torque (SOT) [28-30], and the direction of the motion changes depending on the chirality [31]. In this paper, we propose an electrical selection method to discriminate the chirality of the skyrmion by the combination of SOT and spin-transfer torque (STT) [32], which is confirmed by simulation. When the SOT is applied on a skyrmion moving in a magnetic nanowire, the motion is found to be controlled depending on the chirality. By attaching a branch to the nanowire, the skyrmions with the opposite chiralities can be separated, achieving fully electrical detection of the chirality. This paves a way towards skyrmion memory and logic with multiple-valued operation using the skyrmions (and polarities) and their chiralities as data bits.

Method

A micromagnetic model [33] was used to calculate the motion of magnetic moments in a thin film using the Landau-Lifshitz-Gilbert equation with STT [32] and SOT [30,34] as follows:

$$\frac{\partial \mathbf{m}}{\partial t} = -|\gamma| \mathbf{m} \times \mathbf{H}^{\text{eff}} + \alpha \mathbf{m} \times \frac{\partial \mathbf{m}}{\partial t} - (\mathbf{u} \cdot \nabla) \mathbf{m} + \beta \mathbf{m} \times [(\mathbf{u} \cdot \nabla) \mathbf{m}] - \frac{u \theta^H}{P h} \mathbf{m} \times (\mathbf{m} \times \mathbf{n}_s). \quad (1)$$

Here, \mathbf{m} , \mathbf{H}^{eff} , γ , and α are the unit magnetization vector that represents the direction of a local magnetic moment, the effective magnetic field acting on the magnetization, the gyromagnetic ratio, and the Gilbert damping constant, respectively. The velocity \mathbf{u} is a vector along the direction of electron motion, with an amplitude of

$$u = J P g \mu_B / (2e M_s), \quad (2)$$

where J , P , g , μ_B , e and M_s are the current density, spin polarization, the Lande g-factor, the Bohr magneton, the electron charge, and the saturation magnetization, respectively. β is the dimensionless parameter for STT. θ^H , h , and \mathbf{n}_s are the spin Hall angle, the thickness of the film and the unit vector of the spin Hall torque, respectively. The effective magnetic field is calculated from the magnetic energy density by $\mathbf{H}^{\text{eff}} = -\frac{1}{M_s} \frac{\delta \varepsilon}{\delta \mathbf{m}}$. For the magnetic energy, the exchange, anisotropy, demagnetizing, and Dzyaloshinskii-Moriya exchange interaction (DMI) energies are taken into account in the simulation [35,36].

$$\varepsilon = A(\nabla \mathbf{m})^2 + K_u(1 - m_z^2) - \frac{1}{2} M_s \mathbf{m} \cdot \mathbf{H}^{\text{dem}} + D \left[\left(m_x \frac{\partial m_z}{\partial x} - m_z \frac{\partial m_x}{\partial x} \right) + \left(m_y \frac{\partial m_z}{\partial y} - m_z \frac{\partial m_y}{\partial y} \right) \right] \quad (3)$$

Here, A , K_u , H^{dem} , and D are the exchange stiffness constant, the uniaxial anisotropy constant, the demagnetizing field, which is calculated numerically, and the DM exchange constant, respectively. Here we assumed the interfacial DMI between the ferromagnetic thin film and the non-magnetic layer underneath. A free boundary condition was used at the edge of the film [36].

$$\frac{d\theta}{dn} = \frac{1}{\xi}, \quad \xi = \frac{2A}{D} \quad (4)$$

Here, θ is a polar angle of a magnetic moment, n is the normal direction at the film edge, and ξ is a characteristic length determined by D [36].

Typical material parameters for perpendicularly-magnetized CoFeB thin films at room temperature (300 K) were used, *i.e.*, the saturation magnetization $M_s = 1600 \text{ emu/cm}^3$, the exchange stiffness constant $A = 3.1 \times 10^{-6} \text{ erg/cm}$, the uniaxial anisotropy constant $K_u = 16.2 \text{ Merg/cm}^3$, the gyromagnetic ratio $\gamma = 1.76 \times 10^7 \text{ rad/(s} \cdot \text{Oe)}$, the Gilbert damping constant $\alpha = 1$, the dimensionless STT parameter $\beta = 1$, and the DMI constant $D = 0.6 \text{ erg/cm}^2$ [37,38].

In this paper, two types of simulation were performed. In the first one, we investigate the effect of the D value on the direction of the skyrmion motion by SOT. The second one is the simulation of the skyrmion motion in the nanowire with a branch by SOT and STT. In the first simulation, we use the magnetic strip with 512 nm in length, 128 nm in width and 1.4 nm in thickness. In the second simulation, the branch structure is made by attaching the same strips used in the first simulation. The branch angle is varied from 15 to 90 degree from the nanowire direction. These strips are divided into rectangular prisms with their dimensions of $0.5 \times 0.5 \times 1.4 \text{ nm}^3$ in simulation.

Results and Discussion

First, we show the change of the direction of the motion of the Néel and Bloch type skyrmions by SOT depending on the polarity and the chirality by analytical model [31]. Figure 1 shows representative results. In

the case of the Bloch type skyrmion, the direction of motion by SOT changes 180° depending on the chirality [see Fig. 1(a)]. This means that we can differentiate the chirality of the Bloch type skyrmions by detecting the opposite directions of motion. On the other hand, the direction of motion of the Néel type skyrmion is 90° , which requires further consideration as detailed below.

In the magnetic thin film, not only the diameter of the skyrmion, but also the direction of the magnetization on the domain wall surrounding the skyrmion changes by the D value. As shown in Fig. 1(b), a Bloch type skyrmion in which the magnetization is parallel to the domain wall appears for the $D = 0$ erg/cm² case. The magnetization changes as the D value increases, and Néel type skyrmion appears for the $D = 1.2$ erg/cm² case.

Figure 1(c) shows the simulated results of the change of the direction of the skyrmion motion by the D value and chirality. For the $D = 0$ erg/cm² cases, the same results with the analytical model are obtained. However, the directional angle dependent upon the chirality decreases with increasing the D value. In our previous paper [21], in which we reported the control of the chirality by a heat pulse, we use the Bloch type skyrmion with $D = 0.6$ erg/cm². In that case, the clockwise (CW) skyrmion moves to the $+x$ direction by SOT, however the counter clockwise (CCW) skyrmion moves to the $-y$ direction predominantly (Fig. 2(c), $D = 0.6$ erg/cm²). It shows that the branch structure to discriminate the chirality of the skyrmion should be designed considering the D value.

Figure 2 shows the branch structure to discriminate the chirality of the Bloch type skyrmion. In this figure, the current flows to the $-x$ direction (electron moves to the $+x$ direction), and the skyrmion moves to the $+x$ direction by STT. When SOT with the $+y$ direction is also applied, the CW skyrmion with $D = 0.6$ erg/cm² moves to the $+x$ direction as mentioned before. It moves to the $+x$ direction at the branch, moving into the upper branch. On the other hand, the CCW skyrmion moves to the $-y$ direction by SOT, moving to the below branch by the combination of STT and SOT.

We then investigate the change of the branch directions by chiralities using simulation. Figure 3 shows the results. Figures 3(a) and 3(b) show the motion of the CCW and CW skyrmions for 40 ns, respectively. Here, the branch angle is 45° , and the current density is $j = 0.3 \times 10^{12}$ A/m² with $P = 0.7$ and $\theta^H = 0.1$ rad. These figures show that the direction of motion and the resulting branches for detection changes by the chirality. In both cases, the skyrmion moves to the center of the branches by the demagnetizing field and then moves along the branch. Figure 3(c) shows the demagnetizing field in the branch. The field becomes the maximum at the branch center because the width of the strip is maximum. That is the stable point for the skyrmion, and hence the skyrmion moves to the center of the branch first and then it moves along the branch.

Figures 3(d) and 3(e) show the change of the skyrmion motion by the current density and the spin Hall angle for 80 ns. The current was varied

between 0.1 and 0.4×10^{12} A/m² and the spin Hall angle of 0.1 [see Fig. 3(d)] and 0.3 rad [see Fig. 3(e)]. For the small current cases ($j = 0.1$ and 0.15×10^{12} A/m²), it takes long time to pass through the branch. As an example, the motions for 160 ns is shown in the figure. In Fig. 3(d), the CW skyrmion moves to the upper branch for all cases, The CCW skyrmion moves to the bottom branch when the current is larger than 0.15×10^{12} A/m², however it crashes the branch center and disappears when $j = 0.1 \times 10^{12}$ A/m². In Fig. 3(e), the CW skyrmion moves to the upper branch when the current is smaller than 0.2×10^{12} A/m², however it moves to the lower branch and crashes into the strip edge and disappears when the current is larger than 0.25×10^{12} A/m². The CCW skyrmion moves to the lower branch for all cases, however it crashes into the strip edge and disappear when the current is larger than 0.25×10^{12} A/m², note that SOT is required to change the motion direction. However, when the spin Hall angle is large (~ 0.3 rad), the current range for the main branch decreases by misdirectional motion or annihilation. These results show that the spin Hall angle of 0.1 rad is sufficient for the chirality discrimination, which is experimentally achievable [30,39] and larger angle is not necessary.

Figures 3(f)-(h) show the change of the current range for the main branch by the branch angle. Here, the branch angle and the current are varied between 15 and 90° , and between 0.1 and 0.4×10^{12} A/m². The thick (thin) line shows the maximum (minimum) current density for the main branch. The red line (total) shows the current range of the main branch for the CW and CCW skyrmions. Note that 0.1×10^{12} A/m² is the minimum value we used in the simulation. Therefore, it is not the true minimum for normal operation. These figures show that the effect of the branch angle on the current range is small. The current range decreases because the maximum current decreases as the spin Hall angle increases. The misdirectional motion of the skyrmion does not depend on the branch angle, which is the same as that in Figs. 3(d) and 3(e).

From these results, the skyrmion chiralities are proved to be discriminated electrically by SOT and STT. The branch direction of the Bloch type skyrmion moving by SOT and STT changes depending on the chirality. The spin Hall angle of 0.1 rad is sufficient for the chirality discrimination, which is experimentally achievable and larger angle is not necessary. The effect of the branch angle on the current range is minor, which is advantageous for device miniaturization.

Conclusions

We proposed a method to electrically discriminate the chirality of a skyrmion using a combination of STT and SOT. This proposed method was investigated and confirmed by micromagnetic simulation. This method is found to be highly effective to realize skyrmionics memory and logic devices with using the chirality of the skyrmion, allowing to achieve multiple-valued operation in combination with the presence and polarity of the skyrmion.

References

1. Skyrme, T. H. R. A unified field theory of mesons and baryons. *Nucl. Phys.* **31**, 556–569 (1962).
2. Rösler, U. K., Bogdanov, A. N. & Pfleiderer, C. Spontaneous skyrmion ground states in magnetic metals. *Nature* **442**, 797–801 (2006).
3. Dzyaloshinsky, I. A thermodynamic theory of “weak” ferromagnetism of antiferromagnetics. *J. Phys. Chem. Solids* **4**, 241–255 (1958).
4. Moriya, T. Anisotropic superexchange interaction and weak ferromagnetism. *Phys. Rev.* **120**, 91 (1960).
5. Mühlbauer, S. *et al.* Skyrmion lattice in a chiral magnet. *Science* **323**, 915–919 (2009).
6. Yu, X. Z. *et al.* Real-space observation of a two-dimensional skyrmion crystal. *Nature* **465**, 901–904 (2010).
7. Jonietz, F. Spin transfer torques in MnSi at ultralow current densities. *Science* **330**, 1648–1651 (2010).
8. Yu, X. Z. *et al.* Skyrmion flow near room temperature in an ultralow current density. *Nat. Commun.* **3**, 988 (2012).
9. Iwasaki, J., Mochizuki, M. & Nagaosa, N. Current-induced skyrmion dynamics in constricted geometries. *Nat. Nanotech.* **8**, 742–747 (2013).
10. Sampaio, J., Cros, V., Rohart, S., Thiaville, A. & Fert, A. Nucleation, stability and current-induced motion of isolated magnetic skyrmions in nanostructures. *Nat. Nanotech.* **8**, 839–844 (2013).
11. Romming, N. *et al.* Writing and deleting single magnetic skyrmion. *Science* **341**, 636–639 (2013).
12. Koshibae, W. & Nagaosa, N. Creation of skyrmions and antiskyrmions by local heating. *Nat. Commun.* **5**, 5148 (2014).
13. Finazzi, M. *et al.* Laser-induced magnetic nanostructures with tunable topological properties. *Phys. Rev. Lett.* **110**, 177205 (2013).
14. Tomasello, R. *et al.* A strategy for the design of skyrmion racetrack memories. *Sci. Rep.* **4**, 6784 (2015).
15. Zhang, X. *et al.* Skyrmion-skyrmion and skyrmion-edge repulsions in skyrmion-based racetrack memory. *Sci. Rep.* **5**, 7643 (2015).
16. Jiang, W. *et al.* Blowing magnetic skyrmion bubbles. *Science* **349**, 283–286 (2015).
17. Woo, S. *et al.* Observation of room-temperature magnetic skyrmions and their current-driven dynamics in ultrathin metallic ferromagnets. *Nat. Mater.* **15**, 501–506 (2016).
18. Hrabec, A. *et al.* Current-induced skyrmion generation and dynamics in symmetric bilayers. *Nat. Commun.* **8**, 15765 (2017).
19. Maccariello, D. *et al.* Electrical detection of single magnetic skyrmions in metallic multilayers at room temperature. *Nat. Nanotech.* **13**, 233–237 (2018).
20. Nakatani, Y., Hayashi, M., Kanai, S., Fukami, S. & Ohno, H. Electric field control of Skyrmions in magnetic nanodisks. *Appl. Phys. Lett.* **108**, 152403 (2016).

21. Nakatani, Y., Yamada, K. & Hirohata, A. Switching of Skyrmion chirality by local heating. *Sci. Rep.* **9**, 13475 (2019).
22. Nagaosa, N. & Tokura, Y. Topological properties and dynamics of magnetic skyrmions. *Nat. Nanotech.* **8**, 889-911 (2013).
23. Legrand, W. *et al.* Room-temperature current-induced generation and motion of sub-100 nm skyrmions. *Nano Lett.* **17**, 2703-2712 (2017).
24. Soumyanarayanan, A. *et al.* Tunable room-temperature magnetic skyrmions in Ir/Fe/Co/Pt multilayers. *Nat. Mater.* **16**, 898-904 (2017).
25. Zhang, S., Kronast, F., van der Laan, G. & Hesjedal, T. Real-space observation of skyrmionium in a ferromagnet-magnetic topological insulator heterostructure. *Nano Lett.* **18**, 1057-1063 (2018).
26. Woo, S. *et al.* Spin-orbit torque-driven skyrmion dynamics revealed by time-resolved X-ray microscopy. *Nat. Commun.* **8**, 15573 (2017).
27. Litzius, K. *et al.* Skyrmion Hall effect revealed by direct time-resolved X-ray microscopy. *Nat. Phys.* **13**, 170-175 (2017).
28. Miron, I. M. *et al.* Current-driven spin torque induced by the Rashba effect in a ferromagnetic metal layer. *Nat. Mater.* **9**, 230-234 (2010).
29. Miron, I. M. *et al.* Perpendicular switching of a single ferromagnetic layer induced by in-plane current injection. *Nature* **476**, 189-193 (2011).
30. Liu, L. *et al.* Spin-torque switching with the giant spin hall effect of tantalum. *Science* **336**, 555-558 (2012).
31. Honda, S. & Tanaka, M. Micromagnetic investigations of Néel- and Bloch-type skyrmion dynamics induced by spin Hall effect of cap layers. *Jpn. J. Appl. Phys.* **56**, 098001 (2017).
32. Thiaville, A., Nakatani, Y., Miltat, J. & Suzuki, Y. Micromagnetic understanding of current-driven domain wall motion in patterned nanowires. *Europhys. Lett.* **69**, 990-996 (2005).
33. Nakatani, Y., Uesaka, Y. & Hayashi, N. Direct solution of the Landau-Lifshitz- Gilbert Equation for micromagnetics. *Jpn. J. Appl. Phys.* **28**, 2485 (1989).
34. Lee, K.-S., Lee, S.-W., Min, B.-C. & Lee, K.-J. Threshold current for switching of a perpendicular magnetic layer induced by spin Hall effect. *Appl. Phys. Lett.* **102**, 112410 (2013).
35. Thiaville, A., Rohart, S., Jué, É., Cros, V. & Fert, A. Dynamics of Dzyaloshinskii domain walls in ultrathin magnetic films. *Europhys. Lett.* **100**, 57002 (2012).
36. Rohart, S. & Thiaville, A. Skyrmion confinement in ultrathin film nanostructures in the presence of Dzyaloshinskii-Moriya interaction. *Phys. Rev. B* **88**, 184422 (2013).
37. Kanai, S. *et al.* In-plane magnetic field dependence of electric field-induced magnetization switching. *Appl. Phys. Lett.* **103**, 072408 (2013).
38. Torrejon, J. *et al.* Interface control of the magnetic chirality in CoFeB/MgO heterostructures with heavy-metal underlayers. *Nat. Commun.* **5**, 4655 (2014).

39. Liu, L., Moriyama, T., Ralph, D. C. & Buhrman, R. A. Spin-torque ferromagnetic resonance induced by the spin hall effect. *Phys. Rev. Lett.* **106**, 036601 (2011).

Acknowledgements

A portion of this work was supported by JSPS KAKENHI (Grant Numbers 19H02553, and 20K05255), JSPS Core to Core Program, UK EPSRC (EP/M02458X/1 and EP/V007211/1) and the Collaborative Research Program of the Institute for Chemical Research, Kyoto University.

Author Contributions

All authors conceived the experiments. Y.N. performed the micromagnetic simulations. K.Y. analyzed the data and supported the simulations. Y.N., K.Y. and A.H. wrote the main manuscript text and K.Y. prepared all figures. All authors reviewed the manuscript.

Competing Interests: The authors declare no competing interests.

Data Availability

The datasets generated during the current study are available from the corresponding author on reasonable request.

Figure captions

Figure 1

Motion of a skyrmion by SOT. (a) Direction of a motion of Bloch type skyrmions (CW and CCW) and Néel type skyrmion by SOT (analytical result [31]). (b) Change of the skyrmion structures for CCW and CW by the D value. (c) Change of the motion direction of a skyrmions for CCW and CW by the D value (simulation results).

Figure 2

Illustration of a nanowire with a branch to discriminate a skyrmion chirality.

Figure 3

Motion of a skyrmion by SOT and STT. (a)&(b) Motion of a (a) CCW and (b) CW skyrmions by SOT and STT for 40 ns with the branch angle of 45° , $j = 0.3 \times 10^{12} \text{ A/m}^2$, $P = 0.7$, $\theta^H = 0.1 \text{ rad}$. (c) Distribution of the demagnetizing field at the branch. (d)&(e) Change of the skyrmion motion by the current density and spin Hall angle $\theta^H =$ (d) 0.1 and (e) 0.3 rad. (f)-(h) Effect of the branch angle on the current range for the normal branch with the spin Hall angle $\theta^H =$ (f) 0.1, (g) 0.2 and (h) 0.3 rad.

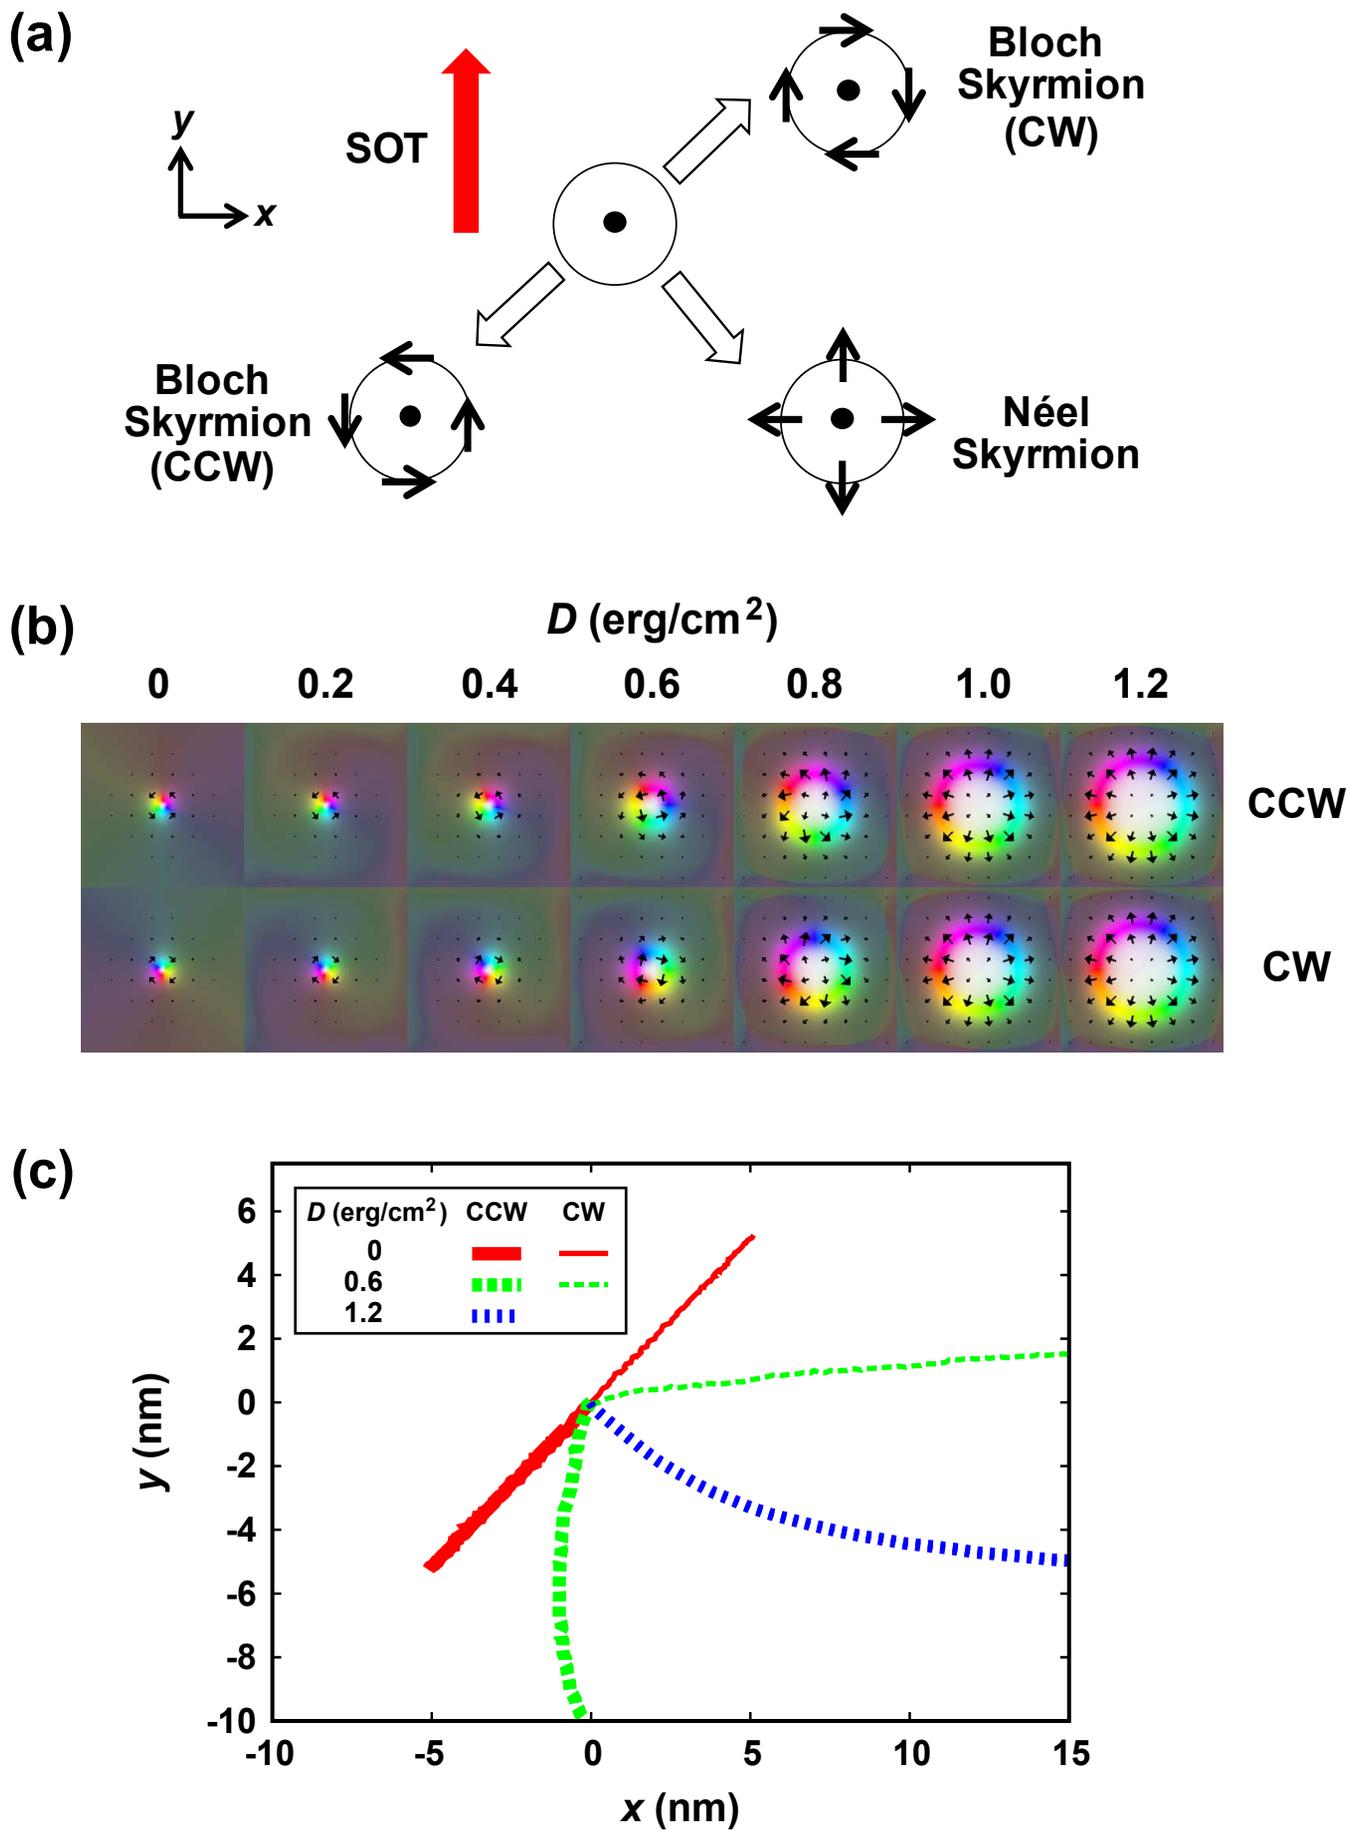


Figure 1 Nakatani, et al.

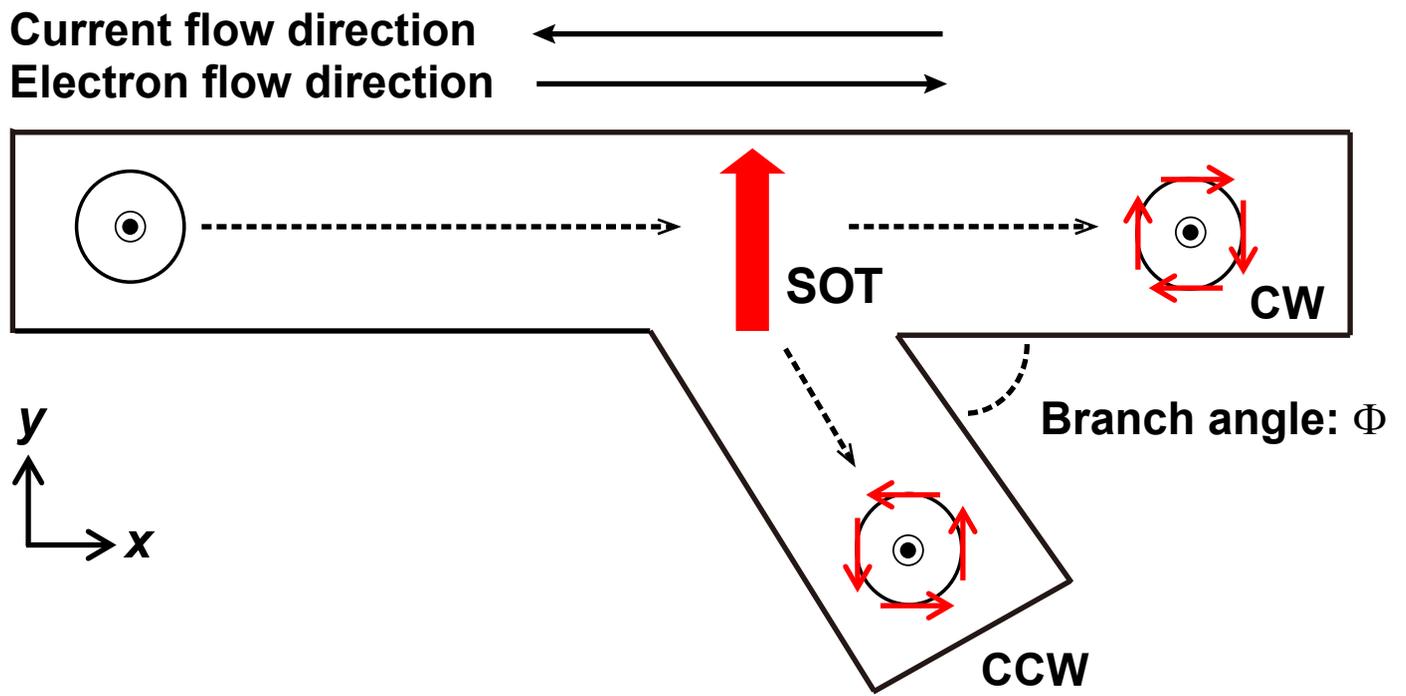


Figure 2 Nakatani, et al.

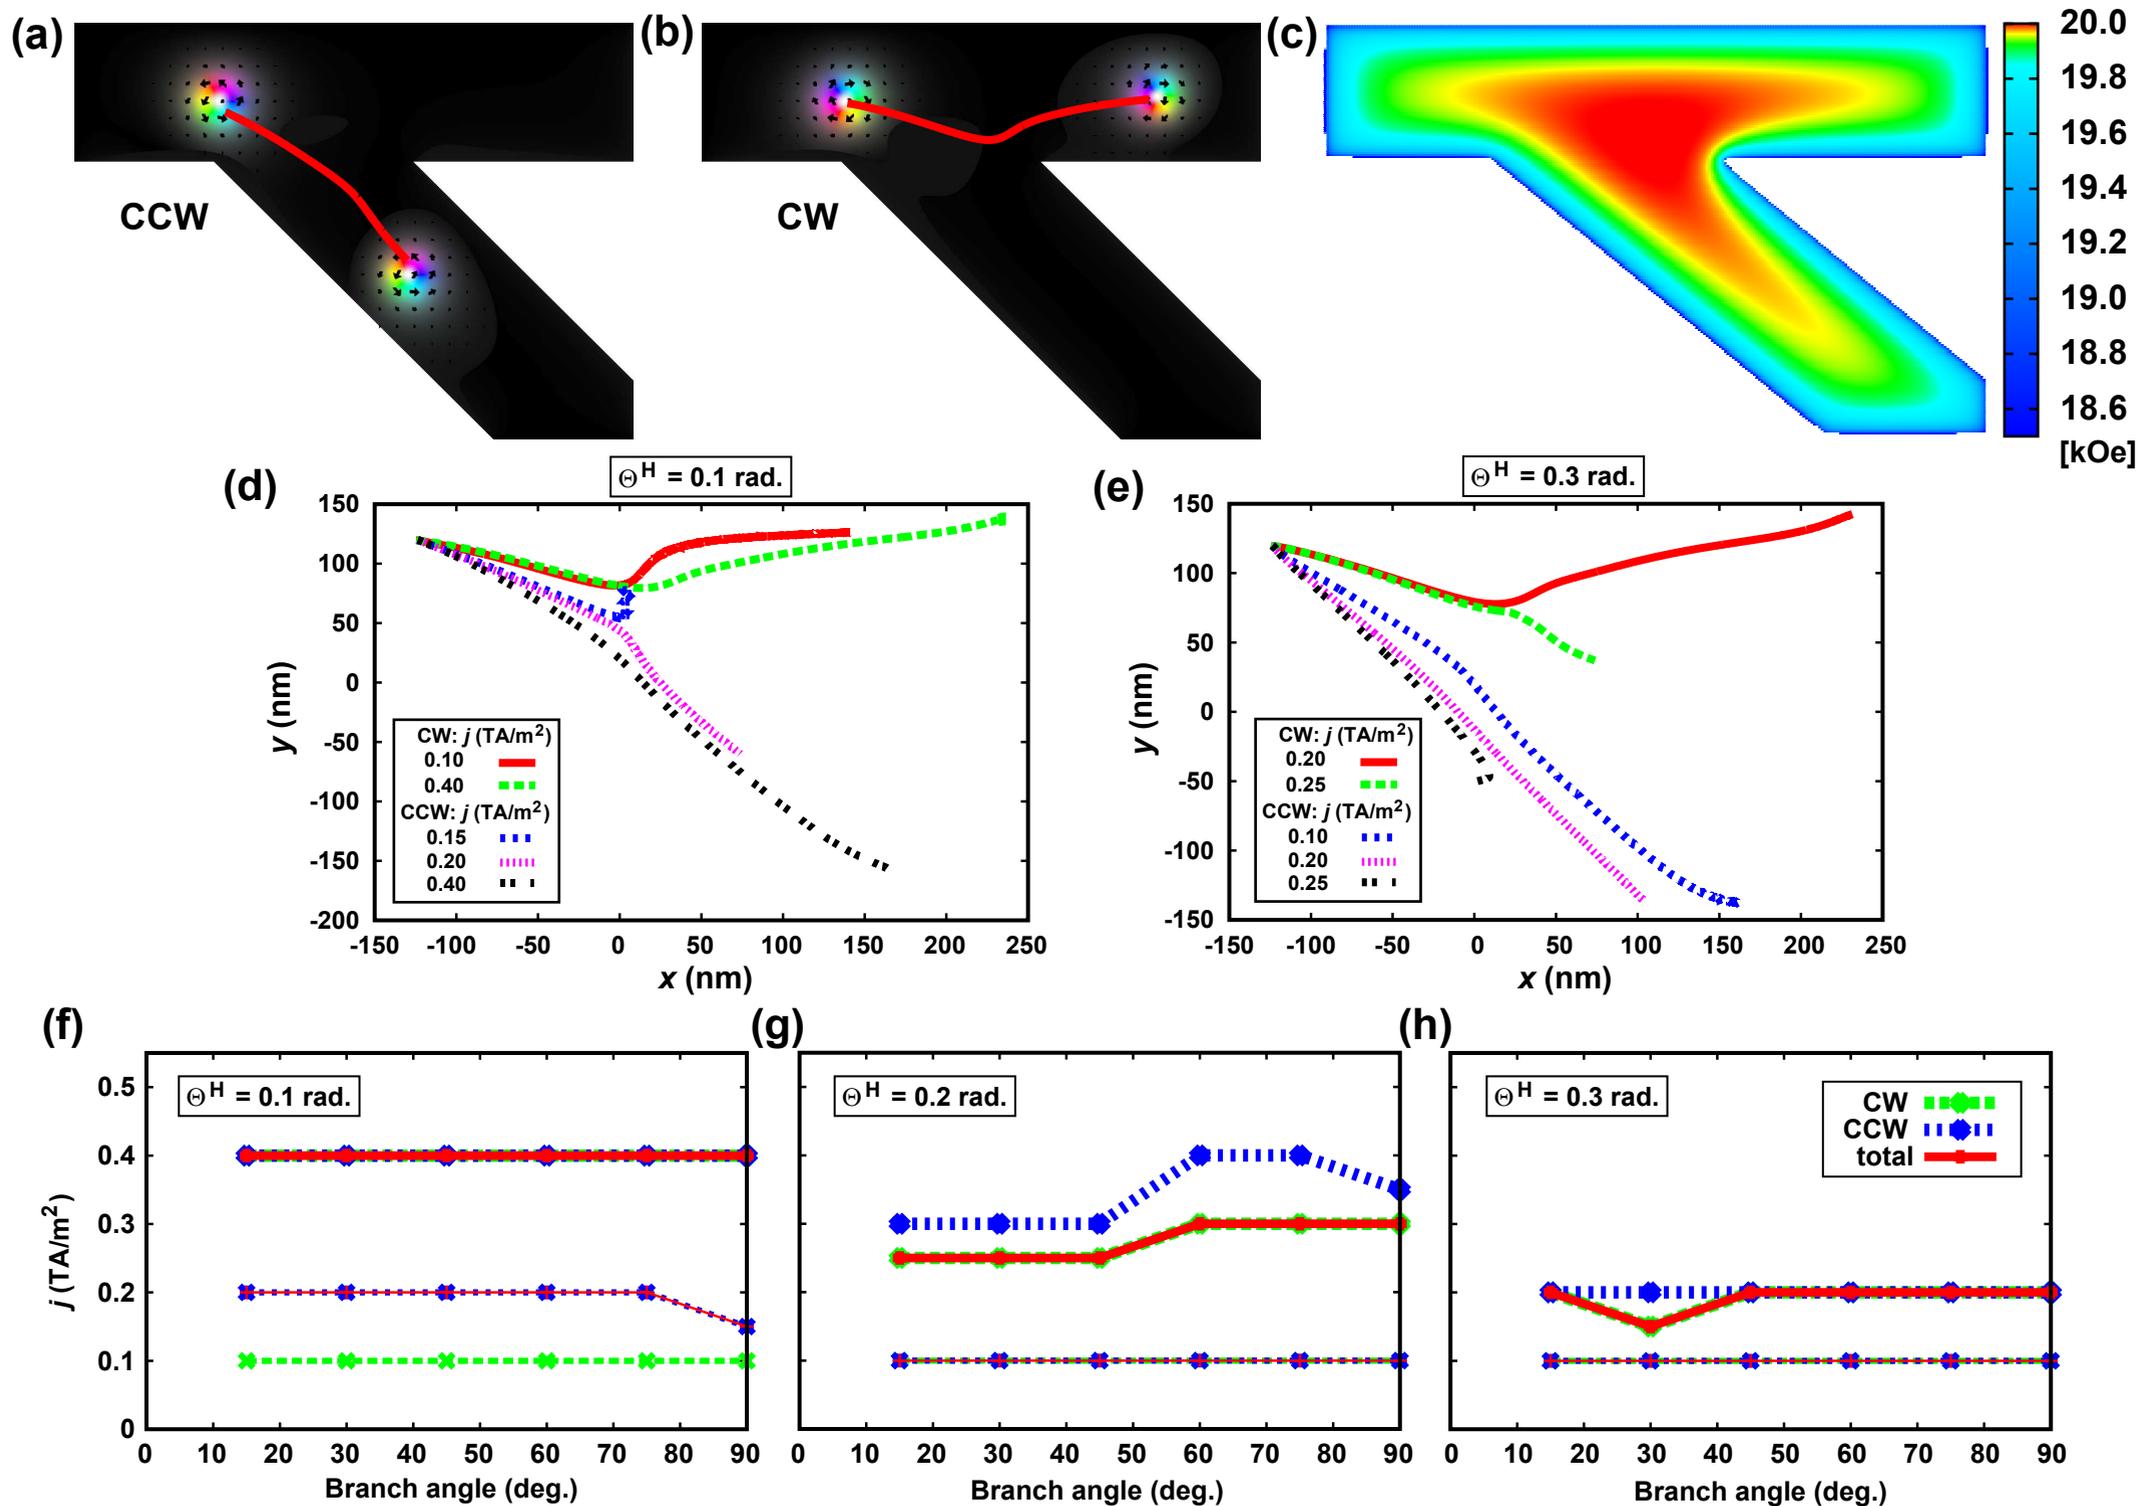


Figure 3 Nakatani, et al.

Figures

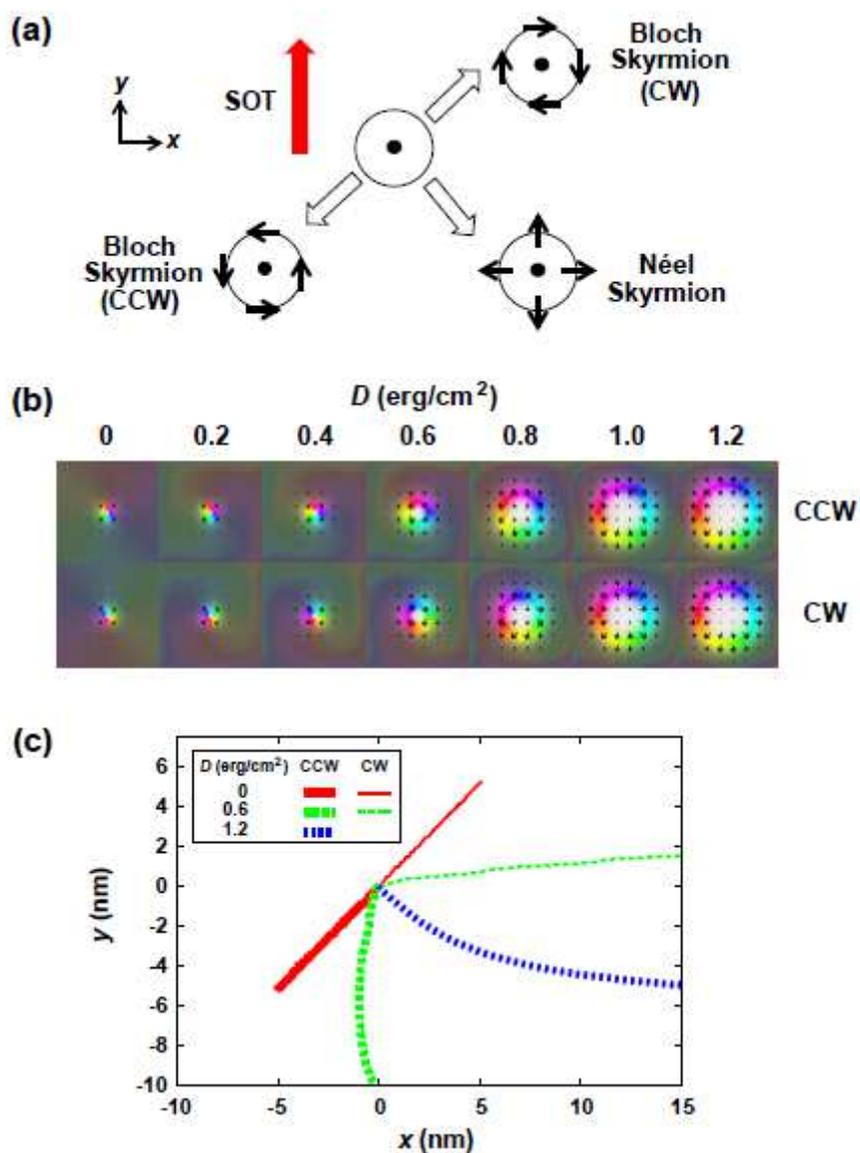


Figure 1

Motion of a skyrmion by SOT. (a) Direction of a motion of Bloch type skyrmions (CW and CCW) and Néel type skyrmion by SOT (analytical result [31]). (b) Change of the skyrmion structures for CCW and CW by the D value. (c) Change of the motion direction of a skyrmions for CCW and CW by the D value (simulation results).

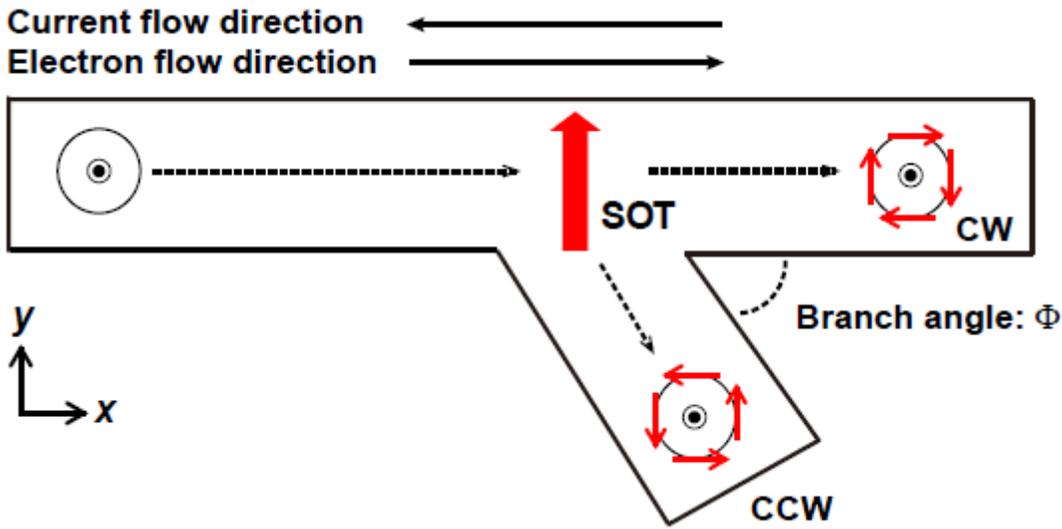


Figure 2

Illustration of a nanowire with a branch to discriminate a skyrmion chirality.

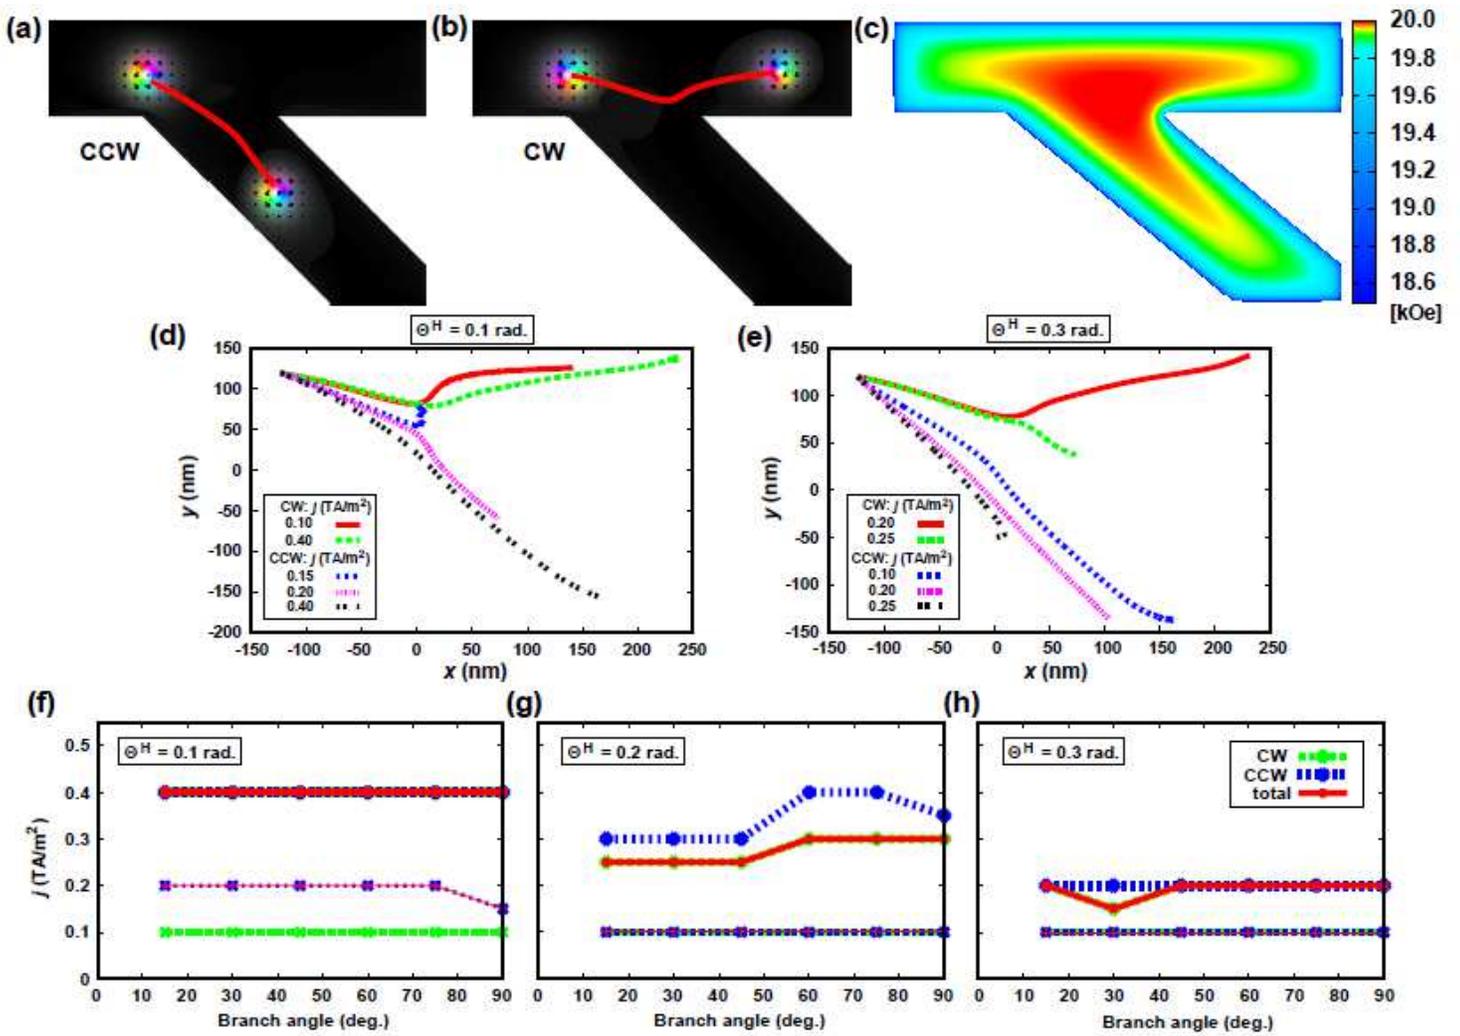


Figure 3

Motion of a skyrmion by SOT and STT. (a)&(b) Motion of a (a) CCW and (b) CW skyrmions by SOT and STT for 40 ns with the branch angle of 45° , $j = 0.3 \times 10^{12} \text{ A/m}^2$, $P = 0.7$, $\theta_H = 0.1 \text{ rad}$. (c) Distribution of the demagnetizing field at the branch. (d)&(e) Change of the skyrmion motion by the current density and spin Hall angle $\theta_H =$ (d) 0.1 and (e) 0.3 rad. (f)-(h) Effect of the branch angle on the current range for the normal branch with the spin Hall angle $\theta_H =$ (f) 0.1, (g) 0.2 and (h) 0.3 rad.