

# Optimization of silver nanocrystals reduced from the functional molecules enriched Spirulina – A potent antibiotic against human and marine pathogen *Vibrio parahaemolyticus*

Raja S (✉ [rajaselvaraju12@kongunaducollege.ac.in](mailto:rajaselvaraju12@kongunaducollege.ac.in))

Kongunadu Arts and Science College

**G. Anjali**

VIT University - Chennai Campus

**Jaganathan Anitha**

Kongunadu Arts and Science College

**Davis K. Ephsy**

Kongunadu Arts and Science College

**Kesavan Sahana**

Kongunadu Arts and Science College

**Kuppusamy Mohan**

VIT University - Chennai Campus

---

## Research Article

**Keywords:** Aquaculture, Spirulina, silver nanoparticles, *Vibrio parahaemolyticus*, antibiotics

**Posted Date:** May 9th, 2022

**DOI:** <https://doi.org/10.21203/rs.3.rs-1611077/v1>

**License:**  This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

---

# Abstract

Organic reduction of nanomaterials is an inexpensive and ecologically feasible method and the major challenge of this method is the optimization. The reduction of metal ions with the conjugation involves either by the extraction from natural materials like plants, algae, fungus, and bacteria or the microorganisms, which includes the intracellular synthesis of these particles. The present investigation deals with the green synthesis of silver nanoparticles (SNPs) reduced by *Spirulina platensis*. The reduced nanoparticle by the microorganism was materialized to inhibit the pathogenic *Vibrio parahaemolyticus* isolated from the aquaculture system of Tamil Nadu. The highest distribution percentage of *V. parahaemolyticus* was recorded in the farm water collected from shrimp farms of Nagapattinam than in the Cuddalore district. The presence of secondary metabolites in qualitative estimation and in GCMS revealed the presence of 32 compounds in both acetone and methanol extract. The essential fatty acids eicosane was found to have antibiotic potency against shrimp infected with pathogenic bacteria. The synthesized *Spirulina* SNPs were characterized by a biophysical technique like UV-Vis spectrophotometer, EDAX, XRD, transmission electron microscopy, and scanning electron microscopy. The analysis revealed a spherical structure without any agglomerates whose reduction absorption was at 200–450 nm. The well diffusion method, it showed inhibition of human and marine pathogen *V. parahaemolyticus*, whose inhibitory zone was at  $15.30 \pm 2.21$  and  $15.19 \pm 2.48$  mm respectively. Thus, the *Spirulina* mediated silver nanoparticles are found to be a simple, economical, and eco-friendly biomaterial to be a potent antibiotic against the shrimp bacteria.

# Introduction

Aquaculture is the main food-producing sector worldwide to make an enormous contribution to the economic and social well-being of the dominant fisheries nations (Flegel 2012; Raja et al. 2015; Naylor et al. 2021). Among that, shrimp aquaculture is one of the major industries which have rapidly grown during the past three decades in subtropical and tropical lowlands of America and Asia (Briggs et al. 2005). A shrimp species has an enriched quantity of proteins, essential amino acids, essential fatty acids, and micronutrients and possesses medicinal values (Gunalan et al. 2013). Large-scale marine aquaculture has been associated with environmental issues worldwide because of the accelerated development and high stocking density. During, the mid-1990s the corporate sector has taken the initiative to run shrimp farming. Unfortunately, the high-risk factor of viral and bacterial diseases and less production of shrimps due to a decrease in the area used for farming were the major challenges. It was reported that the corporate sector diminished shrimp farming activity from 11, 80, 900 ha to 1, 75, 680 ha, which is hardly 15 per cent of the total prospect (Rico et al. 2012; Singh et al. 2017).

In 1993, there was an outbreak of disease that reduced the Chinese shrimp production, The diseases created several problems for the development of Thai shrimp between 1996 and 1997. The severity of shrimp diseases was acknowledged in Ecuador in 1999 and in Brazil in the year 2006. Moreover, bacterial diseases are the most serious threat and often caused mass mortality in shrimp larvae (Ganesh et al. 2010), and *Penaeus vannamei* (Biju and Gunalan 2016). In marine shrimp farming, this is particularly

evident in the disquieting increase in vibriosis bacterial disease incidence as shrimp farmers around the world are coping with extreme damage (Chiu et al. 2007 and Flegel et al. 2008). *Vibrio* species, including *V. harveyi*, *V. parahaemolyticus*, *V. alginolyticus*, *V. anguillarum* and *V. splendidus*, are known to induce severe infections in aquaculture livestock, especially shrimp (Jayasree et al. 2006). They are not only a major economic threat to marine shrimp /farming but represent a public health concern as they are easily transmitted to humans through the consumption of seafood (Fuenzalida et al. 2007; Lee et al. 2008;).

Conventional approaches, such as the use of disinfectants and antimicrobial drugs to control diseases, have had limited success in the prevention or cure of aquatic diseases. The massive usage of commercially available antibiotics results in the natural emergence of antibiotic-resistant bacteria, which can transfer their resistance genes to other bacteria that have never been exposed to the antibiotics (Fair and Tor 2014). The widespread emergence of antimicrobial resistance acquired by *Vibrio* species against various antibiotics worldwide has become a major challenge (Giamarellou 2010). This has paved the way in developing a novel antibiotic approach to fight against bacterial infections on shrimp (Rice 2008; Freire-Moran et al. 2011).

Many of the experimental studies have emphasized the shrimp physiological properties of important therapeutic compounds in *Spirulina* (Ozdemir et al. 2004; Khan et al. 2011). The use of plants and algae for the synthesis of nanoparticles could be advantageous when combined with nanotechnology over other environmentally benign biological processes, the occurrence of several compounds in higher plants is well recorded as having an antioxidant function in biological systems, while in microalgae it is recorded less (Colla et al. 2007). Exploring the components in microalgae in the utilization of the nanoparticles synthesis to combat against various pathogenic microbial species is yet to be explored. Hence based on these facts, the present investigation was aimed at synthesis the silver nanoparticles on micro algae (*Spirulina platensis*) to explore its effect on the bacteria *Vibrio parahaemolyticus* affecting Shrimps with the following issues (a) the exploration of essential components in *Spirulina platensis* using GCMS. (b) Synthesis of *Spirulina* mediated silver nanoparticles. (c) Characterization of the silver nanoparticles using various biophysical techniques like UV, FTIR, XRD, FESEM, and TEM. (d) Assessing the antimicrobial potency against *Vibrio parahaemolyticus* has been done.

## Materials And Methods

### Purchase and maintenance of Spirulina

*Spirulina* stock culture was procured from the commercial farm at Palladam, Coimbatore, Tamil Nadu (Fig. 1) and the cultures were maintained at a temperature of  $25 \pm 1^\circ\text{C}$  in the light intensity of  $40 \mu\text{E} / \text{m}^2/\text{s}$ , photoperiod of 16:8 (Light and Dark) for 20 days. The cells were harvested and centrifuged at 10000 rpm for 5 to 10 minutes and the algal cells were dried at  $100^\circ\text{C}$  for 30 min for further use.

### Screening of shrimp pathogenic bacteria from shrimp farm water samples

The water from the shrimp farm in Nagappattinam and Cuddalore districts was collected in sterile polypropylene containers for microbiological analysis in the laboratory. The samples were serially diluted and were plated on to Thiosulfate-citrate-bile salts-sucrose (TCBS) agar medium at  $28 \pm 2^\circ\text{C}$  for 24 to 48 h. The enumeration of total presumptive *Vibrio spp* was conducted using spread plate technique. In respective samples as described by Beneduce et al. (2010). Hundred microliters of each pre-enriched homogenates with appropriate sample dilution (1:10, 1:100, and 1:1000) were spread in duplicates onto the tryptone soy agar (HiMedia, Mumbai) and incubated at  $37^\circ\text{C}$  for 18–24 h. After incubation, the total colony count is determined and their concentrations in the original shrimp in cfu/mL were calculated.

To isolate *V. parahaemolyticus*, the colonies were further purified by repeated streaking of the isolates on Tryptone Soy Agar (TSA) and added with 1.5% NaCl and incubated at  $37^\circ\text{C}$  for 18 h. The pure *V. parahaemolyticus* bacterial isolates were maintained (in TSA + NaCl) at  $4^\circ\text{C}$  with 15% glycerol at  $-70^\circ\text{C}$  (Thorstenson and Ullrich, 2021).

## Qualitative analysis of *S. platensis*

The aqueous extract of *S. platensis* was subjected to various qualitative analysis for ensuring the presence of active compounds of *S. platensis*, whose protocol is as follows: (i) Alkaloids (Santhi et al. 2011): Aqueous extract of *S. platensis* was added with 1% HCl along with 6 drops of Mayer's reagent followed by Drangendroff's mixture for the presence of precipitation to indicate the presence of alkaloids. (ii) Flavonoids (Beknal et al. 2010): The aqueous extract was added with a few drops of 10% lead acetate to obtain yellow precipitation. (iii) Cardiac glycosides (Santhi et al. 2011): Aqueous extract was added to 2mL of glacial acetic acid (GAA) containing one drop of ferric chloride solution and 1mL of concentrated sulphuric acid. This gives a brown ring to indicate the presence of a deoxy sugar characteristic. The colour changes to a brown ring from a violet ring. (iv) Steroids (Khan et al. 2011): Extract (1mL) + 1mL chloroform + 2–3 drops of conc.  $\text{H}_2\text{SO}_4$  gives pink colouration. (v) Tannins (Thenmozhi et al. 2010): The extract was added on to 1% lead acetate, it leads to yellow colouration indicating the presence of tannins in the sample. (vi) Terpenoids (Chakraborty 2019) :*S. platensis* extract was dissolved in 10mL of chloroform and filtered through Whatman filter paper No.1. Additionally, 2mL of acetic anhydride and 3 drops of concentrated  $\text{H}_2\text{SO}_4$  were added. Finally, the presence of steroids was confirmed with the appearance of the blue/green ring.

## Gas Chromatography Mass Spectrometry (GC-MS) analysis

The methanolic extracts of *S. platensis* samples were analyzed in Gas chromatography mass spectrometry (GC-MS), Shimadzu Mass Spectrometer-2010 series system (SMS Lab, Chennai) with an AB inno-wax column (60 m  $\times$  0.25 mm id and film thickness 0.25  $\mu\text{m}$ ). The ionization system with ionization energy of 70 eV was used for the detection through GC-MS. The Helium gas was used as a carrier gas at a flow rate of 1.2 ml per minute. Injector with mass transfer line of temperature was set at 270 and  $280^\circ\text{C}$  the phyto compounds were identified and the mass spectra obtained were matched with the inbuilt library (NIST/Wiley).

# Synthesis and Characterization of *S. platensis* reduced AgNPs

Aqueous silver nitrate (Sigma-Aldrich, Mumbai) of concentration 1 mM, is added with 150 ml of *S. platensis* extract. This was kept in dark to avoid photo activation of  $\text{AgNO}_3$  at room temperature (Muthusamy et al. 2017). Then obtained dark brown color solution during the heating process was characterized with the following methods (see Fig. 2).

The synthesis of *S. platensis* mediated silver nanoparticles was confirmed by sampling the reaction mixture at regular intervals (Following Anitha et al. (2016), The absorption curve was scanned by UV–vis spectrometer, at the wavelength ranging from 300 to 800 nm in a UV-3600 Shimadzu spectrophotometer at 1-nm resolution. Additionally, the reaction mixture was subjected to centrifugation at 15,000 rpm for 20 min. The pellet was dissolved in deionized water and filtered through a Millipore filter (0.45  $\mu\text{m}$ ). Surface groups of the nanoparticles were qualitatively confirmed by using FTIR spectroscopy (Bruker model, TENSOR 37), with spectra recorded by a Perkin Elmer Spectrum 2000 FTIR spectrophotometer. After freeze-dried the nanoparticles, were analyzed for its structure and composition by XRD analysis (Rigaku RINT 2100 series). The sample (25 $\mu\text{l}$ ) was sputter coated on a copper stub, and the morphology of *S. platensis* – AgNP was investigated using a Hitachi s-3500N SEM-EDX. Finally, the Transmission Electron Microscopic analysis was performed by a TEM, JEM-1200EX, 3 $\mu\text{L}$  by coating the nanoparticle sample on the carbon coated copper grid for making a thin film of sample on the grid. The extra samples were removed using a cone of blotting paper and sequentially kept in the grid box.

## Antibacterial assay

The Minimum inhibitory concentration (MIC) of green synthesized silver nanoparticle of *S. platensis* against *V. Parahaemolyticus* was studied by the method of well diffusion given by Subramanian et al. (2017) The medium containing alkaline peptone water (of  $10^{-1}$  dilution) was employed to grow *Vibrio* strain overnight at 37°C. The sample was seeded in three concentrations (10, 50 and 100  $\mu\text{mm}$ ) filled with 10ml of Mueller Hinton agar (MHA) medium in the Petri plates. In this medium, wells were cut and filled with 10 $\mu\text{l}$  of live suspension of *vibrio* culture with a cell density of  $10^5\text{ml}^{-1}$  CFU $^{-1}$  h and observed for the zone of clearance. The Petri plates were incubated at room temperature ( $28 \pm 1^\circ\text{C}$ ) for 24h and observed for the zone of inhibition which was measured in millimeters (mm).

## Results

*Vibrio parahaemolyticus* is a halophilic gram-negative pathogen found mainly in estuarine, marine, and coastal environments. Their population densities in the environment and seafood vary depending on the season, location, sample type, and analytical methodology employed (Martinez-Urtaza et al. 2008; Zarei et al. 2012). Hence, two shrimp farm water samples collected from Cuddalore and Nagapattinam districts were used for enumerating the presence of *Vibrio* colonies. From the total colonies, the pure culture of *V. Parahaemolyticus* were isolated and cultured for further use (Fig. 3). From these results, it could be

concluded that, more risk factors are associated in samples collected from Nagapattinum and Cuddalore district. The colony count of *V. Parahaemolyticus* was found to be high in Nagapattinum (58%) shrimp farms than in Cuddalore (56%) shrimp farms as given in Table 1.

Table 1  
Frequency distribution of *V. Parahaemolyticus* strain in selected districts of Tamil Nadu

Sampling District	Total Number of other unknown colonies	Total Number of <i>V. Parahaemolyticus</i>	Percentage (%) of appearance
Cuddalore	140	78	55.7
Nagapattinum	173	101	58.3

The various primary and secondary metabolites in *S. Platensis* extract was analyzed using qualitative methods and confirmed the presence of Alkaloids, Terpenoids, Tannins, Saponins, Flavonoids, and Steroids (Table 2) respectively. The GC-MS (Fig. 4A&B) analysis was subjected to the quantification of active components of *S. platensis* in methanolic extract of *S. platensis*, which showed around 16 bioactive components (1-Tridecene, Sulfurous acid, 2-ethylhexyl isohexyl ester, Heptadecene, 1-Pentadecene, Octane, 9-Octadecenoic acid (Z), Methyl Ester, Hexadecanoic acid, Methyl Ester, 3-Eicosene, (E)-6,9,12-Octadecatrienoic acid, 11,14-Eicosadienoic acid, Methyl ester, Oxirane, 1,2,3,4-Tetrakis O (Trimethylsilyl), 2-Undecene, 9-methyl, Tetracosanoic acid, methyl ester, 1,2-benzene dicarboxylic acid) respectively, which is showed in Table 3. Among these compounds, the major compound identified as fatty acid (Eicosane) 42.11% which would be responsible for antibacterial potency.

Table 2  
Qualitative assessment of secondary metabolites of *S. platensis*

S.No.	Phytochemicals	Present/Absent
1.	Alkaloids	+
2.	Flavonoids	+
3.	Glycosides	+
4.	Steroids	+
5.	Tannins	+
6.	Terpenoids	+

Table 3  
GCMS quantification of active components of *S. platensis*

Peak	Retention time (RT)	Area	Area (%)	Active compounds
1	11.271	106819	1.31	1-Tridecene
2	11.318	41868	0.51	Sulfurous acid, 2-Ethylhexyl isohexyl ester
3	12.091	762878	9.37	Heptadecene
4	12.782	91362	1.12	1-Pentadecene
5	13.396	27954	0.34	Octane
6	13.595	196469	2.41	9-Octadecenoic acid (Z), Methyl ester
7	13.702	2688125	33.01	Hexadecanoic acid, Methyl ester
8	14.132	95738	1.18	3-Eicosene (E)
9	14.749	721661	8.86	6,9,12-Octadecatrienoic acid
10	14.831	1875273	23.03	11,14-Eicosadienoic acid, Methyl ester
11	14.950	1249522	15.35	Phytol

*S. platensis* mediated silver nanoparticles has been synthesized using reduction method and the particles were characterized using various biophysical techniques. The reaction mixture changes color from light green to dark reddish-brown, which indicates the formation of AgNPs whose UV-Visible absorption spectrum, recorded a strong, broad peak located at 450 nm (Fig. 5A). Further, the synthesized AgNPs acquired high precipitation of silver particles on the cell surface when analyzed in FTIR (Fig. 5B) (Perkin Elmer Spectrum 2000) which reveals the presence of the functional groups in *S. platensis* and the nanoparticles conjugated with *S. platensis*. The broad, sharp, and narrow stretching frequency was identified as 3788, 3425, 2927, 2343, 1721, 1657, 1641, 1631, 1547, 1535, 1501, 1461, 1408, 1067, 668, 566  $\text{cm}^{-1}$  respectively. These bands may correspond to the various active functional groups like alcohol (O-H), Alkanes (C-H), Carboxylic acids and Alpha, Beta-unsaturated aldehydes (C = O), N-O asymmetric stretch alkyl halides (C-Cl stretch), aromatics (C-C stretch), aliphatic amines (C-N stretch) which are comprehensively postulated in Table 4.

Table 4  
FTIR stretching frequency corresponding bonds with its functional groups

<b>Wavenumbers (<math>cm^{-1}</math>)</b>	<b>Bond</b>	<b>Functional groups</b>
3788.91	O-H stretch, free hydroxyl	Alcohols
3425.49	O-H stretch (alcohols) H-bonded	Alcohols
2927.29	C-H stretch	Alkanes
2343.65	C-H stretch	Alkanes
1721.88	C = O stretch	Carboxylic acids
1657.96	C = O stretch	Alpha, Beta-unsaturated aldehydes
1641.08	-C = C-stretch	Alkenes
1631.02	N-H bend	Primary amines
1547.57	N-O asymmetric stretch	Nitro compounds
1535.68	C-C stretch (in-ring)	Aromatics
1501.66	C-C stretch	Aromatics
1461.31	C-H bend	Alkanes
1408.95	C-C stretch	Aromatics
1067.51	C-N stretch	Aliphatic amines
668.87	C-Cl stretch	Alkyl halides
566	C-Br stretch	Alkyl halides

The morphology of element of nanoparticles was determined by SEM and is shown in the corresponding micrographs in Fig. 6A. With the critical analysis, it has been observed that silver nanoparticles of *S. platensis* were slightly agglomerated, mostly spherical in shape, and found throughout the region. The TEM (Fig. 7) confirmed the spherical nature of the particles and was observed not forming big agglomerates. This indicates the monodispersed nature of NPs reduced by *S. platensis*. The EDX spectrum indicated that the reaction product was composed with the presence of the pure silver metal (55.08% of purity) with strong signals given in Fig. 6B.

Figure 8 showed the X-ray diffraction spectrum of synthesized silver nanoparticles by using aqueous extract *S. platensis*. The reflections were observed in the Bragg's XRD pattern at  $2\theta = 38.48; 44.95; 65.71$  and  $77.18$ . These reflections clearly indicated the presence of observed peaks (at 111, 200, 220 and 311 sets) of lattice planes and further, it can be indexed as a face-centered-cubic (FCC) structure of Ag. Therefore, the present study clearly showed that the X-ray diffraction pattern of AgNPs formed crystalline structures.

Finally, the antimicrobial potency of *S. platensis* reduced silver nanoparticles was tested against shrimp pathogen *V. parahaemolyticus*. The range was expressed as inhibition zone of  $15.19 \pm 2.4$  and  $16.67 \pm 1.3$  mm, when inoculated with 10, 50 and 100  $\mu\text{m}$  respectively. This is shown in Fig. 9. This clearly indicates that, the silver nanoparticles have the potential to control the pathogenic *V. parahaemolyticus* of shrimp pathogens.

## Discussion

The *Spirulina platensis* mediated silver nanoparticles antibacterial results showed excellent inhibition against the human and marine *Vibrio parahaemolyticus* isolated from the aquaculture system of Tamil Nadu. Shrimp farming is a blooming aquaculture industry which altered every time due to disease causing bacterial pathogens in the soil and water which causes bacterial diseases in the aquatic animals (Chellapandian et al. 2021) and their associated people. The few strains of *Vibrio parahaemolyticus* species are human pathogens, causing gastroenteritis (Broberg et al. 2012) it can be inhibited by *Spirulina platensis* mediated silver nanoparticles.

Overall, 55.7% and 58.3% of *Vibrio parahaemolyticus* are present in our study area Cuddalore and in Nagappattinam district which is higher than 20 percent recorded by Gámez-Bayardo et al. 2021. Also, Silvester et al. (2015) reported 71.6% in the Cochin estuary and 53.3% in the shrimp farm. Biju and Gunalan (2016) reported that 29.01% *Vibrio spp.* were isolated from *Penaeus vannamei* from three major shrimp farm villages of Nagappattinam district and the detection rate of *V. parahaemolyticus* reported in shrimp has 6.7% (Gámez-Bayardo et al. 2021), and 4.28% from marine shrimp and 2.5% from freshwater shrimp samples (Patel et al., 2018). According to Borowsky et al. (2007), the quantification of microorganisms present in the samples is important for assessing the risk to consumers.

The gram-negative *Vibrio parahaemolyticus* is usually found in tropical and temperate coastal waters, as well as in shrimp aquaculture (Norma et al. 2009). Also, Zulkifli et al. (2009) mentioned a high marine temperature between 25 and 35°C, resulting in the distribution of *V. parahaemolyticus* all year round. The shrimp ponds with lower dissolved oxygen and higher unionized ammonia level provide *Vibrio spp.* opportunity to enter and cause mortality (Elgendy et al. 2015). In the present investigation, the colony count of the *Vibrio spp.* was found to be high in the Nagappattinam district than in the Cuddalore district, due to the temperature variation as suggested by Naylor (2021). The risk and level of *Vibrios* reduces upon maintaining a cold temperature for storage and transit of Seafood (Elhadi et al. 2004). A high contamination was found in shellfishes with pathogenic *Vibrios* in samples collected from roadside stalls compared to markets in Cochin, India (Sudha et al. 2014). Hence the percentage of *V. parahaemolyticus* distribution depends on the temperature and postulates the differential distribution among the districts selected for the present study.

Among the marine microorganisms, *S. platensis*, a well-known cyanobacterium is an exceptionally rich source of bioactive compounds (Rastogi et al. 2015) in killing cancer cells. It has been reported to have antimicrobial, anti-inflammatory, and antiviral properties (Vijayakumar and Menakha 2015). The major

secondary metabolites (Alkaloids, Terpenoids, Tannins, Saponins, Flavonoids, and Steroids) isolated from this *S. platensis* can be utilized for the antibiotic potency. These Gram-negative photosynthetic prokaryotes produce bioactive secondary metabolites as quorum sensing inhibitory compounds and as a chemical defense against invading pathogens (Mayer and Hamann 2000). Agustini et al. (2015) indicated the absence of alkaloids in *Spirulina*, while Ali et al. (2014) reported qualitative and quantitatively presence of phenolic compounds and total alkaloids like the present study for *S. platensis*. Kannan et al. (2014) has reported the presence of similar phytochemical constitutions in the same species hence there is not many phytochemical compounds difference found.

The GC-MS analysis showed the phytochemicals of secondary metabolites present in the *S. platensis*. The algal species showed 16 bioactive components in methanol extract and in all these compounds eicosanoids (fatty acids) dominated the account. The similar result was also studied by Jubie and Dhanabal (2012) who isolated 15 compounds in *S. Platensis* acetone extract which contains essential fatty acids like gamma linolenic, stearic, myristic, linoleic, heptadecanoic acid, etc. Therefore, the composition of individual fatty acids has been found to influence the retention time and molecular weight that controls the pathogenic microbes. The results of the current study, it is suggested that the silver nanoparticles derived from *S. platensis* help in reducing the effect of shrimp pathogen infection. This may also be a potential alternative to chemicals in the control of pathogenic microbes and ensure sustainable growth of the industry.

In general, silver has greater chemical stability and unique catalytic activity when combined with the plant species it will have greater potency in their application without any residual effects. The UV-vis spectra can provide valuable information on the shape, size, and distribution of nanoparticles based on Surface Plasmon Resonance (SPR) bands. For instance, the appearance of the Ag peak at a shorter wavelength in the UV-vis spectra reveals the small size of Ag-NPs that were formed, while a longer wavelength indicates bigger Ag-NPs (Mashwani et al. 2016). Hence in the present investigation, the UV spectra of synthesized silver nanoparticles was recorded at 450 nm which corroborates with the findings of Anitha et al. (2012). It was suggested that the reduction method of silver nanoparticles reduced at 450nm respectively. In general, the peaks (at 450nm) obtained by colloidal silver nanocomposite in the specified region will be due to the excitation of the surface plasmon vibrations between the functional groups of the *S. platensis* which may facilitate the reduction of  $\text{Ag}^+$  to  $\text{Ag}^0$ . Nandhagopal et al. (2015) studied the UV-vis spectrophotometry, where the peak was detected at 425 nm. The reduction might be due to the primary and secondary metabolites which play an active role as (Anitha et al. 2012) reducing agents in biological agents (Benelli 2016a; Benelli 2016b).

FTIR measurements of greener microalgae mediated AgNPs was carried out to identify the possible biomolecules responsible for the stabilization of silver nanoparticles. The FTIR analysis revealed various functional groups present in the reduction process in which the bands obtained at  $3788$  and  $3425\text{ cm}^{-1}$ , assumes the presence of alcohol group (OH stretch) which always have bonded with oxygen and hydrogen for its functionality (Niraimathi et al. 2013). The unsaturated hydrocarbons which means, more bonds will be present between carbon atoms are the C-H stretch (alkene groups) were at  $2927$  and  $2343$

$\text{cm}^{-1}$ . The C-N and N-H bonds present in 1631 and  $1461\text{cm}^{-1}$  postulates the presence of the glycosides and amines of the protein's in *S. platensis* was in support the findings of Prakash et al. (2013). The presence of flavonoids and proteins may facilitate the reduction of silver ions in to silver nanocomposite was suggested by Zuas et al. (2014). The durable bands at 1547, 1535 and  $1501\text{cm}^{-1}$ , could be due to C = C stretching in the aromatic ring, confirming the presence of the aromatic group which was in accordance with the aromatic rings obtained from the silver nanoparticles studied by Al-Otibi et al. (2021). Further the presence of C = O stretch and N-O asymmetric stretch in the FTIR analysis predicted the presence of nitro compounds which may help in the reduction of the nanoparticles (Silverstein et al. 1991). From this analysis, it has been studied that the functional groups will help in the poly dispersion of the nanoparticles whose vibration frequency are at 668 and  $566\text{cm}^{-1}$  respectively. Similarly, Xie et al. (2007) also reported that carboxyl and hydroxyl groups from the extract of microbial species are involved in the biosynthesis of AgNPs.

The shape of the particles obtained is in accordance with the spherical to oval AgNPs with average particle size of 17.9 and 26.4 nm for *S. platensis* and *A. variabilis*, respectively (Ismail et al. 2020). This might be due to the polydispersity index of the nanoparticles through SEM and TEM studies (Ardani et al. 2017). These measurements are fundamentally different and are based on the hydrodynamic and dry radius of particles, respectively (Kaasalainen et al. 2017). The phase of the silver metal was confirmed in the EDAX pattern of synthesized silver nanoparticles. The intense signal was obtained as a peak for silver and a weak signal was acquired for the copper in the present investigation. From this, it has been confirmed that the reduction of silver ion by the molecules present in *S. platensis* is feasible. The silver nanocrystals usually display a characteristic visual absorption peak approximately at 3KeV due to surface plasmon resonance (Kaviya et al. 2011)

The presence of pure metal peak for silver suggested the confirmation of the presence of silver. The XRD for the synthesized Ag NPs exhibits the behavior diffraction features with  $2\theta$  at 38.48, 44.95, 65.71 and  $77.18^\circ$  which represents the Bragg's reflections (111), (200), (220), (311) and (422) respectively (Baraka et al. 2017; Bryaskova et al. 2011). Biological effectiveness of NPs enhances due to increase in specific surface area and surface energy and used for various therapeutic purposes (Danaei et al. 2018). Silver has severe inhibitory effect even at a very low concentrations on many bacterial strains and microorganisms (Mahdieh et al. 2012) and they inhibit the growth of antibiotic resistant bacteria. The bacterial cell wall charge of bacterial cell wall is negative because of dissociation of carboxylic groups on the cell surface (Parveen et al 2018). Weak positive charges present on AgNPs are attracted towards negative charges (Raffi et al. 2008). In contrast, Sondi and Salopek-Sondi (2004) and Schultz et al. (2000) suggested that the antibacterial effects of AgNPs on bacteria depended on the concentration of AgNPs and closely related to the development of pits on cell wall of bacteria. AgNPs interact with the thiol groups of bacterial proteins and may retard the replication of DNA (Sondi and Salopek 2004).

Silver nanoparticles exhibit effective antimicrobial properties compared to other nanoparticles because of their extremely large surface area, which offers improved interaction with microorganisms (Wang et al. 2017). In the current findings the silver nanoparticles reduced using *S. platensis* showed that the range of

inhabitation zone between  $15.19 \pm 2.48\text{mm}$  and  $16.67 \pm 1.37\text{mm}$ , respectively. This clearly indicates the biogenic silver nanoparticles have the potential to control the pathogenic *V. parahaemolyticus*, a shrimp pathogen. The algal species has contained fatty acids which may be responsible for inhibiting pathogenic bacteria *V. parahaemolyticus* which is supported by the results of Martinez-Castanon et al. (2008) who reported that the fatty acids in *S. platensis* have been more effective against bacterial species (see Fig. 6). Similarly, Sudha et al. (2011) and Abdo et al. (2012) have reported that the *S. platensis* individually and combined with silver nanoparticles exhibited more anti-bacterial activity against human pathogens.

## Conclusions

The current study demonstrates that the silver nanoparticles derived from *S. platensis* can control the *V. parahaemolyticus* bacteria from causing harm to shrimps. The pathogenic bacteria, *Vibrio parahaemolyticus*, produces a variety of deleterious diseases in shrimp and thus causes heavy economic damage to the shrimp industry which yields a considerable foreign exchange to our country. *Vibrio* spp. was found to be high in the Nagappattinam district than in the Cuddalore district. The produced AgNPs were then confirmed by different techniques: UV-vis, FTIR, and GC-MS spectroscopy, SEM-EDAX, SEM, TEM imaging techniques, and XRD analyses. The synthesized AgNPs showed better antibacterial activities against *Vibrio* spp. with the range was expressed as inhabitation zone of  $15.19 \pm 2.4$  and  $16.67 \pm 1.3$  mm, when inoculated with 10, 50 and 100  $\mu\text{mm}$  respectively. The EDX spectrum indicated that, the reaction product was composed with the presence of the pure silver metal (55.08% of purity) with strong signals. This spirulina silver nanoparticles may also be a potential alternative to chemicals control of pathogenic microbes and ensure sustainable growth of the aquaculture industry.

## Declarations

**Ethics approval and consent to participate:** Not Applicable

**Consent for publication:** Not Applicable

**Availability of data and materials:** The datasets used and/or analysed during the current study are available from the corresponding author on reasonable request.

**Competing interest:** The authors declare that they have no competing interests

**Funding:** Not Applicable

**Authors' contributions:** All authors are responsible for the entire manuscript. SR did the experimental work and optimization work was carried out by JA, KS and DKE. Literature review and drafting of manuscript was done by SR, JA, KS and DKE. Editing and revising of manuscript, review and editing of figures and tables were performed by AG and MK. All authors read and approved the final manuscript.

**Acknowledgement:** The authors would like to thank the research department of zoology and biochemistry for rendering their support to complete the work successfully.

## References

- Abdo SM, Hetta MH, Samhan FA, El Din RA, Ali GH (2012). Phytochemical and antibacterial study of five freshwater algal species. *Asian J Plant Sci.* 11:109-116. <https://doi.org/10.3923/ajps.2012.109.116>
- Agustini TW, Suzery M, Sutrisnanto D, Ma'ruf WF., [Hadiyanto](#) (2015). Comparative study of bioactive substances extracted from fresh and dried *Spirulina* sp. *Procedia Environ Sci* 23:282-9. <https://doi.org/10.1016/j.proenv.2015.01.042>
- Ali HE, Shanab SM, Shalaby EA, El Demerdash UM, Abdullah MA (2014) Evaluation of antioxidants, pigments and secondary metabolites contents in *Spirulina platensis*. *Applied Mechanics and Materials; Trans Tech Publ* 625:160-163. [https://doi.org/10.4028/www.scientific.net/AMM.625.160\\_](https://doi.org/10.4028/www.scientific.net/AMM.625.160_)
- [Al-Otibi Fatimah](#), [Shahad K.](#) [Alkhudhair](#), [Raedah I.](#) [Alharbi](#), [Abdulaziz A.](#) [Al-Askar](#), [Reem M.](#) [Aljowaie](#), [Sameha Al-Shehri](#) (2021). The Antimicrobial Activities of Silver Nanoparticles from Aqueous Extract of Grape Seeds against Pathogenic Bacteria and Fungi. *Molecules.* 26(19): 6081. <https://doi.org/10.3390/molecules26196081>
- Anitha J, Jayraaj IA (2012). Nutritional and antioxidant evaluation of earthworm powder (*Eudrillus euginae*). *Int. Res. J. Pharm* 3(2):177-80.
- Anitha J, Murugan K, Panneerselvam C, Madhiyazhagan P, Dinesh D, Vadivalagan C, Chandramohan B, Suresh U, Rajaganesh R, Subramaniam J, Nicoletti M (2016). Earthworm-mediated synthesis of silver nanoparticles: A potent tool against hepatocellular carcinoma, Plasmodium falciparum parasites and malaria mosquitoes. *Parasitology inter.* 65(3):276-84. <https://doi.org/10.1016/j.parint.2016.02.003>
- Ardani HK, Imawan C, Handayani W, Djuhana D, Harmoko A, Fauzia V (2017). Enhancement of the stability of silver nanoparticles synthesized using aqueous extract of *Diospyros discolor* Willd. Leaves using polyvinyl alcohol. *IOP Conf. Ser. Mater. Sci. Eng* 188(1):12056. <https://doi.org/10.1088/1757-899X/188/1/012056>
- Baraka A, Dickson S, Gobara M, El-Sayyad GS, Zorainy M, Awaad MI, Hatem H, Kotb MM, Tawfic A.F (2017). Synthesis of silver nanoparticles using natural pigments extracted from Alfalfa leaves and its use for antimicrobial activity. *Chemical Papers* 71:2271-2281. <https://doi.org/10.1007/s11696-017-0221-9>
- Beknal AK, Korwar PG, Halkai MA, Kulkarni U, Patil BS, Soodam SR (2010). Phytochemical investigation and antioxidant activity study of *Drynaria quercifolia* Linn. rhizome. *Int J Curr Pharmaceut Res* 2(4):36-39.

Beneduce L, Vernile A, Spano G, Massa S, Lamacchia F, Oliver JD (2010) Occurrence of *Vibrio vulnificus* in mussel farms from the Varano lagoon environment. *Let App Micro* 51(4):443-9. <https://doi.org/10.1111/j.1472-765X.2010.02917.x>

Benelli G (2016a). Plant-mediated biosynthesis of nanoparticles as an emerging tool against mosquitoes of medical and veterinary importance: a review. *Parasitol. Res* 115(1):23-34. <https://doi.org/10.1007/s00436-015-4800-9>

Benelli G (2016b). Plant-mediated synthesis of nanoparticles: a newer and safer tool against mosquito-borne diseases?. *Asian Pac. J. Trop. Biomed* 6(4):353-354. <https://doi.org/10.1016/j.apjtb.2015.10.015>

Biju VN, Gunalan B (2016). Prevalence of *Vibrio* infection in *Penaeus (Litopenaeus) Vannamei* Farms. *IJSIT* 5(6), 485-493.

Borowsky LM, Verônica Schmidt, Marisa Cardoso (2007). Estimation of most probable number of *Salmonella* in minced pork samples. *Brazilian Journal of Microbiology* 38(3): 544-546. <https://doi.org/10.1590/S1517-83822007000300030>

Briggs M, Funge-Smith S, Subasinghe RP, Phillips M. Introductions and movement of two penaeid shrimp species in Asia and the Pacific. *FAO Fisheries Technical Paper*. No. 476. Rome, FAO. 2005. 78p.

Broberg CA, Thomas J. Calder, Kim Orth (2011). *Vibrio parahaemolyticus* cell biology and pathogenicity determinants. *Microbes Infect.* 13(12-13): 992–1001. <https://doi.org/10.1016/j.micinf.2011.06.013>

Bryaskova R, Pencheva D, Nikolov S, Kantardjiev T (2011) Synthesis and comparative study on the antimicrobial activity of hybrid materials based on silver nanoparticles (AgNps) stabilized by polyvinylpyrrolidone (PVP). *J. Chem. Biol* 4(4):185-91. <https://doi.org/10.1007/s12154-011-0063-9>

Chellapandian H, Jeyachandran S, A. Vijay Anand, Balamuralikrishnan B (2021). Challenges in Controlling Vibriosis in Shrimp Farms. In book: *Infections and Sepsis Development*, 394pp. <https://doi.org/10.5772/intechopen.97018>

Chakraborty B (2019). Phytochemical screening of *Spirulina platensis* extracts from Rankala Lake Kolhapur, India. *Algal Research* 9(4):38-41.

Chiu CH, Guu YK, Liu CH, Pan TM, Cheng W (2007). Immune responses and gene expression in white shrimp, *Litopenaeus vannamei*, induced by *Lactobacillus plantarum*. *Fis Shel Immunol* 23(2):364-377. <https://doi.org/10.1016/j.fsi.2006.11.010>

Colla LM, Reinehr CO, Reichert C, Costa JA (2007). Production of biomass and nutraceutical compounds by *Spirulina platensis* under different temperature and nitrogen regimes. *Biores tech* 98(7):1489-1493. <https://doi.org/10.1016/j.biortech.2005.09.030>

Danaei M, Dehghankhold M, Ataei S, Hasanzadeh F, Davarani, Javanmard R, Dokhani A, Khorasani S, Mozafari MR (2018). Impact of particle size and polydispersity index on the clinical applications of lipidic nanocarrier systems. *Pharmaceutics* 10(2), 57 <https://doi.org/10.3390/pharmaceutics10020057>

Elgendy M, Waleed Salah Alshamy, Hossam Abbas, AM. Kenawy, Liala AM (2015). Effect of Abrupt Environmental Deterioration on the Eruption of Vibriosis in Mari-Cultured Shrimp, *Penaeus indicus*, in Egypt. *Journal of Fisheries and Aquatic Science*. <https://doi.org/10.3923/jfas.2015.146.158>

Elhadi N, Radu S, Chen CH, Nishibuchi M (2004). Prevalence of potentially pathogenic *Vibrio* species in the seafood marketed in Malaysia. *J Food Protect* 67(7):1469-1475. <https://doi.org/10.4315/0362-028X-67.7.1469>

Fair RJ, Tor Y (2014). Antibiotics and Bacterial Resistance in the 21st Century. *Perspectives in Medicinal Chemistry*, 6:25-64. <https://doi.org/10.4137/PMC.S14459>

Flegel TW, Lightner DV, Lo CF, Owens L (2008) Shrimp disease control: past, present and future. *Diseases in Asian Aquaculture VI*. Fish Health Section, Asian Fisheries Society, Manila, Philippines 505:355-78.

Freire-Moran L, Aronsson B, Manz C, Gyssens IC, So AD, Monnet DL, Cars O, ECDC-EMA working group (2011) Critical shortage of new antibiotics in development against multidrug-resistant bacteria-Time to react is now. *Drug Resist Updat* 14(2):118-24. <https://doi.org/10.1016/j.drup.2011.02.003>

Fuenzalida L, Armijo L, Zabala B, Hernández C, Rioseco ML, Riquelme C, Espejo R.T (2007). *Vibrio parahaemolyticus* strains isolated during investigation of the summer 2006 seafood related diarrhea outbreaks in two regions of Chile. *Int. J. Food Microbiol* 117(3):270-275. <https://doi.org/10.1016/j.ijfoodmicro.2007.03.011>

Gámez-Bayardo S, Gloria Marisol Castañeda-Ruelas, Angélica Espinosa-Plascencia, María del Carmen Bermúdez-Almada, Jiménez-Edeza M (2021). Characterization of *Vibrio parahaemolyticus* strains and evaluation of shrimp cultivation conditions in a farm at the northwestern of Mexico, as risk predictors for its adaptation and dissemination. *Lat. Am. J. Aquat. Res.* 49(1). <http://dx.doi.org/10.3856/vol49-issue1-fulltext-2512>

Ganesh EA, Das S, Chandrasekar K, Arun G, Balamurugan S (2010). Monitoring of total heterotrophic bacteria and *Vibrio* spp. in an aquaculture pond. *Current Research Journal of Biological Sciences* 2(1): 48-52.

Giamarellou H (2010). Multidrug-resistant Gram-negative bacteria: how to treat and for how long, *Int. J. Antimicrob. Agents* 36 (Suppl 2): 50-54. <https://doi.org/10.1016/j.ijantimicag.2010.11.014>

Gunalan BS, Nina TS, Soundarapandian P, Anand T (2013). Nutritive value of cultured white leg shrimp *Litopenaeus vannamei*. *International Journal of Fisheries and Aquaculture*. 5(7):166 – 171. <https://doi.org/10.5897/IJFA2013.0333>

- Ismail GA, Allam NG, El-Gemizy WM, Salem MA (2020). The role of silver nanoparticles biosynthesized by *Anabaena variabilis* and *Spirulina platensis* cyanobacteria for malachite green removal from wastewater. *Env Tech* 42(28):4475-89. <https://doi.org/10.1080/09593330.2020.1766576>
- Jayasree L, Janakiram P, Madhavi R (2006). Characterization of *Vibrio* spp. associated with diseased shrimp from culture ponds of Andhra Pradesh (India). *World aquaculture society* 37(4):523-532. <https://doi.org/10.1111/j.1749-7345.2006.00066.x>
- Kaasalainen M, Aseyev V, von Haartman E, Karaman DŞ, Mäkilä E, Tenhu H, Rosenholm J, Salonen J (2017). Size, stability, and porosity of mesoporous nanoparticles characterized with light scattering. *Nanoscale Res* 12(1):74. <https://doi.org/10.1186/s11671-017-1853-y>
- Kannan M, Pushparaj A, Dheebea B, Nageshwari K, Kannan (2014). Phytochemical screening and antioxidant activity of marine algae *Gracilaria corticata* and *Spirulina platensis*. *J Chem and Pharmaceutical Rese* 6(11):312-318.
- Kaviya S, Santhanalakshmi J, Viswanathan B, Muthumary J, Srinivasan K (2011). Biosynthesis of silver nanoparticles using *Citrus sinensis* peel extract and its antibacterial activity. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy* 79(3):594-8. <https://doi.org/10.1016/j.saa.2011.03.040>
- Khan AM, Qureshi RA, Ullah F, Gilani SA, Nosheen A, Sahreen S, Murad W (2011). Phytochemical analysis of selected medicinal plants of Margalla Hills and surroundings. *J. Med. Plants Res.*, 5(25): 6055-6060. <https://doi.org/10.5897/JMPR11.869>
- Jubie S, Dhanabal SP (2012). Gas chromatography-mass spectrometry analysis and antibacterial activity of fatty acid mixture of *Spirulina platensis*. *J Pharm Sci and Res* 4(6):1836– 1838.
- Lee JK, Jung DW, Eom SY, Oh SW, Kim Y, Kwak HS, Kim YH (2008). Occurrence of *Vibrio parahaemolyticus* in oysters from Korean retail outlets. *Food Control* 19(10):990-994. <https://doi.org/10.1016/j.foodcont.2007.10.006>
- Martínez-Castañón GA, Nino-Martinez N, Martinez-Gutierrez F, Martinez-Mendoza JR, Ruiz F (2008). Synthesis and antibacterial activity of silver nanoparticles with different sizes. *J nanoparticle res* 10:1343-8. <https://doi.org/10.1007/s11051-008-9428-6>
- Martinez-Urtaza J, Huapaya B, Gavilan RG, Blanco-Abad V, Ansedo-Bermejo J, Cadarso-Suarez C, Figueiras A, Trinanés J (2008). Emergence of asiatic *Vibrio* diseases in South America in phase with El Niño. *Epidemiology* 19(6): 829-37. <https://doi.org/10.1097/EDE.0b013e3181883d43>
- Mahdieh M, Zolanvari A, Azimee AS., M. Mahdieh (2012). Green biosynthesis of silver nanoparticles by *Spirulina platensis*. *Scientia Iranica* 19(3):926-9. <https://doi.org/10.1016/j.scient.2012.01.010>
- Mashwani, ZR, Khan MA, Khan,T, Nadhman A (2016). Applications of plant terpenoids in the synthesis of colloidal silver nanoparticles. *Adv. ColloidInterface Sci.* 234, 132–141.

<https://doi.org/10.1016/j.cis.2016.04.008>

Mayer AMS, Hamann MT (2004). Marine pharmacology in 2000: marine compounds with antibacterial, anticoagulant, antifungal, anti-inflammatory, antimalarial, antiplatelet, antituberculosis, and antiviral activities; affecting the cardiovascular, immune, and nervous systems and other miscellaneous mechanisms of action. *Mar Biotechnol* 6(1):37-52. <https://doi.org/10.1007/s10126-003-0007-7>

Muthusamy G, Thangasamy S, Raja M, [Sudhakar Chinnappan](#), [Selvam Kandasamy](#) (2017). Biosynthesis of silver nanoparticles from *Spirulina* microalgae and its antibacterial activity. *Environ Sci Pollut Res* 24, 19459–19464. <https://doi.org/10.1007/s11356-017-9772-0>

Nandagopalan V, Prabha AL, Doss A (2015). Biosynthesis and characterization of nanoparticles from three *Aristolochia* species. *World J. Pharm. Pharm. Sci* 4(7):1094-104.

Naylor RL, Ronald W. Hardy, Alejandro H. Buschmann, [Simon R. Bush](#), Ling Cao, Dane H. Klinger, David C. Little, Jane Lubchenco, Sandra E. Shumway, Max Troell (2021). A 20-year retrospective review of global aquaculture. *Nature* 591(7851):551-563. <https://doi.org/10.1038/s41586-021-03308-6>

Niraimathi KL, Sudha V, Lavanya R, Brindha P (2013). Biosynthesis of silver nanoparticles using *Alternanthera sessilis* (Linn.) extract and their antimicrobial, antioxidant activities. *Colloids and surfaces B: biointerfaces* 102:288-91. <https://doi.org/10.1016/j.colsurfb.2012.08.041>

Norma H, Irene W, Santos G (2009). Microbiologically safe foods. John Wiley & Sons, Inc. New Jersey. <https://doi.org/10.1002/9780470439074>

Ozdemir G, UlkuKarabay N, Dalay MC, Pazarbasi B (2004) Antibacterial activity of volatile component and various extracts of *Spirulina platensis*. *Phytother Res* 18(9):754-757. <https://doi.org/10.1002/ptr.1541>

Parveen A, Yalagatti MS, Abbaraju V, Deshpande R (2018). Emphasized Mechanistic Antimicrobial Study of Biofunctionalized Silver Nanoparticles on Model *Proteus mirabilis*. *Journal of drug delivery* 3850139. <https://doi.org/10.1155/2018/3850139>

[Patel RK](#), [CV. Savalia](#), [Kumar R](#), [Swati Gupta](#), [Alpeshkumar Punjalal Suthar](#), [SA Patel](#), [NG Patel](#), [Irshadullakhan Kalyani](#) (2018). Determination of *Vibrio parahaemolyticus* from Retail Shrimp of South Gujarat of Navsari District and their Drug Resistance Pattern. *International Journal of Current Microbiology and Applied Sciences* 7(2):2704-2710. <https://doi.org/10.20546/ijcmas.2018.702.328>

Prakash P, Gnanaprakasam P, Emmanuel R, Arokiyaraj S, Saravanan M (2013). Green synthesis of silver nanoparticles from leaf extract of *Mimusops elengi*, Linn. for enhanced antibacterial activity against multi drug resistant clinical isolates. *Colloids and Surfaces B: Biointerfaces* 108:255-9. <https://doi.org/10.1016/j.colsurfb.2013.03.017>

Raja. S, Nandhini. E, Sahana. K and Dhanakkodi. B (2015). Beneficial and destructive effects of probiotics in aquaculture systems-A review. *International Journal of Fisheries and Aquatic Studies* 2015; 2(3): 153-

Raffi M, Hussain F, Bhatti TM, Akhter JI, Hameed A, Hasan M.M (2008). Antibacterial characterization of silver nanoparticles against *E. coli* ATCC-15224. *J materials sci tec* 24(2):192-6.

<https://www.jmst.org/EN/Y2008/V24/I02/192>

Rastogi RP, Madamwar D, Incharoensakdi A (2015). Bloom dynamics of cyanobacteria and their toxins: environmental health impacts and mitigation strategies. *Front. Microbiol* 6: 1254.

<https://doi.org/10.3389/fmicb.2015.01254>

Rice LB (2008) Federal funding for the study of antimicrobial resistance in nosocomial pathogens: no ESKAPE. *J. Infect. Dis* 197(8):1079-81. <https://doi.org/10.1086/533452>

Rico A, Satapornvanit K, Haque MM, Min J, Nguyen PT, Telfer TC, Van Den Brink PJ (2012). Use of chemicals and biological products in Asian aquaculture and their potential environmental risks: a critical review 4: 75-93. <https://doi.org/10.1111/j.1753-5131.2012.01062.x>

Santhi R, Lakshmi G, Priyadarshini AM, Anandaraj L (2011). Phytochemical screening of *Nerium oleander* Linn. leaves and *Momordica charantia* leaves. *Int Res J Pharmacy* 2(1):131-135.

Schultz S, Smith DR, Mock JJ, Schultz DA (2000) Single-target molecule detection with nonbleaching multicolor optical immunolabels. *Proceedings of the National Academy of Sciences* 97(3):996-1001.

<https://doi.org/10.1073/pnas.97.3.996>

Silvester R, Alexander D, Ammanamveetil MHA (2015). Prevalence, antibiotic resistance, virulence and plasmid profiles of *Vibrio parahaemolyticus* from a tropical estuary and adjoining traditional prawn farm along the southwest coast of India. *Ann Microbiol* 65, 2141–2149 (2015).

<https://doi.org/10.1007/s13213-015-1053-x>

Silverstein RM, Bassler GC (1911) *Spectrometric identification of organic compounds*. New York, NY: John Wiley and Sons 430pp. <https://doi.org/10.1002/oms.1210260923>

Sudha S, Mridula C, Silvester R, Hatha AA (2014). Prevalence and antibiotic resistance of pathogenic *Vibrios* in shellfishes from Cochin market. *Indian J. Mar. Sci* 43(5): 815–824.

<http://nopr.niscair.res.in/handle/123456789/28767>

Sudha SS, Karthic R, Rengaramanujam J, Athulya R (2011) Anti-microbial activity of *Spirulina platensis* and *Aphanothecep* on selected clinical bacterial isolates and its Antioxidant activity. *South Asian J Biol Sci* 1(2): 87-98.

Singh R, Parihar P, Singh M, Bajguz A, Kumar J, Singh S, Singh VP, Prasad SM (2017) Uncovering potential applications of cyanobacteria and algal metabolites in biology, agriculture and medicine: Current status and future prospects. *Fron in microbio* 8:515. <https://doi.org/10.3389/fmicb.2017.00515>

- Sondi I, Salopek-Sondi B (2004). Silver nanoparticles as antimicrobial agent: a case study on E. coli as a model for Gram-negative bacteria. *J Colloid Inter Sci* 275(1):177-82.  
<https://doi.org/10.1016/j.jcis.2004.02.012>
- Subramanian P, R. Anjali, Periyannan Rajasekar, Ethiraj Kannapiran, Baskaralingam Vaseeharan, Narayanan marimuthu Prabhu (2017). Synthesis and Distribution of Bioinspired Silver Nanoparticles Using *Spirulina* Extract for Control of *Vibrio parahaemolyticus* Infection in Aquaculture. *Asian Journal of Chemistry* 29(4):857-863. <https://doi.org/10.14233/ajchem.2017.20335>
- Thenmozhi M, Sivaraj R, Hiranmai YR (2010). A comparative phytochemical analysis of *Alstonia scholaris*, *Lawsonia inermis*, *Ervatamia divaricata* and *Asparagus racemosus*. *Int J Pharma Res Dev* 2(9):86-91.
- Thorstenson CA, Ullrich MS (2021). Ecological Fitness of *Vibrio cholerae*, *Vibrio parahaemolyticus*, and *Vibrio vulnificus* in a Small-Scale Population Dynamics Study. *Front. Mar. Sci.* 8.  
<https://doi.org/10.3389/fmars.2021.623988>
- Vijayakumar S, Menakha M (2015). Pharmaceutical applications of cyanobacteria-A review. *J Acute Med* 5(1):15-23. <https://doi.org/10.1016/j.jacme.2015.02.004>
- Wang L, Hu C, Shao L (2017). The antimicrobial activity of nanoparticles: present situation and prospects for the future. *Int J Nanomedicine* 12:1227-1249. <https://doi.org/10.2147/IJN.S121956>
- Xie J, Lee JY, Wang DI, Ting YP (2007). Silver nanoplates: from biological to biomimetic synthesis. *ACS nano* 1(5):429-39. <https://doi.org/10.1021/nn7000883>
- Zarei M, Borujeni MP, Jamnejad A, Khezzadeh M (2012). Seasonal prevalence of *Vibrio* species in retail shrimps with an emphasis on *Vibrio parahaemolyticus*. *Food Control* 25(1):107-109.  
<https://doi.org/10.1016/j.foodcont.2011.10.024>
- Zuas O, Hamim N, Sampora Y (2014). Bio-synthesis of silver nanoparticles using water extract of *Myrmecodia pendan* (Sarang Semut plant). *Mater Lett* 123:156-9.  
<https://doi.org/10.1016/j.matlet.2014.03.026>
- Zulkifli Y, Alitheen NB, Raha AR, Yeap SK, Marlina SR, Nishibuchi M (2009) Antibiotic resistance and plasmid profiling of *Vibrio parahaemolyticus* isolated from cockles in Padang, Indonesia. *Int. Food Res. J* 16(1):53-8.

## Figures



Figure 1

Farm processing of *Spirulina platensis*: A) Mass culture B) Drying


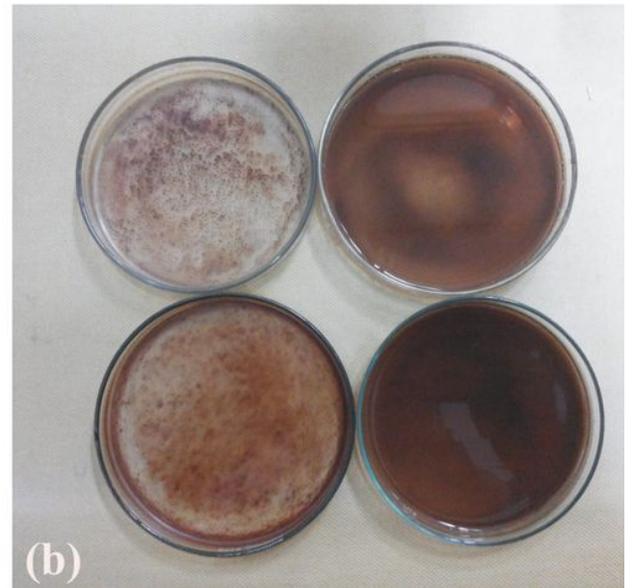



Figure 2

Synthesis of *Spirulina platensis* mediated silver nanoparticles: A) Spirulina extract and its nanoparticle solution B) Dried nano powder

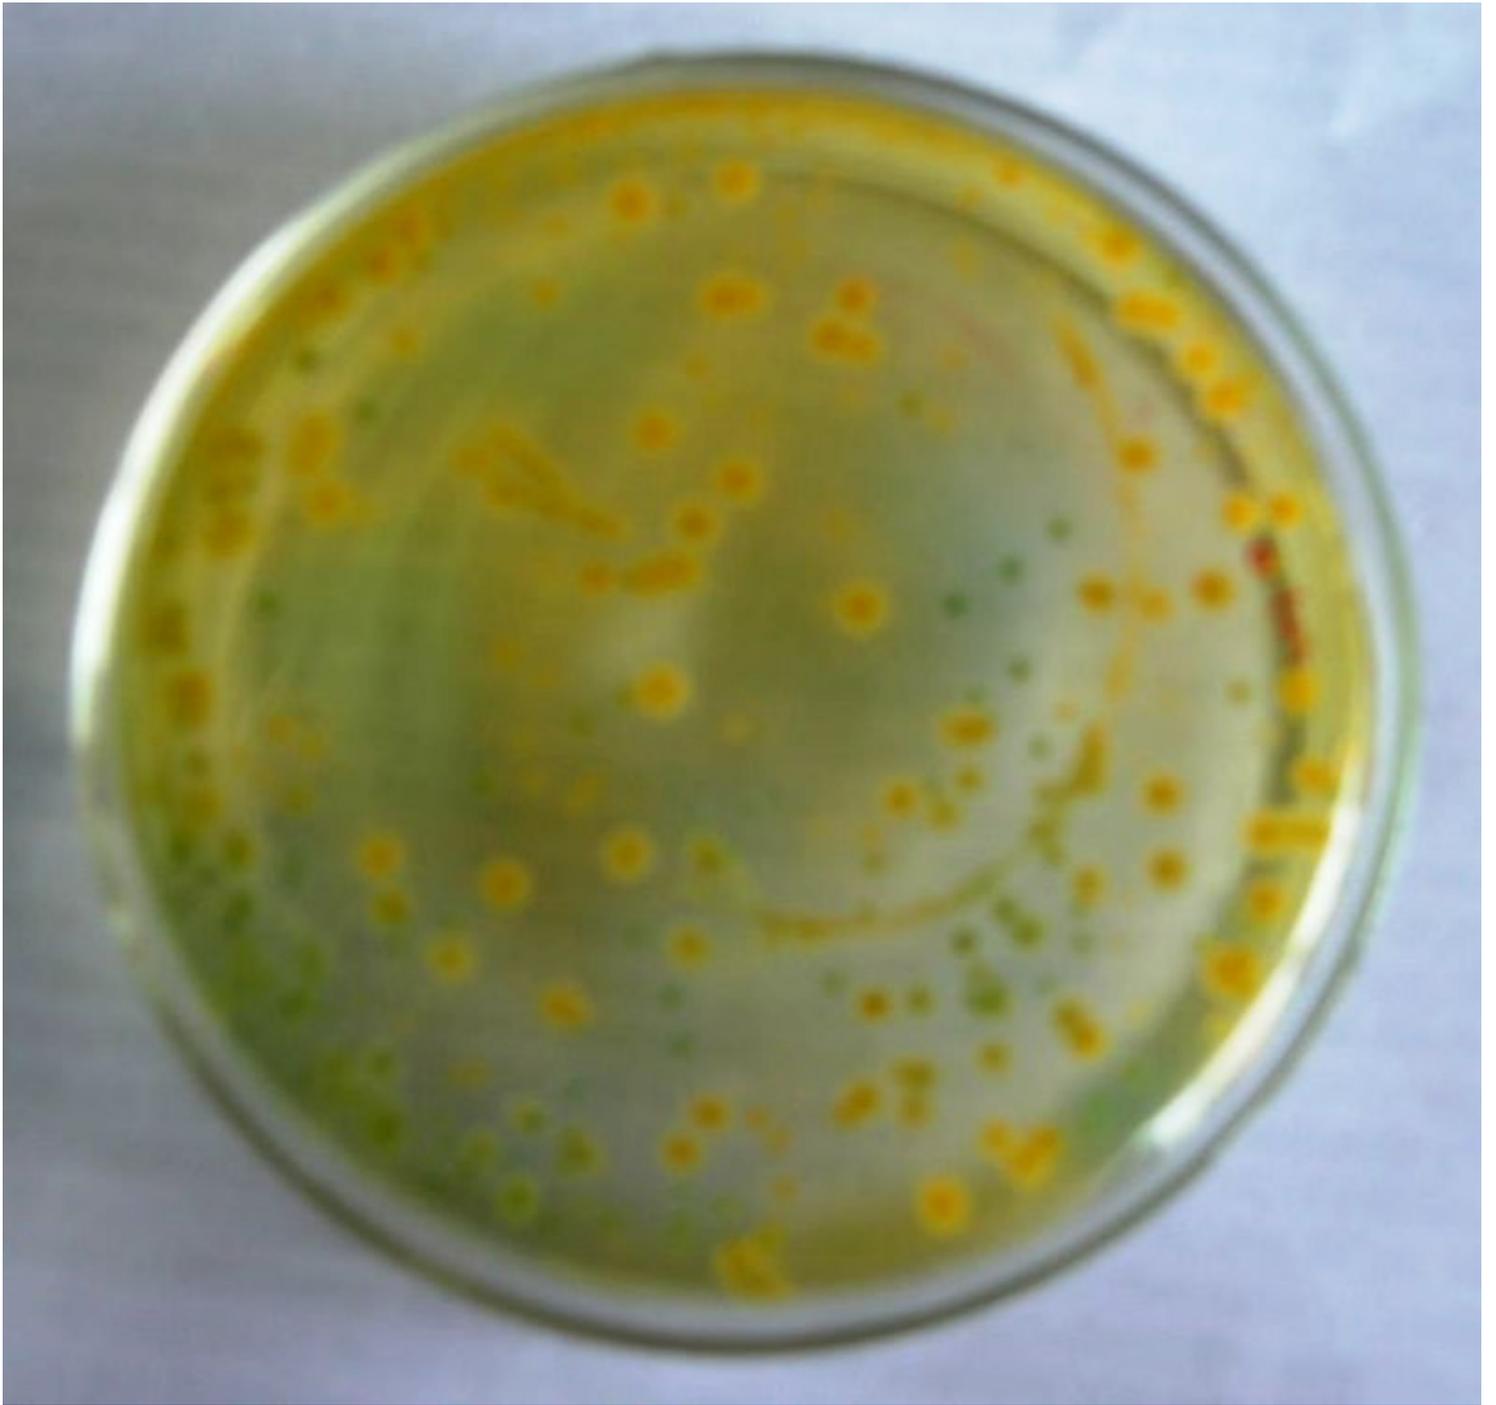


**Figure 3**

Pure culture of *Vibrio parahaemolyticus* isolated from shrimp farm water

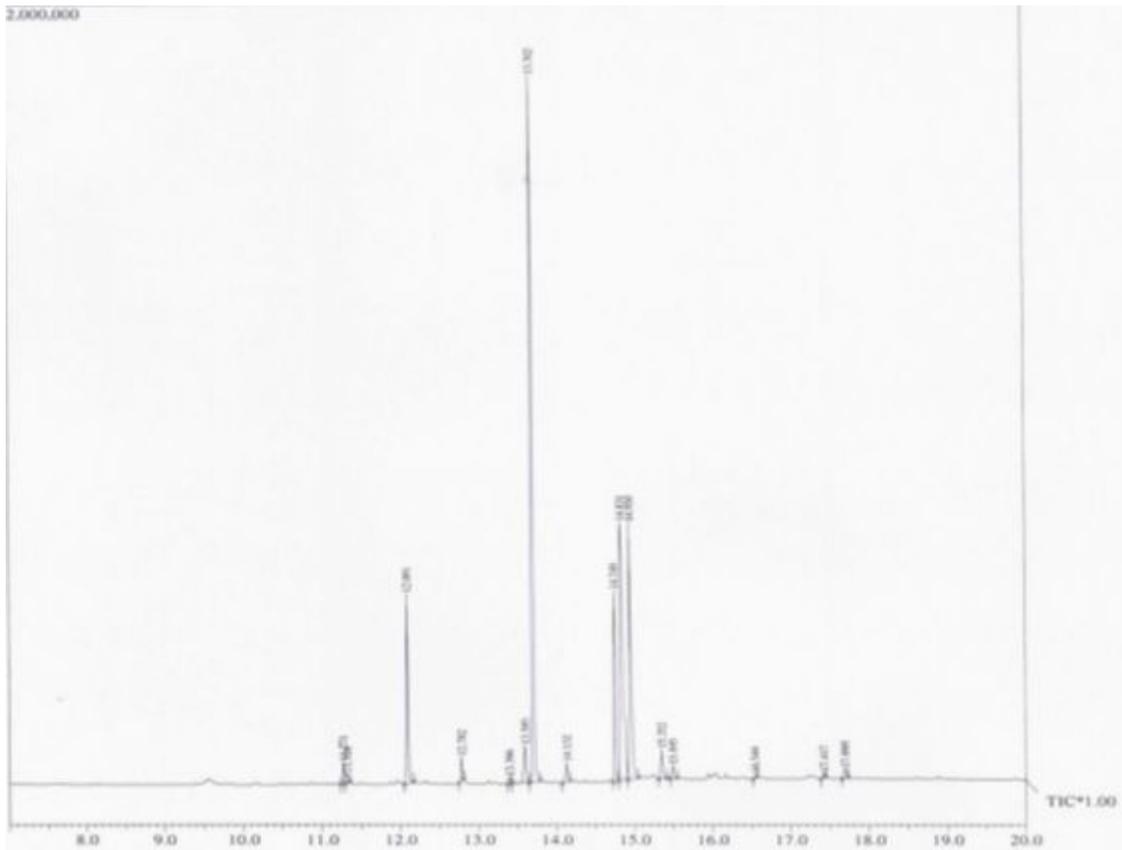


**Figure 4**

GCMS peak profiling of the active components of methanolic extract of *Spirulina platensis*

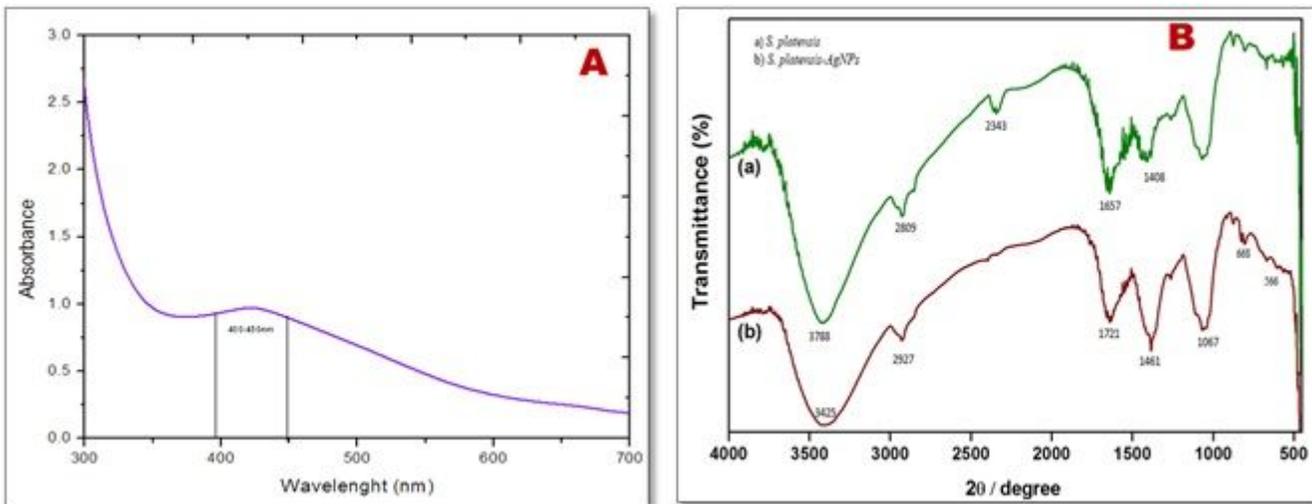

**Figure 5**

Absorbance characterisation of *Spirulina platensis* synthesised silver nanoparticles: a) UV – Visible spectrum b) FTIR spectrum

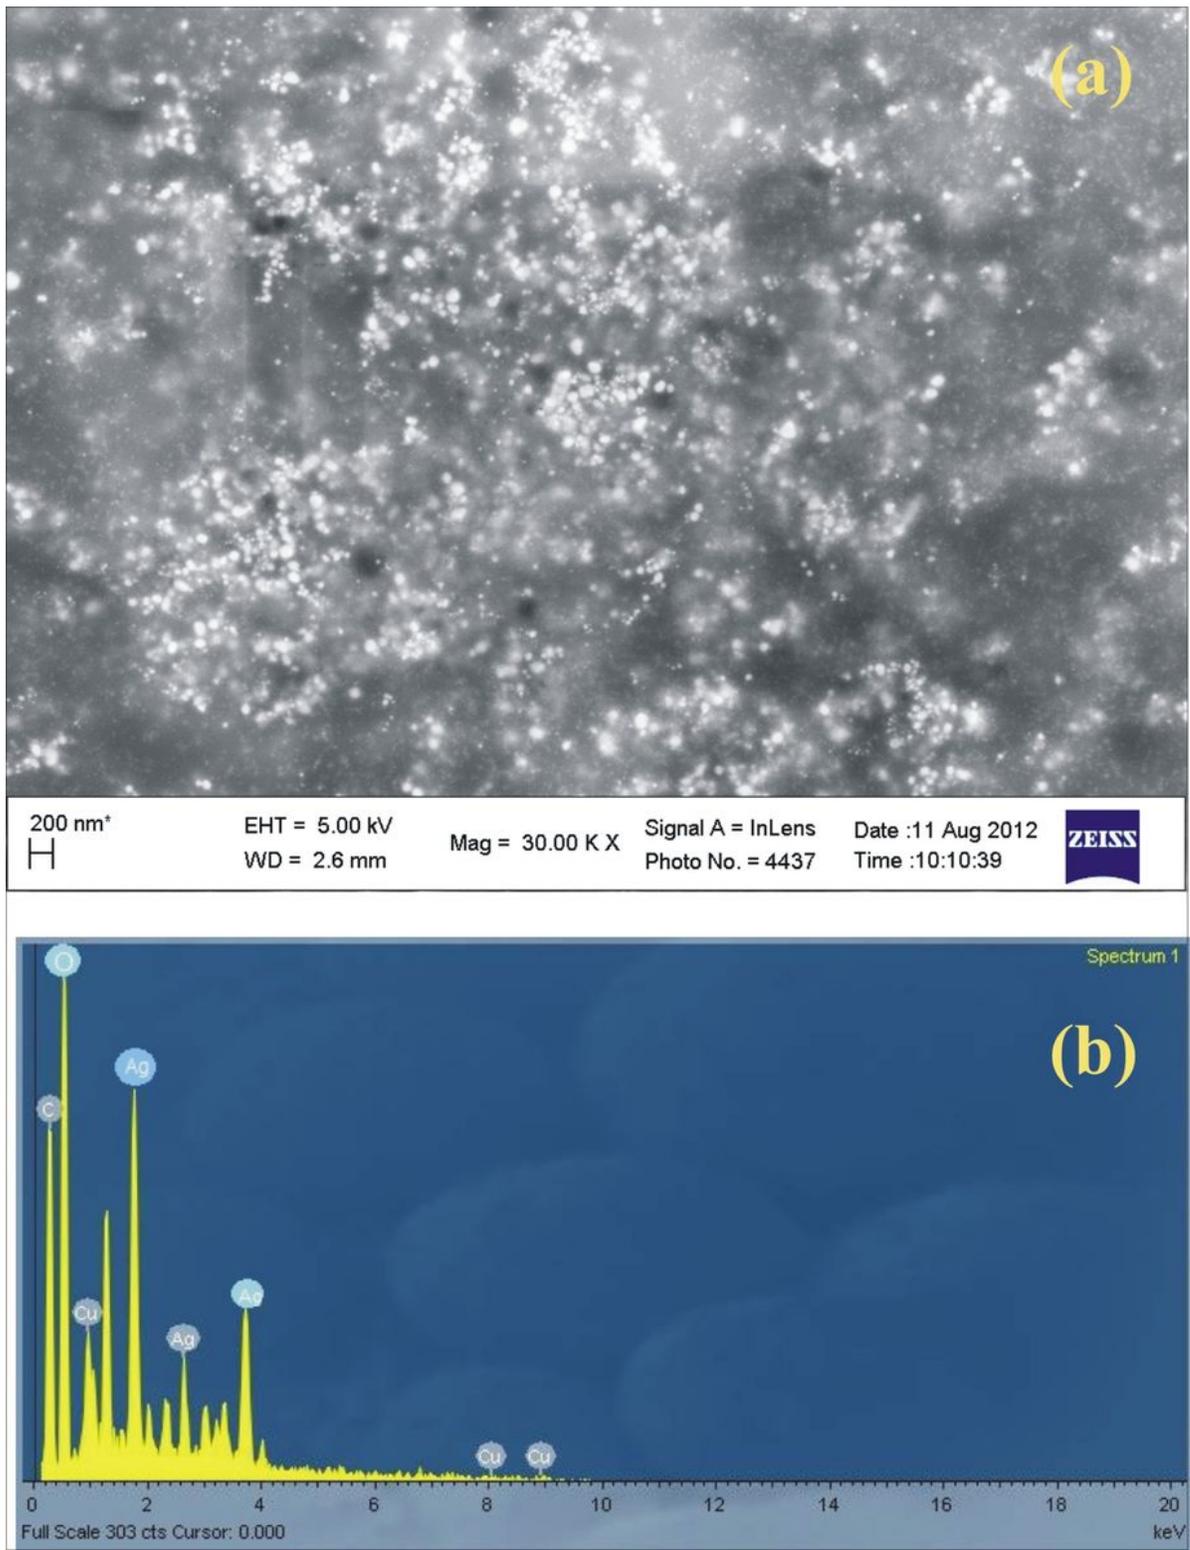

**Figure 6**

Morphology on SEM (A) and pure metal distribution in EDAX (B) of silver nanoparticles synthesised using *Spirulina platensis*

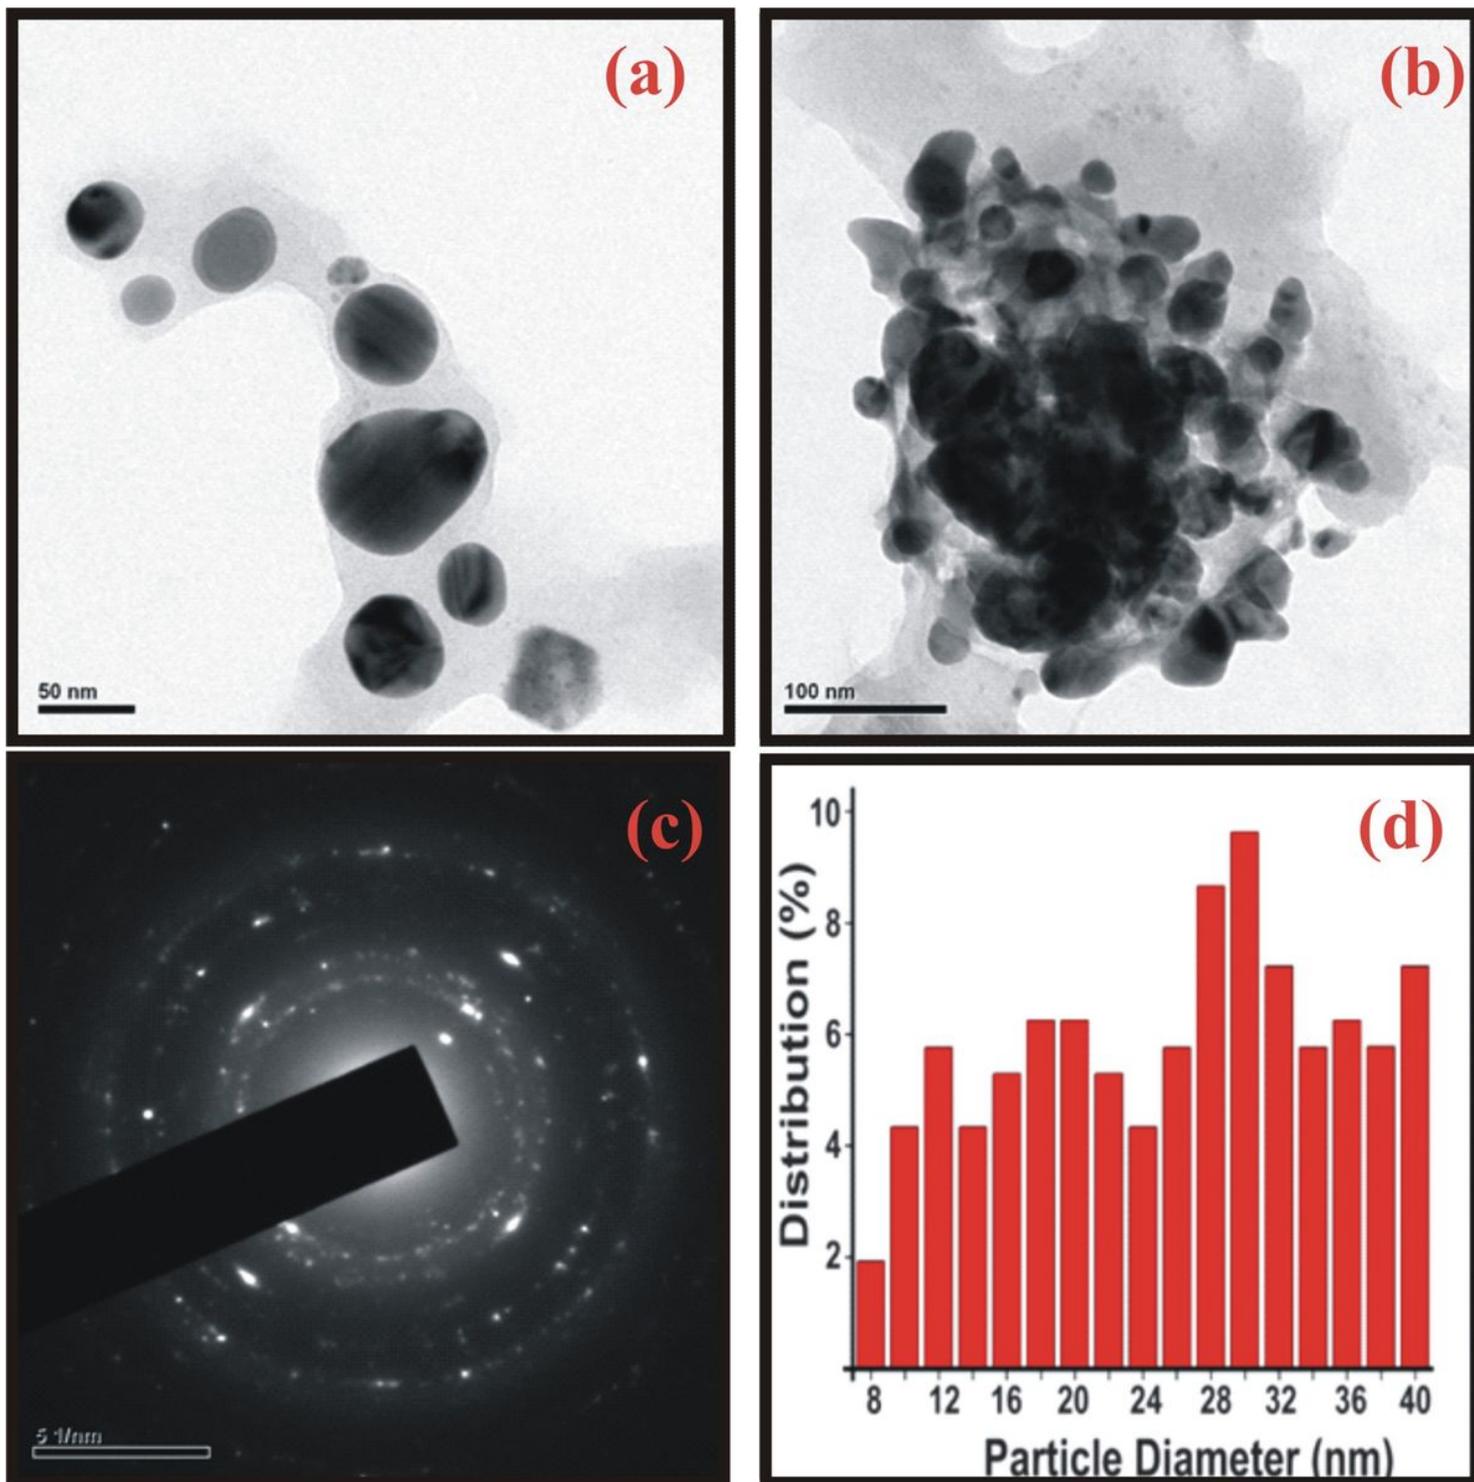


Figure 7

TEM characterization of silver nanoparticles mediated by *Spirulina platensis* for its Particle distribution with various diameter (A,B,C,D)


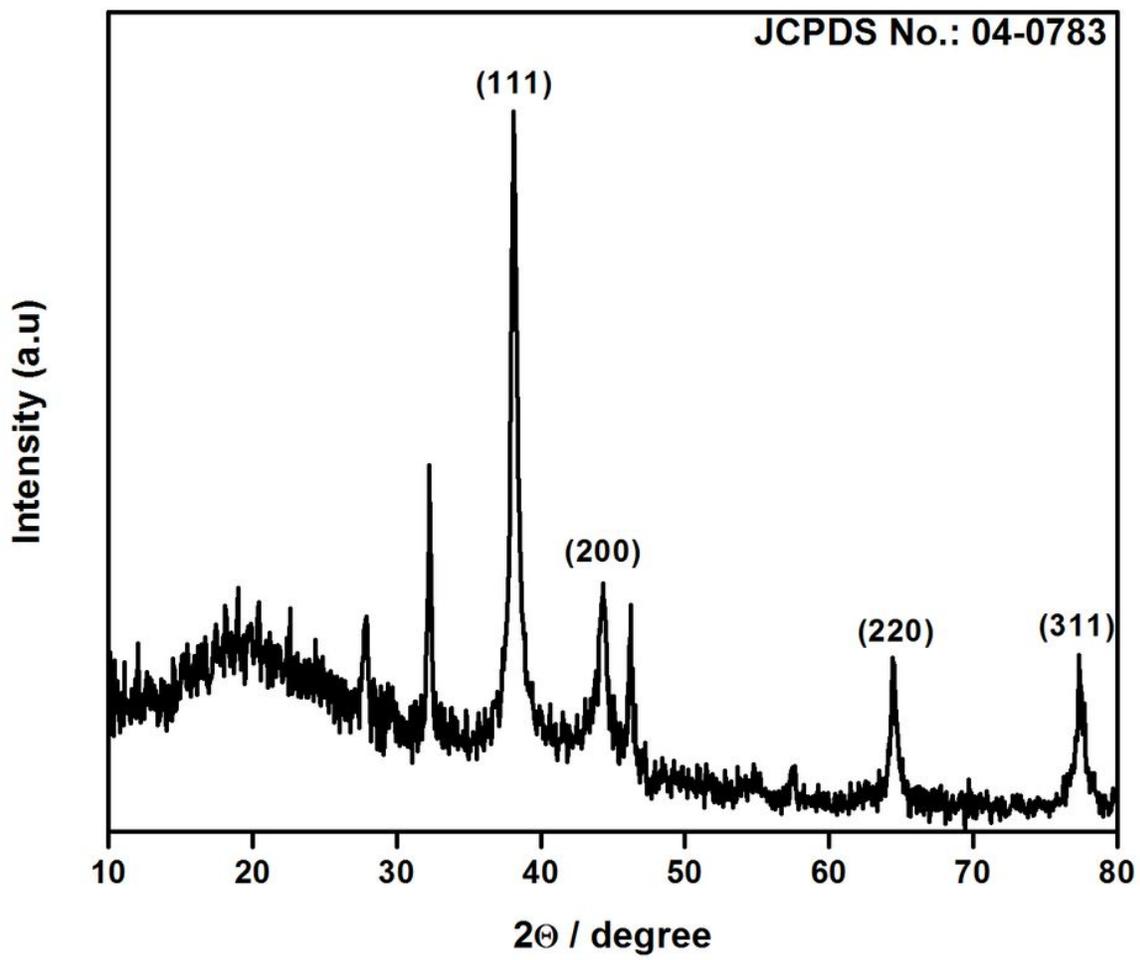


Figure 8

XRD pattern of silver nanoparticles mediated by *Spirulina platensis*

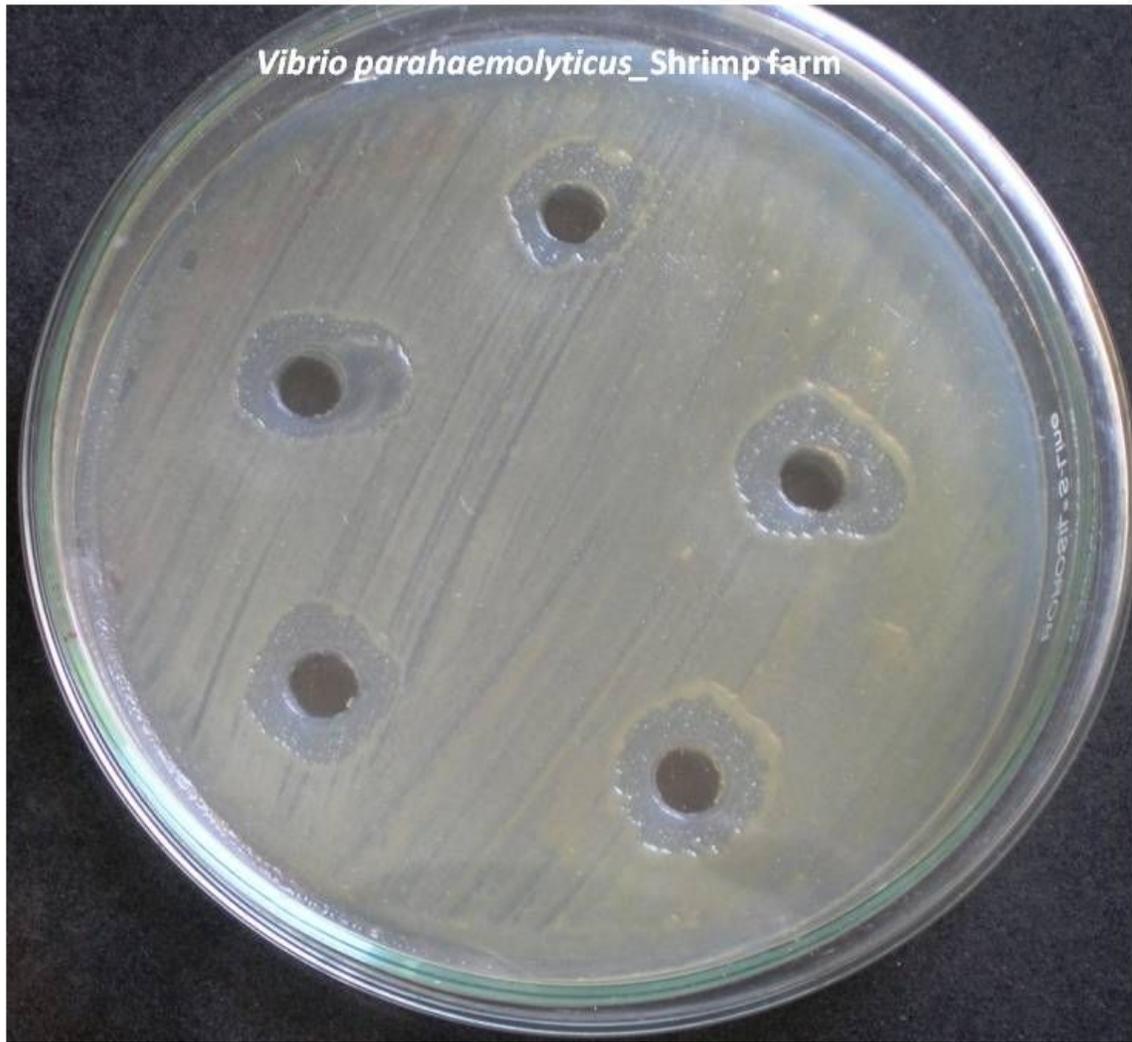

**Figure 9**

Zone of inhibition against *vibrio parahaemolyticus* exhibited by silver nanoparticles mediated by *Spirulina platensis*