

# A Simple Method of Simultaneously Endowing Paper or Fluff Pulp With Both High Softness or Appropriate Fluffing Properties and Antimicrobial Properties

Yongjian Xu (✉ [xuyongjian@sust.edu.cn](mailto:xuyongjian@sust.edu.cn))

Shaanxi University of Science and Technology <https://orcid.org/0000-0002-0338-392X>

Yun Shi

Shaanxi University of Science and Technology

Xuyong Chen

Shaanxi University of Science and Technology

Fenfen Liu

Shaanxi University of Science and Technology

Wei Zhao

Shaanxi University of Science and Technology

---

## Research Article

**Keywords:** Antibacterial activity, softness, debonding agent, fluff pulp, paper

**Posted Date:** March 17th, 2021

**DOI:** <https://doi.org/10.21203/rs.3.rs-305149/v1>

**License:** © ⓘ This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

---

# Abstract

As the living standard improve, disposable sanitary and living paper requires not only softness or easy to fluff in a dry state, but also good antibacterial property. In this study, a series of alkyl quaternary ammonium salts (AQAS), a kinds of antibacterial-debonding agents, were synthesized by using a two-step process. The SN<sub>2</sub> nucleophilic substitution reaction was designed between triethanolamine and sulfoxide chloride, and followed subsequent quaternization by tertiaryamines with different long alkyl chains. The obtained products can be used as an antibacterial and softening/debonding agent for improving the performance of paper or fluff pulp. The results showed that these new compounds can endow antibacterial function and high softness to paper or control appropriate burst strength to fluff pulp board. These AQAS products can be not only used in daily disposable sanitary products, but also have potential applications in other products such as glass spacer paper, advanced household paper, or antibacterial tissue products to prevent microbial contamination.

## 1. Introduction

With an improvement in people's living standard, there has been an increasing demand for disposable sanitary—such as women's sanitary napkins, baby diapers and adult incontinence products (Cordella et al. 2015; Ajmeri and Ajmeri 2016; Widen et al. 2017; Mendoza et al. 2019)<sup>[2-5]</sup>. Since most disposable sanitary products have close contact with human body, high antibacterial activity during uses is usually desired. However, in most cases, the main material, fluff pulp, used to prepare these disposable sanitary products has no antibacterial activity (Forsgren-Brusk et al. 2017). In addition, a large number of microorganisms exist in the natural environment and they can mass propagate once the conditions are suitable, which can cause bacterial infection and create health problem for people (Asri et al. 2014; Paterson and Harris 2016; Mc Carlie et al. 2020; Wang et al. 2020). Therefore, the development of materials with antibacterial activity has attracted significant interest in new material research (El-Naggar et al. 2018; Noorian et al. 2020).

In addition, with the increasing demand for household papers, such as toilet paper, napkins, beauty paper and paper towels, there are increasing requirements for quality and performance of these products, especially the softness (Gashti and Adibzadeh 2014). However, in the manufacturing process of household papers, in order to reduce the production costs, a large number of non-wood and secondary fibers used (Guan et al. 2019; An et al. 2020), which usually makes such products dense and their surface stiff (Illeez et al. 2015; Liu et al. 2020). Although creping is an effective way to increase the softness, it has limited impact. Hence, much attention has been paid to develop novel paper softeners (Tang et al. 2017; Mazzon et al. 2019). In the textile industry, softeners are used widely, but textile softeners are seldom used in papermaking due to some disadvantages, such as the large loading, high cost and poor effectiveness. Therefore, there is a clear need to develop special softening agents for this kind of papers or debonding agents for fluff pulp board. In order to make the final tissue products possess high antibacterial activity and at the same time create enough softness or appropriate burst strength, antibacterial agents (Hayashi et al. 2019; Xu et al. 2020) and softening/debonding agent (Igarashi et al.

2016) are usually added together during the papermaking process. However, there are few reports on chemical additives which have both antibacterial and softening/debonding effects. Hence, it is imperative to come up with a concoction as antibacterial-debonding agent to endow paper or fluff pulp with antibacterial and softening/debonding effects.

At present, antibacterial agents have two main types: inorganic and organic agents. Inorganic antibacterial agents such as Au (Lai et al. 2015), Ag (Alahmadi et al. 2018; Caschera et al. 2020; Rabbi et al. 2020; Yousaf et al. 2020), Cu (Jose et al. 2020; Li et al. 2021), TiO<sub>2</sub> (Alizadeh-Sani et al. 2020) and Zn (Zhao et al. 2017; Lallo da Silva et al. 2019; Farooq et al. 2020) and other metal nanoparticles have the advantages of low cost and good antibacterial properties, but at the same time there are disadvantages such as easy discoloration, manufacturing difficulties, and complex processing processes that limit their application in real life. Organic antibacterial agents such as chitosan (Salari et al. 2018; Tu et al. 2019), chlorhexidine (Bashir et al. 2019), triclosan (Alfhili and Lee 2019), polyethyleneimine (Wahid et al. 2019), quaternary ammonium salts (Quinlan et al. 2015; Jiao et al. 2017; Li et al. 2018) have the advantages of fast sterilization speed, strong sterilization ability, convenient processing, and good color stability. The quaternary ammonium salts have been studied by a large number of researchers because of their convenient synthesis and excellent antibacterial ability, and have been greatly developed. Li et al. (Li et al. 2018) achieved functionality by surface modification of cellulose nanocrystals grafted 2-(dimethylamino) ethyl methacrylate (DMAEMA) onto the surface of CNCs to prepare CNCs-g-pDMAEMA. Subsequently, the tertiary amine group of CNCs-g-PDMAEMA was transferred to the quaternary ammonium group by adding alkyl bromide (C10-C18) with different carbon chain lengths. The results of the study showed that the antimicrobial activity of the prepared antimicrobial materials was related to the alkyl chains of the prepared materials. The best antimicrobial effect was observed for the materials containing C10 alkyl groups in the quaternary ammonium salts.

In a word, compared with other antibacterial agents, organic antibacterial agent with quaternary ammonium group has been widely studied by researchers worldwide because of its advantages of low cost, high antibacterial efficiency, good safety and convenience for applications (Ma et al. 2012; Liu et al. 2015; Jung et al. 2020). Also, the alkyl group on the side chain of QAS has a certain hydrophobicity, which can improve the softness of tissue products (Gao et al. 2019) and may weaken the bonding strength between fibers as debonding agent for fluff pulp board.

In this work, a series of multibranched long-chain alkyl quaternary ammonium salt compounds (AQAS), a kinds of antibacterial-debonding agents, were synthesized, which played double roles in fluff pulp board or paper preparation. Subsequently, the effect of the amount of AQAS on the physical properties of fluff pulp board and paper were evaluated and analysed. The softness is changed mainly due to an increase of the length of alkyl chains and the number of long alkyl chains on the side chains in the AQAS molecules. The antibacterial effect is mainly due to an increase of the number of nitrogen positive ions in the AQAS molecules, and the antibacterial properties of the product are measured by the inhibition circle method based on the antibacterial mechanism of nitrogen positive ions. These AQAS products have potential applications in daily disposable sanitary products and other antibacterial tissue products to

prevent microbial contamination. These AQAS products have potential applications in daily disposable sanitary products and other antibacterial tissue products to prevent microbial contamination. The research results have important application value for developing compound functional chemicals and improving the quality of disposable sanitary products, household paper and industrial paper for special needs.

## 2. Material And Methods

### 2.1 Materials

Triethanolamine, ethyl acetate and absolute ethanol were obtained from Tianjin Tianli Chemical Reagent Co., Ltd. Sulfoxide chloride, chloroform, and N,N-dimethylhexadecylamine were obtained from Sinopharm Chemical Reagent Co., Ltd. N,N-dimethyloctylamine was obtained from Aladdin Reagent Co., Ltd., China. N,N-dimethyltetradecylamine was obtained from TCI Tokyo Chemical Industry Co., Ltd, and all chemicals and reagents were used as received. Bleached softwood and hardwood pulps (in dry lap form) were all provided by Guangxi Fenghuang Co., Ltd., China. In addition, nutrient agar used for antibacterial test was obtained from Beijing Aobox Biotechnology Co., Ltd.

### 2.2 Methods

The synthesis schematic of AQAS

The AQAS with different long alkyl chains was synthesized by using a two-step process. The  $SN_2$  nucleophilic substitution reaction was carried out first via the reaction between triethanolamine and sulfoxide chloride, resulting in tris(2-chloroethyl)amine and then long-chain alkyl groups were introduced to the molecule of tris(2-chloroethyl)amine by the quaternization reactions with different alkyl tertiaryamines ( Scheme 1).

#### The synthesis of tris(2-chloroethyl)amine

Chloroform (0.3 mol) and triethanolamine (0.075 mol) were added into a 250 mL three mouth flask, and then sulfoxide chloride was dropped into the reaction mixture. The above solution was stirred in an ice-water bath. During reaction, there was a slow release of gas, which was absorbed by the sodium hydroxide solution. After the addition, the reaction temperature was slowly raised to 30°C and the reactor was kept stirring for 3h, and then heated up to 60°C and stirred until no gas was released. Finally, the flask was cooled in ice-water and a large amount of white solid was precipitated, which was then filtered and repeatedly washed with chloroform and ethanol absolute and dried at 50°C to obtain the intermediate product tris(2-chloroethyl)amine hydrochloride white crystals.

#### The synthesis of AQAS

Tris(2-chloroethyl)amine (0.0083mol) was first added into a 250 mL glass flask. Dilute sodium hydroxide solution was added dropwise into aqueous emulsion to adjust the pH value of the system within a certain range. After heating up to 60°C, and N,N-dimethyl-octylamine (N,N-dimethyl-tetradecylamine and N,N-dimethyl-octadecylamine) (0.0332 mol) were gently dropped into the three flask to react with the intermediate product. Afterwards the mixture was stirred at 90°C for 7 h. Finally, the flask was cooled in ice water bath and a large amount of yellowish solid was separated out, which was then filtered and washed with ethyl acetate and ethanol absolute several times and dried at 50°C to obtain the product. The products were named as AQAS2a, AQAS2b and AQAS2c.

## The preparation of antibacterial paper (or fluff pulp board)

AQAS2a, AQAS2b and AQAS2c with concentration of 0.01 g·ml<sup>-1</sup> were added into the pulp suspensions at 0, 0.25%, 0.5% and 0.75%, respectively. A thorough mixing was provided and paper sheets (or fluff pulp board) with the basis weight of 60 g·m<sup>-2</sup> (660 g·m<sup>-2</sup>) were then prepared. The wet sheet was pressed three times under 4 MPa for 2 min, and then the two sides of wet paper was dried for the same time at 105°C in the glazing machine, to ensure the moisture content of the sheet or pad is between 8%~12%. Finally, the dried papers (fluff pulp boards) were conditioned in sealable bags for 12 h to stabilize the moisture content (Scheme 2).

## 2.3 Characterization

The <sup>1</sup>H nuclear magnetic resonance (<sup>1</sup>H NMR) spectrum of AQAS were recorded using an AVII-500 MHz spectrometer (Bruker, Germany) with deuterated chloroform (CDCl<sub>3</sub>) as the solvent.

Fourier transform infrared spectroscopy (FTIR) of AQAS were recorded on a spectrometer (VECTOR22, Bruker, Germany) in the range of 400 ~ 4000 cm<sup>-1</sup>, with 4 cm<sup>-1</sup> resolution. The samples were ground with potassium bromide (KBr) and pressed into transparent pellets.

The burst strength index of fluff pulp board was performed on a bursting strength tester (DCP-NPY5600, Changjiang Papermaking Instrument, Sichuan, China) according to GB/T 1539-2007. The fluff-specific volume, absorption rate and absorbibility were determined according to GB/T 21331-2008. The mechanical performance of each specimen was determined parallelly for three times. The fluff-specific volume (A), absorption rate (B), and absorbibility (C) were calculated according to the formula as follow:

$$A = s \cdot h / (10 \cdot x)$$

$$B = (y - x) / t$$

$$C = (y - x) / x$$

Where  $s$  is the area of specimen ( $19.64\text{cm}^2$ ),  $h$  is the initial height of pulp specimens (cm),  $x$  is a constant weight (3.00g) for specimen,  $y$  is the weight of specimen with sufficient absorption (g),  $t$  is the penetrating time of water from the bottom to top of specimens (s).

The softness of the prepared antibacterial paper was performed on a Tissue Softness Analyzer apparatus (Drake Co. Ltd, Shandong, China).

The surface morphology of antibacterial paper was observed with a scanning electron microscopy (SEM, VEGA 3 S-4800, HITACHI, Tokyo, Japan). All samples were sputtered with a layer of gold in vacuum for 60 s before analysis.

The antibacterial capability of the prepared antibacterial paper was investigated using the inhibition zone method which is also called the agar disk diffusion method. *E. coil* and *S. aureus* were used in the antibacterial experiment as typical Gram-negative and Gram-positive bacteria, respectively. The medium was prepared as follows: 0.5 g beef extract, 0.5 g sodium chloride, 1.0 g peptone and 1.5 g agar were added into 100 mL distilled water and autoclaved at  $121^\circ\text{C}$  for 15 min. Then 20 mL medium was poured into the sterilized petri dish. After the medium was solidified, 50 mL bacterial suspensions were uniformly smeared over the dish. Then, the cellulosic specimens were cut into circles with a diameter of 12 mm and then were gently placed on Petri dishes. After being incubated for 24 h at  $37^\circ\text{C}$ , the diameter (mm) of the inhibition zone was calculated using the following formula:

$$H=(D-d)/2.$$

Where  $H$  is the bacteriostatic belt width,  $D$  is the average outside diameter of inhibition zone, and  $d$  is the diameter of the specimens or the control ones.

## 3. Results And Discussion

### 3.1 The $^1\text{H}$ NMR and FT-IR spectra analysis of AQAS 2a

The  $^1\text{H}$ NMR spectra (500 MHz,  $\text{CDCl}_3$ ,  $25^\circ\text{C}$ ) of AQAS2a is shown in Fig. 1. The peaks at 0.88, 1.26 and 1.74 ppm originate from the AQAS2a and are attributed to the terminal methyl of  $-\text{CH}_2-\text{CH}_3$ , side chain methylene group ( $(-\text{CH}_2)_5$ ) of AQAS2a and methylene of  $\text{N}^+-\text{CH}_2-\text{CH}_2-$ , respectively. The peak at 3.35 ppm belongs to methyl of  $\text{N}^+-\text{CH}_3$ , the peak at 3.42 ppm is attributed to the methylene ( $\text{N}^+-\text{CH}_2-\text{CH}_2-\text{CH}_2-$ ) of AQAS2a and the methylene peak of  $\text{N}-\text{CH}_2$  was observed at 3.62 ppm. In addition, the peak at 4.11 ppm assigned to methylene of  $\text{N}-\text{CH}_2-\text{CH}_2$  (Kang et al. 2016), indicates that the target product has been successfully synthesized (Fig. 1). However, the methyl peak (2.79 ppm) in  $-\text{CH}_2-\text{CH}_3$ , methylene peak (2.94 ppm) in  $\text{N}^+-\text{CH}_2-\text{CH}_2-$ , and the peak of  $\text{N}^+-\text{H}$  at around 2.21 ppm are also weakly observed in Fig. 1, which indicates the presence of by-products (tertiary ammonium hydrochloride) in terminal product.

Fig. 1.  $^1\text{H}$  NMR spectra of (1) tris(2-chloroethy)amine, (2) N, N-dimethyloctylamine and (3) AQAS2a

The AQAS2a was further characterized by FT-IR spectra (Fig. 2). The strong absorption peak at  $1470\text{ cm}^{-1}$  belongs to methyl bending vibration peak in  $\text{N}^+(\text{CH}_3)_2$ , and the symmetric bending vibration absorption peak of methyl in  $-\text{CH}_2-\text{CH}_3$  could be observed at  $1379\text{ cm}^{-1}$ , which is a characteristic absorption peak of moderate intensity. The weak absorption peak near  $1040\text{ cm}^{-1}$  is the characteristic absorption frequency of quaternary ammonium salt, which confirms the formation of AQAS2a. Compared with Line 2 in Fig. 2, the characteristic absorption peaks of methyl and quaternary ammonium salt group appear for the first time. Besides, there still exist the methylene asymmetric and symmetric stretching vibration absorption peaks at  $2927\text{ cm}^{-1}$  and  $2870\text{ cm}^{-1}$  region in  $\text{NR}_2-\text{CH}_2-\text{R}$ . In addition, the strong absorption peak at  $760\text{ cm}^{-1}$  is weakened, which indicates the weakened C-Cl stretching vibration peak in  $-\text{CH}_2-\text{Cl}$ . This may be attributed to the presence of by-products that incomplete quaternary ammonium salt in the product. We successfully synthesized AQAS2b and AQAS2c by using a similar method to AQAS2a. For detailed characterization and spectra please refer to the supporting information (Fig. S1, Fig. S2, Fig. S3, Fig. S4).

Fig. 2. FT-IR spectra. 1. N,N-dimethyl-octylamine, 2. tris(2-chloroethyl)amine and 3. AQAS2a

## 3.2 The properties of the fluff pulp board and fluff fiber

### *The apparent density and burst strength index*

As shown in Fig. 3a and b, the apparent density and burst strength index of the fluff pulp boards decrease with increasing the addition of AQAS, and the decrease is more significant with the increase of the addition. The decreasing trend of the apparent density and burst strength index becomes flat after the amount of AQAS is more than 0.75%. From this experimental results it was deduced that the bonding force becomes weak because of the increase in spacing between the fibers in fluff pulp boards and decrease in hydroxyl with the addition of AQAS. The effect of long alkyl chain is more obvious.

### *The water absorbability and water absorption rate of fluff pulp*

As the amount of AQAS increased, the water absorbability and water absorption rate of fluff pulp show a decreasing trend (Fig. 3c and d). When the amount of AQAS is up to 0.5%, the decreasing trend is gradually leveled off. The alkyl chain in AQAS plays the role of shielding hydroxyl group, and with the increase of AQAS, the shielding effect becomes more obvious. The longer the alkyl chain, the greater the shielding effect of the hydroxyl group. More alkyl groups with hydrophobic effect are attached to the surface of the fluff pulp fibers, resulting in less absorbency of the fibers and consequently less water absorption rate of the fluff pulp.

### *The fluff-specific volume of fluff pulp*

As shown in Fig. 3e, with increasing the addition of AQAS, the fluff-specific volume tends to rise first and then fall. The three hydrophobic alkyl chains in AQAS on the fiber surface hinder the combination between fibers, making the gap between fibers increase and become fluffy, so that the fluff-specific

volume of the fluff pulp board is on the rise; and when the amount of AQAS is high, the three long alkyl chains in AQAS are easy to cross and tangle with each other, so that when the pulp board is dry dissociated, the fiber pile is uneven and appears to be knotted and fall off in pieces. It affects the fluff-specific volume of antibacterial pulp fiber.

#### *The surface morphology of fluff pulp fibers*

*Surface morphology of antibacterial fluff pulp fibers with AQAS 2c was examined using SEM as shown in Fig. 4, we can see that the surface of fibers in the blank sample is very rough, and some microfibrils are broken away from the surface. This would have an adverse impact on the softness of fluff pulp board. However, the SEM images of fluff pulp fibers treated by AQAS 2c show that the fiber surface is smoother with the increase of the loading of AQAS 2c. Therefore, adding proper amounts of AQAS 2c to pulp fiber is an effective way improve the softness of antibacterial paper.*

### **3.3 The softness and air permeability of antibacterial paper**

In order to explore the effect of AQAS 2a, AQAS 2b and AQAS 2c on the air permeability and softness of antibacterial paper, the different amounts of AQAS were added into pulp suspension to make paper that the basis weight is  $60 \text{ g m}^{-2}$  (Scheme 2), and the testing results are shown in Fig. 5.

The air permeability of paper gradually increases with the amount of AQAS increases, the shielding effect of alkyl chains on fiber hydroxyl groups also increases, and the bonding force between pulp fibers decreases (Fig. 5a). The reason is that the hydrogen bonds between fibers can not form when the AQAS was used. On the other hand, the three hydrophobic alkyl chains in AQAS on the fiber surface hinder the combination between fibers, and when the amount of AQAS increases, the three long alkyl chains in AQAS are easy to cross and tangle with each other, which make the gap between fibers increase and the paper become bulky.

As shown in Fig. 5b, the softness of control sample is 2428.5 mN. However, the softness of paper decreases with the amount of AQAS increases, indicating that the softness is constantly improved. The result supports the conclusion that AQAS 2a, AQAS 2b and AQAS 2c also have softening effect. Moreover, it is found that the softness of all samples decrease slowly with the AQAS loading up to 0.25wt%. When their loading is more than 0.25wt%, the softness of paper adding AQAS 2a or AQAS 2b also drops slowly, but the decreasing trend is clear for adding AQAS 2c. This indicates for AQAS 2c can endow paper the best softening effect. It may be attributed to the alkyl groups with hydrophobicity of AQAS 2c which are more than that of AQAS 2a and AQAS 2b. The alkyl groups can form hydrophobic external reverse adsorption on the surface of fibers, and reduce the dynamic and static friction factors of paper fiber. Therefore, the AQAS 2c can be used as a softener with antibacterial activity for tissue papermaking.

#### 3.4 The antibacterial activity of fluff pulp board and paper

The antibacterial activity testing results are shown in Fig. 6. It was found that no inhibition zone appeared around the blank sample, indicating the poor antibacterial activity for original fiber. However, the inhibition zone appeared for other samples of paper made with AQAS 2a (AQAS 2b, AQAS 2c), and the inhibition zone increased with the increase of the loading amount of AQAS, which all confirmed the addition of 2a (2b, 2c) afforded fluff pulp board with antibacterial activity. AQAS 2a, AQAS 2b and AQAS 2c are excellent antibacterial agents against *S. aureus* and *E. coli*.

The comparison of antibacterial activity of different AQAS is shown in Fig. 7, As can be seen on the two plates, the diameter of inhibition zone around the samples decreased significantly with the increase of alkyl group on the side chain of AQAS, which means the antibacterial activity of AQAS 2a is the strongest against either *S. aureus* or *E. coli*, the second is AQAS 2b, and the antibacterial activity of AQAS 2c is the weakest. Furthermore, compared with *E. coli*, the antibacterial activity of fluff pulp with different AQAS against *S. aureus* is better, which is consistent with the above conclusion in Fig. 3.

### 3.5 The antibacterial and softening mechanism of AQAS

*As shown in Scheme 3, when a certain loading of AQAS is added to the pulp fiber, the AQAS can be attached to the fiber surface by electrostatic adsorption to*

form something like water film. Then it hinders the bacteria from getting closer to achieve certain antibacterial effect. Besides, the AQAS contacts with the surface of bacteria, and the structure of bacteria cell membrane is destroyed, so that the bacteria die (Jung et al. 2019), to achieve the purpose of sterilization. However, the softening effect can be attributed to: (1) the quaternary nitrogen positive ions combine with free hydroxyl groups on the surface of fibers, reduce the formation of hydrogen bonds, weaken the bond between fibers, decrease the static friction coefficient between fibers, and then the surface of the fibers became smoother, (2) long alkyl chains have a certain hydrophobicity, which reduces the formation of hydrogen bonds between fibers and makes the structure of fibers more loose. Therefore, both of them can make the antibacterial products have certain softening effect, and control the burst strength of fluff pulp board suitable for dry disintegration.

## 4. Conclusions

The antibacterial effect is mainly by increasing the number of nitrogen positive ions in the AQAS molecule, based on the antibacterial mechanism of nitrogen positive ions to achieve the purpose of product antibacterial. And the softness is mainly by increasing the length of alkyl chains and the number of long alkyl chains on the side chains of AQAS molecules, relying on the hydrophobicity of alkyl chains, reducing the hydrogen bonding, and using electrostatic adsorption to attach to the fiber surface, reducing the static friction coefficient between fibers, so that the product has a certain degree of softness.

A series of AQAS products were successfully synthesized and evaluated as antibacterial and softening agents in paper making and debonding agents in fluff pulp board. The obtained fluff pulp and paper with these AQAS products showed excellent antibacterial activity against *S. aureus* and *E. coli*. At the same

time, the softness for the antibacterial tissue and the burst strength for antibacterial fluff pulp board has been improved. These AQAS products can be used in daily disposable sanitary products, but also have potential applications in other products such as Liquid Crystal Display (LCD) glass spacer paper, advanced household paper, or antibacterial tissue products to prevent microbial contamination.

## Declarations

# Acknowledgement

The authors are grateful for the support of the Open Fund of the State Key Laboratory of Pulp and Paper Engineering, South China University of Technology (201730); National Demonstration Center for Experimental Light Chemistry Engineering Education, Shaanxi University of Science and Technology; Key Scientific Research Group of Shaanxi Province (2017KCT-02) and Shaanxi University of Science and Technology Academic Leader Training Program (2013XSD25).

## References

Ajmeri JR, Ajmeri CJ (2016) Developments in the use of nonwovens for disposable hygiene products.473-496. <https://doi.org/10.1016/b978-0-08-100575-0.00018-8>

Alahmadi NS, Betts JW, Heinze T, Kelly SM, Koschella A, Wadhawan JD (2018) Synthesis and antimicrobial effects of highly dispersed, cellulose-stabilized silver/cellulose nanocomposites. *RSC Advances* **8**(7):3646-3656. <https://doi.org/10.1039/c7ra12280b>

Alfhili MA, Lee M-H (2019) Triclosan: An Update on Biochemical and Molecular Mechanisms. *Oxidative Medicine and Cellular Longevity* **2019**:1-28. <https://doi.org/10.1155/2019/1607304>

Alizadeh-Sani M, Mohammadian E, McClements DJ (2020) Eco-friendly active packaging consisting of nanostructured biopolymer matrix reinforced with TiO<sub>2</sub> and essential oil: Application for preservation of refrigerated meat. *Food Chemistry* **322**:126782. <https://doi.org/10.1016/j.foodchem.2020.126782>

An X, Liu J, Liu L, Zhang H, Nie S, Cao H, Xu Q, Liu H (2020) Improving the flexibility of bamboo mechanical pulp fibers for production of high soft tissue handsheets. *Industrial Crops and Products* **150**. <https://doi.org/10.1016/j.indcrop.2020.112410>

Asri LATW, Crismaru M, Roest S, Chen Y, Ivashenko O, Rudolf P, Tiller JC, van der Mei HC, Loontjens TJA, Busscher HJ (2014) A Shape- Adaptive, Antibacterial- Coating of Immobilized Quaternary- Ammonium Compounds Tethered on Hyperbranched Polyurea and its Mechanism of Action. *Advanced Functional Materials* **24**(3):346-355. <https://doi.org/10.1002/adfm.201301686>

Bashir MH, Hollingsworth A, Schwab D, Prinsen KS, Paulson JE, Morse DJ, Bernatchez SF (2019) Ex vivo and in vivo evaluation of residual chlorhexidine gluconate on skin following repetitive exposure to saline

and wiping with 2% chlorhexidine gluconate/70% isopropyl alcohol pre-operative skin preparations. *Journal of Hospital Infection* **102**(3):256-261. <https://doi.org/10.1016/j.jhin.2018.10.004>

Caschera D, Toro RG, Federici F, Montanari R, de Caro T, Al-Shemy MT, Adel AM (2020) Green approach for the fabrication of silver-oxidized cellulose nanocomposite with antibacterial properties. *Cellulose* **27**(14):8059-8073. <https://doi.org/10.1007/s10570-020-03364-7>

Cordella M, Bauer I, Lehmann A, Schulz M, Wolf O (2015) Evolution of disposable baby diapers in Europe: life cycle assessment of environmental impacts and identification of key areas of improvement. *Journal of Cleaner Production* **95**:322-331. <https://doi.org/10.1016/j.jclepro.2015.02.040>

El-Naggar ME, Shaarawy S, Hebeish AA (2018) Multifunctional properties of cotton fabrics coated with in situ synthesis of zinc oxide nanoparticles capped with date seed extract. *Carbohydr Polym* **181**:307-316. <https://doi.org/10.1016/j.carbpol.2017.10.074>

Farooq A, Patoary MK, Zhang M, Mussana H, Li M, Naeem MA, Mushtaq M, Farooq A, Liu L (2020) Cellulose from sources to nanocellulose and an overview of synthesis and properties of nanocellulose/zinc oxide nanocomposite materials. *International Journal of Biological Macromolecules* **154**:1050-1073. <https://doi.org/10.1016/j.ijbiomac.2020.03.163>

Forsgren-Brusk U, Yhlen B, Blomqvist M, Larsson P (2017) Method for Bacterial Growth and Ammonia Production and Effect of Inhibitory Substances in Disposable Absorbent Hygiene Products. *Journal of Wound Ostomy and Continence Nursing* **44**(1):78-83. <https://doi.org/10.1097/won.0000000000000275>

Gao D, Li Y, Lyu B, Jin D, Ma J (2019) Silicone quaternary ammonium salt based nanocomposite: a long-acting antibacterial cotton fabric finishing agent with good softness and air permeability. *Cellulose* **27**(2):1055-1069. <https://doi.org/10.1007/s10570-019-02832-z>

Gashti MP, Adibzadeh H (2014) Ultrasound for efficient emulsification and uniform coating of an anionic lubricant on cotton. *Fibers and Polymers* **15**(1):65-70. <https://doi.org/10.1007/s12221-014-0065-7>

Guan M, An X, Liu H (2019) Cellulose nanofiber (CNF) as a versatile filler for the preparation of bamboo pulp based tissue paper handsheets. *Cellulose* **26**(4):2613-2624. <https://doi.org/10.1007/s10570-018-2212-6>

Hayashi K, Nozaki K, Tan Z, Fujita K, Nemoto R, Yamashita K, Miura H, Itaka K, Ohara S (2019) Enhanced Antibacterial Property of Facet-Engineered TiO<sub>2</sub> Nanosheet in Presence and Absence of Ultraviolet Irradiation. *Materials (Basel)* **13**(1). <https://doi.org/10.3390/ma13010078>

Igarashi T, Nakamura K, Hoshi M, Hara T, Kojima H, Itou M, Ikeda R, Okamoto Y (2016) Elucidation of Softening Mechanism in Rinse-Cycle Fabric Softeners. Part 2: Uneven Adsorption-The Key Phenomenon to the Effect of Fabric Softeners. *J Surfactants Deterg* **19**:759-773. <https://doi.org/10.1007/s11743-016-1815-x>

- İlleez AA, Dalbaşı ES, Kayseri GÖ (2015) Improving of Sewability Properties of Various Knitted Fabrics with the Softeners. *Procedia - Social and Behavioral Sciences* **195**:2786-2795.  
<https://doi.org/10.1016/j.sbspro.2015.06.394>
- Jiao Y, Niu L-n, Ma S, Li J, Tay FR, Chen J-h (2017) Quaternary ammonium-based biomedical materials: State-of-the-art, toxicological aspects and antimicrobial resistance. *Progress in Polymer Science* **71**:53-90. <https://doi.org/10.1016/j.progpolymsci.2017.03.001>
- Jose M, Szymańska K, Szymański K, Moszyński D, Mozia S (2020) Effect of copper salts on the characteristics and antibacterial activity of Cu-modified titanate nanotubes. *Journal of Environmental Chemical Engineering* **8**(6):104550. <https://doi.org/10.1016/j.jece.2020.104550>
- Jung J, Bae Y, Kwan Cho Y, Ren X, Sun Y (2020) Structural insights into conformation of amphiphilic quaternary ammonium chitosans to control fungicidal and anti-biofilm functions. *Carbohydr Polym* **228**:115391. <https://doi.org/10.1016/j.carbpol.2019.115391>
- Jung J, Wen J, Sun Y (2019) Amphiphilic quaternary ammonium chitosans self-assemble onto bacterial and fungal biofilms and kill adherent microorganisms. *Colloids Surf B Biointerfaces* **174**:1-8.  
<https://doi.org/10.1016/j.colsurfb.2018.10.078>
- Kang CK, Kim SS, Kim S, Lee J, Lee JH, Roh C, Lee J (2016) Antibacterial cotton fibers treated with silver nanoparticles and quaternary ammonium salts. *Carbohydr Polym* **151**:1012-1018.  
<https://doi.org/10.1016/j.carbpol.2016.06.043>
- Lai H-Z, Chen W-Y, Wu C-Y, Chen Y-C (2015) Potent Antibacterial Nanoparticles for Pathogenic Bacteria. *ACS Applied Materials & Interfaces* **7**(3):2046-2054. <https://doi.org/10.1021/am507919m>
- Lallo da Silva B, Caetano BL, Chiari-Andréo BG, Pietro RCLR, Chiavacci LA (2019) Increased antibacterial activity of ZnO nanoparticles: Influence of size and surface modification. *Colloids and Surfaces B: Biointerfaces* **177**:440-447. <https://doi.org/10.1016/j.colsurfb.2019.02.013>
- Li M, Liu X, Liu N, Guo Z, Singh PK, Fu S (2018) Effect of surface wettability on the antibacterial activity of nanocellulose-based material with quaternary ammonium groups. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* **554**:122-128. <https://doi.org/10.1016/j.colsurfa.2018.06.031>
- Li M, Nan L, Liang C, Sun Z, Yang L, Yang K (2021) Antibacterial behavior and related mechanisms of martensitic Cu-bearing stainless steel evaluated by a mixed infection model of *Escherichia coli* and *Staphylococcus aureus* in vitro. *Journal of Materials Science & Technology* **62**:139-147.  
<https://doi.org/10.1016/j.jmst.2020.05.030>
- Liu D, Yang X, Liu P, Mao T, Shang X, Wang L (2020) Synthesis and characterization of gemini ester surfactant and its application in efficient fabric softening. *Journal of Molecular Liquids* **299**.  
<https://doi.org/10.1016/j.molliq.2019.112236>

- Liu WS, Wang CH, Sun JF, Hou GG, Wang YP, Qu RJ (2015) Synthesis, characterization and antibacterial properties of dihydroxy quaternary ammonium salts with long chain alkyl bromides. *Chem Biol Drug Des* **85**(1):91-97. <https://doi.org/10.1111/cbdd.12427>
- Ma S, Izutani N, Imazato S, Chen J-h, Kiba W, Yoshikawa R, Takeda K, Kitagawa H, Ebisu S (2012) Assessment of bactericidal effects of quaternary ammonium-based antibacterial monomers in combination with colloidal platinum nanoparticles. *Dental Materials Journal* **31**(1):150-156. <https://doi.org/10.4012/dmj.2011-180>
- Mazzon G, Zahid M, Heredia-Guerrero JA, Balliana E, Zendri E, Athanassiou A, Bayer IS (2019) Hydrophobic treatment of woven cotton fabrics with polyurethane modified aminosilicone emulsions. *Applied Surface Science* **490**:331-342. <https://doi.org/10.1016/j.apsusc.2019.06.069>
- Mc Carlie S, Boucher CE, Bragg RR (2020) Molecular basis of bacterial disinfectant resistance. *Drug Resist Updat* **48**:100672. <https://doi.org/10.1016/j.drup.2019.100672>
- Mendoza JMF, D'Aponte F, Gualtieri D, Azapagic A (2019) Disposable baby diapers: Life cycle costs, eco-efficiency and circular economy. *Journal of Cleaner Production* **211**:455-467. <https://doi.org/10.1016/j.jclepro.2018.11.146>
- Noorian SA, Hemmatinejad N, Navarro JAR (2020) Ligand modified cellulose fabrics as support of zinc oxide nanoparticles for UV protection and antimicrobial activities. *International Journal of Biological Macromolecules* **154**:1215-1226. <https://doi.org/10.1016/j.ijbiomac.2019.10.276>
- Paterson DL, Harris PNA (2016) Colistin resistance: a major breach in our last line of defence. *Lancet Infectious Diseases* **16**(2):132-133. [https://doi.org/10.1016/s1473-3099\(15\)00463-6](https://doi.org/10.1016/s1473-3099(15)00463-6)
- Quinlan PJ, Tanvir A, Tam KC (2015) Application of the central composite design to study the flocculation of an anionic azo dye using quaternized cellulose nanofibrils. *Carbohydrate Polymers* **133**:80-89. <https://doi.org/10.1016/j.carbpol.2015.06.095>
- Rabbi MA, Rahman MM, Minami H, Habib MR, Ahmad H (2020) Ag impregnated sub-micrometer crystalline jute cellulose particles: Catalytic and antibacterial properties. *Carbohydrate Polymers* **233**:115842. <https://doi.org/10.1016/j.carbpol.2020.115842>
- Salari M, Sowti Khiabani M, Rezaei Mokarram R, Ghanbarzadeh B, Samadi Kafil H (2018) Development and evaluation of chitosan based active nanocomposite films containing bacterial cellulose nanocrystals and silver nanoparticles. *Food Hydrocolloids* **84**:414-423. <https://doi.org/10.1016/j.foodhyd.2018.05.037>
- Tang K-pM, Kan C-w, Fan J-t, Tso S-I (2017) Effect of softener and wetting agent on improving the flammability, comfort, and mechanical properties of flame-retardant finished cotton fabric. *Cellulose* **24**(6):2619-2634. <https://doi.org/10.1007/s10570-017-1268-z>

Tu C, Zhang R-d, Yan C, Guo Y, Cui L (2019) A pH indicating carboxymethyl cellulose/chitosan sponge for visual monitoring of wound healing. *Cellulose* **26**(7):4541-4552. <https://doi.org/10.1007/s10570-019-02378-0>

Wahid F, Bai H, Wang F-P, Xie Y-Y, Zhang Y-W, Chu L-Q, Jia S-R, Zhong C (2019) Facile synthesis of bacterial cellulose and polyethyleneimine based hybrid hydrogels for antibacterial applications. *Cellulose* **27**(1):369-383. <https://doi.org/10.1007/s10570-019-02806-1>

Wang Y, Yang Y, Shi Y, Song H, Yu C (2020) Antibiotic-Free Antibacterial Strategies Enabled by Nanomaterials: Progress and Perspectives. *Adv Mater* **32**(18):e1904106. <https://doi.org/10.1002/adma.201904106>

Widen H, Alenljung S, Forsgren-Brusk U, Hall G (2017) Sensory Characterization of Odors in Used Disposable Absorbent Incontinence Products. *J Wound Ostomy Continence Nurs* **44**(3):277-282. <https://doi.org/10.1097/WON.0000000000000326>

Xu Y, Shi Y, Lei F, Dai L (2020) A novel and green cellulose-based Schiff base-Cu (II) complex and its excellent antibacterial activity. *Carbohydr Polym* **230**:115671. <https://doi.org/10.1016/j.carbpol.2019.115671>

Yousaf H, Mehmood A, Ahmad KS, Raffi M (2020) Green synthesis of silver nanoparticles and their applications as an alternative antibacterial and antioxidant agents. *Materials Science and Engineering: C* **112**:110901. <https://doi.org/10.1016/j.msec.2020.110901>

Zhao S-W, Zheng M, Zou X-H, Guo Y, Pan Q-J (2017) Self-Assembly of Hierarchically Structured Cellulose@ZnO Composite in Solid-Liquid Homogeneous Phase: Synthesis, DFT Calculations, and Enhanced Antibacterial Activities. *ACS Sustainable Chemistry & Engineering* **5**(8):6585-6596. <https://doi.org/10.1021/acssuschemeng.7b00842>

## Figures

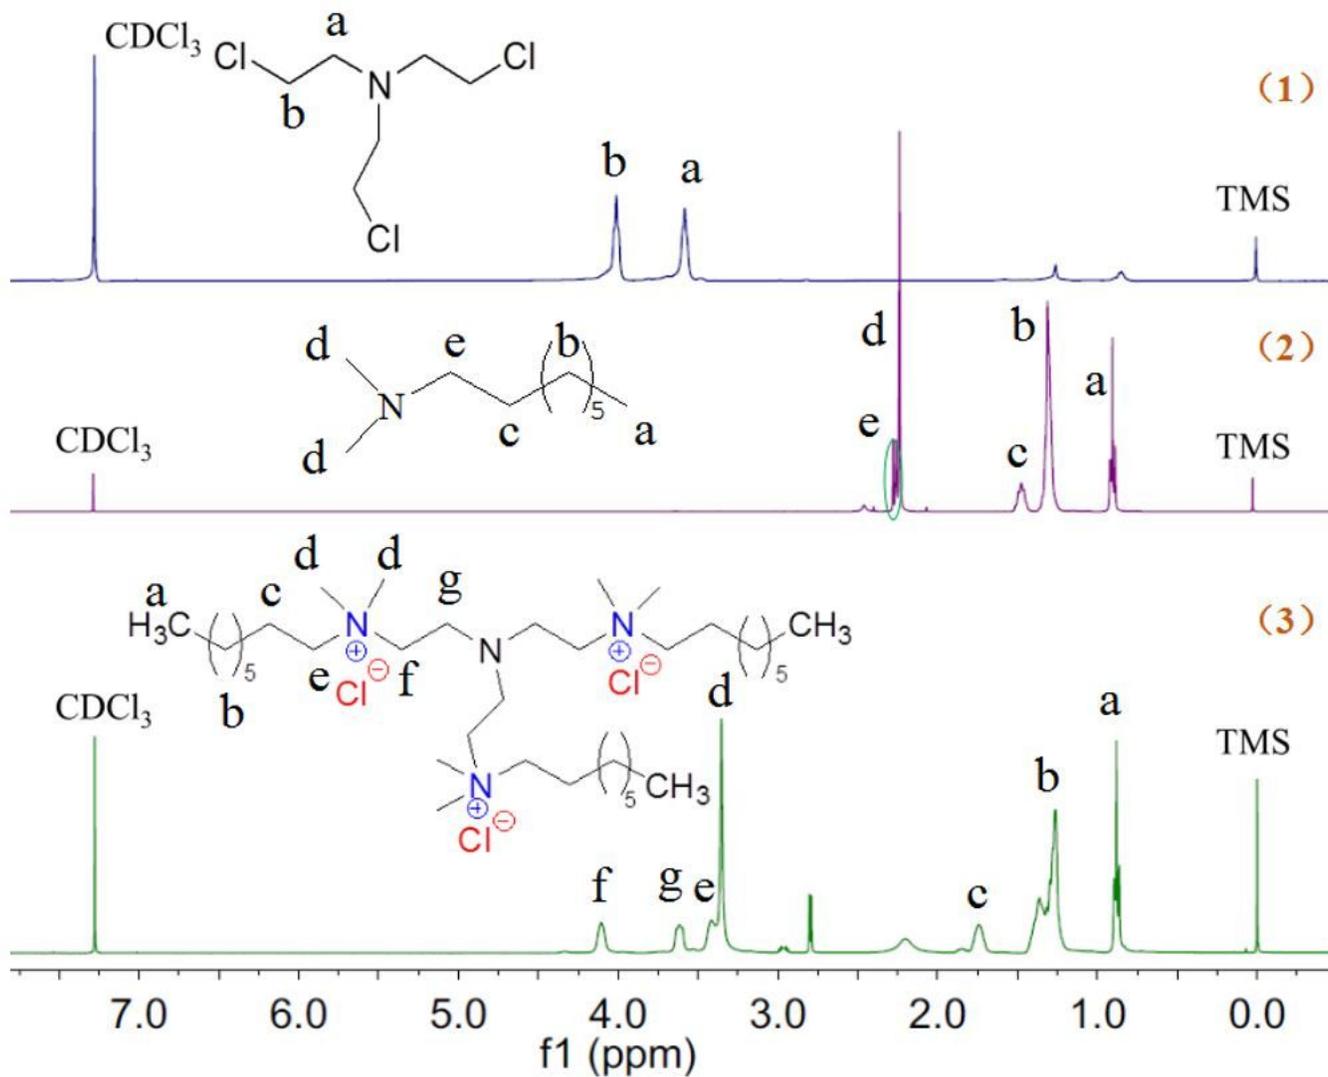


Figure 1

$^1\text{H}$  NMR spectra of (1) tris(2-chloroethyl)amine, (2) N, N-dimethyloctylamine and (3) AQAS 2a


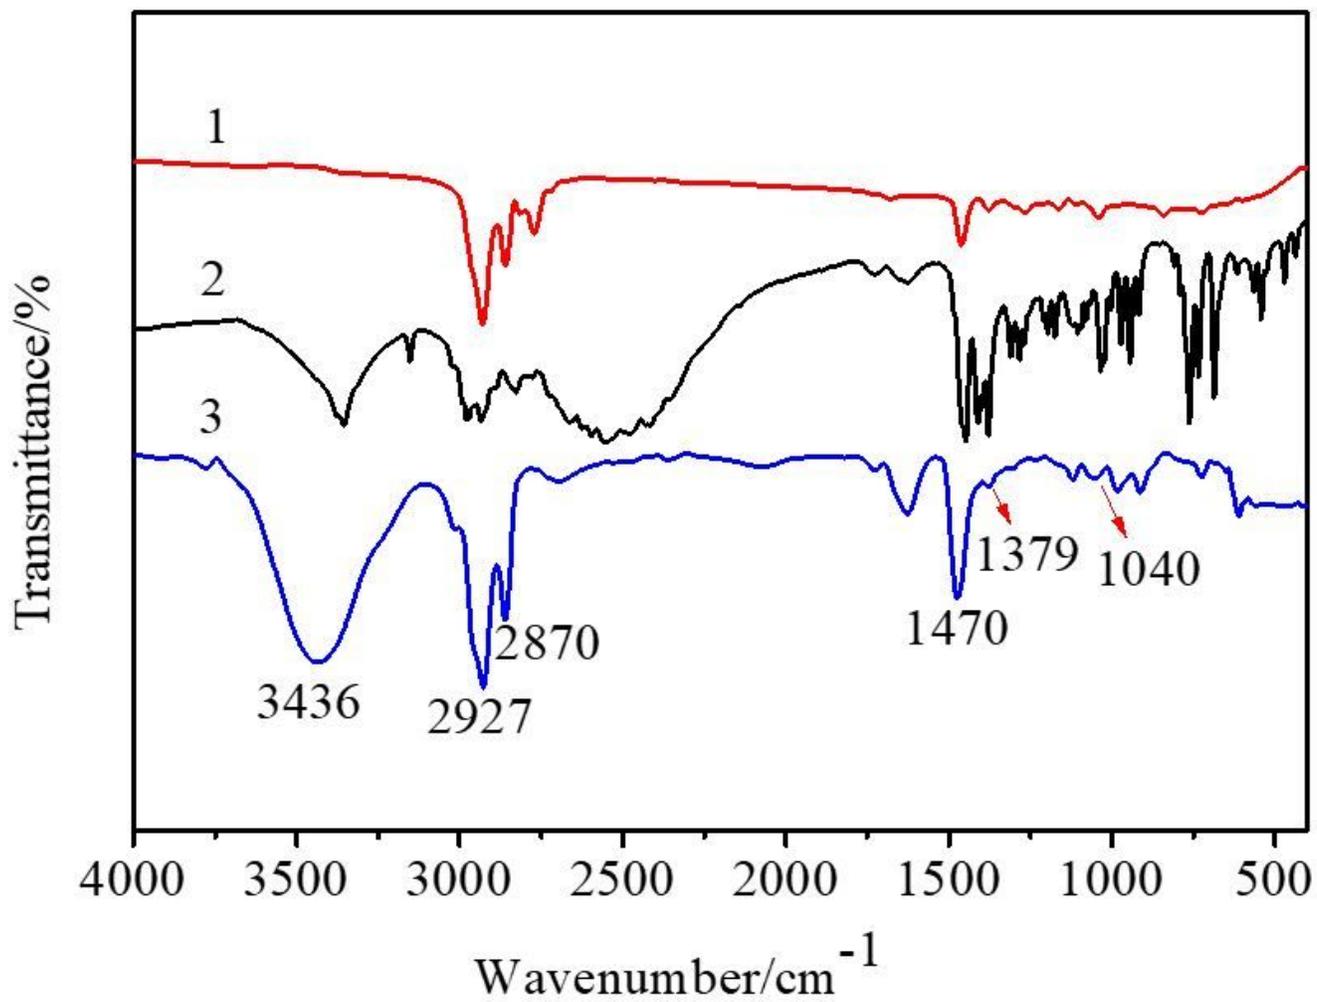



Figure 2

FT-IR spectra. 1. N,N-dimethyl-octylamine, 2. tris(2-chloroethyl)amine and 3. AQAS 2a

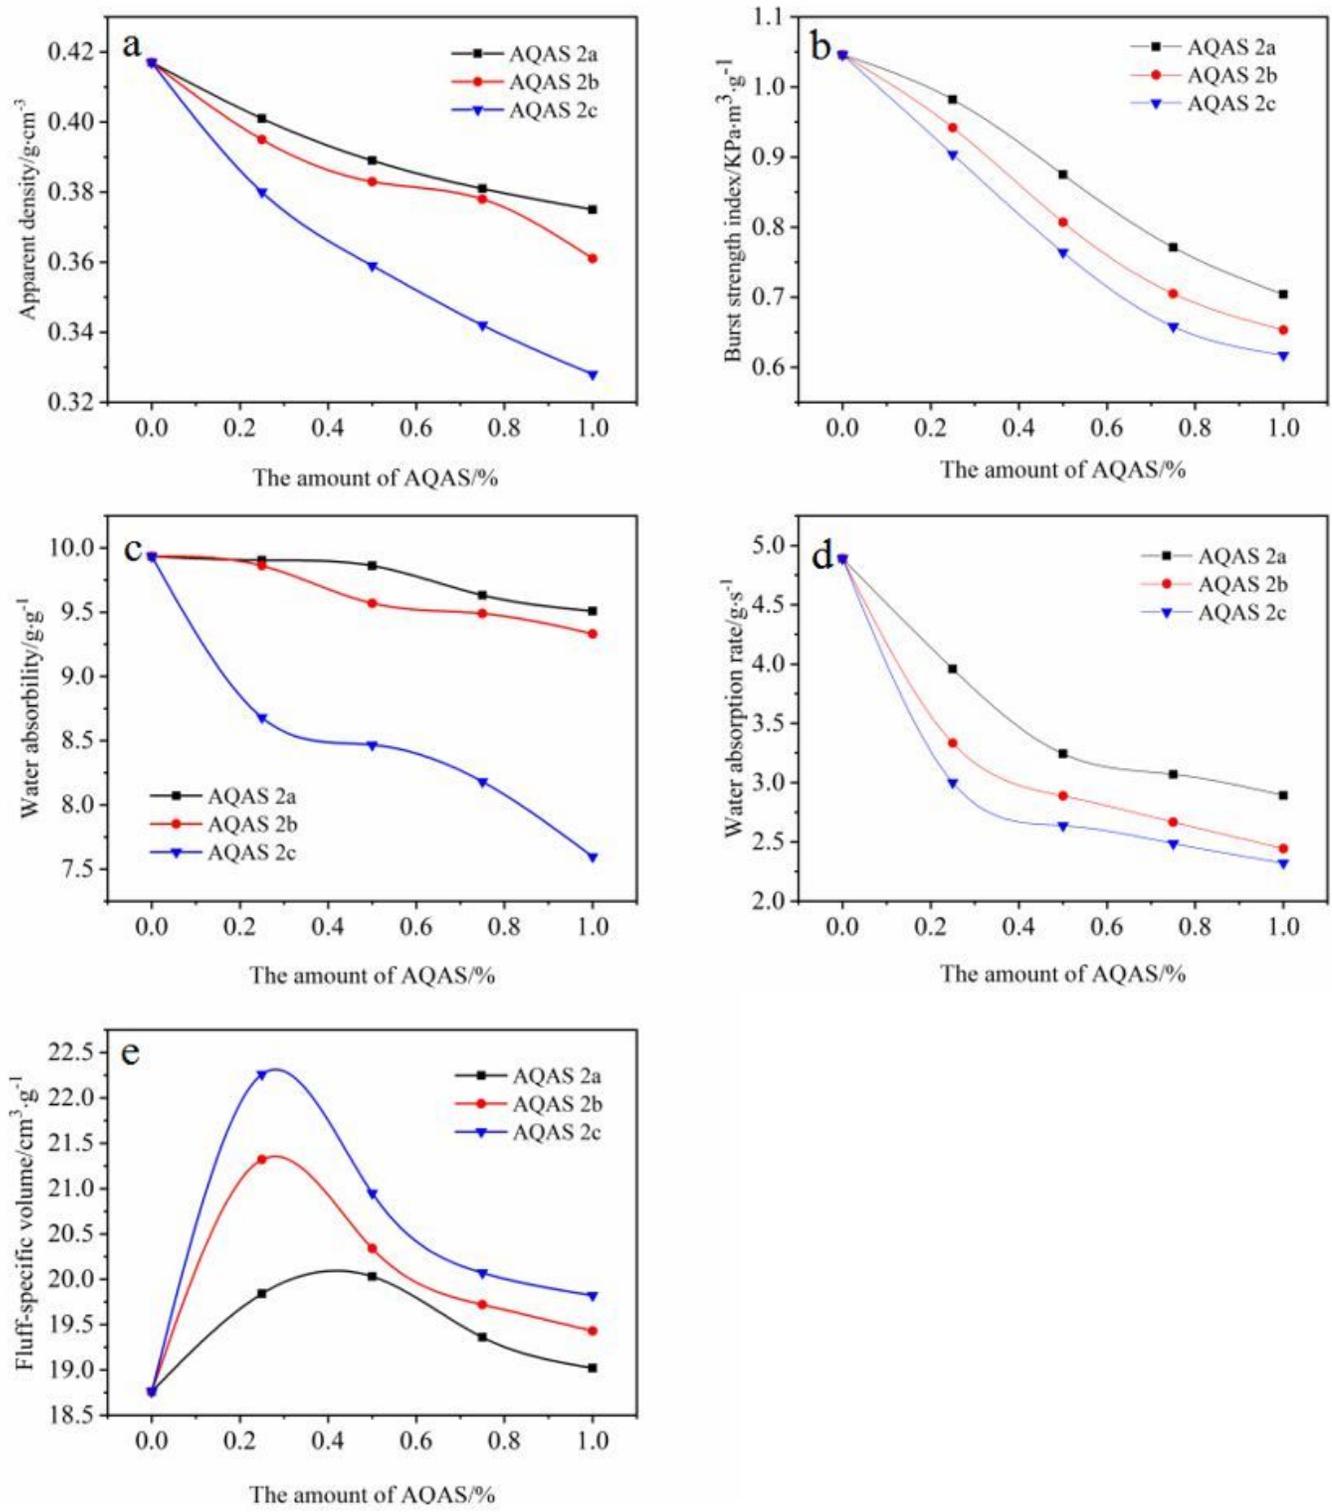


**Figure 3**

The properties of fluff pulp board with the loading amounts of AQAS. a. apparent density, b. burst strength index, c. water absorbibility, d. water absorption rate, e. fluff-specific volume

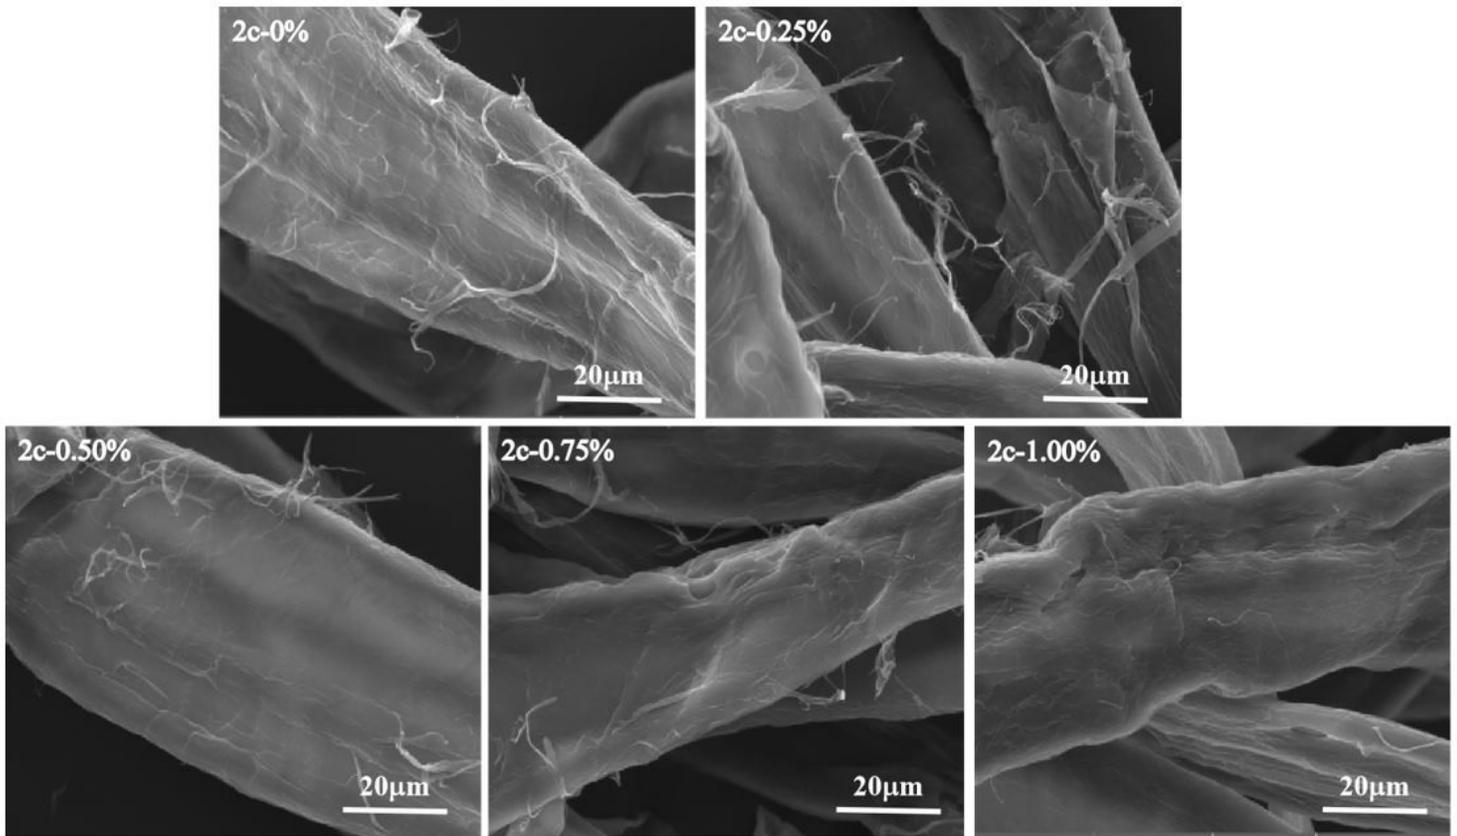


**Figure 4**

The surface morphology of paper with different loading amounts of AQAS 2c

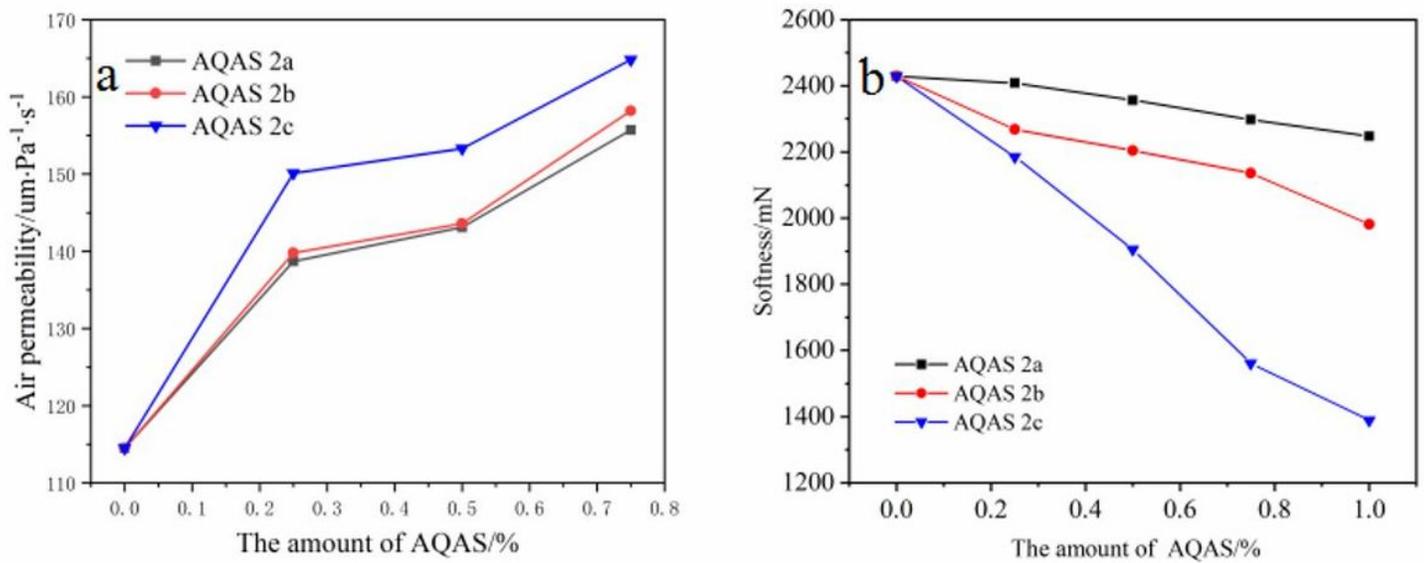

**Figure 5**

The properties of paper with different loading amounts of AQAS. a. air permeability, b. softness

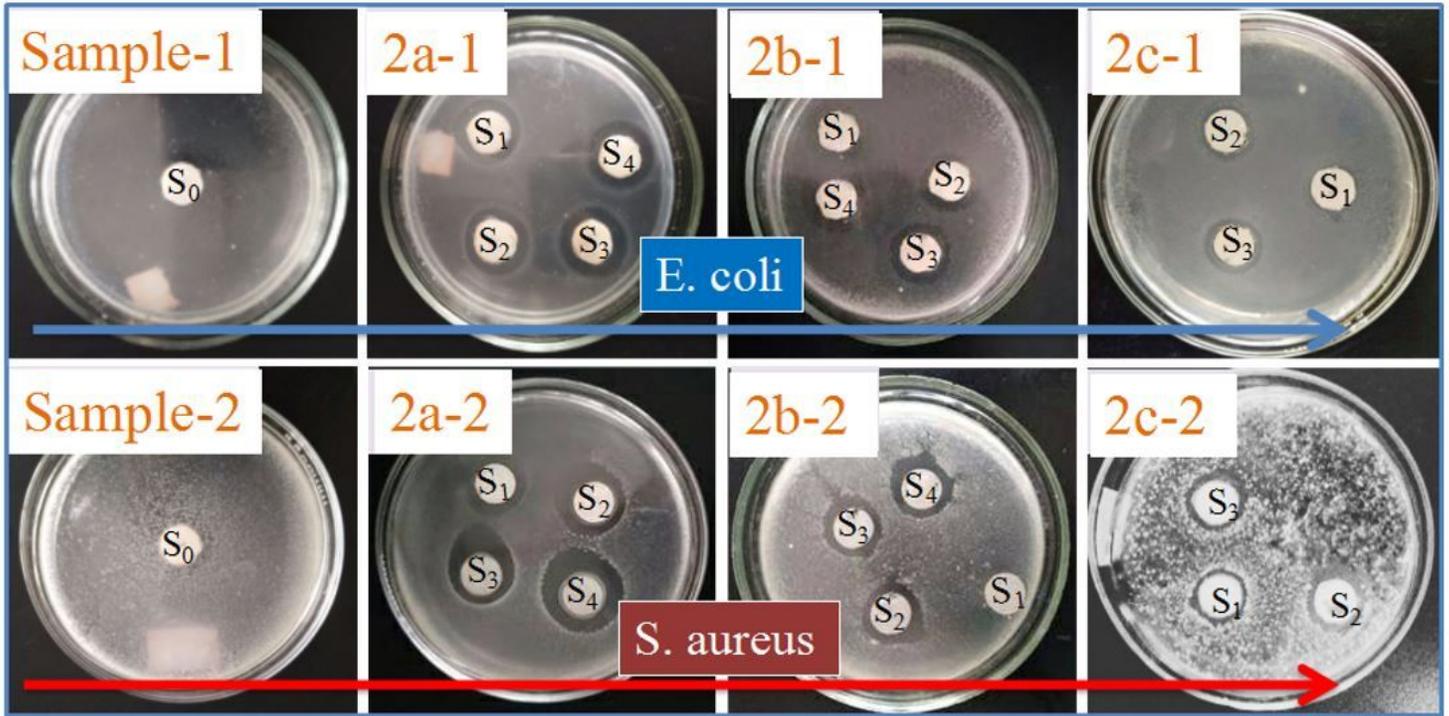

**Figure 6**

Antibacterial activity of fluff pulp board with different loading amount of AQAS 2a, AQAS 2b and AQAS 2c. S0, S1, S2, S3 and S4 stand for the amount of 0, 0.25%, 0.5%, 0.75% and 1.0%, respectively.

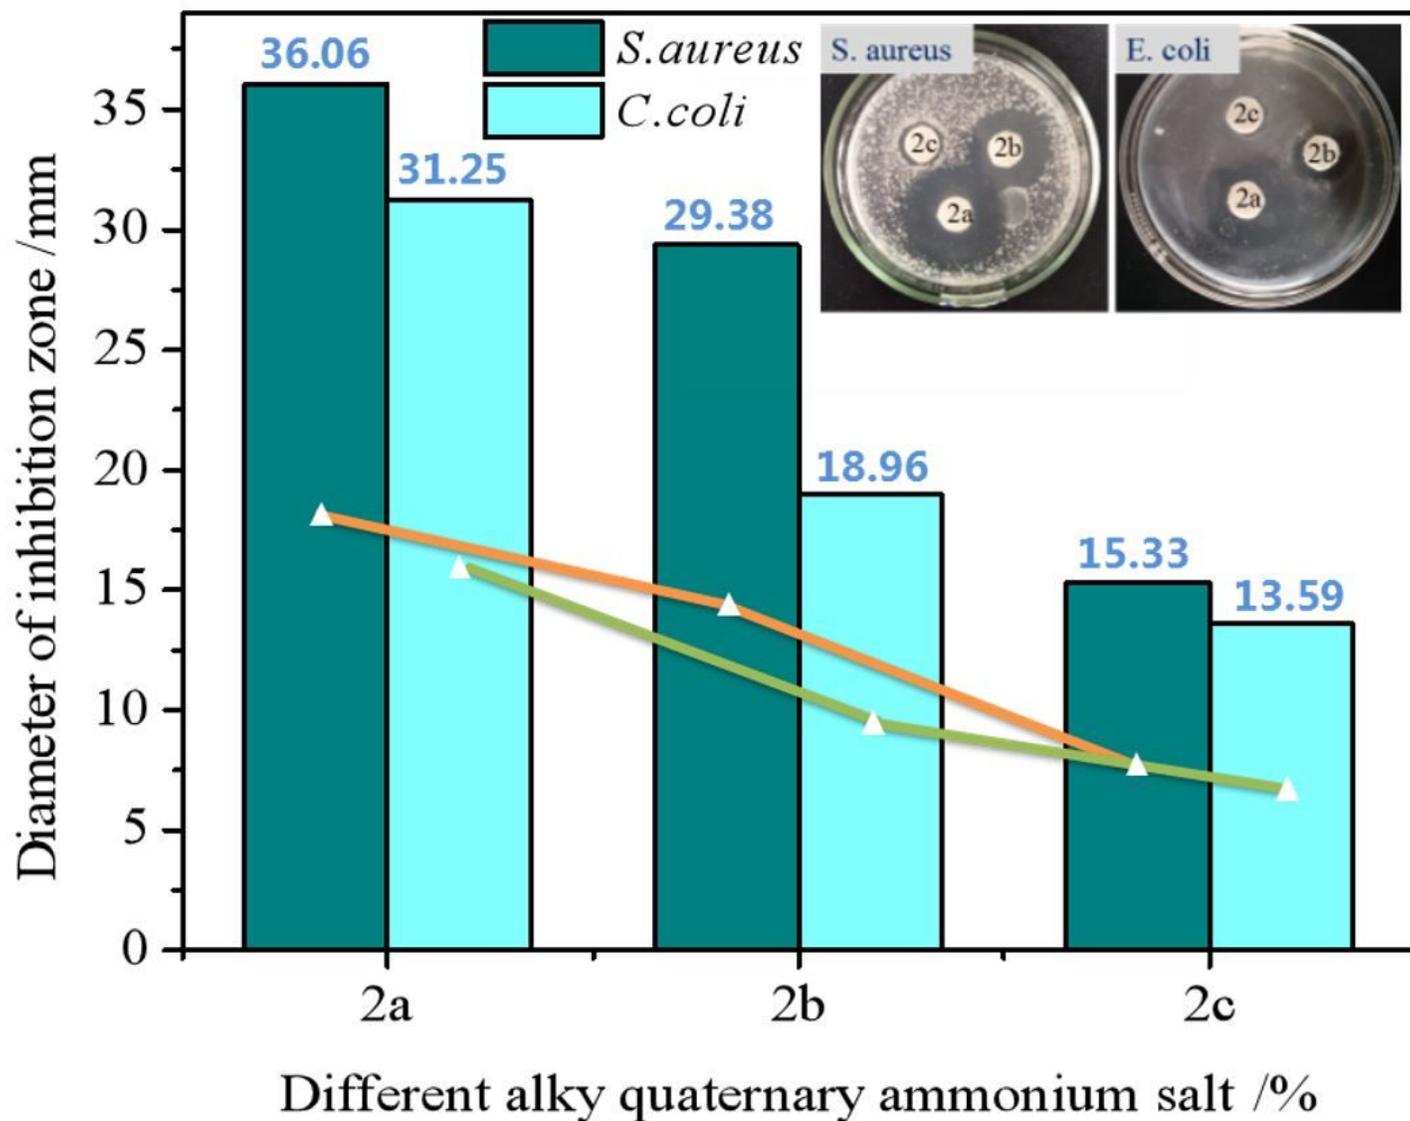


Figure 7

Antibacterial activity of fluff pulp with different AQAS

## Supplementary Files

This is a list of supplementary files associated with this preprint. Click to download.

- [scheme1.jpg](#)
- [scheme2.jpg](#)
- [scheme3.jpg](#)
- [Supportinginformation.docx](#)