

Production of NiMn_2O_4 Hollow Spheres and CoFe_2O_4 Bowl-Like Structures by Using Block Copolymer Stabilized Polystyrene Spheres as a Hard Template

Gökhan Kocak

Adiyaman University Vocational School of Higher Education

Vural Bütün (✉ vbutun@ogu.edu.tr)

Eskisehir Osmangazi Universitesi Fen Edebiyat Fakultesi <https://orcid.org/0000-0003-4542-5080>

Research Article

Keywords: Block copolymer, polystyrene latex, dispersion polymerization, hollow spheres, NiMn_2O_4 , CoFe_2O_4

Posted Date: April 3rd, 2021

DOI: <https://doi.org/10.21203/rs.3.rs-378803/v1>

License: © ⓘ This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

Abstract

The aim of this study is to highlight the use of polystyrene (PS) latexes stabilized with block copolymers as a hard template in the production of metal oxide hollow spheres. PS latexes produced by dispersion polymerization by stabilizing with tertiary amine methacrylate-based diblock copolymer were used as a hard template in the preparation of nickel manganese oxide (NiMn_2O_4) hollow spheres and iron cobalt oxide (CoFe_2O_4) bowl-like structures. Thanks to the diblock copolymer stabilizer with tertiary amine functional groups on the PS surface, precursor salts of CoFe_2O_4 and NiMn_2O_4 were first homogeneously deposited on the surface of PS latexes with a controlled precipitation technique. Then, metal oxide hollow spheres and bowl-like structures were produced by calcination. XRD results showed that CoFe_2O_4 and NiMn_2O_4 structures were successfully obtained after calcination. The thermogravimetric analysis results showed that the CoFe_2O_4 and NiMn_2O_4 contents of the hybrid PS spheres were in the range of 26.0-28.6 wt%. SEM images showed that the inorganic-polymer spheres fused with each other after calcination to form larger magnetic CoFe_2O_4 bowl-like structures. SEM images also indicated successful production of highly rough NiMn_2O_4 hollow spheres with nano-sheets on the surface.

1 Introduction

Nano and micro-sized metal oxides, especially used in catalysis applications, are very popular structures in material science. Among them, inorganic hollow and bowl-like micro/nanostructures, a special class of materials, are good candidates for many applications due to their large surface area, low density and large amount of interior space compared to their solid counterparts, as well as other optical and catalytic properties [1–6]. In addition, various magnetic metal oxides such as α -/ γ - Fe_2O_3 , Fe_3O_4 , Co_3O_4 , CoFe_2O_4 , NiMn_2O_4 and NiFe_2O_4 can be produced [7–9]. The magnetic nature of these materials provides them with significant advantages, such as being able to be directed in the magnetic field, as well as the reduction of repetitive use and physical losses, especially in catalysis and adsorption applications [7–9]. For practical applications, it is important to produce hollow spheres and bowl-like structures in the desired size, monodisperse size distribution, repeatable and cost-effective [1–5]. Using many different approaches, it is possible to produce uniform and repeatable hollow spheres and bowl-like structures [1–4]. Among these techniques, the use of hard templates (polymer, silica and carbon) is conceptually the simplest [1, 2]. Polystyrene (PS), PS derivatives, poly(methyl methacrylate) (PMMA) and formaldehyde resins are often used as polymeric hard templates due to their easy and low cost [1, 2].

Polymeric spheres have been designed using different strategies, with the necessity of having groups that enable interactions on the surface of the polymeric spheres produced, in order to accumulate inorganic compounds. One of them is the spheres produced by the emulsifier-free emulsion polymerization method, and the functionality in such structures is due to the anionic or cationic structure of the radical initiator used [10, 11]. Other widely preferred method is to modify the surface of PS spheres using sulfuric acid [2, 10, 12]. Another polymeric hard screen approach is the production of spherical brushes by polymerization initiated from the polymer surface [13–16]. Many different techniques such as photodeposition, chemical

vapor deposition, electrodeposition, controlled precipitation, hydrothermal deposition, electrostatic layer-by-layer (LbL) can be used for the coating of the surface of template materials with inorganic species [1–5]. After coating process, the hollow structures are obtained by dissolving the polymeric structure in a suitable solvent or by calcination [1–5]. With a pioneering approach proposed by us before, it is the use of block copolymer stabilizers that provide the basis for the interaction of inorganic species with PS spheres, allowing the accumulation of inorganic species on the PS surface. In our previous studies, we reported successful production of double layer nickel oxide and manganese oxide hollow spheres with a very rough surface with nano-sheets on the surface [17], nickel oxide [18] and nickel iron oxide [19] hollow spheres.

In the present study, nickel manganese oxide (NiMn_2O_4) hollow spheres and iron cobalt oxide (CoFe_2O_4) bowl-like structures were produced by using block copolymer stabilized PS latexes as a hard template. The PS spheres with various size were produced by using poly[2-(diisopropylamino)ethyl methacrylate]-*block*-poly[2-(dimethylamino)ethyl methacrylate] (PDPA-*b*-PDMA), poly[2-(diethylamino)ethyl methacrylate]-*block*-poly[2-(dimethylamino)ethyl methacrylate] (PDEA-*b*-PDMA) and poly[2-(dimethylamino)ethyl methacrylate]-*block*-poly[2-*N*-mopholinoethyl methacrylate] (PDMA-*b*-PMEMA) diblock copolymers as stabilizer via dispersion polymerization. Thanks to the functionality provided by the tertiary amine methacrylate containing block copolymer fringes on the PS surface, it has been homogeneously coated (or deposited) with metal oxide precursor salts (metal hydroxides) in the presence of urea with the controlled precipitation technique. Finally, both polymeric compounds were removed and metal oxides were converted to CoFe_2O_4 and NiMn_2O_4 structures by calcination process. As stated above, PS spherical latexes stabilized with block copolymer, which can be produced in a simpler and more functional way than polymeric spheres to be used for this purpose, are candidates to be a new model in the production of different types of metal oxide hollow spheres.

2 Experimental Section

2.1 Materials

2-(diisopropylamino)ethyl methacrylate (DPA, SI-AL), 2-(dimethylamino)ethyl methacrylate (DMA, SI-AL), 2-(diethylamino)ethyl methacrylate (DEA, Aldrich) and 2-*N*-mofolinoethyl methacrylate (MEMA, Polysciences Inc.) monomers were first passed through the basic alumina column (SI-AL). Then, 2,2-diphenyl-1-picrylhydrazyl (DPPH) and granular calcium hydride were added and stored at -18°C in a freezer. The monomers were distilled under vacuum before use. 1-Methoxy-1-trimethylsiloxy-2-methyl-1-propene (MTS), which is used as the initiator of the group transfer polymerization (GTP), was distilled under vacuum at room temperature. Tetra-*n*-butyl ammonium bibenzoate (TBABB) as a catalyst was synthesized in accordance with the literature [20]. THF was first dried with the addition of finely chopped solid sodium pieces by stirring 3 days at room temperature. It was then refluxed under dry nitrogen in the presence of solid potassium and used as a solvent in the polymerization reaction. PDPA-*b*-PDMA, PDEA-*b*-PDMA and PDMA-*b*-PMEMA diblock copolymers were synthesized by using group transfer

polymerization technique as described before [21]. *n*-pentane (Merck) was used to remove homopolymer contaminants from the diblock copolymers before proton NMR spectroscopy measurements.

Styrene (Merck) as a monomer, 2,2'-azodiisobutyronitrile (AIBN, Acros) as a radical initiator, 1-propanol (SI-AL) and methanol (SI-AL) as a solvent and a diblock copolymer as stabilizer were used in the production of PS spheres via dispersion polymerization. Fe(NO₃)₃·9H₂O (Panreac), Co(NO₃)₂·6H₂O (Merck), MnCl₂ (Merck), Ni(NO₃)₂·6H₂O (Merck) were used for coating the surface of PS spheres. Urea (SI-AL) has been used in the production of spherical inorganic-polymer materials for the purpose of controlled precipitation.

2.2 Instrumentation

Molecular weight distributions (M_w/M_n) and number average molecular weights (M_n) of the polymers were measured using gel permeation chromatography (GPC) having the following parameters: An Agilent Iso Pump 1200 Series and a refractive index detector, connected to PLgel Mixed-D and Mixed-E (5 and 3 μm , respectively, 300 mm×7.5 mm, Polymer Laboratories, Amherst, MA) columns and eluted with HPLC-grade tetrahydrofuran that was stabilized with BHT (0.5 g L⁻¹) and TEA (0.02%) at a flow rate of 1.0 mL min⁻¹. PMMA standards (ex. Polymer Labs, M_n : 1100-220000 g mol⁻¹) were used for calibration. The comonomer ratio of PDPA-*b*-PDMA, PDEA-*b*-PDMA and PDMA-*b*-PMEMA diblock copolymers were determined from proton NMR spectra (deuteron solvents) by comparing related peaks of both blocks. The hydrodynamic diameters (R_h) and polydispersity index values (PDI or μ_2/Γ^2) of PS spheres were determined by dynamic light scattering (DLS). DLS studies were performed using the ALV/CGS-3 compact goniometer system (Malvern, Inc, UK). This goniometer system is equipped with a 22 mW He-Ne laser at λ_0 632.8 nm, a photodiode detector operating with high quantum efficiency and an ALV/LSE-5003 multi-tau digital correlator electronic system. All measurements were made with 90° constant angle scattering of polymer dispersions. The data were evaluated by second order cumulative analysis. The solution temperature was kept constant at ± 1 °C sensitivity with a temperature controlled water bath. The wt% ratio of metal oxide or composites of metal oxide structures were determined with thermogravimetric analysis (TGA) device (Seiko SII Extar 6000 TG/DTA). Measurements were performed at different heating rates (1–10 °C min⁻¹) and under a flowing dry air atmosphere of 2 mL min⁻¹. Protherm furnaces PAF 110/10 muffle furnace was used in the calcination process. The morphologies of PS latexes and metal oxide hollow spheres prepared were examined by light microscope (Leica DM750), and scanning electron microscope (SEM, Zeiss Evo LS10). Powder diffraction patterns of metal oxide hollow spheres were determined by X-ray diffraction (powder-XRD, PANalytical Empyrean) analysis using Cu K α -radiation ($\lambda_{1/4}$ 1.54 Å) with 2 θ angle in the range of 1–90 at room temperature. The powder diffraction patterns were examined in the High Score Plus software and the peak determinations were made, and the phase content of the sample was illuminated with the reference phases found by searching from the ICDD PDF4+ library.

2.3 Production of PS microspheres by dispersion polymerization

In this study, PDPA-*b*-PDMA, PDEA-*b*-PDMA [21] and PDMA-*b*-PMEMA [22] diblock copolymers, which we previously produced and characterized by GTP method, were used as stabilizers (Fig. 1). The detail of the production of PDPA-*b*-PDMA diblock copolymer with GTP, which is used as a stabilizer in the synthesis of PS spheres, is given in the Supporting Information.

Synthesis of PS microspheres (latexes) was performed using PDPA_{0.17}-*b*-PDMA_{0.83} diblock copolymer (1.0 g, 25500 g mol⁻¹, M_w/M_n: 1.08) stabilizer, AIBN initiator (50 mg), styrene monomer (5.0 mL), 1-butanol or H₂O/methanol (50.0 mL) under nitrogen atmosphere in oil bath at 60°C at 1000 rpm stirring speed (Fig. 2). The reaction was continued overnight. The solution was centrifuged twice at 10000 rpm for 10 minutes to precipitate PS microspheres. PS spheres were dried overnight in vacuum. Experimental conditions of other produced PS spheres are given in Table 1. The spheres were characterized by DLS after centrifugation.

2.4 Preparation of metal oxide structures

Schematic representation of the production of NiMn₂O₄ hollow spheres and CoFe₂O₄ bowl-like structures using PS spheres stabilized with block copolymer are given in Fig. 2. The deposition of metal hydroxides on the surface using the controlled precipitation technique in the presence of urea and then the production of both CoFe₂O₄ [9, 23–26] and NiMn₂O₄ [27, 28] structures by calcination process have been studied previously. The production of metal oxides was carried out very similar to these previous studies.

First, PS spheres (0.2 g) were dispersed in 180.0 mL of water (pH 7.0). The amounts of Fe(NO₃)₃ and Co(NO₃)₂ solutions given in Table 2 were then added and stirred for 24 hours. Finally, urea was dissolved in water (20.0 mL) and added to the reaction medium and stirred at 80°C for 24 hours. Similar process was carried out using Ni(NO₃)₂ and MnCl₂ solutions, all details are given in Table 2. The products were centrifuged three times at 5000 rpm and washed three times with distilled water. It was seen that the centrifuged solution part was completely clear, that is, all metal oxide precursor salt deposited on the PS surface in a controlled precipitation. It was observed that the PS spheres coated with both metal oxide precursor salts turned from white to brown tones over time (see Fig. 3). The resulting material was dried in an oven at 100°C overnight. The productions of all metal oxide structures are given in Table 2.

Finally, PS-inorganic hybrid spheres containing Co/Fe and Ni/Mn were calcinated at 700 °C for 1 hour and at 600 °C for 2 hours in air atmosphere, respectively. In these calcination processes in the furnace, both types of hybrid spheres were heated up to 300 °C and kept at this temperature for 1 hour, removing most of the polymeric structure. Then it was heated from 300 °C to calcination temperatures (600 or 700) with a heating rate of 1 °C/min and the calcination process was terminated by keeping at this temperature. The difference in the colors of the hybrid spheres before the calcination and the metal oxide structures formed after the calcination is given in Fig. 3.

The wt% ratios of metal oxides in PS-inorganic hybrid spheres were determined with by thermogravimetric analysis (TGA). TGA measurements were carried out in a dry air atmosphere (2 mL

min⁻¹) and the heating program applied in the measurements is given in Fig. 4. It was aimed to remove polymeric parts by keeping at ~ 300 °C for 60 minutes in TGA measurements of hybrid spheres as in the calcination process performed in the furnace. Since deviation was observed in TGA chromatograms due to intense combustion, it was planned to be kept at these temperatures for 60 minutes and to completely burn the polymeric part in a controlled manner. However, unexpected fluctuations were observed in TGA chromatograms, which we thought to be due to the polymer not being completely removed. The contents and morphology of the produced metal oxide structures were determined by XRD, light microscope and SEM.

3 Results And Discussion

3.1 Production of PS microspheres

The tertiary amine methacrylate containing PDPA-*b*-PDMA, PDEA-*b*-PDMA and PDMA-*b*-PMEMA diblock copolymers each served as a good dispersing agent in the production of PS spheres and enabled the production of monodisperse PS spheres (Table 1). In PS latex stabilization using this block copolymer, the less soluble PDPA, PDEA or PMEMA block are adsorbed on the latex surface, while the more soluble PDMA blocks are responsible for the stabilization of latexes. The polymer chains belonging to the PDMA block are located in the form of fringes in the shell of PS spheres, just like spherical brushed polymers.

Polymeric spheres stabilized with block copolymers have been preferred by polymer scientists to produce more monodisperse or environmentally sensitive spherical particles [29–33]. The resulting spherical particles exhibit changes in swelling-shrinkage behavior or surface properties with external stimuli such as temperature and pH [29–33]. In other words, interactions are established between block copolymers and polymeric spheres used as stabilizers in emulsion and dispersion polymerization techniques. These interactions are more stronger in emulsion polymerization, but some of these block copolymers remain on the surfaces of latex after their synthesis via dispersion polymerization as well [29, 33, 34].

As a result of DLS studies, hydrodynamic radius (R_h) values and polydispersity index values (μ_2/Γ^2) of PS spheres stabilized with different block copolymers are given in Table 1. According to these results, it can be said that PS spheres are produced as monodisperse with a diameter of 1–2 μm . There are many studies showing that PS spheres can be produced in planned diameters by changing many factors such as heterogeneous polymerization technique, stabilizer type, stabilizer amount, mixing speed and solvent type [29–35]. When the previous studies are examined, if the amount of stabilizer increases or the mixing speed increases, the diameter becomes smaller. Comonomer ratios in the block copolymer have a significant effect on the diameter. The type of solvent and solvent mixtures are also very effective on diameter change. Since the comonomer ratios and molecular weights of the stabilizers used in the production of each PS sphere are different, it will be very difficult to compare with each other. However, it can be easily said here that the change in PS diameters is due to the stabilizer content.

Table 1

Experimental conditions in the synthesis of the PS latexes with various size and DLS measurements (styrene 5.0 mL, 1000 rpm and at 60 °C)

Code	Stabilizer Type	Stabilizer Amount	AIBN	Media (50 mL)	Diameter (nm)	μ_2/Γ^2
PS1	^a PDPA _{0.17} - ^b PDMA _{0.83} ^b (M _n : 25500 g mol ⁻¹ , PDI: 1.08)	1.0 g	60 mg	H ₂ O/MeOH (1/9)	2150	0.02
PS2	^a PDMA _{0.86} - ^b PMEMA _{0.14} ^b (M _n : 45600 g mol ⁻¹ , PDI: 1.13)	0.6 g	45 mg	1-butanol	1050	0.08
PS3	^a PDEA _{0.30} - ^b PDMA _{0.70} ^b (M _n : 14900 g mol ⁻¹ , PDI: 1.06)	0.6 g	45 mg	H ₂ O/MeOH (1/12)	1400	0.06

^a Mole% content determined by proton NMR spectroscopy.

^b GPC results (THF eluent, PMMA standards).

3.2 Preparation of metal oxide structures

In the previous section, it was mentioned that block copolymers used as stabilizers in dispersion (or emulsion) polymerization adhere to the surface [29, 33, 34]. The polymer fringes with this DMA unit provided a suitable environment for the absorption of metal ions. However, in this way, the metal oxide precursor salt can be deposited or adsorbed homogeneously on the structure used as a hard template. Incidentally, it is also known that PS spheres are frequently used as a hard template in the coating of polymeric cores with an inorganic layer [1, 2]. PS spheres are preferred because the phenyl ring is modifiable, easy to prepare, and is a low cost polymer that is easily available commercially. In addition, poly(methylmethacrylate) and formaldehyde resin are other common polymers used for this purpose [1, 2].

Together with our previous studies [17–19], it will be very useful for the reader to compare diblock copolymer stabilized PS spheres which is used as a hard template with other polymeric rigid templates in terms of functionality and production technique in this pioneering work. Inorganic species must have a surface charge (or functionality) in order to adsorb to the surface of PS spheres. This can only be achieved with stabilizing agent [29–33], anionic radical (ammonium persulfate and potassium persulfate) and cationic radical [2,2'-azobis(2-methylpropionamidine) dihydrochloride] initiators used in the emulsifier-free polymerization method [10, 11], various modifications made on the phenyl ring in PS

spheres [2, 10, 12], and spherical polymeric brush polymers, which are surface initiated polymerization products [13–16]. In addition, the fact that PS spheres have a charged surface is important in that it allows the coating of PS spheres with inorganic species with the layer-by-layer coating (LbL) technique [36]. Polymeric spheres stabilized with block copolymers contain polymer fringes around them, just like brush polymers, can be produced quite simply compared to brush polymers which are surface-initiated polymerization products that require special monomers or various modifications [13–16]. It is worth to mention that these polymeric spherical brushes are frequently used in the production of inorganic nanoparticles (NP) rather than the production of hollow spheres [13–16]. On the other hand, it is quite common to use anionic PS spheres formed by the sulfonation of the polystyrene surface with the H_2SO_4 treatment, but it can still be said that the PS spheres stabilized with the block copolymers used in this study are more functional [2, 10, 12]. It can be said that the polymer fringes on the surface of the PS spheres stabilized with block copolymers will contribute to the prevention of the adsorption of inorganic species and their separation from the surface and to ensure a completely homogeneous coating, by forming a steric barrier for the polymer fringes during the nucleation and growth stages of inorganic species [13–16].

In this study, it was thought that the mechanism of action of the diblock copolymer used to stabilize PS spheres was to establish interaction with metal ions, increase the concentration of metal ions on the PS surface with adsorption, form nuclei on the surface of the inorganic species in the basic medium, and the growth of the crystals of metal oxide precursor salts on the PS surface thanks to the polymer fringes. The fact that tertiary amine methacrylate based polymers and many other polymers have already been discussed in many studies as metal ion adsorbents [37, 38]. However, it should be kept in mind that many different types of block copolymers can be designed and used for this purpose [37, 38]. It is also important that the polymer to be selected for this purpose has to have high metal ion adsorption capacity, low cost and easy availability.

Using the controlled precipitation technique as in this study, many metal oxide hollow spheres and bowl-like structures such as CuO , ZnO , SnO_2 , CeO_2 , MgO , $\alpha\text{-Fe}_2\text{O}_3$, Cr_2O_3 , In_2O_3 , Co_3O_4 , NiO , CoFe_2O_4 , NiFe_2O_4 and other [6, 39] can be produced for different applications. To summarize briefly, urea added to the reaction mixture slowly decomposes to NH_3 at $80\text{ }^\circ\text{C}$, that is, the hydroxide ion concentration in the mixture increases and metal hydroxides begin to precipitate in the PDMA fringes on the PS surface. In other words, $\text{Fe}(\text{OH})_3/\text{Co}(\text{OH})_2$ and $\text{Mn}(\text{OH})_2/\text{Ni}(\text{OH})_2$ crystals are grown in a controlled manner on the PS surface. It is then converted to CoFe_2O_4 and NiMn_2O_4 by thermal decomposition (calcination) and polymeric compounds are removed at this time [9, 23–27].

According to the results of thermogravimetric analysis (TGA), it was observed that 26.0-28.6 wt% residue remains at $650\text{ }^\circ\text{C}$ (Table 2). Considering that PS spheres did not leave any residue at the same temperature, almost all of the structures formed after the calcination of polymer-inorganic hybrid structures belonged to CoFe_2O_4 and NiMn_2O_4 residues (Fig. 4). Of course, by adding higher proportions of

precursor metal salts, these residue amounts can be further increased, and this change causing an increase in the shell thickness contributes to the hollow spheres remaining unbreakable.

Table 2
Experimental conditions in the synthesis of the inorganic-PS hybrid spheres (in 200 mL water, at 80 °C)

Code	PS Spheres (0.2 g)	Urea	Fe(NO₃)₃ (0.20 M)	Co(NO₃)₂ (0.20 M)	Residue at 650 °C (wt%)
P-CoFe1	PS1	2.0 g	4.0 mL	2.0 mL	26.3
P-CoFe2	PS2	2.0 g	4.0 mL	2.0 mL	28.6
Code	PS Spheres (0.2 g)	Urea	Ni(NO₃)₃ (0.20 M)	MnCl₂ (0.20 M)	Residue at 650 °C (wt%)
P-NiMn1	PS3	3.0 g	2.0 mL	4.0 mL	26.7
P-NiMn2	PS3	4.0 g	2.0 mL	4.0 mL	26.0

Determination of the crystal phase identification of the synthesized CoFe₂O₄ and NiMn₂O₄ structures was done with XRD analysis. After 1 hour of calcination at 700 °C, it was determined that CoFe1 and CoFe2 were iron cobalt oxide (CoFe₂O₄) with cubic (ICDD: 04-006-6582) and rhombohedral (ICDD: 04-015-9870) crystal structure, respectively (Fig. 5). After 2 hours of calcination at 600 °C, it was determined that nickel manganese oxide (NiMn₂O₄) was formed in cubic (ICDD: 04-008-6983) crystal structure. As seen in Fig. 5, there is no other peaks related to cobalt oxide, nickel oxide, manganese oxide, iron oxide or other phases which indicate that we have pure CoFe₂O₄ [25] and NiMn₂O₄ [40].

It can be easily understood by comparing the light microscope images of PS spheres and inorganic-PS hybrid spheres that the surfaces of all PS spheres are successfully homogeneously coated with Fe(OH)₃/Co(OH)₂ and Ni(OH)₂/Mn(OH)₂ (Fig. 6). Again, these images showed that no other precipitate structures were formed except for the PS surface (Fig. 6). By taking SEM images of metal oxide structures, both their homogeneity and more detailed morphological structures were revealed. SEM images of the metal oxide structures taken after calcination also indicated that the PS spheres were coated homogeneously (Fig. 7). From the SEM images of CoFe1 and CoFe2, it was seen that the inorganic-PS hybrid spheres fused with each other after calcination process to form larger structures (Fig. 7a and b). Magnetic CoFe₂O₄ hollow bowl-like structures were obtained in the outer layer of this structure, and hollow spheres were obtained in the inner layers. The diameters of the bowl-like structures formed on the surface were, as expected, ~ 1.85 μm for CoFe1 and ~ 0.80 μm for CoFe2, in relation to the diameters of the PS spheres used. In another study where polymeric spheres were used as a rigid template and similar metal oxide type was also similar, structures with similar morphological properties

were obtained, which revealed the effect of temperature [41]. Although the first structure planned to be produced is metal oxide hollow spheres, the obtained bowl-like structures can be related to the nature of the metal oxide as well as the calcination temperature and time. It is possible to produce metal oxide hollow spheres by experimenting with different calcination temperature and time. SEM images of NiMn1 and NiMn2 samples showed that NiMn₂O₄ hollow spheres with a diameter of ~ 2.50 μm were successfully produced (Fig. 7c and d). The reason why both have similar diameters is, of course, because they are produced using the same PS template. The difference between NiMn1 and NiMn2 is the amount of urea and a change in the color of the resulting inorganic-PS hybrid sphere was observed. There were nano-sheets on the surface of both NiMn₂O₄ hollow spheres. It has been emphasized in previous studies that the presence of nano-sheets has an effect on increasing the surface area of the structure [42].

The iron cobalt oxide (CoFe₂O₄) is an important type of metal oxide that has applications in various fields such as sensor [43], photocatalysts [8, 9], electrocatalyst [44], cancer therapy [45], batteries [24, 26], magnetic optical behavior [46] and supercapacitors [47]. It is n-type semiconductor, highly stable, small optical band gaps (~ 2.6 eV) making them active under visible light treatment [48]. The nickel manganese oxide (NiMn₂O₄) has been widely studied and applied in many fields such as sensor [49], negative temperature coefficient thermistors [50], photocatalysts [51], electrocatalyst [52], supercapacitors [27, 49], and batteries [53] owing to its various advantages, such as low cost, resource abundance, good stability, environmental friendliness, convenience in use and excellent electrochemical performance [54]. The effectiveness of the materials also depends on their morphology, size and composition of the materials. In this respect, it is undoubted that reproducible and uniform metal oxide structures with varying diameters depending on the choice of polymeric sphere used as template can be used in many similar applications with the positive effect of high surface area.

4 Conclusions

The PS spheres produced in different diameters by dispersion polymerization using different diblock copolymers as stabilizers were used in the production of NiMn₂O₄ hollow spheres and CoFe₂O₄ bowl-like structures. The dimensions of these structures formed according to the diameters of the spherical spheres also changed as expected.

This study reports successful usage of spherical PS latexes stabilized with tertiary amine methacrylate based diblock copolymer as a template, which offers a new approach in terms of the use of hard templates. The surfaces of PS spheres are surrounded by a hydrated PDMA block of steric stabilizer PDPA-*b*-PDMA, PDEA-*b*-PDMA, or PDMA-*b*-PMEMA diblock copolymers. These stabilizers give them the ability to adsorb inorganic species at a higher capacity and stabilize the formed seeds on the surface, allowing the homogeneous metal oxide precursor salt to accumulate on the surface. Moreover, it should be noted that these PS spheres can be produced with a wide variety of block copolymers. Such hard templates have important advantages such as having more functional groups than surface modified PS spheres and being prepared with a simpler technique compared to spherical PS brushes. It is quite

possible that the spheres produced in this study and other inorganic hollow spheres we continue to produce will be used in various catalysis studies in the future.

Declarations

Declaration of Competing Interest

We confirm that there is no conflict of interest. Our work has no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

We would like to thank both Dr. Gökhan Dikmen and Gökhan Solmaz from Eskisehir Osmangazi University, Central Research Laboratory Application and Research Center (ARUM) for the capture and interpretation of XRD analyzes.

References

1. X.J. Wang, J. Feng, Y.C. Bai, Q. Zhang, Y.D. Yin, Synthesis, Properties, and Applications of Hollow Micro-/Nanostructures. *Chem. Rev.* 116(18), (2016) <https://doi.org/10.1021/acs.chemrev.5b00731>
2. J. Hu, M. Chen, X.S. Fang, L.W. Wu, Fabrication and application of inorganic hollow spheres. *Chem. Soc. Rev.* 40(11), (2011) <https://doi.org/10.1039/c1cs15103g>
3. J. Liang, H.R. Kou, S.J. Ding, Complex Hollow Bowl-Like Nanostructures: Synthesis, Application, and Perspective. *Adv. Funct. Mater.* 31(10), (2021) <https://doi.org/10.1002/adfm.202007801>
4. S.K. Yang, Y. Lei, Recent progress on surface pattern fabrications based on monolayer colloidal crystal templates and related applications. *Nanoscale* 3(7), (2011) <https://doi.org/10.1039/c1nr10296f>
5. B. Ai, H. Mohwald, D.Y. Wang, G. Zhang, Advanced Colloidal Lithography Beyond Surface Patterning. *Advanced Materials Interfaces* 4(1), (2017) <https://doi.org/10.1002/admi.201600271>
6. Y. Boyjoo, M.W. Wang, V.K. Pareek, J. Liu, M. Jaroniec, Synthesis and applications of porous non-silica metal oxide submicrospheres. *Chem. Soc. Rev.* 45(21), (2016) <https://doi.org/10.1039/c6cs00060f>
7. Y.Q. Zhang, Z.B. Huang, F.Q. Tang, J. Ren, Ferrite hollow spheres with tunable magnetic properties. *Thin Solid Films* 515(4), (2006) <https://doi.org/10.1016/j.tsf.2006.04.049>
8. D.F. Zhang, G.Z. Zhang, L. Zhang, Multi-shelled FeCo₂O₄ hollow porous microspheres/CCFs magnetic hybrid and its dual-functional catalytic performance. *Chem. Eng. J.* 330 (2017) <https://doi.org/10.1016/j.cej.2017.08.018>
9. B. Bhuyan, B. Paul, A. Paul, S.S. Dhar, *Paederia foetida* Linn. promoted synthesis of CoFe₂O₄ and NiFe₂O₄ nanostructures and their photocatalytic efficiency. *IET Nanobiotechnol* 12(3), (2018) <https://doi.org/10.1049/iet-nbt.2017.0131>

10. A. Syouflan, Y. Inoue, M. Yada, K. Nakashima, Preparation of submicrometer-sized titania hollow spheres by templating sulfonated polystyrene latex particles. *Mater Lett* 61(7), (2007)
<https://doi.org/10.1016/j.matlet.2006.07.081>
11. M. Watanabe, H. Aritomo, I. Yamaguchi, T. Shinagawa, T. Tamai, A. Tasaka, M. Izaki, Selective preparation of zinc oxide nanostructures by electrodeposition on the templates of surface-functionalized polymer particles. *Chem Lett* 36(5), (2007) <https://doi.org/10.1246/cl.2007.680>
12. H. Amari, M. Guerrouache, S. Mahouche-Chergui, R. Abderrahim, B. Carbonnier, 2-Aminothiazole-functionalized triazine-modified polystyrene decorated with gold nanoparticles as composite catalyst for the reduction of 4-nitrophenol. *React. Funct. Polym.* 121 (2017)
<https://doi.org/10.1016/j.reactfunctpolym.2017.10.018>
13. Y. Zhu, K.M. Chen, X. Wang, X.H. Guo, Spherical polyelectrolyte brushes as a nanoreactor for synthesis of ultrafine magnetic nanoparticles. *Nanotechnology* 23(26), (2012)
<https://doi.org/10.1088/0957-4484/23/26/265601>
14. G. Nie, G. Li, L. Wang, X. Zhang, Nanocomposites of polymer brush and inorganic nanoparticles: preparation, characterization and application. *Polym Chem-Uk* 7(4), (2016)
<https://doi.org/10.1039/C5PY01333J>
15. Y. Lu, M. Hoffmann, R.S. Yelamanchili, A. Terrenoire, M. Schrunner, M. Drechsler, M.W. Moller, J. Brey, M. Ballauff, Well-Defined Crystalline TiO₂ Nanoparticles Generated and Immobilized on a Colloidal Nanoreactor. *Macromol Chem Phys* 210(5), (2009) <https://doi.org/10.1002/macp.200800608>
16. F. Polzer, E. Holub-Krappe, H. Rossner, A. Erko, H. Kirmse, F. Plamper, A. Schmalz, A.H.E. Muller, M. Ballauff, Structural analysis of colloidal MnO_x composites. *Colloid Polym Sci* 291(3), (2013)
<https://doi.org/10.1007/s00396-012-2725-8>
17. G. Kocak, Use of Block Copolymer Stabilized Polystyrene Microspheres as Templates for Preparation of Hollow Metal Oxide Spheres. *Afyon Kocatepe University Journal of Science and Engineering* 20(3), (2020) <https://doi.org/10.35414/akufemubid.680013>
18. G. Kocak, The Use of Block Copolymer Stabilized Polystyrene Microspheres as a Template in the Preparation of Hollow Nickel Oxide Spheres, The 32nd National Chemistry Congress, 2020, p. 51
19. G. Kocak, Use of Block Copolymer Stabilized Polystyrene Microspheres As Templates For Preparation of Magnetic Hollow NiFe₂O₄ Spheres, in: R. Talwar, P. Agarwal (Eds.) 4th International Mardin Artuklu Scientific Researches Conference, 7–8 August 2020, Farabi, Mardin, 2020, pp. 165–166
20. I.B. Dicker, G.M. Cohen, W.B. Farnham, W.R. Hertler, E.D. Laganis, D.Y. Sogah, Oxyanions catalyze group-transfer polymerization to give living polymers. *Macromolecules* 23(18), (1990)
<https://doi.org/10.1021/ma00220a002>
21. V. Butun, S.P. Armes, N.C. Billingham, Synthesis and aqueous solution properties of near-monodisperse tertiary amine methacrylate homopolymers and diblock copolymers. *Polymer* 42(14), (2001) [https://doi.org/10.1016/s0032-3861\(01\)00066-0](https://doi.org/10.1016/s0032-3861(01)00066-0)
22. V. Bütün, B. Kaynak, E. Esenoğlu, G. Gül, Synthesis and selective quaternization of tertiary amine methacrylate-containing water-soluble copolymers and their use in latex synthesis as stabilizers,

- Polymer Processing and Recycling Symposium and Exhibition (POLYSEM2004), Mersin, 2004
23. V. Suba, G. Rathika, E.R. Kumar, M. Saravanabhavan, Influence of Magnetic Nanoparticles on Surface Changes in CoFe₂O₄/Nerium Oleander Leaf Waste Activated Carbon Nanocomposite for Water Treatment. *J Inorg Organomet P* 28(5), (2018) <https://doi.org/10.1007/s10904-018-0831-x>
 24. D. Narsimulu, O. Padmaraj, E.S. Srinadhu, N. Satyanarayana, Synthesis, characterization and electrical properties of mesoporous nanocrystalline CoFe₂O₄ as a negative electrode material for lithium battery applications. *J Mater Sci-Mater El* 28(22), (2017) <https://doi.org/10.1007/s10854-017-7650-7>
 25. W.C. Li, X.J. Qiao, Q.Y. Zheng, T.L. Zhang, One-step synthesis of MFe₂O₄ (M = Fe, Co) hollow spheres by template-free solvothermal method. *J. Alloy. Compd.* 509(21), (2011) <https://doi.org/10.1016/j.jallcom.2011.02.157>
 26. S. Yoon, Facile microwave synthesis of CoFe₂O₄ spheres and their application as an anode for lithium-ion batteries. *J. Appl. Electrochem.* 44(9), (2014) <https://doi.org/10.1007/s10800-014-0716-9>
 27. H.L. Yan, T. Li, K.W. Qiu, Y. Lu, J.B. Cheng, Y.X. Liu, J.Y. Xu, Y.S. Luo, Growth and electrochemical performance of porous NiMn₂O₄ nanosheets with high specific surface areas. *J Solid State Electr* 19(10), (2015) <https://doi.org/10.1007/s10008-015-2946-0>
 28. X.L. Wang, J.Q. Zhang, S.B. Yang, H.Y. Yan, X.D. Hong, W. Dong, Y. Liu, B.Y. Zhang, Z. Wen, Interlayer space regulating of NiMn layered double hydroxides for supercapacitors by controlling hydrothermal reaction time. *Electrochim. Acta* 295 (2019) <https://doi.org/10.1016/j.electacta.2018.10.021>
 29. A. Bousquet, E. Ibarboure, V. Heroguez, E. Papon, C. Labrugere, J. Rodriguez-Hernandez, Single-Step Process to Produce Functionalized Multiresponsive Polymeric Particles. *J Polym Sci Pol Chem* 48(16), (2010) <https://doi.org/10.1002/pola.24112>
 30. B.M. Reis, S.P. Armes, S. Fujii, S. Biggs, Characterisation of the dispersion stability of a stimulus responsive core-shell colloidal latex. *Colloid Surface A* 353(2–3), (2010) <https://doi.org/10.1016/j.colsurfa.2009.11.015>
 31. J.I. Amalvy, G.F. Unali, Y. Li, S. Granger-Bevan, S.P. Armes, B.P. Binks, J.A. Rodrigues, C.P. Whitby, Synthesis of sterically stabilized polystyrene latex particles using cationic block copolymers and macromonomers and their application as stimulus-responsive particulate emulsifiers for oil-in-water emulsions. *Langmuir* 20(11), (2004) <https://doi.org/10.1021/la035921c>
 32. A. Munoz-Bonilla, A.M. van Herk, J.P.A. Heuts, Adding stimuli-responsive extensions to antifouling hairy particles. *Polym Chem-Uk* 1(5), (2010) <https://doi.org/10.1039/c0py00054j>
 33. T. Itoh, I. Abe, T. Tamamitsu, H. Shimomoto, K. Inoue, E. Ihara, Surface structure of stimuli-responsive polystyrene particles prepared by dispersion polymerization with a polystyrene/poly(L-lysine) block copolymer as a stabilizer. *Polymer* 55(16), (2014) <https://doi.org/10.1016/j.polymer.2014.06.069>
 34. F.L. Baines, S. Dionisio, N.C. Billingham, S.P. Armes, Use of block copolymer stabilizers for the dispersion polymerization of styrene in alcoholic media. *Macromolecules* 29(9), (1996) <https://doi.org/10.1021/ma951767s>

35. A. Tuncel, R. Kahraman, E. Piskin, Monosize Polystyrene Latices Carrying Functional-Groups on Their Surfaces. *J. Appl. Polym. Sci.* 51(8), (1994) <https://doi.org/10.1002/app.1994.070510816>
36. Y. Wang, A.S. Angelatos, F. Caruso, Template synthesis of nanostructured materials via layer-by-layer assembly. *Chem Mater* 20(3), (2008) <https://doi.org/10.1021/cm7024813>
37. B.L. Rivas, E.D. Pereira, I. Moreno-Villoslada, Water-soluble polymer-metal ion interactions. *Prog Polym Sci* 28(2), (2003) [https://doi.org/10.1016/s0079-6700\(02\)00028-x](https://doi.org/10.1016/s0079-6700(02)00028-x)
38. B.L. Rivas, E. Pereira, A. Maureira, Functional water-soluble polymers: polymer-metal ion removal and biocide properties. *Polym Int* 58(10), (2009) <https://doi.org/10.1002/pi.2632>
39. J. Jiang, Y.M. Yang, L.C. Li, Surfactant-assisted synthesis of nanostructured NiFe₂O₄ via a refluxing route. *Mater Lett* 62(12–13), (2008) <https://doi.org/10.1016/j.matlet.2007.10.063>
40. S. Periyasamy, P. Subramanian, E. Levi, D. Aurbach, A. Gedanken, A. Schechter, Exceptionally Active and Stable Spinel Nickel Manganese Oxide Electrocatalysts for Urea Oxidation Reaction. *ACS Appl Mater Inter* 8(19), (2016) <https://doi.org/10.1021/acsami.6b02491>
41. A.K. Srivastava, S. Madhavi, T.J. White, R.V. Ramanujan, Cobalt-ferrite nanobowl arrays: Curved magnetic nanostructures. *J. Mater. Res.* 22(5), (2007) <https://doi.org/10.1557/JMR.2007.0149>
42. S.S. Chu, H. Li, Y.Z. Wang, Q. Ma, H. Li, Q. Zhang, P. Yang, Porous NiO/ZnO flower-like heterostructures consisting of interlaced nanosheet/particle framework for enhanced photodegradation of tetracycline. *Mater Lett* 252 (2019) <https://doi.org/10.1016/j.matlet.2019.05.145>
43. C. Charan, V.K. Shahi, Cobalt ferrite (CoFe₂O₄) nanoparticles (size: similar to 10 nm) with high surface area for selective non-enzymatic detection of uric acid with excellent sensitivity and stability. *Rsc Adv* 6(64), (2016) <https://doi.org/10.1039/c6ra08746a>
44. Y. Wang, Q. Liu, T.J. Hu, L.M. Zhang, Y.Q. Deng, Carbon supported MnO₂-CoFe₂O₄ with enhanced electrocatalytic activity for oxygen reduction and oxygen evolution. *Appl Surf Sci* 403 (2017) <https://doi.org/10.1016/j.apsusc.2017.01.127>
45. P.B. Kharat, S.B. Somvanshi, P.P. Khirade, K.M. Jadhav, Induction Heating Analysis of Surface-Functionalized Nanoscale CoFe₂O₄ for Magnetic Fluid Hyperthermia toward Noninvasive Cancer Treatment. *ACS Omega* 5(36), (2020) <https://doi.org/10.1021/acsomega.0c03332>
46. D. Erdem, N.S. Bingham, F.J. Heiligtag, N. Pilet, P. Warnicke, L.J. Heyderman, M. Niederberger, CoFe₂O₄ and CoFe₂O₄-SiO₂ Nanoparticle Thin Films with Perpendicular Magnetic Anisotropy for Magnetic and Magneto-Optical Applications. *Adv. Funct. Mater.* 26(12), (2016) <https://doi.org/10.1002/adfm.201504538>
47. N. Sapna, V. Budhiraja, S.K. Kumar, Singh, Synergistic effect in structural and supercapacitor performance of well dispersed CoFe₂O₄/Co₃O₄ nano-heterostructures. *Ceram. Int.* 44(12), (2018) <https://doi.org/10.1016/j.ceramint.2018.04.224>
48. E. Casbeer, V.K. Sharma, X.Z. Li, Synthesis and photocatalytic activity of ferrites under visible light: A review. *Sep. Purif. Technol.* 87 (2012) <https://doi.org/10.1016/j.seppur.2011.11.034>

49. A. Umar, M.S. Akhtar, S. Ameen, M. Imran, R. Kumar, Y. Wang, A.A. Ibrahim, H. Albargi, M. Jalalah, M.A. Alsaiari, M.S. Al-Assiri, Colloidal synthesis of NiMn₂O₄ nanodisks decorated reduced graphene oxide for electrochemical applications. *Microchem J* 160 (2021) <https://doi.org/10.1016/j.microc.2020.105630>
50. M. Schubert, C. Munch, S. Schuurman, V. Poulain, J. Kita, R. Moos, Novel Method for NTC Thermistor Production by Aerosol Co-Deposition and Combined Sintering. *Sensors* 19(7), (2019) <https://doi.org/10.3390/s19071632>
51. M.J. Abel, A. Pramothkumar, V. Archana, N. Senthilkumar, K. Jothivenkatachalam, J.J. Prince, Facile synthesis of solar light active spinel nickel manganite (NiMn₂O₄) by co-precipitation route for photocatalytic application. *Res. Chem. Intermed.* 46(7), (2020) <https://doi.org/10.1007/s11164-020-04159-y>
52. Q. Qin, L.L. Chen, T. Wei, Y.M. Wang, X.E. Liu, Ni/NiM₂O₄ (M = Mn or Fe) supported on N-doped carbon nanotubes as trifunctional electrocatalysts for ORR, OER and HER. *Catal. Sci. Technol.* 9(7), (2019) <https://doi.org/10.1039/c8cy02504e>
53. L.J. Li, Q. Yao, J.Q. Liu, K.B. Ye, B.Y. Liu, Z.S. Liu, H.P. Yang, Z.Y. Chen, J.F. Duan, B. Zhang, Porous Hollow Superlattice NiMn₂O₄/NiCo₂O₄ Mesocrystals as a Highly Reversible Anode Material for Lithium-ion Batteries. *Front Chem* 6 (2018) <https://doi.org/10.3389/fchem.2018.00153>
54. Z.B. Wang, Z.H. Zhu, C.L. Zhang, C.Q. Xu, C.N. Chen, Facile synthesis of reduced graphene oxide/NiMn₂O₄ nanorods hybrid materials for high-performance supercapacitors. *Electrochim. Acta* 230 (2017) <https://doi.org/10.1016/j.electacta.2017.02.023>

Figures

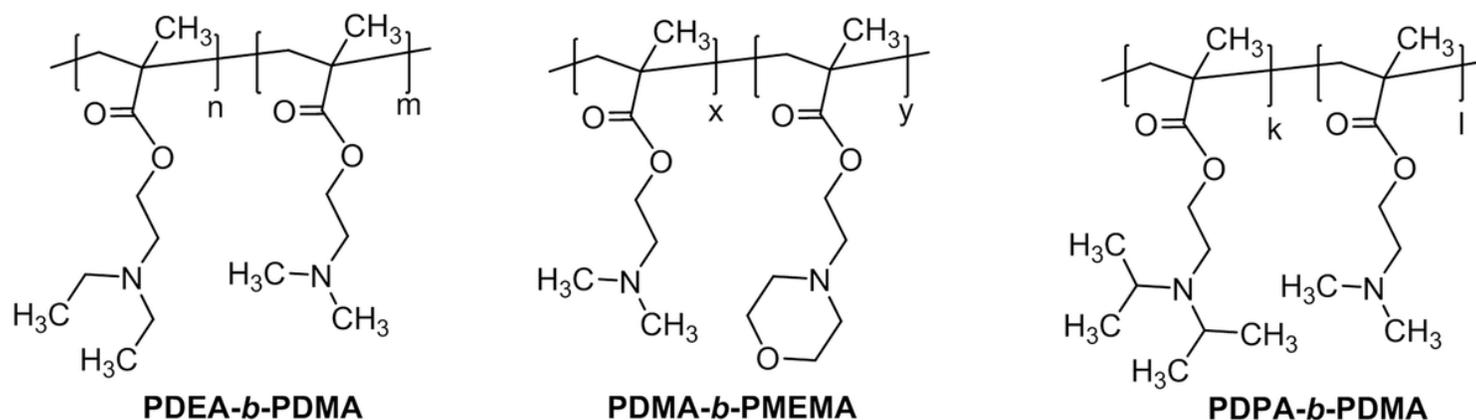


Figure 1

Chemical structures of the diblock copolymer stabilizers

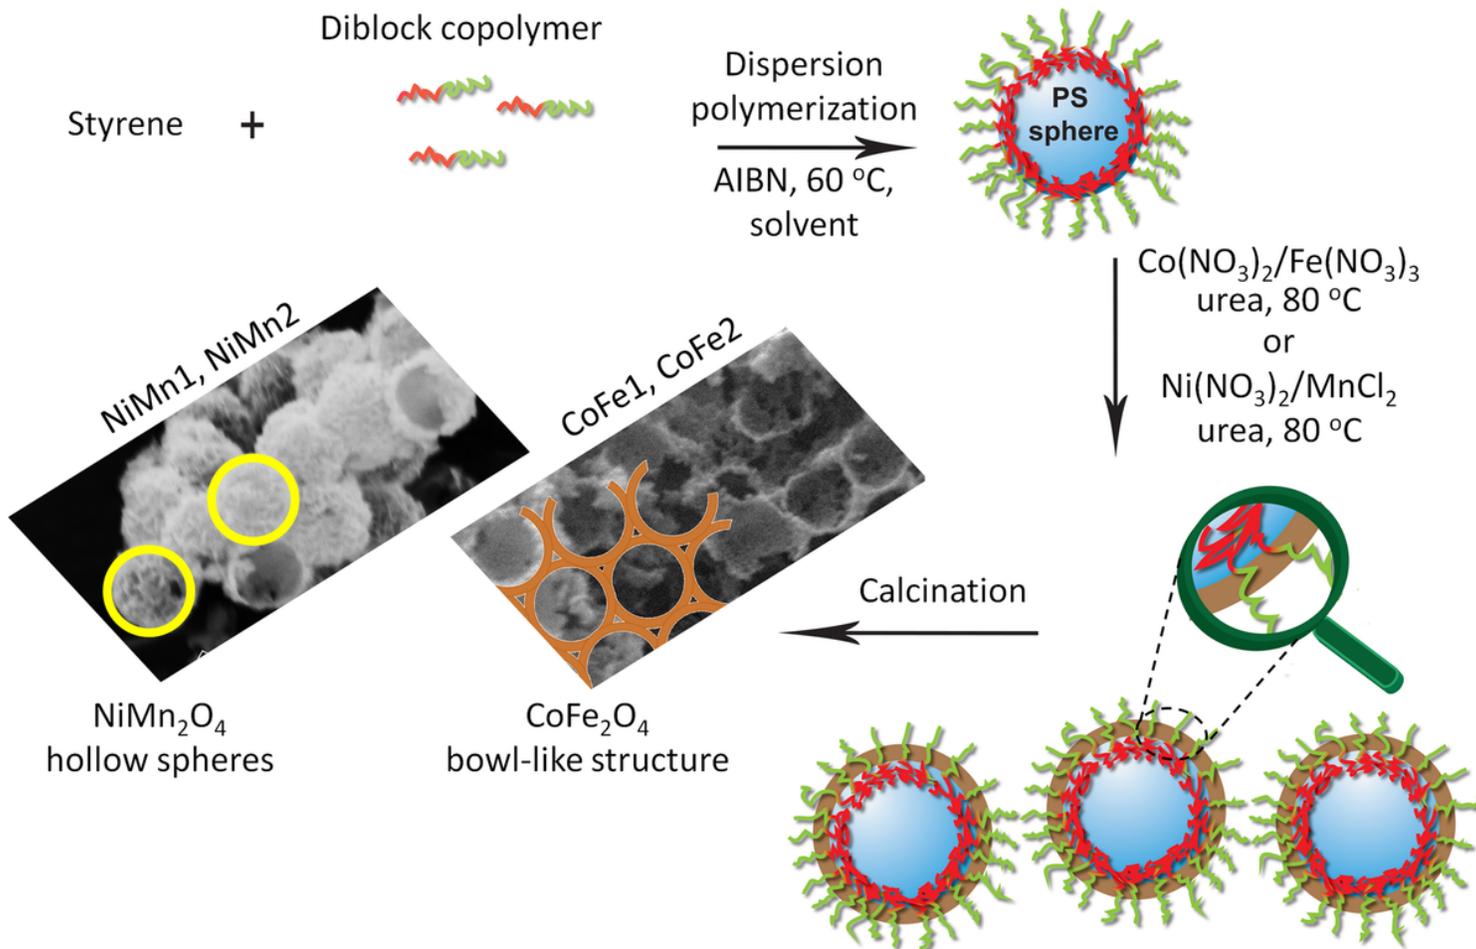


Figure 2

Schematic representation of the production of NiMn_2O_4 hollow spheres and CoFe_2O_4 bowl-like structures using PS spheres stabilized with block copolymer

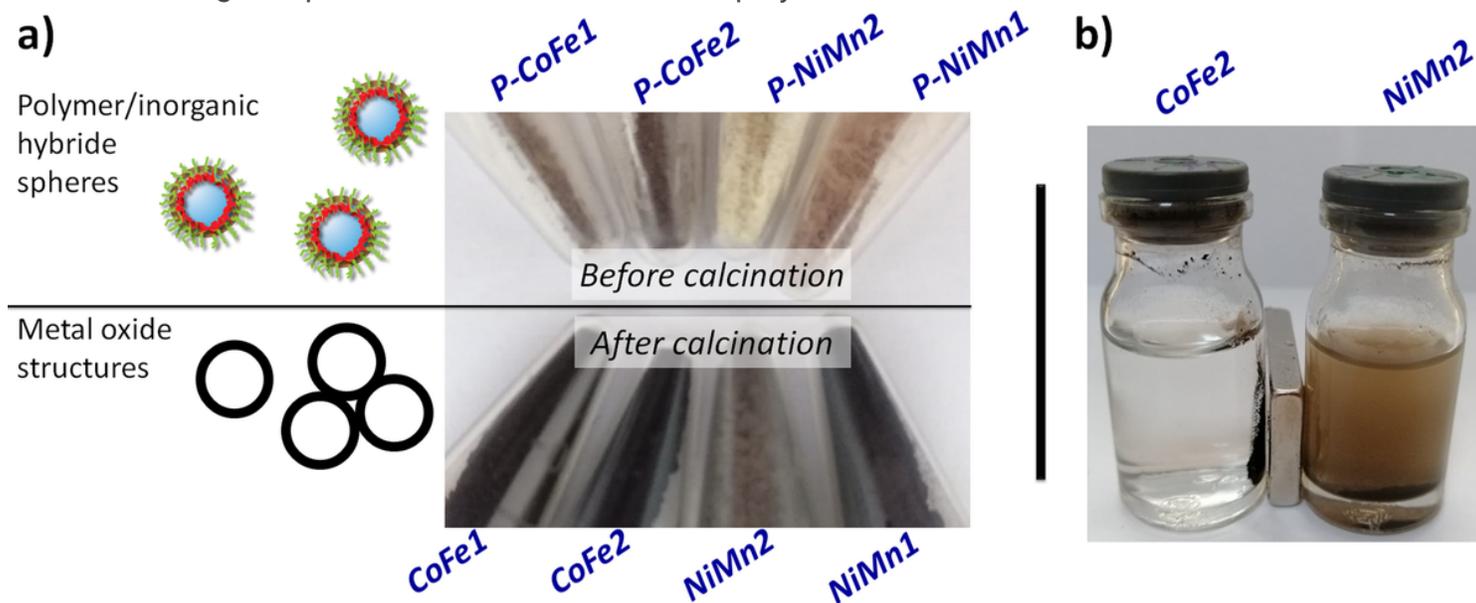


Figure 3

Digital pictures of PS-inorganic hybrid spheres (before calcination) and metal oxide structures (after calcination) (a) and the behavior of metal oxide species in the magnetic field (b)

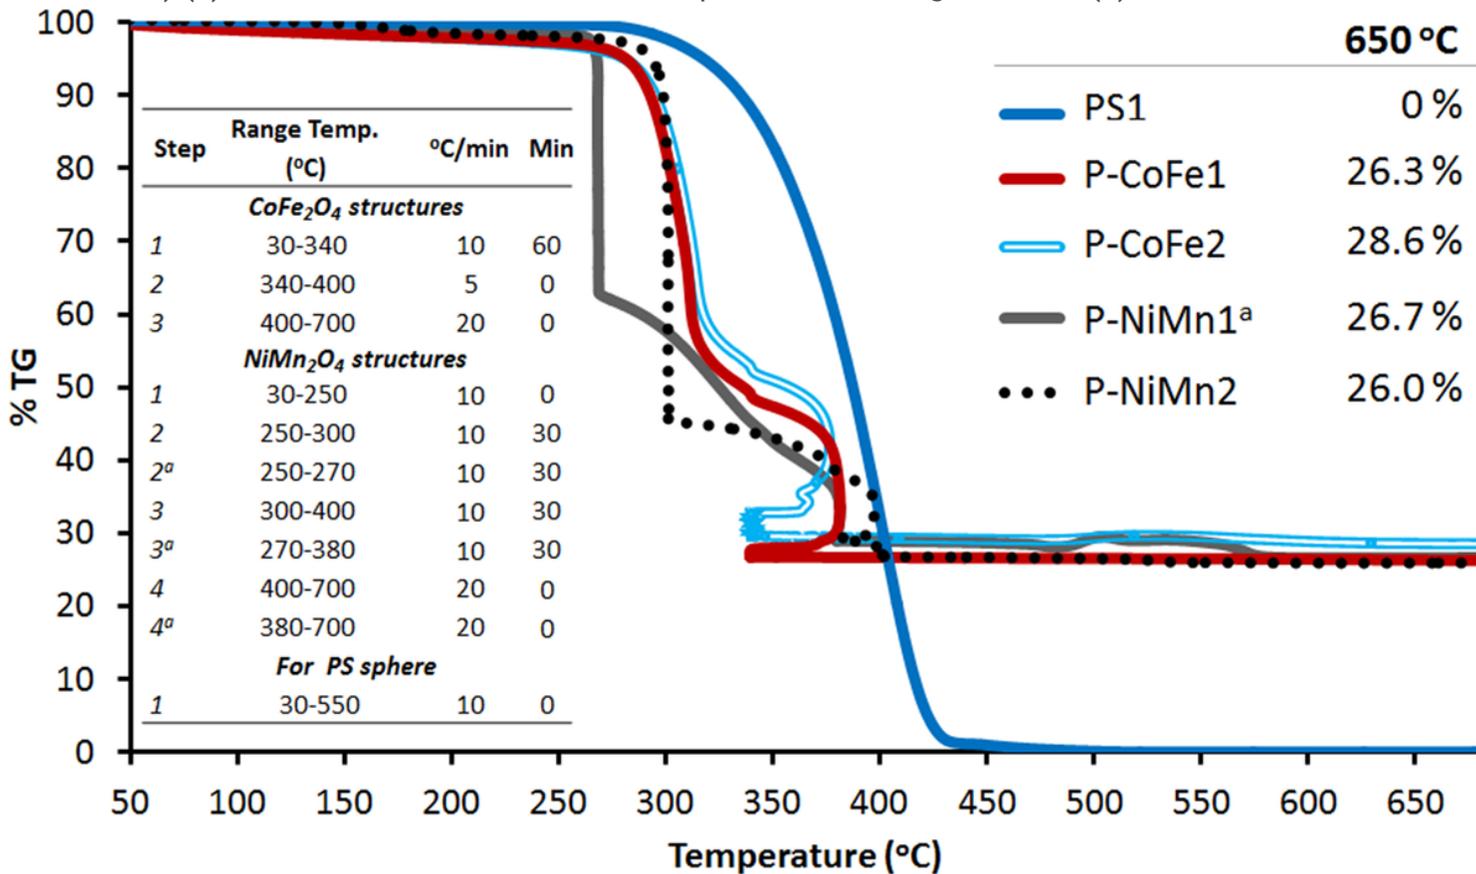


Figure 4

TGA chromatograms of PS sphere (PS1) and metal oxide structures

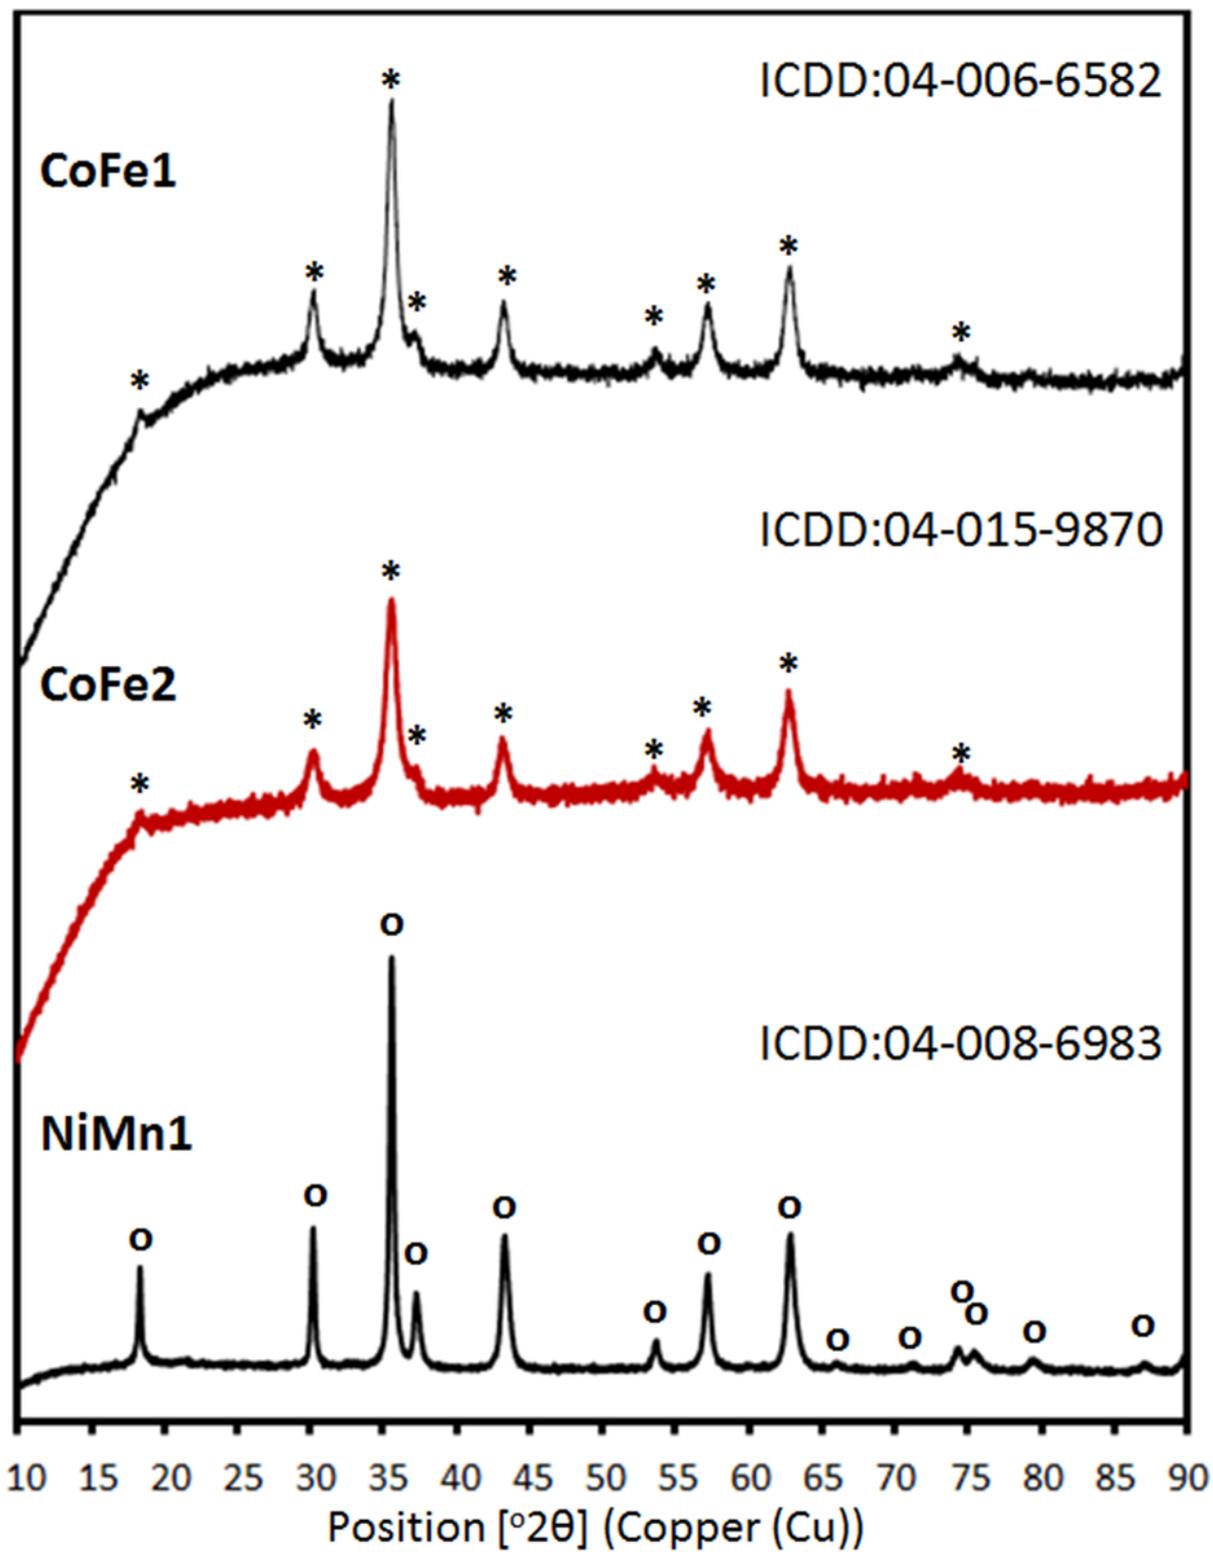


Figure 5

X-ray diffraction pattern of the prepared CoFe₂O₄ ve NiMn₂O₄ structures

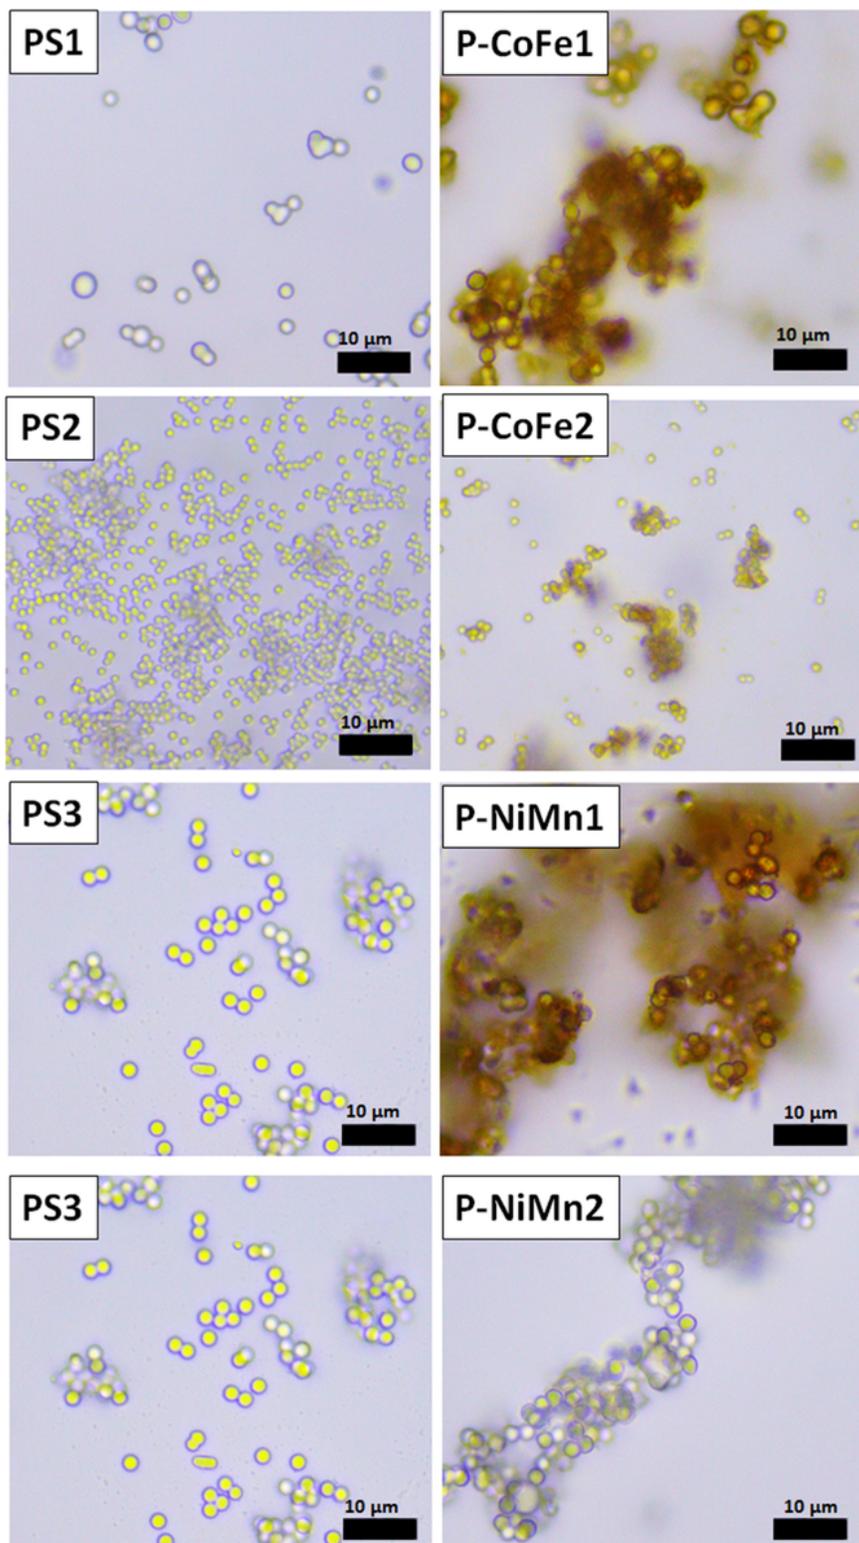


Figure 6

Light microscope images of PS spheres and inorganic-PS hybrid spheres (before calcination)

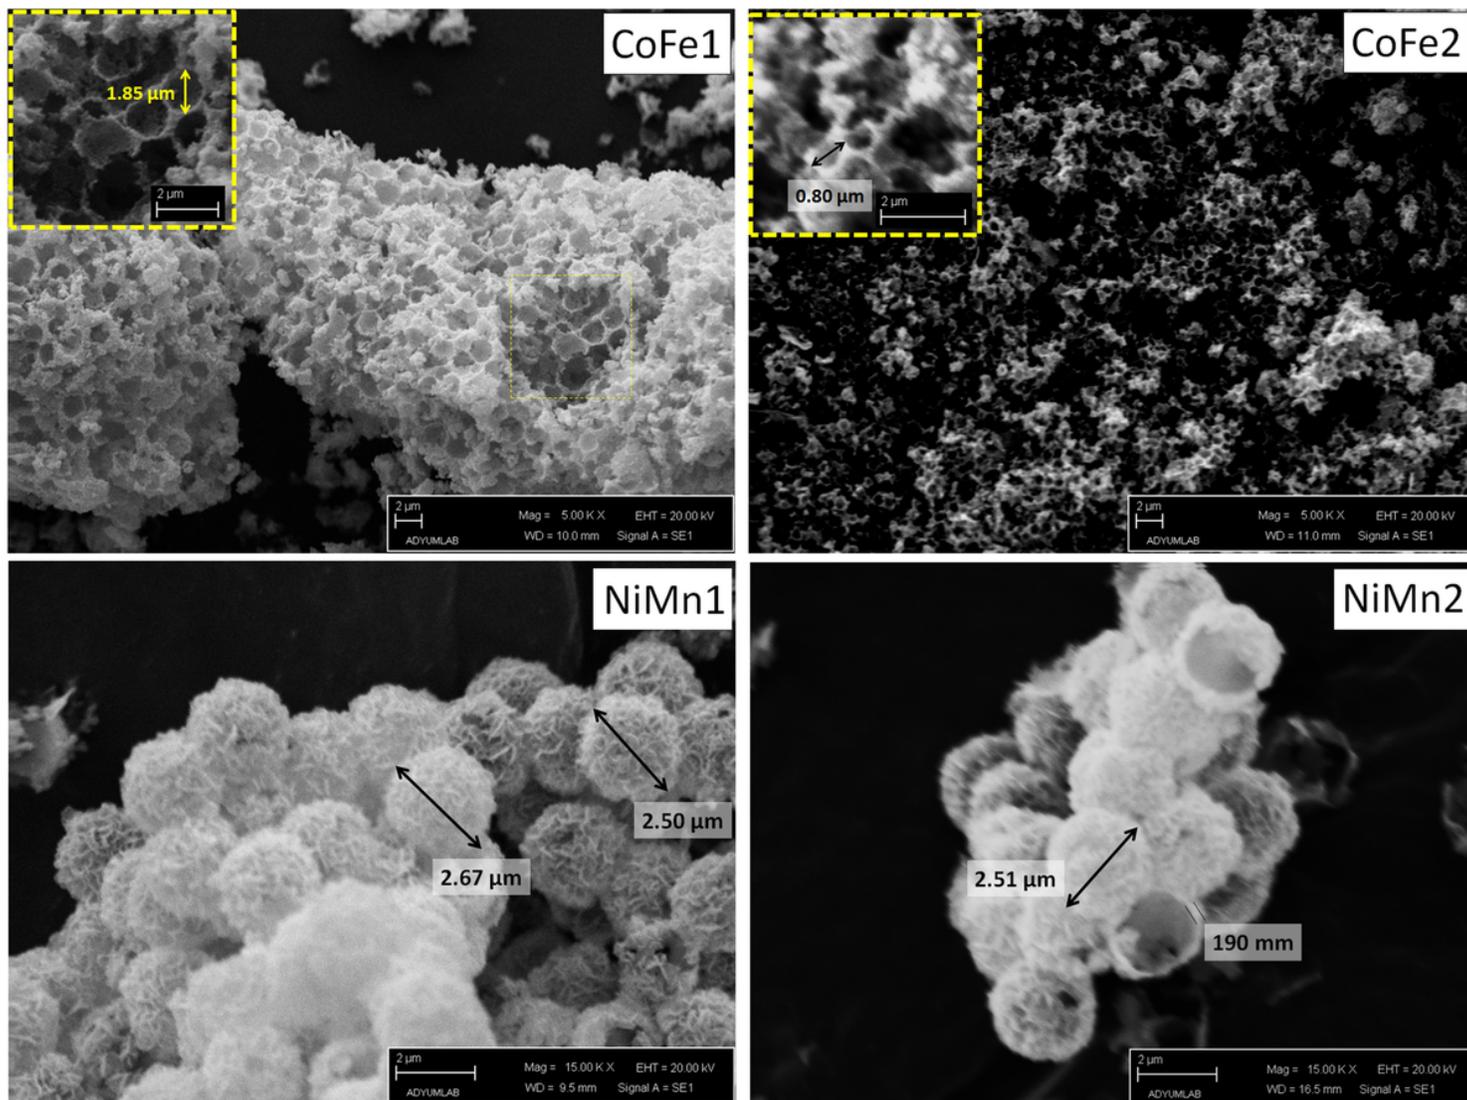


Figure 7

SEM images of CoFe_2O_4 (CoFe1 and CoFe2) and NiMn_2O_4 (NiMn1 and NiMn2) structures produced after calcination

Supplementary Files

This is a list of supplementary files associated with this preprint. Click to download.

- [SupplementaryInformation.docx](#)