

Facilely reducing recalcitrance of lignocellulosic biomass by a newly developed ethylamine based deep eutectic solvent for biobutanol fermentation

Guochao Xu

Jiangnan University

Hao Li

Jiangnan University

Wanru Xing

Jiangnan University

Lei Gong

Jiangnan University

Jinjun Dong

Jiangnan University

Ye Ni (✉ yni@jiangnan.edu.cn)

Jiangnan University <https://orcid.org/0000-0003-4887-7517>

Research

Keywords: Deep eutectic solvent, Lignocellulosic biomass, Ethylamine, Pretreatment, Biobutanol

Posted Date: September 18th, 2020

DOI: <https://doi.org/10.21203/rs.3.rs-46954/v2>

License:  This work is licensed under a Creative Commons Attribution 4.0 International License. [Read Full License](#)

Version of Record: A version of this preprint was published on October 9th, 2020. See the published version at <https://doi.org/10.1186/s13068-020-01806-9>.

Abstract

Background: Biobutanol is promising and renewable alternative to traditional fossil fuels and could be produced by *Clostridium* species from lignocellulosic biomass. However, biomass is recalcitrant to be hydrolyzed into fermentable sugars attributed to the densely packed structure by layers of lignin. Development of pretreatment reagents and processes for increasing surface area, removing hemicellulose and lignin, and enhancing the relative content of cellulose is currently an area of great interest. Deep eutectic solvents (DESs), a new class of green solvents, are effective in the pretreatment of lignocellulosic biomass. However, it remains challenging to achieve high titers of total sugars and usually requires combinatorial pretreatment with other reagents. In this study, we aim to develop novel DESs with high application potential in biomass pretreatment and high biocompatibility for biobutanol fermentation.

Results: Several DESs with betaine chloride and ethylamine chloride (EaCl) as hydrogen bond acceptors were synthesized. Among them, EaCl:LAC with lactic acid as hydrogen bond donor displayed the best performance in the pretreatment of corncob. Only by single pretreatment with EaCl:LAC, total sugars of as high as $53.5 \text{ g}\cdot\text{L}^{-1}$ could be reached. Consecutive batches for pretreatment of corncob were performed using gradually decreased cellulase by $5 \text{ FPU}\cdot\text{g}^{-1}$. At the end of the sixth batch, the concentration and specific yield of total sugars were $58.8 \text{ g}\cdot\text{L}^{-1}$ and $706 \text{ g}\cdot\text{kg}^{-1}$ pretreated corncob, saving a total of 50% cellulase. Utilizing hydrolysate as carbon source, butanol titer of $10.4 \text{ g}\cdot\text{L}^{-1}$ was achieved with butanol yield of $137 \text{ g}\cdot\text{kg}^{-1}$ pretreated corncob by *Clostridium saccharobutylicum* DSM13864.

Conclusions: Ethylamine and lactic acid based deep eutectic solvent is promising in pretreatment of corncob with high total sugar concentrations and compatible for biobutanol fermentation. This study provides an efficient pretreatment reagent for facilely reducing recalcitrance of lignocellulosic materials and a promising process for biobutanol fermentation from renewable biomass.

Background

Biofuels are promising, renewable and natural alternatives to traditional fossil fuels and have gained great interests [1]. Among them, biobutanol possesses great potential due to its high hydrophobicity, high energy density, low corrosiveness and more compatibility in mixing with gasoline [2,3]. Moreover, biobutanol could be produced by *Clostridium* species from lignocellulosic biomass including agricultural waters, forestry residues, grasses and woody materials, which are abundant and renewable resources on the earth. Generally, there are about 10–25% lignin, 20–30% hemicellulose, and 40–50% cellulose in most agricultural lignocellulosic biomass, which can be converted into fermentable sugars, value added fine chemicals and materials etc [4]. Nevertheless, most of agricultural lignocellulosic resources have been improperly disposed by open field burning. This common practice has led to the emission of pollutants such as CO_2 , CO, NO_x , SO_2 and dioxins etc [5–7], resulting in air pollution and threatening public health [8,9]. According to statistics, more than 800 million tons of agricultural lignocellulosic biomass has been produced annually in China since 2008, and only about half of the biomass was utilized as fertilizer or feed. Among them, corncob is one of the most important lignocellulosic materials with relatively higher contents of cellulose and hemicellulose and lower lignin amount, especially suitable for biofuels production [10,11].

Although lignocellulosic biomass displays great potential in producing renewable energy, it is recalcitrant to be hydrolyzed into fermentable sugars attributed to the densely packed structure by layers of lignin [12,13]. Pretreatment of biomass, aiming at increasing surface area, removing hemicellulose and lignin, and enhancing the relative content of cellulose, is required to enhance its accessibility to cellulases for conversion into fermentable sugars. An ideal pretreatment method should be efficient in removal of lignin and hemicellulose, cost-effective and energy-efficient, and highly biocompatible [4,14]. There are various pretreatment methods, including alkali, acids, ionic liquids, organic solvents, thermal and pressure etc [15,16]. Among them, acidic pretreatment methods have been intensively studied, possessing significant advantages of low-cost and high efficiency in destruction of biomass recalcitrance [17]. However, acids are corrosive to equipment and toxic to cellulases and microorganisms. Ionic liquids (ILs), generally consisted of hydrogen bond donor (HBD) and hydrogen bond acceptor (HBA), are promising reagents and have gained tremendous attention due to their low melting temperature, tunable combinations of various cation and anion, easy preparation, low vapour pressure, recyclability and biocompatibility [18]. Various ILs have been developed and applied in biomass pretreatment, such as [Bmim][Cl], [Bmin][H_2SO_4] or [Emim][Cl] [19–21]. However, traditional ILs are expensive and less effective in reducing the recalcitrance, usually requiring other combinatorial methods such as alkaline. Deep eutectic solvents (DESs) are also made up of HBD and HBA, and emerging as a new class of ILs with similar physical and chemical properties. Most importantly, DESs are advantageous due to their easy preparation, high stability, good biodegradability and biocompatibility [22–24]. Choline chloride (ChCl), a bulk chemical, based deep eutectic solvents was firstly synthesized by Abbott at 2004 [25]. Since then, various ChCl based DESs have been developed and attempted in the pretreatment of various lignocellulosic biomass such as corn stover, corncob, rice straw and bamboo shell etc with high efficiency in removing lignin [3, 26–29]. Endeavour has been committed in optimizing the HBDs including organic or inorganic acids, amino acids, alcohols and sugars. In fact, ChCl based DESs display similar or even higher efficiency in reducing the recalcitrance of lignocellulosic biomass than traditional ILs such as [BMIM][Cl], attributing to the similar mechanism of providing or receiving H-bond or

localizing charges on the chemical bonds of biomass through electrostatic forces of the ionic pairs [30]. However, high titers ($>50\text{-gL}^{-1}$) of fermentable sugars are hard to be achieved by single pretreatment with ChCl based DESs. Generally, condensation under vacuum or combinatorial pretreatment methods such as NaOH, Na_2CO_3 or microwave radiation should be introduced, inevitably complicating the process and resulting in low solid yield and high consumption of water for removing residual alkaline. As a result, the utilization of lignocellulosic biomass with high yields and titers of total sugars remains challenging [31]. Development of novel DESs with enhanced properties in pretreating biomass is of significant interest for biofuels production from abundant and renewable biomass.

In principle, ammonium, phosphonium, or sulfonium cation in halide form could be used as HBAs, while amides, carboxylic and alcohols could be used as HBDs [32]. Development of novel DESs can be achieved by rational complexation of HBDs and HBAs to form eutectic liquids. However, the procedures are empirical and labor-intensive, and most combinations are unsuccessful in forming homogeneous and clear liquids. Density functional theory (DFT) calculations play an important role in elucidating the mechanism of chemical or enzymatic reactions and also predicting the reactivity [33,34]. Here, DFT calculation was adopted to evaluate the feasibility in synthesis of novel DESs. Cheap and bulk chemicals including ChCl, betaine chloride (BaCl) and ethylamine chloride (EaCl) were investigated as HBAs (**Scheme 1**) for developing efficient DESs. Newly synthesized DESs were evaluated for removing of lignin and hemicellulose, as well as their effects on increasing cellulose accessibility of biomass. Corn cob hydrolysates were also examined in biobutanol fermentation by *Clostridium saccharobutylicum* DSM13864.

Scheme 1 Structures of ethylamine chloride, choline chloride and betaine chloride used as hydrogen bond acceptors. Atoms are carbon (gray), nitrogen (blue), oxygen (red), and hydrogen (white). Cl^- ion is not shown.

Results And Discussion

Synthesis of DESs

Betaine chloride (BaCl) and ethylamine chloride (EaCl) possess similar structure as ChCl, they were explored as HBA in the synthesis of DESs. As shown in Scheme 1, EaCl is smaller than ChCl, while BaCl is similar to ChCl. All of them contain quaternary nitrogen cation, which is favourable to DES formation. There is a free hydroxy group in ChCl, a carboxyl group in BaCl and a free aliphatic terminal in EaCl. Lactic acid (LAC), ethyl glycol (EG), glycerol (GLY) and urea (UR), which have been commonly used and proved to be effective in forming DESs with ChCl, were introduced as HBDs. Generally, DESs were empirically synthesized by combination of various kinds and ratios of HBD and HBA. However, most of the combinations were hard to be synthesized. Considering these unpredictable combination patterns, both experimental synthesis employing methods for ChCl based DESs and DFT calculations with different functions were performed to explore the feasibility of rational design of DESs.

For ChCl and EaCl based DESs, all of the four combinations, ChCl:LAC, ChCl:EG, ChCl:GLY and ChCl:UR, EaCl:LAC, EaCl:EG, EaCl:GLY and EaCl:UR respectively, were successfully obtained. However, with regard to BaCl as HBA, only BaCl:EG and BaCl:GLY could be facilely synthesized in clear and homogenous liquid. It should be mentioned that further optimization of reaction conditions such as ratios of HBD to HBA and temperature might also produce BaCl:LAC and BaCl:UR. Furthermore, ΔG_{rxn} of the reaction ($\Delta G_{\text{rxn}} = G_{\text{DES}} - G_{\text{HBA}} - n \times G_{\text{HBD}}$) was calculated employing three mostly common used DFT including B3LYP, M062X and ω B97X and basis set of 6-311+G**. Negative values of ΔG_{rxn} can be used to indicate the thermodynamically feasibility. Previously, B3LYP and M062X have been used in the simulation of ChCl based DESs [35–38]. In **Table 1**, ΔG_{rxn} values of easily obtained DESs were lower than 0, according to the ΔG_{rxn} results of B3LYP ($\Delta G_{\text{B3LYP rxn}}$). Especially, the $\Delta G_{\text{B3LYP rxn}}$ values of ChCl:LAC and EaCl:LAC were the lowest. With regard to BaCl:LAC and BaCl:UR, the $\Delta G_{\text{B3LYP rxn}}$ values were 3.59 and 1.03 $\text{kcal}\cdot\text{mol}^{-1}$ respectively. For the results using M062X, there is no definite patterns. For example, the $\Delta G_{\text{M062X rxn}}$ value of BaCl:UR was $-10.8 \text{ kcal}\cdot\text{mol}^{-1}$, ranking the lowest, whereas, $\Delta G_{\text{B3LYP rxn}}$ of BaCl:UR was the highest. All the $\Delta G_{\omega\text{B97XD rxn}}$ values were negative, which were hard to be correlated with the reactivity. As a result, calculation method of B3LYP/6-311+G** is more favorable in predicting the potential of DES synthesis, and might be used to elucidate the reactivity and mechanism of DES mediated systems in pretreatment of lignocellulosic biomass.

Table 1 Deep eutectic solvents synthesized in this study.

DES	Ratio of HBA to HBD	$\Delta G_{\text{B3LYP rxn}}$ [kcal·mol ⁻¹]	$\Delta G_{\text{M062X rxn}}$ [kcal·mol ⁻¹]	$\Delta G_{\omega\text{B97XD rxn}}$ [kcal·mol ⁻¹]
ChCl:UR	1:2	-2.54	-6.39	-6.50
ChCl:EG	1:2	-2.84	-7.15	-6.55
ChCl:GLY	1:2	-2.27	-2.86	-2.58
ChCl:LAC	1:1	-8.96	-10.3	-9.95
BaCl:UR	1:2	3.59	-10.8	-0.54
BaCl:EG	1:2	-1.42	-11.2	-7.15
BaCl:GLY	1:2	-1.21	-9.88	-1.73
BaCl:LAC	1:1	1.03	-4.92	-3.23
EaCl:UR	1:2	-2.25	-4.55	-3.80
EaCl:EG	1:2	-1.62	-4.21	-1.73
EaCl:GLY	1:2	-2.38	-4.19	-3.31
EaCl:LAC	1:1	-4.67	-7.94	-8.23

Note: ChCl: choline chloride, BaCl: betaine chloride, EaCl: ethylamine chloride, UR: urea, EG: ethylene glycol, GLY: glycine, LAC: lactic acid.

The optimized geometries of EaCl:LAC, ChCl:LAC and BaCl:LAC were obtained from DFT calculations. Distance and interactions among HBD and HBA were also analyzed. Three potential hydrogen bonds could be formed between EaCl and LAC, which are favorable for the formation of EaCl:LAC (**Fig. 1A**). In addition, due to the small size of EaCl, the strong electrostatic interaction between nitrogen cation of ethylamine and carboxy group of lactic acid could also contribute to the stabilization of EaCl:LAC. In ChCl:LAC, two hydrogen bonds could be formed between ChCl and LAC (**Fig. 1B**). However, the distance from nitrogen cation and carboxyl group is too large to form stable interaction. With regard to BaCl:LAC, few interactions were found between BaCl and LAC (**Fig. 1C**), which might account for the high ΔG_{rxn} value and also the difficulties in preparation of BaCl:LAC. It is well known that electrostatic forces of the ions in ILs or DESs could provide or receive H-bond or localize charges on the chemical bonds of the matrix of lignocellulosic biomass. As a result, EaCl:LAC is presumably to display high efficacy in pretreatment of lignocellulosic biomass.

Evaluation of EaCl:LAC in the pretreatment of lignocellulosic biomass

The effect of newly synthesized DESs in pretreatment was investigated with rice straw. ChCl:LAC was regarded as a positive control since it had been applied in pretreatment of rice straw and lignin extraction [39,40]. Total sugars including glucose, xylose and arabinose were determined. As illustrated in **Fig. 2A**, EaCl:LAC exhibited the highest efficacy, with total sugars concentration of 32.1 g·L⁻¹. The concentration of total sugars obtained from ChCl:LAC is 17.4 g·L⁻¹, ranking the second. The good performance of EaCl:LAC and ChCl:LAC proves the effectiveness of DESs with lactic acid as HBD. About 17.2 g·L⁻¹ total sugars were achieved for rice straw pretreated by BaCl:GLY, which was similar to that of ChCl:LAC. To further prove the effectiveness of EaCl:LAC, EaCl and LAC were separately applied in the pretreatment of RS. The total sugars concentrations of EaCl and LAC were 9.32 and 13.0 g·L⁻¹, accounting for 29.0% and 40.6% of that of EaCl:LAC respectively, indicating the synergistic effect EaCl and LAC. Moreover, the remarkable performance of EaCl:LAC in pretreatment of biomass is in consistence with its structural property.

To further explore the potential of this newly synthesized EaCl:LAC, pretreatment of various lignocellulosic biomass including rice husk, pod, wheat straw, corncob and bagasse were performed. As illustrated in **Fig. 2B**, EaCl:LAC was effective in the pretreatment of various lignocellulosic biomass except for rice husk. The highest sugar concentration of 53.5 g·L⁻¹ was obtained with corncob, including 48.5 g·L⁻¹ glucose, 2.48 g·L⁻¹ xylose and 2.60 g·L⁻¹ arabinose. The sugar concentration of corncob was 38.1%-489% higher than 38.8 g·L⁻¹ of bagasse, 34.8 g·L⁻¹ of rice straw, 29.2 g·L⁻¹ of wheat straw, 22.3 g·L⁻¹ of pod and 9.0 g·L⁻¹ of rice husk respectively. Furthermore, the total sugars concentration of corncob pretreated by EaCl:LAC was even higher than those of corn stover and RS which were combinatorial pretreated by [Bmim][Cl] and NaOH or ChCl:FA:AA and Na₂CO₃ [3,41]. This newly synthesized ethylamine based DES, EaCl:LAC, is promising in reducing the recalcitrance of various lignocellulosic biomass.

To further evaluate the effects of EaCl:LAC in reducing the recalcitrance of biomass, component analysis was conducted. Contents of cellulose, hemicellulose and lignin were determined and shown in **Table 2**. For raw biomass, the cellulose content of corncob was 30.0%, which was higher than that of pod (21.8%) whereas much lower than 38.1% of wheat straw, 35.0% of rice husk, 32.0% bagasse and 31.7% of rice straw. Remarkably, the cellulose content of corncob was increased to 70% after pretreatment with EaCl:LAC. In fact, cellulose contents of all other tested biomass were increased to some extent (11–34%), indicating the effectiveness of EaCl:LAC in reducing recalcitrance of biomass. The cellulose yield of corncob was as high as 98.0%, much higher than other biomass. The hemicellulose contents of corncob, rice straw, pod, wheat straw, bagasse and rice husk were 14.6%, 10.0%, 10.9%, 8.4%, 11.6% and 6.7% respectively. After EaCl:LAC pretreatment, the hemicellulose removal of 87.9%, 81.1%, 75.3%, 69.9%, 83.1% and 62.7% were achieved for corncob, rice straw, pod, wheat straw, bagasse and rice husk. With regard to lignin including acid-soluble and acid-insoluble, their content in corncob was 26.5%,

while in rice straw, pod, wheat straw and rice husk were higher than 30%. The lignin removal of corncob and wheat straw was 71.5% and 67.0% respectively, much higher than 61.3%, 42.7%, 57.2% and 62.7% of rice straw, pod, bagasse and rice husk. The solid recovery rate of all the tested biomass fell into a range of 40–58%. It should be noted that other components including pigments, proteins and fatty acids etc accounted for 9.7–44.5% of raw biomass (**Table 2**). Most of them could also be efficiently removed by EaCl:LAC pretreatment (**Table 2**). The results suggest that EaCl:LAC could effectively reduce the stubborn resistance of lignocellulose and lignin in corncob and enhance the cellulose accessibility to cellulase. The excellent performance of EaCl:LAC in lignin removal is consistent with the high potential of DES in the extraction of lignin and metals [32]. In comparison with other DESs in the pretreatment of corncob, EaCl:LAC displayed higher efficiency in removing both hemicellulose and lignin, which is usually difficult to be achieved by choline chloride or betaine based DESs (Additional file 1) [42]. Generally, combinatorial pretreatment method using alkaline or oxidant should be introduced to achieve higher glucose yield. As a result, the newly developed EaCl:LAC is an efficient pretreatment reagent for lignocellulosic biomass.

Table 2 Component analysis of various lignocellulosic biomass before and after treatment with EaCl:LAC.

Component (%)	Corncorb		Rice straw		Pod		Wheat straw		Bagasse		Rice husk	
	Raw	Treated	Raw	Treated	Raw	Treated	Raw	Treated	Raw	Treated	Raw	Treated
Cellulose	30.0±0.8	70.0±3.1	31.7±2.2	51.0±2.4	21.8±0.1	42.0±0.4	38.1±0.8	63.8±1.4	32.0±1.1	66.0±2.7	35.0±1.7	44.0±1.7
Cellulose yield	–	98.0	–	70.7	–	92.4	–	92.3	–	82.5	–	72.9
Hemicellulose	14.6±0.1	4.2±0.2	10.0±1.2	4.3±0.4	10.9±0.7	5.6±0.7	8.4±0.8	4.6±0.3	11.6±1.4	4.9±0.2	6.7±1.1	4.3±0.4
HC removal ^a	–	87.9	–	81.1	–	75.3	–	69.9	–	83.1	–	62.7
AS lignin ^b	2.3±0.1	0.9±0.1	1.5±0.2	0.7±0.0	1.5±0.2	0.7±0.1	0.9±0.1	0.7±0.0	1.5±0.0	0.9±0.0	0.8±0.1	0.5±0.0
AIS lignin ^c	24.2±1.4	17.1±1.9	31.4±1.2	28.2±0.2	31.1±0.5	38.2±0.5	37.1±1.0	21.9±1.0	9.8±0.6	11.2±1.4	36.1±1.3	29.6±1.2
Lignin removal	–	71.5	–	61.3	–	42.7	–	67.0	–	57.2	–	52.7
Solid yield	–	42.0	–	44.0	–	48.0	–	55.0	–	40.0	–	58.0
Ash	0.4±0.0	0.7±0.0	6.6±0.0	11.7±0.0	0.5±0.1	0.4±0.1	1.0±0.0	1.9±0.0	0.6±0.0	1.2±0.0	11.7±0.2	17.0±1.0
Others	28.9±2.3	7.1±0.7	18.8±3.6	4.1±0.3	34.2±1.1	13.1±0.7	14.5±1.4	7.1±2.0	44.5±3.0	18.8±1.9	9.7±1.0	4.6±1.7

Note: ^a HC removal: hemicellulose removal; ^b AS Lignin: acid-soluble lignin; ^c AIS lignin: acid-insoluble lignin.

Physical characterization of corncob pretreated by EaCl:LAC

In corncob, lignin and hemicellulose form a tight network structure wrapping around the outer layer of cellulose, which seriously hinders the accessibility of cellulose by cellulase [13]. SEM analysis was implemented to monitor the surface structure of untreated and pretreated corncobs (Additional file 2). In untreated corncob, a smooth and compact surface with strong rigid structure was observed. However, an entirely different landscape was detected in the pretreated corncob. The surface of pretreated corncob became loose and rough with obvious fracture delamination, revealing destroyed lignin and hemicellulose around cellulose, which was favorable for improved cellulose accessibility in corncob. Moreover, the observed changes in corncob surface are consistent with the high lignin and hemicellulose removal after EaCl:LAC pretreatment.

Furthermore, XRD assay was conducted to explore changes of the crystallinity index (Crl) of untreated and pretreated corncobs. According to the overlapped XRD spectrum (Additional file 3), no new peak appeared in the pretreated corncob, indicating no structural change after pretreatment. The diffraction peaks at 16° and 21° represent the typical crystalline structures of cellulose I, and could be used to calculate Crl [11]. The Crl value could be regarded as an indicator for the exposure and accessibility of cellulose. Above two characteristic absorption peaks of pretreated corncob were much higher than those of raw corncob, largely due to the increased cellulose content after removal of lignin and hemicellulose. The Crl values of raw and pretreated corncob were 31.0% and 42.8%, respectively. The increased Crl value of pretreated corncob agrees with the increased cellulose content (**Table 2**), and indicates the successful removal of certain stubborn components wrapped around the cellulose. It is favorable for increasing the accessibility of cellulase to cellulose in lignocellulosic biomass [43].

FTIR spectrum of untreated and pretreated corncobs was obtained (Additional file 4). The absorption peaks at 830 and 1166 cm⁻¹ refers to the vibration of C-C bond in lignin, indicating the lignin in corncob is SGH lignin (Syringyl-guaiacyl-*p*-hydroxyphenyl) [44]. In comparison with untreated corncob, the characteristic absorption peaks of lignin in pretreated corncob were significantly reduced, revealing that a large amount of lignin was removed. The absorption peak at 1638 cm⁻¹ is attributed to the stretching vibration of γ -lactone, and the decrease value means that the lignin was largely removed after pretreatment [28,45]. The increased absorption peak at 895 cm⁻¹, relating to β -glycosidic bond in cellulose, indicates the removal of hemicellulose and exposure of more cellulose. Furthermore, the absorption peak at 1383 cm⁻¹ is caused by the stretching vibration of C-H bond in cellulose, and the increased value shows that the amorphous cellulose was removed after EaCl:LAC pretreatment. The absorption peak at 1736 cm⁻¹ represents the vibration of carboxyl group in hemicellulose, and the decreased adsorption peak of pretreated corncob reveals the removal of hemicellulose in comparison with raw corncob [44]. In

summary, the FTIR result agrees with the composition analysis. After pretreatment with EaCl:LAC, a large amount of lignin and hemicellulose in corncob were removed, and the relative content of cellulose was significantly increased to 70.0%, resulting in enhanced cellulose accessibility.

Development of fed-batch pretreatment process

To establish an efficient and economic corncob pretreatment process, various factors were optimized. Firstly, conditions including temperature, incubation time and solid-liquid ratios were systematically investigated, and the resultant corncobs pretreated by EaCl:LAC were subjected to enzymatic hydrolysis for determination of total sugars (Additional file 5). At 90°C and 110°C, elongated pretreatment time from 0.5 h to 3.0 h resulted in higher total sugars. However, when the temperature increased to 130°C and 150°C, different profiles were observed. At over 130°C, longer incubation time led to decreased total sugars, which might be attributed to the destruction of cellulose structure. As a result, either high temperature for short time or low temperature for long time is beneficial to the performance of EaCl:LAC. Under the optimum pretreatment conditions of 150°C for 0.5 h and solid-liquid ratio of 1:15, the highest total sugars concentration of about 55.6 g·L⁻¹ were obtained from the pretreated corncob (Additional file 5).

Furthermore, factors including cellulase dosage, hydrolysis time, solid to liquid ratio and supplementation of Tween80, which might influence the enzymatic hydrolysis process, were investigated. Different amounts of cellulase, ranging from 10 to 70 FPU·g⁻¹ pretreated corncob, were loaded, and the released total sugars were monitored as illustrated in **Fig. 3A**. Along with the increase of hydrolysis time, the total sugars elevated rapidly during the initial 24 h, and then slowly increased until 72 h. Although longer hydrolysis time could lead to higher concentrations of total sugars, it also results in compromised space-time yield. At 50 FPU·g⁻¹ cellulase, total sugars of 57.0 g·L⁻¹ was obtained at 24 h, merely 4.5 g·L⁻¹ lower than that of 70 FPU·g⁻¹ cellulase. Considering the relative lower loading of cellulase and higher efficiency, hydrolysis with 50 FPU·g⁻¹ cellulase for 24 h was selected as the suitable condition. Influence of solid to liquid ratios at 1:8, 1:10, 1:12 and 1:15 on releasing of total sugars were also investigated at 50 FPU·g⁻¹ cellulase (**Fig. 3B**). Increased liquid ratios represent lower addition of biomass. Along with the increase of solid to liquid ratios, the total sugars decreased from 64 g·L⁻¹ to 44 g·L⁻¹ after 24 h of hydrolysis. The total sugar yield per pretreated corncob increased from 513 g·kg⁻¹ to 661 g·kg⁻¹. Although enhanced total sugar yield could be achieved at a relatively high liquid ratio at the expense of cellulase, however, lower titer of total sugars could be resulted, which is disadvantageous for biobutanol fermentation since extra energy-consuming concentration step is required to increase the sugar concentration. In the view of better mass transferring and relatively higher total sugars, solid to liquid ratio of 1:12 is considered as optimum, at which the total sugars of 50 g·L⁻¹ could be achieved after 24 h of hydrolysis.

Although most of the lignin and hemicellulose could be removed from corncob after EaCl:LAC pretreatment, residual lignin could competitively adsorb free cellulase, which might result in losing of cellulase and impairing hydrolysis efficiency. Supplementation of bovine serum albumin (BSA) or Tween80 has been proved to be effective solutions for reducing inefficient adsorption of cellulase on lignin and deactivation of absorbed cellulase by enzyme-substrate interaction [46,47]. Herein, addition of Tween80 was also attempted (**Fig. 3C**). In comparison with the control (without Tween80), supplementation of 0.1%–1.0% (v/v) of Tween80 resulted in increased total sugars. At 1.0% Tween80, total sugars concentration of as high as 55.1 g·L⁻¹ was attained, 10.2% higher than 50.0 g·L⁻¹ of control. Excessive addition of Tween80 could however complicate the compositions and affect the biocompatibility of hydrolysates in biobutanol fermentation. At 0.5% Tween80, the total sugar reached 53.8 g·L⁻¹, which was adequate for butanol fermentation [38]. As a result, addition of 0.5% Tween80 is selected for the hydrolysis of pretreated corncob into fermentable sugars.

To further reduce the enzyme loading, cellulases absorbed on residual corncobs were recycled and reused in the consecutive batches. Herein, two processes with and without addition of 0.5% Tween80 were evaluated. At the end of each batch, the residual solids which might absorb cellulases as previous reported [3], were collected and reloaded into the next batch. The loadings of cellulase were decreased by 5 FPU·g⁻¹ for the following batches. The absorbed cellulases were recycled for five times, and sugars including glucose, xylose and arabinose were determined and illustrated in **Fig. 4**. The total sugars increased rapidly within the initial 6 h, and the addition of cellulase attached to corncob did not result in a decrease in enzymatic efficiency since it could lead to compromised mass transfer compared with the first batch (Cycle I). In the process with Tween80 (**Fig. 4B**), total sugars concentration of Cycle I was 52.9 g·L⁻¹, while it was 49.5 g·L⁻¹ in control (without Tween80) (**Fig. 4A**). Addition of Tween80 was favorable for the enzymatic hydrolysis, exhibiting 7–14% increase in total sugars at each batch. In the sixth batch (Cycle IV), only 25 FPU·g⁻¹ of fresh cellulase was supplemented. The total sugars reached 58.8 g·L⁻¹ and 54.9 g·L⁻¹ for processes with and without Tween80 respectively, which were 706 and 659 g·kg⁻¹ corncob pretreated by EaCl:LAC. The total sugars increased by about 11% than that of Cycle I. It is presumed that Tween80 might reduce the inactivation of cellulase caused by interaction between cellulase and substrate. Thus, the cellulases adsorbed on corncob displayed stable and even improved enzymatic activity in the next cycle, which is consistent with previous study [47]. The total sugars concentrations of each batch were enough as carbon

source for the butanol fermentation with *C. saccharobutylicum*. It should be noted that about 50% of cellulases could be saved through this newly developed recycling process.

Biobutanol fermentation with corncob hydrolysates by *C. saccharobutylicum* DSM13864

Application of hydrolysates from EaCl:LAC-pretreated corncob was evaluated in biobutanol fermentation. *C. saccharobutylicum* DSM13864 could utilize pentoses, such as xylose, as carbon sources and is regarded as one of the most promising bacteria for biobutanol fermentation. Hydrolysates of the sixth batch were collected and designated as Cycle VI_{Tween80} and Cycle VI for with and without Tween80 addition respectively. The total sugars concentrations of Cycle VI_{Tween80} and Cycle VI were determined to be 58.8 g·L⁻¹ and 54.9 g·L⁻¹. Control experiments were also carried out with glucose as carbon source instead of hydrolysates. The glucose concentrations of the control groups were kept at the same level with the total sugars of the hydrolysates from Cycle VI_{Tween80} and Cycle VI. Consumption of reducing sugars and production of acetone, butanol and ethanol (ABE) were monitored and illustrated in **Fig. 5** and **Table 3**. During the initial 48 h, *C. saccharobutylicum* grew quickly with high sugar consumption and ABE production rates. After 48 h, ABE production decreased, along with a slower sugar consumption rate. After 72 h, butanol titers of 10.2 and 10.4 g·L⁻¹ were reached for Cycle VI (**Fig. 5A**) and Cycle VI_{Tween80} (**Fig. 5C**) respectively, slightly lower than the corresponding glucose controls of 11.2 (**Fig. 5B**) and 11.4 g·L⁻¹ (**Fig. 5D**). Although the concentrations of total sugars in hydrolysates are at same level with glucose controls, they are mixture of arabinose, xylose and glucose. The lower ABE titers of hydrolysates might be attributed to the lower glucose concentrations and the complicated metabolite fluxes of hydrolysates. It should be noted that the butanol yield and productivity of Cycle VI_{Tween80} and Cycle VI hydrolysates were 194 g·kg⁻¹ total sugar and 0.15 g·L⁻¹·h⁻¹, and 206 g·g⁻¹ total sugar, and 0.14 g·L⁻¹·h⁻¹ respectively, which are at similar level with those of glucose controls (**Table 3**). The specific yields of butanol of Cycle VI_{Tween80} and Cycle VI per pretreated corncob were 137 and 136 g·kg⁻¹. With regard to total solvents of ABE, the titers of Cycle VI_{Tween80} and Cycle VI were 15.8 and 15.6 g·L⁻¹, with calculated yields per total sugars of 295 and 315 g·kg⁻¹ total sugar, and calculated yields per pretreated corncob of 208 and 207 g·kg⁻¹ respectively. As a result, corncob hydrolysates from Cycle VI could be efficiently utilized by *C. saccharobutylicum* as carbon source for biobutanol fermentation. Moreover, the corncob hydrolysates did not display obvious inhibitory effect on the growth and biobutanol production of *C. saccharobutylicum*.

Table 3 Biobutanol fermentation with corncob hydrolysates by *C. saccharobutylicum* DSM13864.

Carbon source	Butanol			Acetone-butanol-ethanol (ABE)		
	Titer [g·L ⁻¹]	Yield ^a [g·kg ⁻¹]	Prod. ^b [g·L ⁻¹ ·h ⁻¹]	Titer [g·L ⁻¹]	Yield ^a [g·kg ⁻¹]	Prod. [g·L ⁻¹ ·h ⁻¹]
Cycle VI	10.2	206 (136)	0.14	15.6	315 (207)	0.21
Control I ^c	11.2	210	0.15	16.3	320	0.22
Cycle VI _{Tween80}	10.4	194 (137)	0.15	15.8	295 (208)	0.22
Control II ^d	11.4	206	0.16	16.9	306	0.23

Note: ^a Numbers outside the brackets represent specific yields per total sugars or glucose, numbers inside the brackets refer to specific yields per pretreated corncob. ^b Prod.: productivity. ^c Control I: 54 g·L⁻¹ glucose. ^d Control II: 59 g·L⁻¹ glucose.

This study provides a simple and biocompatible process for the facile conversion of corncob into biobutanol. Compared with other established processes, EaCl:LAC is a low-price, environmental friendly and biocompatible reagent. The specific ABE yields per pretreated and raw biomass of this process were calculated to be 208 and 87.4 g·kg⁻¹, second only to that of corncob pretreated by 0.5 M NaOH [48]. In view of its low price and high biocompatibility, EaCl:LAC is more efficient and promising than traditional ionic liquids such as [Bmim][Cl], and DESs such as ChCl:FA and ChCl:FA:AA. There is no need to add other reagents which are commonly used in combinatorial pretreatments, such as NaOH or Na₂CO₃ [3,41]. Moreover, EaCl:LAC could also be facily recycled by filtration. The hydrolysates with high titers of reducing sugars could presumably be applied in the biosynthesis of other biofuels, amino acids and high-valued natural products. Consequently, this study provides a promising reagent for significantly reducing the recalcitrance of lignocellulosic biomass, and an economic cellulase recycling process for biobutanol production.

Conclusions

In this study, several DESs, based on betaine and ethylamine as hydrogen bond acceptors, were newly synthesized and evaluated in the pretreatment of various lignocellulosic biomass. EaCl:LAC with lactic acid as hydrogen bond donor was the most efficient for reducing the recalcitrance of lignocellulosic biomass. Only employing single pretreatment with EaCl:LAC, both high hemicellulose and lignin removal were achieved. Facile pretreatment process was established with recycled cellulase. The hydrolysate of pretreated corncob was

biocompatible and could be directly utilized by *C. saccharobutylicum* for biobutanol fermentation with similar butanol titer and yield as glucose counterpart.

Methods

Biomass, chemicals and strains

All lignocellulosic biomass used in this study was sourced from a farm in Jinan, Shandong province, China. The biomass was milled by grinder and passed through a 380 μm sieve, and dried at 60°C for 24 h before use.

Ethylamine chloride (EaCl) was purchased from Macklin Biochemical Co., Ltd. Cellulase was a generous gift from *Vland* Biotech Co Ltd. All other chemicals were of analytical grade and purchased from Sinopharm Chemical Reagent Co., Ltd.

Clostridium saccharobutylicum DSM 13864 was purchased from DSMZ. In order to induce sporulation, it was cultivated in Reinforced Clostridia Medium (RCM) at 37°C for 7 days and stored at room temperature. Spore suspension (10%, v/v) was inoculated in 12 mL sterilized RCM and transferred to a desiccator evacuated to a vacuum level of 0.065 MPa. Afterwards, the culture was cultivated at 37°C for 12-18 h for further used as the seed medium [27].

Synthesis of ethylamine chloride based DES.

ChCl, BaCl and EaCl as hydrogen bond acceptor, and lactic acid, ethyl glycol, glycerol and urea as hydrogen bond donors were mixed at the ratios as listed in **Table 1**. The mixture was heated and stirred at 180 rpm in a conical flask with plug to reduce volatilization until a homogenous colorless liquid was formed. The DESs were kept in vacuum desiccator with silica gel for further use.

DFT calculations

The initial structures for these DESs were constructed with ChemDraw software and optimized via DFT calculations using Gaussian 09 suite. Functionals of B3LYP [49], M062X [37], ω B97XD [50] and basis set of 6-311+G** were selected to optimize the geometrical structures and calculate the free energy differences. Grimme correction was performed for entropy and Head-Gordon correction was performed for enthalpy. The coordinates of the optimized structure of DESs could be found in Additional file 6.

Pretreatment of corncob with EaCl:LAC

Ten grams of corncob was added into a three-necked flask containing 150 g of EaCl:LAC, followed by heating up to 150°C in an oil bath. Then the mixture was incubated for 0.5 h with mechanical agitation (200 rpm). Furthermore, cellulose was regenerated by adding appropriate volume of hot deionized water (85°C). The regenerated cellulose was filtrated with a 380-mesh sieve, and then washed with water and dehydrated to obtain the pretreated corncob, which was stored at 4°C for further use.

Effects of temperature, pretreatment time and solid to liquid ratio on the pretreatment of corncob with EaCl:LAC were performed as mentioned above, except for varying the incubation temperature of 90, 110, 130 and 150°C, pretreatment time of 0.5, 1.0, 1.5 and 2.0 h, solid to liquid ratios of 1:8, 1:10, 1:12 and 1:15. The pretreated corncobs were subjected to hydrolysis with cellulase and the released sugars were determined employing HPLC (Agilent 1100) equipped with an Aminex HPX-87H column at 60°C with 5 mM H₂SO₄ as eluent at a flow rate of 0.6 mL·min⁻¹ [41].

Enzymatic hydrolysis of pretreated corncob

One gram of the pretreated corncob was added to 12 mL citrate buffer (50 mM, pH4.8) containing 100 μL ampicillin (1 g·L⁻¹) and 50 FPU cellulase in a 50-mL flask. The mixture was incubated in a water bath at 50°C and 120 rpm for 24 h for releasing of arabinose, xylose and glucose. Samples (300 μL) were withdrawn at 6, 12, 24 h and centrifuged at 12000×g for 10 min. The resultant supernatants (100 μL) were mixed with 900 μL ultrapure water. The concentrations of arabinose, xylose and glucose were determined as above described.

Effect of cellulase dosage, hydrolysis time, solid to liquid ratios were investigated. Cellulase was supplemented at dosages of 10, 30, 40, 60 and 70 FPU·g⁻¹ pretreated corncob. Different solid to liquid ratios of 1:8, 1:10, 1:12 and 1:15 were adopted. Tween80 was also added in the hydrolysis mixture at 0.1%, 0.5% and 1.0%. Samples (100 μL) were withdrawn from the reaction mixture at 24, 48, and 72 h, and then analyzed as above mentioned.

Recovery of cellulases adsorbed to corncob

Cycle I of enzymatic hydrolysis was conducted in a 250-mL conical flask, consisted of 5 g pretreated corncob dispersing in 60 mL citrate buffer (50 mM, pH 4.8) and 50 FPU cellulase. After 24 h, the cellulase adsorbed on residual corncob was collected by filtration and supplemented to the next cycle. Based on previous study, the amount of cellulase added could be reduced by 10% for each cycle to achieve similar level of total sugars as Cycle I. Samples were prepared and analyzed as above mentioned.

Biobutanol fermentation of *C. saccharobutylicum* DSM 13864

The corncob hydrolysates of Cycle VI_{Tween80} and Cycle VI was utilized as carbon source for butanol fermentation by *Clostridium saccharobutylicum* DSM 13864. Other components of fermentation medium included 10 g·L⁻¹ of corn steep liquor (CSL), 4 g·L⁻¹ of CaCO₃, 2 g·L⁻¹ of (NH₄)₂SO₄, 0.5 g·L⁻¹ of K₂HPO₄ and 0.01 g·L⁻¹ of MnSO₄·H₂O. Furthermore, the pH of medium was adjusted to 6.5 with 4.0 M NaOH and autoclaved at 115°C for 20 min. Control experiment was conducted with fermentation medium containing 54 or 59 g·L⁻¹ of glucose. 10% (v/v) of actively growing cell culture was inoculated into sterilized fermentation medium, and anaerobically incubated at 37°C in a desiccator (0.065 MPa) [4]. Samples were withdrawn at different time intervals and the contents of acetone, butanol and ethanol (ABE) were analyzed by GC according to previously described methods [27]. All fermentation experiments were carried out in triplicate.

Component analysis and physical characterization of corncob pretreated by EaCl:LAC

Component analysis. Amount of cellulose, hemicellulose, lignin and ash in raw and pretreated corncobs was determined according to previously reported methods.⁴ Removal of hemicellulose and lignin was calculated according to the following formulas:

$$\text{Hemicellulose removal(\%)} = \left(1 - \frac{\text{Hemicellulose in pretreated corncob}}{\text{Hemicellulose in untreated corncob}} \times \text{solid yield}\right) \times 100\%$$

$$\text{Delignification(\%)} = \left(1 - \frac{\text{Lignin in pretreated corncob}}{\text{Lignin in untreated corncob}} \times \text{solid yield}\right) \times 100\%$$

SEM analysis. Scanning electron microscopy (5.0 kV, ×1200 Hitachi S-4800, Japan) analysis was operated to monitor the surface morphological features of corncob before and after pretreatment.

XRD analysis. The crystallinity of corncob was measured with X-ray diffractometer (XRD), using a D/max 2500 PC diffractometer with Cu/Kα radiation source (Rigaku Corporation, Tokyo, Japan). It was operated at a voltage of 60 kV and a current of 300 Ma with a scanning speed of 0.02 °/min and the 2θ range from 5° to 40°. Crystallinity index (CrI) was calculated as following.

$$\text{CrI (\%)} = \frac{I_{002} - I_{am}}{I_{002}} \times 100\%$$

I_{002} and I_{am} imply the intensities of the peaks at near 21.4° and 16.0° respectively.

FTIR analysis. FTIR was performed to detect the chemical structure of corncob using a Nicolet PROTÉGÉ 460 FT-IR Spectrometer (Nicolet, Thermo Scientific, Shanghai, People's Republic of China) [20]. FTIR spectra of the samples was recorded between 2000 and 600 cm⁻¹.

Abbreviations

DES: deep eutectic solvent; BaCl: betaine chloride; EaCl: ethylamine chloride; ChCl: choline chloride; LAC: lactic acid; EG: ethyl glycol; GLY: glycerol; UR: urea; DFT: density functional theory; CrI: crystallinity index; BSA: bovine serum albumin; Cycle I: hydrolysate of the first batch; Cycle I_{Tween80}: hydrolysate of the first batch with addition of Tween80; Cycle VI: hydrolysate of the sixth batch; Cycle VI_{Tween80}: hydrolysate of the sixth batch with addition of Tween80; Control I: control medium with 54 g·L⁻¹ glucose; Control II: control medium with 59 g·L⁻¹ glucose; ABE: acetone, butanol and ethanol.

Declarations

Acknowledgement

We are grateful to Dr. YC He from Changzhou University for support and discussion in XRD and FTIR analysis. We thank American Journal Experts (AJE) for English language editing.

Authors' contributions

Guochao Xu and Hao Li contributed equally to this work.

Guochao Xu: Conceptualization, Methodology, Data curation, Writing - original draft, Writing - review & editing. Hao Li: Formal analysis, Investigation, Data curation, Writing - original draft. Wanru Xing: Methodology, Validation, Formal analysis. Lei Gong: Resources, Data curation. Jinjun Dong: Writing - review & editing. Ye Ni: Writing - review & editing, Supervision, Project administration.

Funding

This work was supported by National Key R&D Program of China (2018A0901700), National Natural Science Foundation of China (21776112), National First-Class Discipline Program of Light Industry Technology and Engineering (LITE2018-07), Natural Science Foundation of Jiangsu Province (BK20171135), Program of Introducing Talents of Discipline to Universities (111-2-06), and Top-notch Academic Programs Project of Jiangsu Higher Education Institutions for the financial support of this research.

Availability of data and materials

The datasets generated during this study are included in this published article and its additional files.

Ethics approval and consent to participate

Not applicable.

Consent for publication

Not applicable.

Competing interest

The authors declare no competing financial interest.

References

1. Li J, Zhang M, Wang D. Enhancing delignification and subsequent enzymatic hydrolysis of corn stover by magnesium oxide-ethanol pretreatment. *Bioresour. Technol.* 2019;279:124–
2. Durre P. Biobutanol: An attractive biofuel. *Biotechnol. J.* 2007;2:1525–15
3. Xing WR, Xu GC, Dong JJ, Han RZ, Ni Y. Novel dihydrogen-bonding deep eutectic solvents: Pretreatment of rice straw for butanol fermentation featuring enzyme recycling and high solvent yield. *Chem. Eng. J.* 2018;333:712–720.
4. Anwar Z, Gulfracz M, Irshad M. Agro-industrial lignocellulosic biomass a key to unlock the future bio-energy: A brief review. *J. Rad. Red. Appl. Sci.* 2014;7:163–173.
5. Yang HH, Tsai CH, Chao MR, Su YL, Chien SM. Source identification and size distribution of atmospheric polycyclic aromatic hydrocarbons during rice straw burning period. *Atmos. Environ.* 2006;40:1266–1274.
6. Gadde B, Bonner S, Menke C, Garivait S. Air pollutant emissions from rice straw open field burning in India, Thailand and the Philippines. *Environ. Pollut.* 2009;157:1554–1558.
7. Korenaga T, Liu X, Huang Z. The influence of moisture content on polycyclic aromatic hydrocarbons emission during rice straw burning. *Chemosphere-Global Change Sci.* 2001;3:117–122.
8. Jacobs J, Kreutzer R, Smith D. Rice burning and asthma hospitalization, butte country, California, 1983-1992. *Environ. Health Perspect* 1997;105:980.
9. Torigoe K, Hasegawa S, Numata O, Yazaki S, Matsunaga M, Boku N. Influence of emission from rice straw burning on bronchial asthma in children. *Pediatr. Int.* 2000;42:143–150.
10. Zhang Z, Xie Y, He X, Li X, Hu J, Ruan Z, Zhao S, Peng N, Liang Y. Comparison of high-titer lactic acid fermentation from NaOH- and $\text{NH}_3\text{-H}_2\text{O}_2$ -pretreated corncob by *Bacillus coagulans* using simultaneous saccharification and fermentation. *Sci. Rep.* 2016;6:37245.
11. He YC, Jiang CX, Chong GG, Di JH, Wu YF, Wang BQ, Xue XX, Ma CL. Chemical-enzymatic conversion of corncob-derived xylose to furfuralcohol by the tandem catalysis with $\text{SO}_4(2-)/\text{SnO}_2$ -kaoline and *coli* CCZU-T15 cells in toluene-water media. *Bioresour. Technol.* 2017;245:841–849.

12. Himmel ME, Ding SY, Johnson DK, Adney WS, Nimlos MR, Brady JW, Foust TD. Biomass recalcitrance: Engineering plants and enzymes for biofuels production. *Science* 2007;315:804–807.
13. Reddy N, Yang Y. Properties and potential applications of natural cellulose fibers from the bark of cotton stalks. *Bioresour. Technol.* 2009;100:3563–3569.
14. Chiamonti D, Prussi M, Ferrero S, Oriani L, Ottonello P, Torre P, Cherchi F. Review of pretreatment processes for lignocellulosic ethanol production, and development of an innovative method. *Biomass Bioenergy* 2016;46:25–35.
15. Binod P, Sindhu R, Singhania RR, Vikram S, Devi L, Nagalakshmi S, Kurien N, Sukumaran RK, Pandey A. Bioethanol production from rice straw: An overview. *Bioresour. Technol.* 2010;101:4767–4774.
16. Kumari D, Singh RR. Pretreatment of lignocellulosic wastes for biofuel production: A critical review. *Renew. Sustain. Energy Rev.* 2018;90:877–891.
17. Hsu TC, Guo GL, Chen WH, Hwang WS. Effect of dilute acid pretreatment of rice straw on structural properties and enzymatic hydrolysis. *Bioresour. Technol.* 2010;101:4907–4913.
18. Elgharrawy AA, Alam MZ, Moniruzzaman M, Goto M. Ionic liquid pretreatment as emerging approaches for enhanced enzymatic hydrolysis of lignocellulosic biomass. *Biochem. Eng. J.* 2016;109:252–267.
19. Moniruzzaman M, Goto M. Ionic liquids: future solvents and reagents for pharmaceuticals. *J. Chem. Eng. Jpn.* 2011;44:370–381.
20. Sharma V, Nargotra P, Bajaj BK. Ultrasound and surfactant assisted ionic liquid pretreatment of sugarcane bagasse for enhancing saccharification using enzymes from an ionic liquid tolerant *Aspergillus assiutensis* *Bioresour. Technol.* 2019;285:121319.
21. Sorn V, Chang KL, Phitsuwan P, Ratanakhanokchai K, Dong CD. Effect of microwave-assisted ionic liquid/acidic ionic liquid pretreatment on the morphology, structure, and enhanced delignification of rice straw. *Bioresour. Technol.* 2019;293:121929.
22. Zhang Q, de Oliveira Vigier K, Royer S, Jerome F. Deep eutectic solvents: syntheses, properties and applications. *Chem. Soc. Rev.* 2012;41:7108–7146.
23. Zhang CW, Xia SQ, Ma PS. Facile pretreatment of lignocellulosic biomass using deep eutectic solvents. *Bioresour. Technol.* 2016;219:1–5.
24. Dai Y, Huan B, Zhang HS, He YC. Effective biotransformation of ethyl 4-chloro-3-oxobutanoate into ethyl (*S*)-4-chloro-3-hydroxybutanoate by recombinant *E. coli* CCZU-T15 whole cells in [ChCl][Gly]-water media. *Appl. Biochem. Biotechnol.* 2017;181:1347–1359.
25. Abbott AP, Boothby D, Capper G, Davies DL, Rasheed RK. Deep eutectic solvents formed between choline chloride and carboxylic acids: versatile alternatives to ionic liquids. *J. Am. Chem. Soc.* 2004;126:9142–9147.
26. Gunny AAN, Arbain D, Nashef EM, Jamol P. Applicability evaluation of deep eutectic solvents-cellulase systems for lignocellulose hydrolysis. *Bioresour. Technol.* 2015;181:297–232.
27. Xu GC, Ding JC, Han RZ, Dong JJ, Ni Y. Enhancing cellulose accessibility of corn stover by deep eutectic solvent pretreatment for butanol fermentation. *Bioresour. Technol.* 2016;203:364–369.
28. Lynam JG, Kumar N, Wong MJ. Deep eutectic solvents' ability to solubilize lignin, cellulose, and hemicellulose, thermal stability, and density. *Bioresour. Technol.* 2019;238:684–689.
29. Dai Y, Zhang HS, Huang B, He YC. Enhancing the enzymatic saccharification of bamboo shoot shell by sequential biological pretreatment with *Galactomyces* CCZU11-1 and deep eutectic solvent extraction. *Bioprocess Biosyst. Eng.* 2017;40:1427–1436.
30. Zhang QG, Hu JJ, Lee DJ. Pretreatment of biomass using ionic liquids: research updates. *Renewable Energy*, 2017;111:77–
31. Hou XD, Li N, Zong MH. Facile and simple pretreatment of sugar cane bagasse without size reduction using renewable ionic liquids–water mixtures. *ACS Sustain. Chem. Eng.* 2013;1:519–526.
32. Smith EL, Abbott AP, Ryder KS. Deep eutectic solvents (DESs) and their applications. *Chem. Rev.*, 2014;114:11060–11082.
33. Chermette H. Chemical reactivity indexes in density functional theory. *J. Comput. Chem.* 1999;20:129–154.
34. Cohen AJ, Mori-Sanchez P, Yang WT. Challenges for density functional theory. *Chem. Rev.* 2012;112:289–320.
35. Zhang C, Jia YZ, Jing Y, Wang HY, Hong K. Main chemical species and molecular structure of deep eutectic solvent studied by experiments with DFT calculation: a case of choline chloride and magnesium chloride hexahydrate. *J. Mol. Model* 2014;20:2374.
36. Chen ZF, McLean B, Ludwig M, Stefanovic R, Warr GG, Webber GB, Page AJ, Atkin R. Nanostructure of deep eutectic solvents at graphite electrode interfaces as a function of potential. *J. Phys. Chem. C* 2016;120:2225–2233.
37. Zhao Y, Truhlar DG. The M06 suite of density functionals for main group thermochemistry, thermochemical kinetics, noncovalent interactions, excited states, and transition elements: Two new functionals and systematic testing of four M06-class functionals and 12 other functionals. *Theor. Chem. Acc.* 2008;120:215–241.

38. Atilhan M, Altamash T, Aparicio S, Quantum chemistry insight into the interactions between deep eutectic solvents and SO₂. *Molecules* 2019;24:2963.
39. Kumar AK, Shah E, Patel A, Sharma S, Dixit G. Physico-chemical characterization and evaluation of neat and aqueous mixtures of choline chloride+lactic acid for lignocellulosic biomass fractionation, enzymatic hydrolysis and fermentation. *J. Mol. Liquids* 2018;271:540–549.
40. Tan YT, Ngoh GC, Chua ASM. Effect of functional groups in acid constituent of deep eutectic solvent for extraction of reactive lignin. *Bioresour. Technol.* 2019;281:359–366.
41. Ding JC, Xu GC, Han RZ, Ni Y. Biobutanol production from corn stover hydrolysate pretreated with recycled ionic liquid by *Clostridium saccharobutylicum* DSM 13864. *Bioresour. Technol.* 2016;199:228–234.
42. Liang Y, Duan WJ, An XX, Qiao YY, Tian YY, Zhou HF. Novel betaine-amine acid based natural deep eutectic solvents for enhancing the enzymatic hydrolysis of comcob. *Bioresour. Technol.*, 2020;310:123389.
43. Pandiyan K, Tiwari R, Rana S, Arora A, Singh S, Saxena AK, Nain L. Comparative efficiency of different pretreatment methods on enzymatic digestibility of *Parthenium*. *World J. Microbiol. Biotechnol.* 2014;30:55–64.
44. You T, Li X, Wang R, Zhang X, Xu F. Effects of synergistic fungal pretreatment on structure and thermal properties of lignin from comcob. *Bioresour. Technol.* 2019;272:123–129.
45. Ma L, Ma Q, Guo G, Du L, Zhang Y, Cui Y, Xiao D. Optimization of sodium percarbonate pretreatment for improving 2,3-butanediol production from comcob. *Prep. Biochem. Biotechnol.* 2018;48:218–225.
46. Yang B, Wyman CE, BSA treatment to enhance enzymatic hydrolysis of cellulose in lignin containing substrates. *Biotechnol. Bioeng.* 2006;94:611–617.
47. Yang M, Zhang A, Liu B, Li W, Xing J. Improvement of cellulose conversion caused by the protection of Tween-80 on the adsorbed cellulase. *Biochem. Eng. J.* 2011;56:125–129.
48. Gao K, Rehmann L. ABE fermentation from enzymatic hydrolysate of NaOH-pretreated comcobs. *Biomass Bioenergy* 2014;66:110–115.
49. Becke AD. Density-functional exchange-energy approximation with correct asymptotic behaviour. *Phys. A* 1988;38:3098–3100.
50. Chai JD, Head-Gordon M. Systematic optimization of long-range corrected hybrid density functionals. *J. Chem. Phys.* 2008;128:084106.

Figures

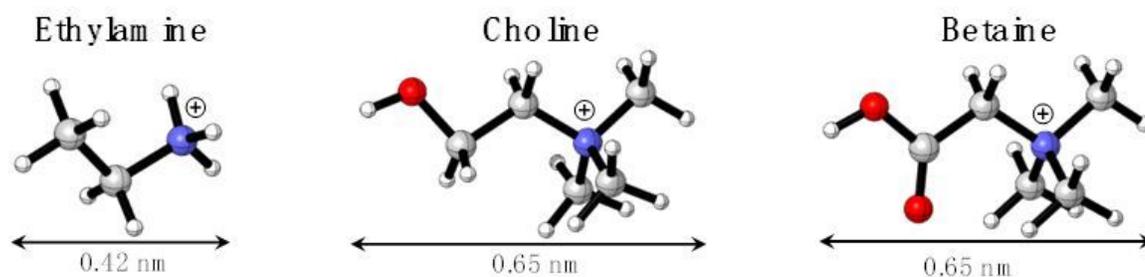


Figure 1

Structures of ethylamine chloride, choline chloride and betaine chloride used as hydrogen bond acceptors. Atoms are carbon (gray), nitrogen (blue), oxygen (red), and hydrogen (white). Cl⁻ ion is not shown.

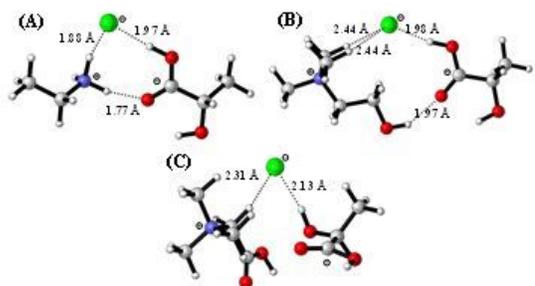


Figure 2

Chemical structures of EaCl:LAC (A), ChCl:LAC (B) and BaCl:LAC obtained from geometry optimization.

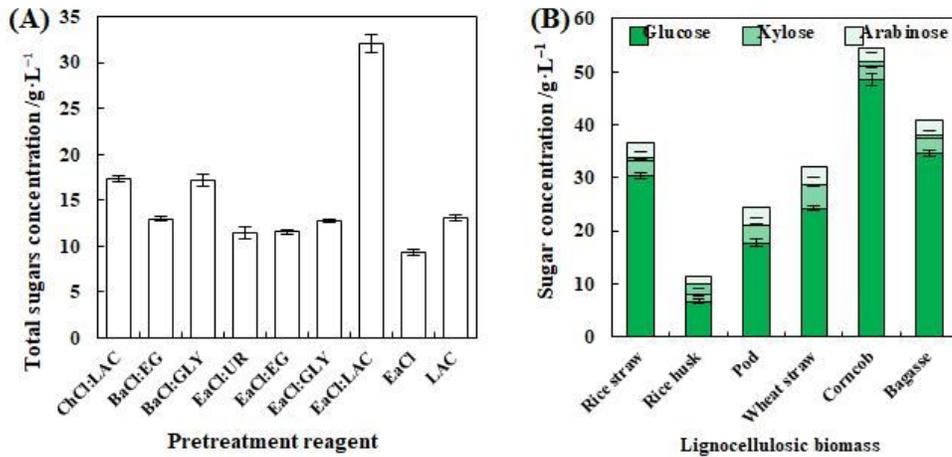


Figure 3

Evaluation of newly synthesized DESs in the pretreatment of various lignocellulosic biomass. (A) Pretreatment of rice straw by various DESs. (B) Pretreatment of various lignocellulosic biomass by EaCl:LAC. (□), glucose; (▨): xylose, (▩) arabinose.

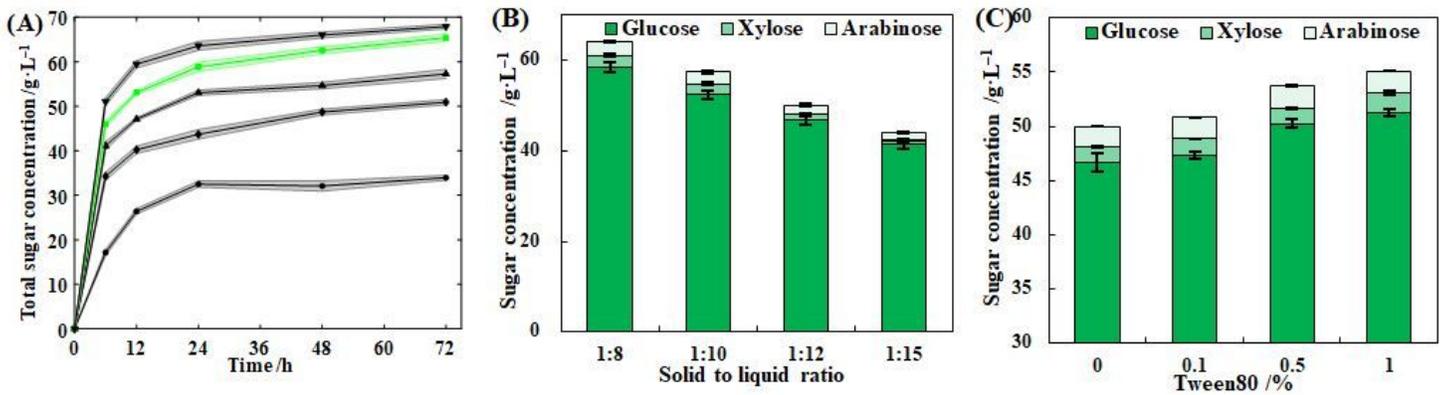


Figure 4

Optimization of enzymatic hydrolysis conditions. (A) Cellulase loading and hydrolysis time, (▼): 70 FPU·g⁻¹; (▨): 50 FPU·g⁻¹, (▩) 40 FPU·g⁻¹, (⊗) 30 FPU·g⁻¹, (□) 10 FPU·g⁻¹, shadow refers to standard deviation. (B) Solid-liquid ratio, (□): glucose; (▨): xylose, (▩): arabinose. (C) Tween80, (□): glucose; (▨): xylose, (▩): arabinose. All pretreatment was performed in triplicate.

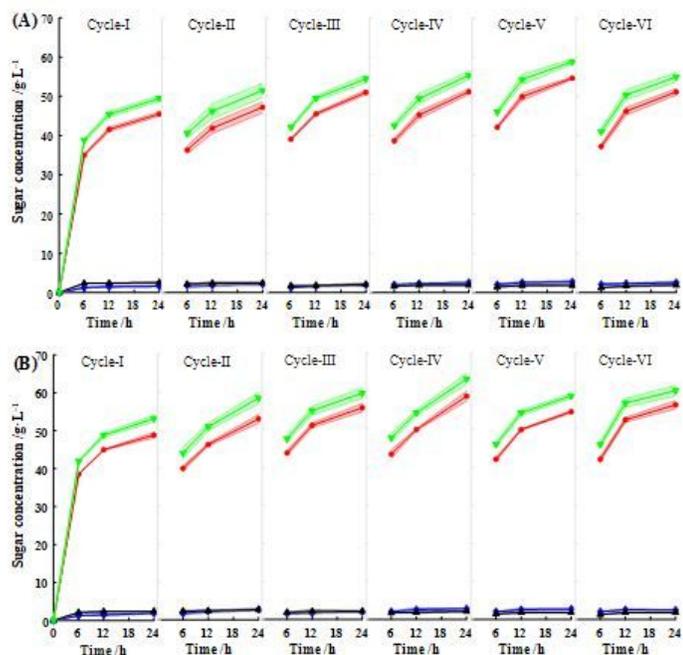


Figure 5

Reusability of cellulase absorbed on pretreated corncob. (A) without addition of Tween80, (B) 0.5% (v/v) Tween80. (▼): total sugar; (◻): glucose; (▲): xylose; (◼): arabinose. Shadow refers to standard deviation, and all reactions were performed in triplicate.

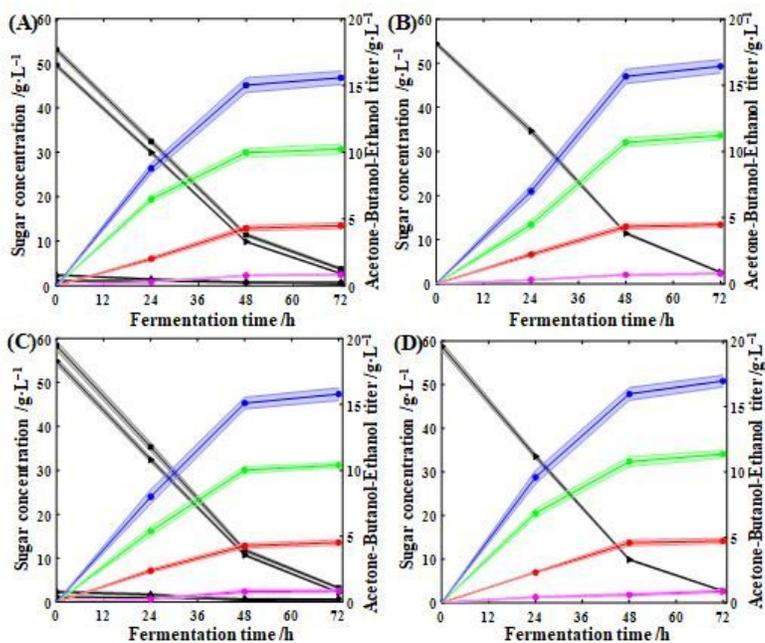


Figure 6

Biobutanol production from hydrolysates of corncob and glucose as carbon sources. (A) hydrolysate of Cycle VI, (B) Control I (54 g L⁻¹ glucose), (C) hydrolysate of Cycle VI with Tween80 (D) Control II (59 g L⁻¹ glucose). (◻): total sugars; (◻): glucose; (◻): xylose; (◻): arabinose; (◻): total solvents; (◻): butanol; (◻): ethanol; (◻): acetone. Shadow refers to standard deviation, and all fermentations were performed in triplicate.

Supplementary Files

This is a list of supplementary files associated with this preprint. Click to download.

- [Additionalfile1.pdf](#)

- [Additionalfile2.pptx](#)
- [Additionalfile3.pptx](#)
- [Additionalfile4.pptx](#)
- [Additionalfile5.pdf](#)
- [Additionalfile6.pdf](#)