

Improved performances of lithium disilicate glass-ceramics by seeds induced crystallization

Ting Zhao

Shaanxi University of Science and Technology

Mei-Mei Lian

Shaanxi University of Science and Technology

Yi Qin (✉ qinyi@sust.edu.cn)

Shaanxi University of Science and Technology

Jian-Feng Zhu

Shaanxi University of Science and Technology

Xin-Gang Kong

Shaanxi University of Science and Technology

Jian-Feng Yang

Xi'an Jiaotong University

Research Article

Keywords: Lithium disilicate, Seeds, Mechanical properties, Translucency

Posted Date: July 29th, 2020

DOI: <https://doi.org/10.21203/rs.3.rs-48775/v1>

License:   This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

Version of Record: A version of this preprint was published at Journal of Advanced Ceramics on March 3rd, 2021. See the published version at <https://doi.org/10.1007/s40145-021-0463-4>.

Abstract

Self-reinforced lithium disilicate ($\text{Li}_2\text{Si}_2\text{O}_5$) glass-ceramics were hot pressing sintered by introducing 5 wt% $\text{Li}_2\text{Si}_2\text{O}_5$ crystal seeds into two different glass systems. The results show that the seeds play an important role in the crystallization inducement, microstructural and properties improvement of the glass, especially for the glass powder without the nucleating agent of P_2O_5 . The microstructure features a wider bimodal grain size distribution with large rod-like crystals epitaxially grown along the seeds and small crystals nucleated from the glass powder itself, contributes to the improvement of the performance especially the fracture toughness. The 4C5S specimen exhibited the best comprehensive properties with a good flexural strength (396 ± 7 MPa), improved fracture toughness (3.31 ± 0.19 MPa·m^{1/2}) and comparable translucency as IPS e.max. This research will provide a new idea and method for the perfect matching of the fracture toughness and the aesthetic appearance of lithium disilicate glass-ceramics, and lay the foundation for its clinical applications.

1. Introduction

Lithium disilicate glass-ceramics, as a new kind of dental restorative materials, has many incomparable advantages with the traditional metal materials, macromolecule materials and ceramics, such as high mechanical properties (flexural strength ~300-400 MPa), comparable wear resistance, aesthetical characteristics as natural teeth, good machinability and so on [1-6]. Because of which, it has gained increasing attention in the latest research. However, due to its intrinsic brittleness and low defect tolerance, the fracture toughness of $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics is far less than that of zirconia, alumina and other traditional ceramics restorations [7-9]. Therefore, how to improve the fracture toughness on the basis of maintaining good aesthetics has become an urgent research topic, which has a very important practical significance for its large-scale application in the field of dental restoration.

However, there are few reports on the toughening of lithium disilicate glass-ceramics. The most common method is to introduce zirconia into the glass composition, by using its transformation toughening effect [10-12], glass-ceramics can be reinforced [13, 14]. Huang et al. [10] successfully prepared t- ZrO_2 (3Y-TZP) toughened lithium disilicate glass-ceramic by vacuum hot-pressing sintering, with the highest strength of 340 MPa and fracture toughness of 3.50 MPa·m^{1/2}. However, the addition of zirconia also had some adverse effects such as the difficulty of uniform distribution and the obstacle to densification, making the porosity as high as 1.90%. Also toughening of other second phases such as whisker, SiC nanowire, alumina, carbon fiber were involved to toughen glass-ceramics [15-19]. Although the toughening mechanisms of heterogeneous phase transformation, crack deflection, crack bridging and pull-out effect were analyzed [20], the effects of these toughening measures on the translucency of glass-ceramics were not explicitly mentioned. In addition, the introduction of heterogeneous toughening phases has some problems, such as difficulty in densification and the matrix powder can not filling the fiber skeleton uniformly without damaging the fibers. It will inevitably lead to strong lights scattering and refraction caused by non-uniformly dispersed second phase, heterogeneous interface and mismatch of the

refractive index, which will decrease the translucency of lithium disilicate glass-ceramics and make it difficult to match the appearance of natural teeth.

Considering the shortcomings of the toughening by heterogeneous phases mentioned above, and the fact that $\text{Li}_2\text{Si}_2\text{O}_5$ crystalline phase and its glass phase have nearly the same refractive index [21], many researchers tried to improve the fracture toughness and translucency of $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics by using different nucleating agents and changing the heat treatment processes (casting, sintering, etc.) [22-27]. However, the effect is not satisfactory. The reason is that no matter the overall crystallization (melting method) or surface crystallization (powder sintering method) applied, all the crystalline phases are from the crystallization of parent glass. The nucleation number is very large so the precipitated $\text{Li}_2\text{Si}_2\text{O}_5$ crystals usually display small grain size with a narrow size distribution, which form more interfacial area with the glass matrix [23, 27-29]. These interfaces not only easily generate more flaws acting as a cracking source, but also shorten the crack propagation path, limiting the improvement of fracture toughness [30]. At the same time, many small interfaces can not effectively reduce the scattering and refraction of visible light, making the translucency poor. Therefore, for the homogeneous toughening of lithium disilicate glass-ceramics, it is necessary to control the number of nucleation sites and the size of crystals, that is, crystallization controllable.

In our previous studies [31, 32], the coexistence of large-sized rod-like $\text{Li}_2\text{Si}_2\text{O}_5$ and small-sized LD grains formed by solid state reaction of LM crystal and SiO_2 glass can effectively improve mechanics performance, especially the fracture toughness of $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics. Seeds toughening is one of the most effective methods to obtain this kind of microstructure and it has been widely used in traditional ceramic materials such as Si_3N_4 [33, 34], Al_2O_3 [35] and SiAlON [36]. It is known that the so-called in-situ growth is to make some grains grow into elongated grains with high aspect ratio by controlling the sintering process, thus obtaining the microstructure similar to that of fiber or whisker reinforced composites [37]. This microstructure with a bimodal grain size distribution can play a good role in deflection and bridging cracks to improve the fracture toughness and strength of materials, while basically not affecting other properties [38, 39].

However, few reports concerning the seeds toughening in glass-ceramics have been mentioned. In this paper, $\text{Li}_2\text{Si}_2\text{O}_5$ seeds were added to different glass systems to induce crystallization and help crystals epitaxially grow to large-sized rod-like grains, while the parent glass powders with high surface energy precipitate small-sized rod-like crystals through spontaneous surface nucleation, thus forming the coexistence of multi-scale crystals, as shown in Fig. 1. The effect of $\text{Li}_2\text{Si}_2\text{O}_5$ seeds on the microstructure, mechanical properties and translucency characteristics of lithium disilicate glass-ceramics was also discussed. We believe that marrying the very good aesthetics with good mechanical properties may help open the area of restorative application of $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics, and provides a new way for preparing toughened glass-ceramics.

2. Materials And Methods

2.1. Synthesis of rod-like $\text{Li}_2\text{Si}_2\text{O}_5$ seeds

99.9% purity Li_2CO_3 powder and SiO_2 powder were used as the starting materials, and $\text{Li}_2\text{Si}_2\text{O}_5$ seeds were solid-state reaction synthesized according to the following reaction: $\text{Li}_2\text{CO}_3 + 2\text{SiO}_2 = \text{Li}_2\text{Si}_2\text{O}_5 + \text{CO}_2$. The mixture of Li_2CO_3 and SiO_2 in molar ratio of 1:2 were ball-milled for 5 h and dried by using a rotatory evaporator. Then the powders were placed in a corundum crucible and underwent a two-step heat treatment in an electric furnace. The mixture was firstly heated at 710 °C for 2 h, and then the temperature was raised to 980 °C for 4 h at a heating rate of 3 °C•min⁻¹. After that, the heated powders were milled, dispersed and acid washed at 1 vol.% HF to remove the residual glass phase.

2.2. Preparation of $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics

In order to explore the controlled crystallization effect of seeds on different glass systems, two $\text{Li}_2\text{Si}_2\text{O}_5$ glass powders were prepared and the compositions are shown in Table 1. They have the same molar ratio of $\text{SiO}_2:\text{Li}_2\text{O} = 2.39:1$ to ensure that the main crystalline phase is $\text{Li}_2\text{Si}_2\text{O}_5$ [40, 41]. Besides that, 4C LD glass only contains K_2O to promote the glass melting process [42] and La_2O_3 to decrease the viscosity of the glass [43], while removing the nucleating agent of P_2O_5 compared with 7C LD glass. Reagent grade powders of Li_2CO_3 , SiO_2 , $\text{NH}_4\text{H}_2\text{PO}_4$, ZrO_2 , Al_2O_3 , K_2CO_3 and La_2O_3 were used as the raw materials. After mixing, melting (at 1450 °C for 2 h), quenching and ball-milling (10 h, with high purity zirconia balls in an ethanol environment), the glass powders with D50 values of ~ 5 µm were obtained. The detailed process is the same as our previous studies [31, 32].

Table 1 The compositions of $\text{Li}_2\text{Si}_2\text{O}_5$ glass (mol.%)

	Li_2O	SiO_2	P_2O_5	ZrO_2	Al_2O_3	K_2O	La_2O_3
7C LD	27.6	66.0	0.8	1.4	1.8	1.8	0.6
4C LD	28.6	68.6	–	–	–	2.0	0.8

The starting powder mixtures containing 4C or 7C LD glass and 5 wt.% $\text{Li}_2\text{Si}_2\text{O}_5$ seeds were wet mixed with ZrO_2 balls in anhydrous alcohol for 2 h. The slurry was dried, uniaxially pressed (30 MPa in a hardened steel die, $\Phi 30$ mm × 10 mm), and presintered in a furnace (SN33810297, DeguDent GmbH, Germany) at 800 °C for 20 min. After that, the middle compacts were hot-pressing sintered in a vacuum furnace at 850 °C for 1 h under a pressure of 20 MPa. Finally, after cooling down to ambient temperature, the surface layers of the samples were removed.

2.3. Characterization

To evaluate the densification degree, the bulk density was measured by using archimedes method and from that the relative density was calculated. Three samples were estimated to get the mean value. Crystalline phases were identified by X-ray diffraction analysis (XRD, D/MAX-RA, Rigaku, Japan) with Cu K α radiation and scanning from 10° to 70°. The sampling interval was 0.02° 2 θ . The crystallinity was calculated by the locations of the diffraction peaks, their number and relative intensity in the XRD pattern according to Equation (1) [28, 44].

$$X_c = \frac{\sum_i I_{ci}}{\sum_i I_{ci} + KI_a} \times 100\% \quad (1)$$

Electron backscatter diffraction (EBSD, Phenom Pro-X, Netherland) and field emission scanning electron microscope (FESEM, S-4800, Hitachi, Tokyo, Japan) were used to characterize microstructures and phases of the unetched and etched samples (5 vol. % HF for 1 min), respectively. The grain size was counted and analyzed. More than 200 grains were chosen for each sample. Transmission electron microscopy (TEM) and selected area electron diffraction (SAED) investigations were performed using a JEM 200CX microscope with 120 kV electron beam. For the preparation of TEM specimen, the disc specimens were first ground to about 20 μ m thick, then polished and followed by ion beam thinning (Gatan Model 691 PIPS).

Rectangular bars (3 mm \times 4 mm \times 20 mm, after polishing) were used to determine the three-point flexural strength with a span of 16 mm at a cross-head speed of 0.5 mm/min by the universal testing machine (INSTRON1195, Britain). For the fracture toughness measurement, the samples (3 mm \times 4 mm \times 20 mm) with a V-notch depth of 0.8 mm to 1.2 mm and the single edge V-notched beam (SEVNB) testing method were used. The fracture toughness was calculated according to ISO 6872 (International Standard). The average flexural strength and fracture toughness were obtained from five samples and three specimens, respectively. For the determination of optical properties, the required fine surface and uniform thickness (0.8 mm in thickness) of the specimens were obtained by polishing with wet silicon carbide papers. Translucent characteristics of the final glass-ceramics were evaluated in term of contrast ratio (CR) [21], which is defined as the ratio of illuminance of the material when it is placed over a black background to the illuminance of the same material when it is placed over a white background. Illuminance values were tested using a colorimeter and CR values were calculated, which is 0.0 for a transparent material and 1.0 for a totally opaque material.

3. Results

3.1. Characterization of Li₂Si₂O₅ Seeds

Fig. 2 shows the SEM images and XRD patterns of the Li₂Si₂O₅ seeds synthesized by solid-state reaction. In Fig. 2(a), the seeds are rod-like crystals with a length of 1.2-6.5 μ m and a width of 0.1-1.0 μ m. The average length is \sim 2 μ m and the aspect ratio of the seeds is 3~6. The XRD analysis in Fig. 2(b) indicated

the existence of $\text{Li}_2\text{Si}_2\text{O}_5$ crystalline phase and no other secondary phase, confirming the reaction of Li_2CO_3 and SiO_2 is complete. And most of the glass phases were removed after acid rinse treatments. Thus, the synthesized high-quality $\text{Li}_2\text{Si}_2\text{O}_5$ seeds provide the development of the self-toughed $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics microstructure with elongated grains.

3.2. Phase formation

Fig. 3 shows the XRD patterns and crystallinity of the $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics from 4C and 7C glass powders without and with 5 wt.% $\text{Li}_2\text{Si}_2\text{O}_5$ seeds. In Fig. 3(a), it can be found despite the difference in composition, the main crystalline phase of all the samples was only $\text{Li}_2\text{Si}_2\text{O}_5$ (ICCD card 01-040-0376). The intensity of the $\text{Li}_2\text{Si}_2\text{O}_5$ diffraction peaks varied slightly, indicating the crystallinity changed. In Fig. 3(b), it can be seen that for the two kinds of glass powders with different composition, by adding 5 wt.% $\text{Li}_2\text{Si}_2\text{O}_5$ seeds helped the crystallinities of the samples increased by ~10%.

3.3. Morphology

Fig. 4 shows the SEM morphologies of the etched $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics with different compositions. All the specimens showed a closely packed and multi-directionally interlocked microstructure of numerous rod-like $\text{Li}_2\text{Si}_2\text{O}_5$ crystals protruding from the glass matrix. However, the crystals morphology especially the grain size are quite different, and the statistical results are clearly shown in Table 2. It is found that the $\text{Li}_2\text{Si}_2\text{O}_5$ crystals in 7C and 7C5S samples have smaller grain size but larger aspect ratio, making them typical long rod-like crystals. Another interesting phenomenon is that the grain size of 4C and 7C samples are more uniform and no larger grain is found. While in the seeds addition samples of 4C5S and 7C5S, some larger grains with high aspect ratio embedded in a smaller grained matrix was observed. It is consistent with the microstructural design (in Fig. 1) that large rod-like crystals was believed to result from epitaxy growth of the $\text{Li}_2\text{Si}_2\text{O}_5$ seeds while the small grains are grown from the spontaneous nucleation of the glass powders. The bimodal distribution morphology is more obvious in 4C5S so that the average grain size increased.

Table 2 The average length (\bar{L}), width (\bar{W}) and aspect ratio (\bar{R}) of the $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics with different compositions.

Specimens	4C	4C5S	7C	7C5S
$\bar{L}/\mu\text{m}$	2.94	3.34	1.88	2.29
$\bar{W}/\mu\text{m}$	0.86	0.87	0.32	0.43
\bar{R}	3.41	3.83	5.88	5.37

To further explore the variation of the grain size caused by the seeds addition in different glass powders, the grain size distribution in length and width directions of the samples is statistical analyzed, as shown in Fig. 5. Compared to 7C, the grain size of 7C5S sample increased slightly both in the direction of length and width and apparently a small number of large grains appeared. Nevertheless, the overall grain size distribution of 7C5S was still concentrated. By contrast, the grain size of 4C5S sample shows a much wider bimodal distribution with the length covers from 2 to 8 μm and the width in the range of 0.5-1.5 μm . And the aspect ratio is also larger than that of 4C.

To further understand the microstructure with a bimodal grain size distribution caused by the heterogeneous nucleation of $\text{Li}_2\text{Si}_2\text{O}_5$ crystal seeds, a specimen of 4C5S was subjected to TEM investigation. The bright field TEM micrographs and their related electron diffraction patterns are shown in Fig. 6. In Fig. 6(a), it shows a large crystal with the length up to $\sim 6 \mu\text{m}$ and some smaller grains embedded in the glass matrix. The corresponding diffraction pattern of this large crystal in Fig. 6(b) reveals that the crystal was oriented with the [110] plane parallel to the beam direction. And based on that, the calibrated diffraction pattern matches that of a single crystalline $\text{Li}_2\text{Si}_2\text{O}_5$ lattice. Thus, the TEM analysis confirmed that crystalline phase in sample 4C5S is lithium disilicate. The diffraction pattern in Fig. 6(c) indicated that the matrix was amorphous. More often than not, the thinnest part collapsed dramatically if the focused electron beam was on (the region marked in red shown in Fig. 6(d)), indicating that the local heat was so high that the specimen was rapidly perforated. So the epitaxial growth mode of large crystals along the seeds has not been observed yet in the TEM investigation.

3.4. Mechanical properties

Fig. 7 shows the relative density, three-point flexural strength and fracture toughness of the $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics with different compositions. It can be seen that the relative densities are all above 98.80%, indicating the densification degree is very high. The relative density decreased with the addition of seeds and the highest relative density up to $99.72 \pm 0.09\%$ was obtained in the 4C sample. The flexure strength of 4C5S, 7C and 7C5S samples are very close to each other, all of which are approximately 400 MPa. The lowest flexural strength of $356 \pm 11 \text{ MPa}$ was recorded for the 4C specimen. It can be concluded that by adding 5 wt.% seeds, the strength of 4C glass system increased by 11% while that of 7C glass system was not improved. As for the fracture toughness, the values of the both two glass systems increased with the addition of $\text{Li}_2\text{Si}_2\text{O}_5$ seeds. The toughness of 7C5S sample increased by 15% compared with 7C, reaching the maximum value of $3.48 \pm 0.17 \text{ MPa}\cdot\text{m}^{1/2}$, and that of 4C5S samples increased by 10% compared with 4C, reaching $3.31 \pm 0.19 \text{ MPa}\cdot\text{m}^{1/2}$.

3.5. Translucency characteristics

For dental restorative materials, in addition to the good mechanical properties, they also need to have a certain degree of translucency to simulate the gloss of natural teeth. Fig. 8 compares the contrast ratio

and appearances of the sintered samples with the commercially used IPS e.max (Ivoclar-Vivadent, casting-crystallization treatment at 850 °C for 1 h). The contrast ratio of the specimens in this study was in a range of 0.47-0.68. All the samples except the 7C5S specimen showed clearly underlying black-and-white backing, indicating a high visual degree of translucency.

4. Discussion

Regardless of the different glass systems with or without the seeds addition, $\text{Li}_2\text{Si}_2\text{O}_5$ was detected as the only crystalline phase in Fig. 2. This is because the composition of the original glass powders are very close to that of the added seeds, which satisfies the requirements of $\text{Li}_2\text{O}:\text{SiO}_2 \approx 1:2.4$ to easily form $\text{Li}_2\text{Si}_2\text{O}_5$ crystals without other impurities. The added $\text{Li}_2\text{Si}_2\text{O}_5$ seeds could act as nuclei sites, so the simultaneous effect of homogeneous nucleation from the glass powders and nucleation induced by the seeds increased the degree of crystallization. In addition, P_2O_5 in the 7C LD glass powder can also promote phase separation nucleation [23] so the crystallinities of 7C and 7C5S were higher than that of 4C and 4C5S, respectively. It is worth noting that the crystallinity of 4C5S is 64.0% is higher than that of 7C (60.2%), which means that the seeds can completely replace the nucleating agent of P_2O_5 in promoting crystallization of the glass powder without nucleating agent, and the effect is even better.

The addition of P_2O_5 in 7C glass as the nucleating agent can promote the nucleation and increase the nucleation number, but cause a decrease in the linear growth rate of crystals [23]. Therefore, the grain size of 7C and 7C5S samples decreased. While in the 4C glass powder without P_2O_5 , the mechanism of phase separation nucleation is eliminated so that the nucleation rate decreased resulting in an increase in the grain size of $\text{Li}_2\text{Si}_2\text{O}_5$ crystals, especially in the direction of width. Actually $\text{Li}_2\text{Si}_2\text{O}_5$ crystal is layered silicate structure, due to its higher growth rate along the *c*-axis direction, 'long flake' grains piled up layer by layer so that the anisotropic rod-shaped morphology was formed [45]. In the 4C and 4C5S samples, the number of layers in the width direction increased. Consequently, the lamellar morphology was more obvious and the aspect ratio decreased. While for the 7C glass already containing P_2O_5 , by adding seeds increased the nuclei number and the nuclei will grow in competition with each other, which is not conducive to the formation of large size grains. Therefore it can be concluded that the addition of $\text{Li}_2\text{Si}_2\text{O}_5$ seeds is more effective for improving the microstructure of the glass without the nucleating agent. The TEM observation of 4C5S in Fig. 6 is consistent with the EBSD observation on the microstructure (the inset of Fig. 5(b)), and it is believed that such a microstructure consisted with large crystals induced by seeds embedded in small crystals may contribute to the enhancement of mechanical properties especially the fracture toughness.

The high density in powder sintered glass-ceramics played an important role in the improvement of mechanical properties and translucency. For the sintering of glass-ceramics, both the crystallization and the densification processes tend to meet the simultaneous motivation to decrease the free energy of

glass powder [23]. The relative density decreased with the addition of seeds, which is due to the fact that on one hand, the crystalline phase increases the viscosity of the glass system so that hinders the flow of liquid phase in the sintering process to make the pore difficult to drain out. On the other hand, seeds promoted the nucleation and increased the crystallinities as shown in Fig. 3(b), leading to a high viscosity hinders densification. Moreover, the relative density of 4C and 4C5S were higher than that of 7C and 7C5S, respectively. It is because the 7C glass system has the nucleating agent of P_2O_5 , which could promote phase separation nucleation and increase the crystallinities. Consequently, it can be concluded that the variation of relative density was closely related with the crystallinity, the higher crystallinity and the lower relative density.

Besides the higher relative density, improvement of the mechanical properties of the glass-ceramics can also be obtained with the higher crystallinity and the appropriate morphology of precipitated crystals [4, 46, 47]. From the above we can conclude that the mechanical properties are improved even when the density decreased with the addition of seeds, indicating the unfavorable influence of seeds on the densification can be minimized and made up by microstructure adjustment. For the 4C LD glass, because of its dependence only on surface nucleation, its crystallinity is not high. Moreover, the grain size distribution is concentrative and the aspect ratio is small (see Fig. 4 and Fig. 5), which can not effectively prevent the crack propagation. The effect of these factors is that despite having a high relative density, the strength and fracture toughness of 4C specimen are not ideal. By contrast, the increased strength of 4C5S specimen was mainly due to its increased crystallinity and higher aspect ratio of crystals. Because the thermal expansion coefficient of $Li_2Si_2O_5$ crystalline phase is larger than that of the glass matrix, and thereby the crystals could develop a significant residual compressive stress in the surface of the glass during the cooling process, which strengthens the glass-ceramics [45]. The higher the crystallinity, the more obvious the strengthening effect is. The increased fracture toughness of 4C5S sample might be related to the bimodal grain size distribution and large rod-like grains, which was ascribed to grain bridging and crack deflection. As for the 7C specimen, the high crystallinity, small grain size and large aspect ratio contributed to the excellent mechanical properties. When seeds are added, the density decreased but the crystallinity increased, making the flexure strength remains unchanged. And appearance of few large grains can effectively improve the fracture toughness.

It is reported that the translucency of glass-ceramics is highly dependent on light scattering, and is closely related to the type and the size of the precipitated crystals, the crystallinity and the porosity [4]. For $Li_2Si_2O_5$ glass-ceramics, the refractive index of the crystalline phase and the parent glass are 1.55 and 1.50 [21], respectively, which are very close to each other. The grains size of the samples obtained in this study are all larger than $1 \mu m$, it is beyond the range of strong light scattering ($0.39-0.78 \mu m$) so the scattering effect of the type and size of crystals could be negligible [4]. Therefore, the porosity and crystallinity are the main factors affecting the translucency. The 7C5S sample shows a low relative density ($98.92 \pm 0.22\%$) and a high crystallinity up to $72.08 \pm 2.50\%$, which means the pores become the strong light scattering centers and the glass phase does not meet the requirement (30-40 vol.%) for dental restorative glass-ceramics [4, 21]. Thus, its translucency is poor. By contrast, owing to the higher relative

density (99.10%) and lower crystallinity (64%), the other three groups of samples show a high translucency and their appearance are very close to the IPS e.max. From them we can clearly see the black and white background, and also they have a certain shading ability, similar to many dental restorative materials reported in the literature [7, 21].

Table 3 shows a comparison of the reported properties of lithium disilicate glass-ceramics and the results of the current study. It can be seen that different preparation methods lead to different results. The comprehensive properties in this study was comparable to the heat pressing IPS Empress 2 reported by Hölland et al.[48], but better than other listed materials especially the hot-pressing sintered ones. The point is that compared with other methods, it is easier to add pigments to the glass powder during sintering, which can impart the end product with tooth-like optical properties. In addition, from the energy saving point of view, it is helpful to reduce the melting temperature of the glass system without adding the refractory nucleating agents. Consequently, the seeds was demonstrated to have great potential for improving the properties of glass-ceramics, and the sintered 4C5S specimen features a high potential as dental restorative materials.

Table 3

Comparison of the properties of lithium disilicate glass-ceramics between the published papers and the current study

Authors	Processing	Flexural strength (MPa)	Fracture toughness (MPa·m ^{1/2})	Translucency
our work	Conventional hot-pressing technology	$\sigma = 396 \pm 7$ (three-point)	$K_{IC} = 3.31 \pm 0.19$ (SEVNB)	CR = 0.47 ± 0.02 (0.8 mm thickness)
Ref. [7]	IPS e.max	$\sigma = 462 \pm 15$ (four-point)	$K_{IC} = 3.1 \pm 0.2$ (Double-torsion technique)	CR = 0.28 ± 0.01 (0.5 mm thickness)
Ref. [10]	Conventional hot-pressing technology	$\sigma = 340 \pm 38$ (three-point)	$K_{IC} = 3.5 \pm 0.3$ (SENB)	—
Ref. [5]	Melting and two-stage heat treatment	$\sigma = 562 \pm 107$ (three-point)	$K_{IC} = 3.5 \pm 0.1$ (SENB)	—
Ref. [23]	Conventional hot-pressing technology	$\sigma = 290 \pm 10$ (three-point)	$K_{IC} = 3.3 \pm 0.1$ (SENB)	—
Ref. [27]	Heat-pressed + two stage heat treatment	$\sigma = 308 \pm 25$ (three-point)	—	TP = 21.2 ± 0.4 (0.5 mm thickness)
Ref. [17]	Heat pressing LD GCs	$\sigma = 303 \pm 49$ (three-point)	$K_{IC} = 3.0 \pm 0.65$ (Indentation method)	—
Ref. [48]	Heat pressing IPS Empress 2	$\sigma = 400 \pm 40$ (three-point)	$K_{IC} = 3.3 \pm 0.3$ (SENB)	CR = 0.55 (1 mm thickness)
Ref. [4]	Melting and two-stage heat treatment	$\sigma = 310$ (three-point)	—	CR = 0.51 (0.5 mm thickness)

SENB: Single edge notched beam.

TP: Translucency parameter.

CR: Contrast ratio.

5. Conclusions

A high-performance lithium disilicate glass-ceramics was successfully hot-pressed by adding $\text{Li}_2\text{Si}_2\text{O}_5$ crystal seeds to different two glass systems. After adding seeds, the crystallinity increased, the relative density decreased, and the samples show a bimodal microstructure in which some large elongated $\text{Li}_2\text{Si}_2\text{O}_5$ grains with high aspect ratio epitaxial grew along the seeds, and fine grains directly crystallized from the parent glass powder. The role of heterogeneous nucleation by seeds was more effective in the 4C glass powder without the nucleating agent of P_2O_5 , so the grain size distribution of 4C5S sample was more dispersed. Accordingly, although the 4C5S specimen did not possess the highest relative density ($99.13 \pm 0.07\%$), it demonstrated the best comprehensive properties with a good flexural strength (396 ± 7 MPa), improved fracture toughness (3.31 ± 0.19 MPa·m^{1/2}) and comparable translucency as IPS e.max. The high crystallinity and interlocking microstructure contributed to high strength, the epitaxial grew elongated $\text{Li}_2\text{Si}_2\text{O}_5$ crystals along the seeds led to high fracture toughness, and the proper content of glass phase helped gain a good translucency. The high-performance glass-ceramics with seeds is promising for dental restorative applications especially three-unit posterior bridges, and offers a novel route for preparing toughened glass-ceramics without sacrifice other properties.

Declarations

Acknowledgments

This work was supported by the National Natural Science Foundation of China (Grant No. 51702193, 51502165), the General Project in Industrial Area of Shaanxi Province (Grant No. 2020GY-281), the Natural Science Foundation of Shaanxi Provincial Department of Education (Grant No. 20JK0525), the Shaanxi Provincial Education Department serves Local Scientific Research Plan (Grant No. 20JC008) and the Scientific Research Fund of Shaanxi University of Science & Technology (Grant No. BJ16-20, BJ16-21).

References

- [1] Thieme K, Avramov I, Ruessel C. The mechanism of deceleration of nucleation and crystal growth by the small addition of transition metals to lithium disilicate glasses. *Sci Rep* 2016, 6: 1-16.
- [2] Gaddam A, Fernandes HR, Tulyaganov DU, *et al.* Role of manganese on the structure, crystallization and sintering of non-stoichiometric lithium disilicate glasses. *Rsc Adv* 2014, 4: 13581-13592.
- [3] Zhao T, Qin Y, Wang B, *et al.* Improved densification and properties of pressureless-sintered lithium disilicate glass-ceramics. *Mat Sci Eng A-Struct* 2015, 620: 399-406.

- [4] Wang F, Gao J, Wang H, *et al.* Flexural strength and translucent characteristics of lithium disilicate glassceramics with different P_2O_5 content. *Mater Des* 2010, 31: 3270-3274.
- [5] Huang SF, Li Y, Wei SH, *et al.* A novel high-strength lithium disilicate glass-ceramic featuring a highly intertwined microstructure. *J Eur Ceram Soc* 2017, 37: 1083-1094.
- [6] Lien W, Roberts HW, Plate JA, *et al.* Microstructural evolution and physical behavior of a lithium disilicate glass-ceramic. *Dent Mater* 2015, 31: 928-940.
- [7] Zhang F, Reveron H, Spies BC, *et al.* Trade-off between fracture resistance and translucency of zirconia and lithium-disilicate glass ceramics for monolithic restorations. *Acta Biomater* 2019, 91: 24-34.
- [8] Tinschert J, Natt G, Mautsch W, *et al.* Fracture resistance of lithium disilicate-, alumina-, and zirconia-based three-unit fixed partial dentures: A laboratory study. *Int J Prosthodont* 2001, 14: 231-238.
- [9] Harada K, Raigrodski AJ, Chung KH, *et al.* A comparative evaluation of the translucency of zirconias and lithium disilicate for monolithic restorations. *J Prosthet Dent* 2016, 116: 257-263.
- [10] Huang X, Zheng X, Zhao G, *et al.* Microstructure and mechanical properties of zirconia-toughened lithium disilicate glass-ceramic composites. *Mater Chem Phys* 2014, 143: 845-852.
- [11] Thieme K, Ruessel C. Nucleation and growth kinetics and phase analysis in zirconia-containing lithium disilicate glass. *J Mater Sci* 2015, 50: 1488-1499.
- [12] Schweiger M, Frank M, Von Clausbruch SC, *et al.* Microstructure and properties of a composite system for dental applications composed of glass-ceramics in the SiO_2 - Li_2O - ZrO_2 - P_2O_5 system and ZrO_2 -ceramic (TZP). *J Mater Sci* 1999, 34: 4563-4572.
- [13] Elsaka SE, Elnaghy AM. Mechanical properties of zirconia reinforced lithium silicate glass-ceramic. *Dent Mater* 2016, 32: 908-914.
- [14] Bergamo ETP, Bordin D, Ramalho IS, *et al.* Zirconia-reinforced lithium silicate crowns: Effect of thickness on survival and failure mode. *Dent Mater* 2019, 35: 1007-1016.
- [15] Zhang NZ, Anusavice KJ. Effect of alumina on the strength, fracture toughness, and crystal structure of fluorcanasite glass-ceramics. *J Am Ceram Soc* 1999, 82: 2509-2513.
- [16] Tzeng JM, Duh JG, Chung KH, *et al.* Al_2O_3 -modified and ZrO_2 -modified dental glass-ceramics. *J Mater Sci* 1993, 28: 6127-6135.
- [17] Guazzato M, Albakry M, Ringer SP, *et al.* Strength, fracture toughness and microstructure of a selection of all-ceramic materials. Part I. Pressable and alumina glass-infiltrated ceramics. *Dent Mater* 2004, 20: 441-448.

- [18] Kotoul M, Pokluda J, Sandera P, *et al.* Toughening effects quantification in glass matrix composite reinforced by alumina platelets. *Acta Mater* 2008, 56: 2908-2918.
- [19] Xia L, Wang XY, Wen GW, *et al.* Influence of brick pattern interface structure on mechanical properties of continuous carbon fiber reinforced lithium aluminosilicate glass-ceramics matrix composites. *J Eur Ceram Soc* 2012, 32: 409-418.
- [20] Sarno RD, Tomozawa M. Toughening mechanisms for a zirconia-lithium aluminosilicate glass-ceramic. *J Mater Sci* 1995, 30: 4380-4388.
- [21] Heffernan MJ, Aquilino SA, Diaz-Arnold AM, *et al.* Relative translucency of six all-ceramic systems. Part II: Core and veneer materials. *J Prosthet Dent* 2002, 88: 10-15.
- [22] Gonzaga CC, Okada CY, Cesar PF, *et al.* Effect of processing induced particle alignment on the fracture toughness and fracture behavior of multiphase dental ceramics. *Dent Mater* 2009, 25: 1293-1301.
- [23] Wen G, Zheng X, Song L. Effects of P₂O₅ and sintering temperature on microstructure and mechanical properties of lithium disilicate glass-ceramics. *Acta Mater* 2007, 55: 3583-3591.
- [24] Denry IL, Holloway JA. Effect of post-processing heat treatment on the fracture strength of a heat-pressed dental ceramic. *J Biomed Mater Res B* 2004, 68B: 174-179.
- [25] Albakry M, Guazzato M, Swain MV. Influence of hot pressing on the microstructure and fracture toughness of two pressable dental glass-ceramics. *J Biomed Mater Res B* 2004, 71B: 99-107.
- [26] Yuan K, Wang F, Gao J, *et al.* Effect of zircon-based tricolor pigments on the color, microstructure, flexural strength and translucency of a novel dental lithium disilicate glass-ceramic. *J Biomed Mater Res B* 2014, 102: 98-107.
- [27] Yuan K, Wang F, Gao J, *et al.* Effect of sintering time on the microstructure, flexural strength and translucency of lithium disilicate glass-ceramics. *J Non-Cryst Solids* 2013, 362: 7-13.
- [28] Zheng X, Wen G, Song L, *et al.* Effects of P₂O₅ and heat treatment on crystallization and microstructure in lithium disilicate glass ceramics. *Acta Mater* 2008, 56: 549-558.
- [29] Molla AR, Chakradhar RPS, Kesavulu CR, *et al.* Microstructure, mechanical, EPR and optical properties of lithium disilicate glasses and glass-ceramics doped with Mn²⁺ ions. *J Alloy Compd* 2012, 512: 105-114.
- [30] Thompson JY, Anusavice KJ, Balasubramaniam B, *et al.* Effect of microcracking on the fracture toughness and fracture surface fractal dimension of lithia-based glass-ceramics. *J Am Ceram Soc* 1995, 78: 3045-3049.

- [31] Zhao T, Li AJ, Qin Y, *et al.* Influence of SiO₂ contents on the microstructure and mechanical properties of lithium disilicate glass-ceramics by reaction sintering. *J Non-Cryst Solids* 2019, 512: 148-154.
- [32] Zhao T, Qin Y, Zhang P, *et al.* High-performance, reaction sintered lithium disilicate glass-ceramics. *Ceram Int* 2014, 40: 12449-12457.
- [33] Hirao K, Nagaoka T, Brito ME, *et al.* Microstructure control of silicon nitride by seeding with rodlike β -silicon nitride particles. *J Am Ceram Soc* 1994, 77: 1857-1862.
- [34] Pyzik AJ, Beaman DR. Microstructure and properties of self-reinforced silicon nitride. *J Am Ceram Soc* 1993, 76: 2737-2744.
- [35] Yoshizawa Y, Toriyama M, Kanzaki S. Preparation of high fracture toughness alumina sintered bodies from bayer aluminum hydroxide. *J Ceram Soc Jpn* 1998, 106: 1172-1177.
- [36] Chen IW, Rosenflanz A. A tough SiAlON ceramic based on α -Si₃N₄ with a whisker-like microstructure. *Nature* 1997, 389: 701-704.
- [37] Peillon FC, Thevenot F. Microstructural designing of silicon nitride related to toughness. *J Eur Ceram Soc* 2002, 22: 271-278.
- [38] Becher PF, Hsueh CH, Angelini P, *et al.* Toughening behavior in whisker-reinforced ceramic matrix composites. *J Am Ceram Soc* 1988, 71: 1050-1061.
- [39] Wang B, Yang J, Guo R, *et al.* Microstructure and property enhancement of silicon nitride-barium aluminum silicate composites with β -Si₃N₄ seed addition. *J Mater Sci* 2009, 44: 1351-1356.
- [40] Höland W, Apel E, van't Hoen C, *et al.* Studies of crystal phase formations in high-strength lithium disilicate glass-ceramics. *J Non-Cryst Solids* 2006, 352: 4041-4050.
- [41] Soares PC, Zanotto ED, Fokin VM, *et al.* TEM and XRD study of early crystallization of lithium disilicate glasses. *J Non-Cryst Solids* 2003, 331: 217-227.
- [42] Fernandes HR, Tulyaganov DU, Goel A, *et al.* Effect of K₂O on structure-property relationships and phase transformations in Li₂O-SiO₂ glasses. *J Eur Ceram Soc* 2012, 32: 291-298.
- [43] Thieme K, Rüssel C. Nucleation inhibitors-the effect of small concentrations of Al₂O₃, La₂O₃ or TiO₂ on nucleation and crystallization of lithium disilicate. *J Eur Ceram Soc* 2014, 34: 3969-3979.
- [44] Daguano JKMF, Suzuki PA, Strecker K, *et al.* Development and characterization of 3CaO·P₂O₅-SiO₂-MgO glass-ceramics with different crystallization degree. *J Adv Ceram* 2013, 2: 378-388.
- [45] Höland W, Beall GH. Glass-Ceramic Technology. Second ed. New Jersey (America): John Wiley & Sons, Inc., 2012.

[46] Tulyaganov DU, Agathopoulos S, Kansal I, *et al.* Synthesis and properties of lithium disilicate glass-ceramics in the system $\text{SiO}_2\text{-Al}_2\text{O}_3\text{-K}_2\text{O-Li}_2\text{O}$. *Ceram Int* 2009, 35: 3013-3019.

[47] Zhang JY, Zhan H, Fu ZY, *et al.* In-situ synthesis and sintering of mullite glass composites by SPS. *J Adv Ceram* 2014, 3: 165-170.

[48] Höland W, Schweiger M, Frank M, *et al.* A comparison of the microstructure and properties of the IPS Empress[®]2 and the IPS Empress[®] glass-ceramics. *J Biomed Mater Res* 2000, 53: 297-303.

Figures

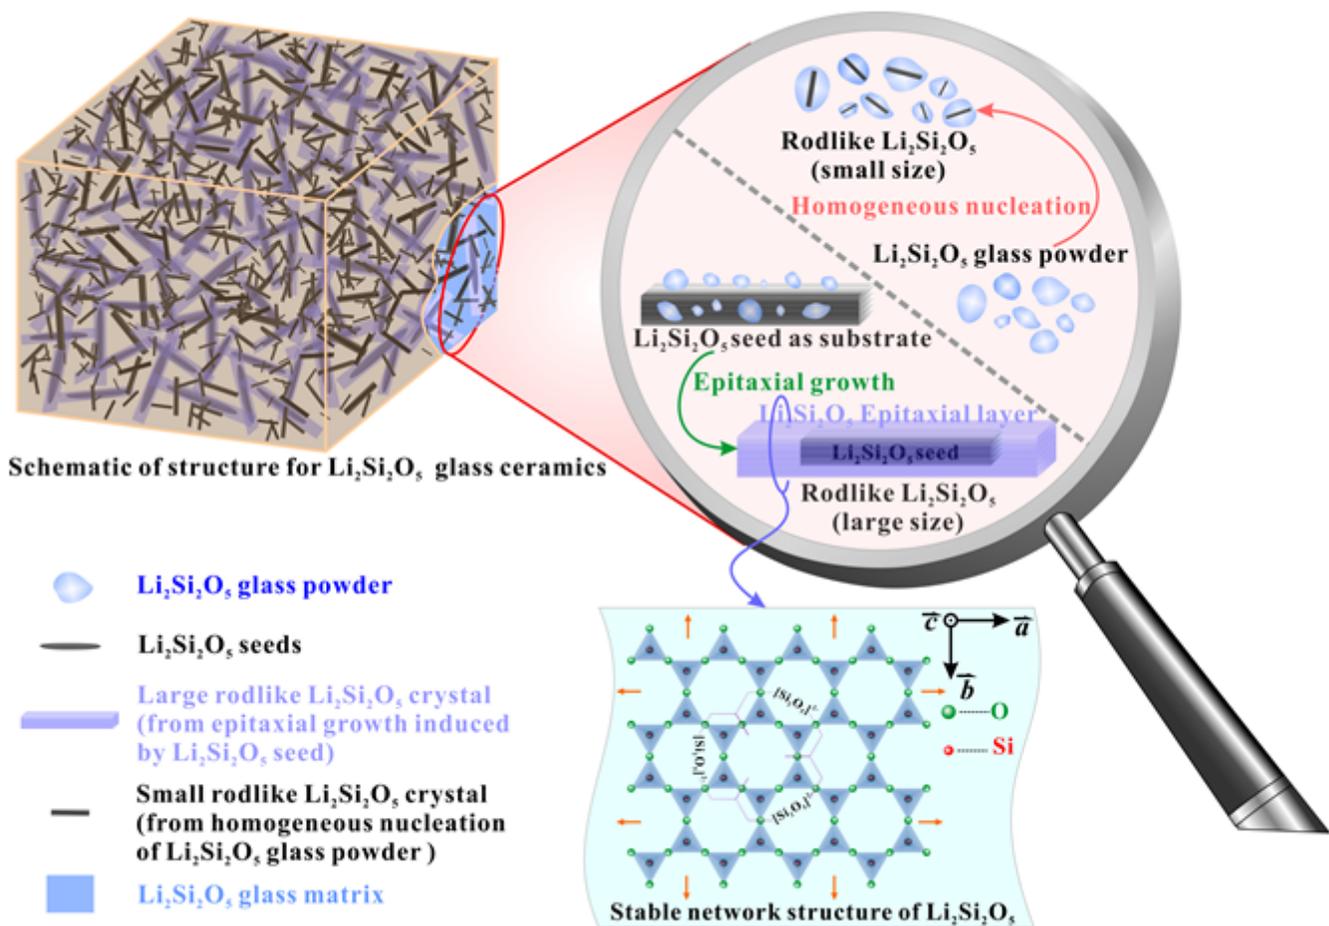


Figure 1

Microstructure design of the seeds-toughening lithium disilicate glass-ceramics.

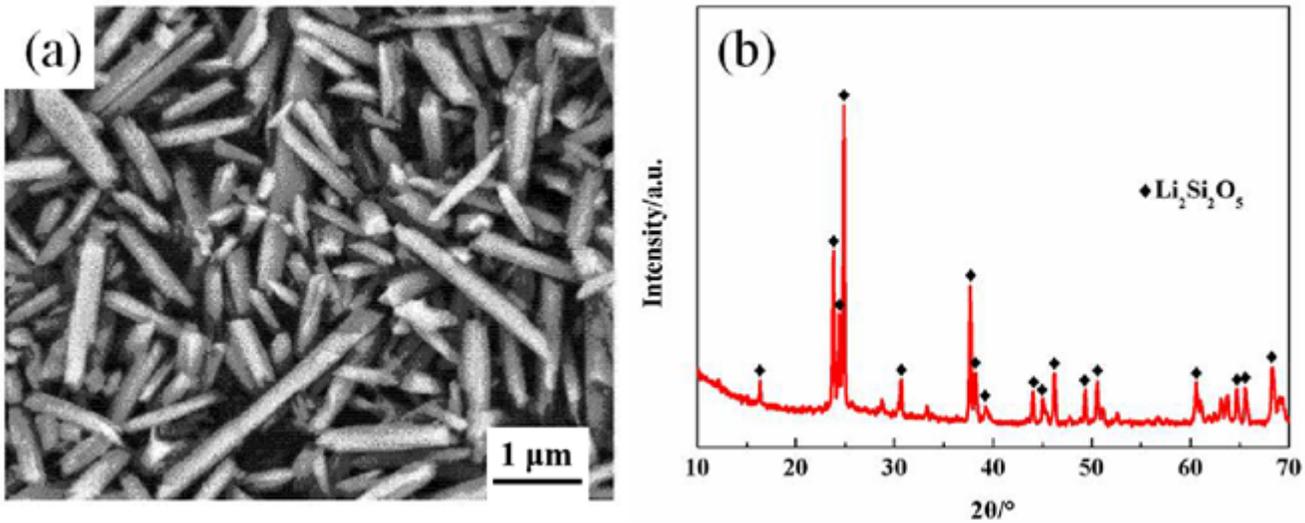


Figure 2

The SEM images (a) and XRD patterns (b) of the Li₂Si₂O₅ seeds synthesized by solid-state reaction

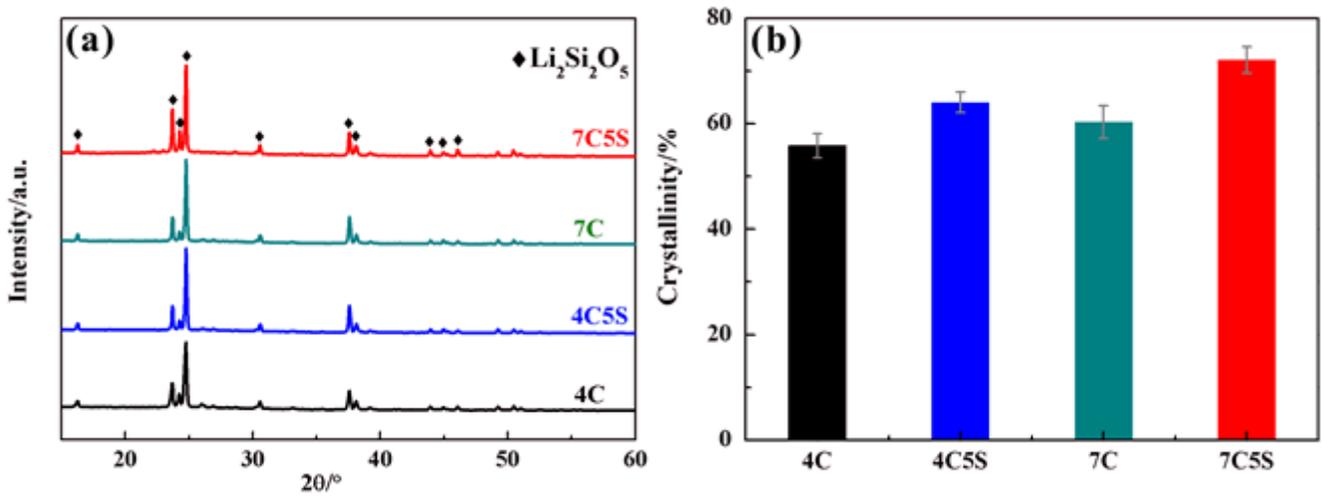


Figure 3

The XRD patterns (a) and crystallinity (b) of the Li₂Si₂O₅ glass-ceramics with different compositions hot-pressed at 850 °C for 0.5 h. (Li₂Si₂O₅: ICDD card 01-040-0376)

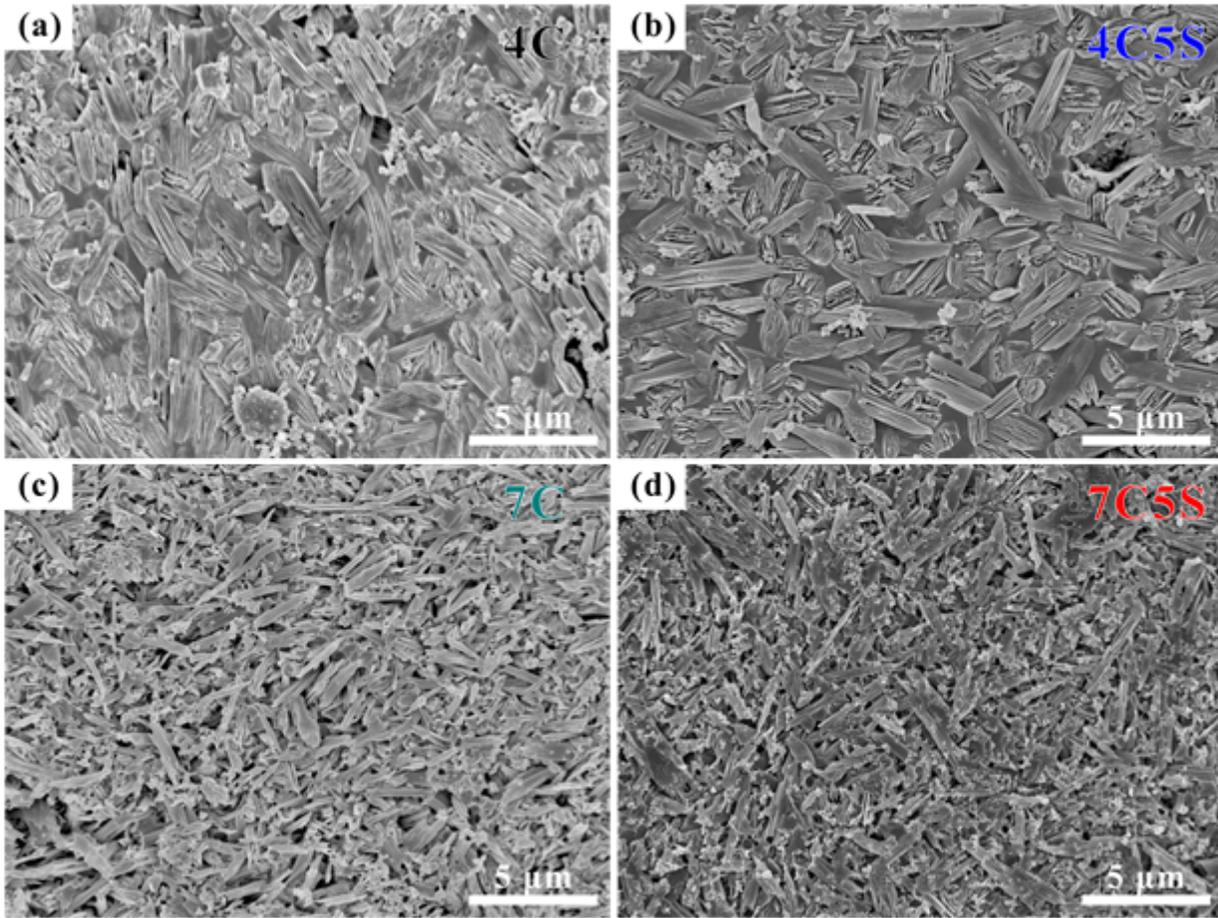


Figure 4

The SEM images of the $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics with different compositions hot-pressed at 850 °C for 0.5 h, (a) 4C; (b) 4C5S; (c) 7C; (d) 7C5S.

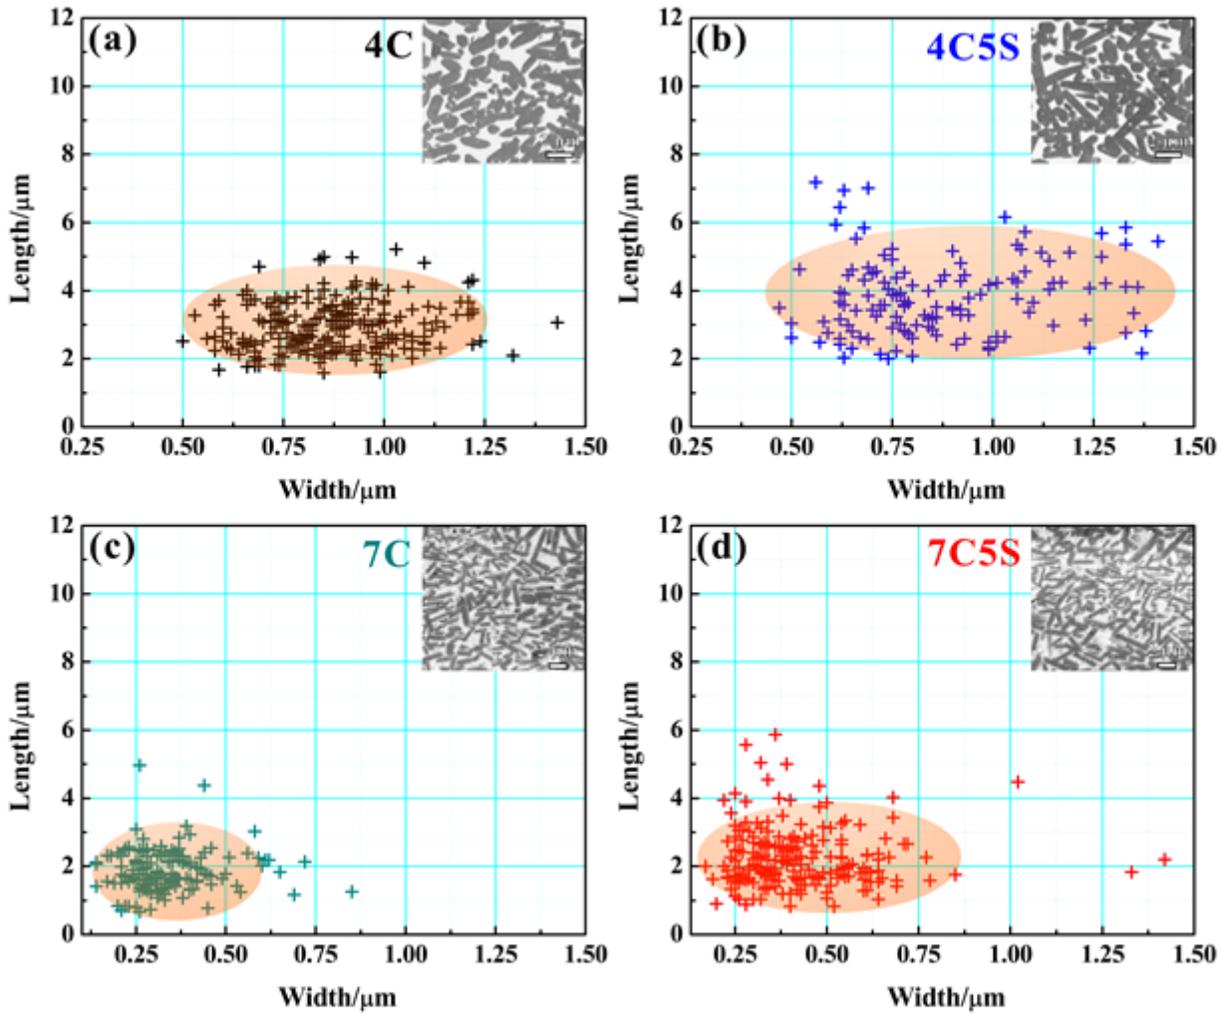


Figure 5

The grain size distribution of the Li₂Si₂O₅ glass-ceramics with different compositions hot-pressed at 850 °C for 0.5 h, (a) 4C; (b) 4C5S; (c) 7C; (d) 7C5S. The insets are the corresponding EBSD micrographs.

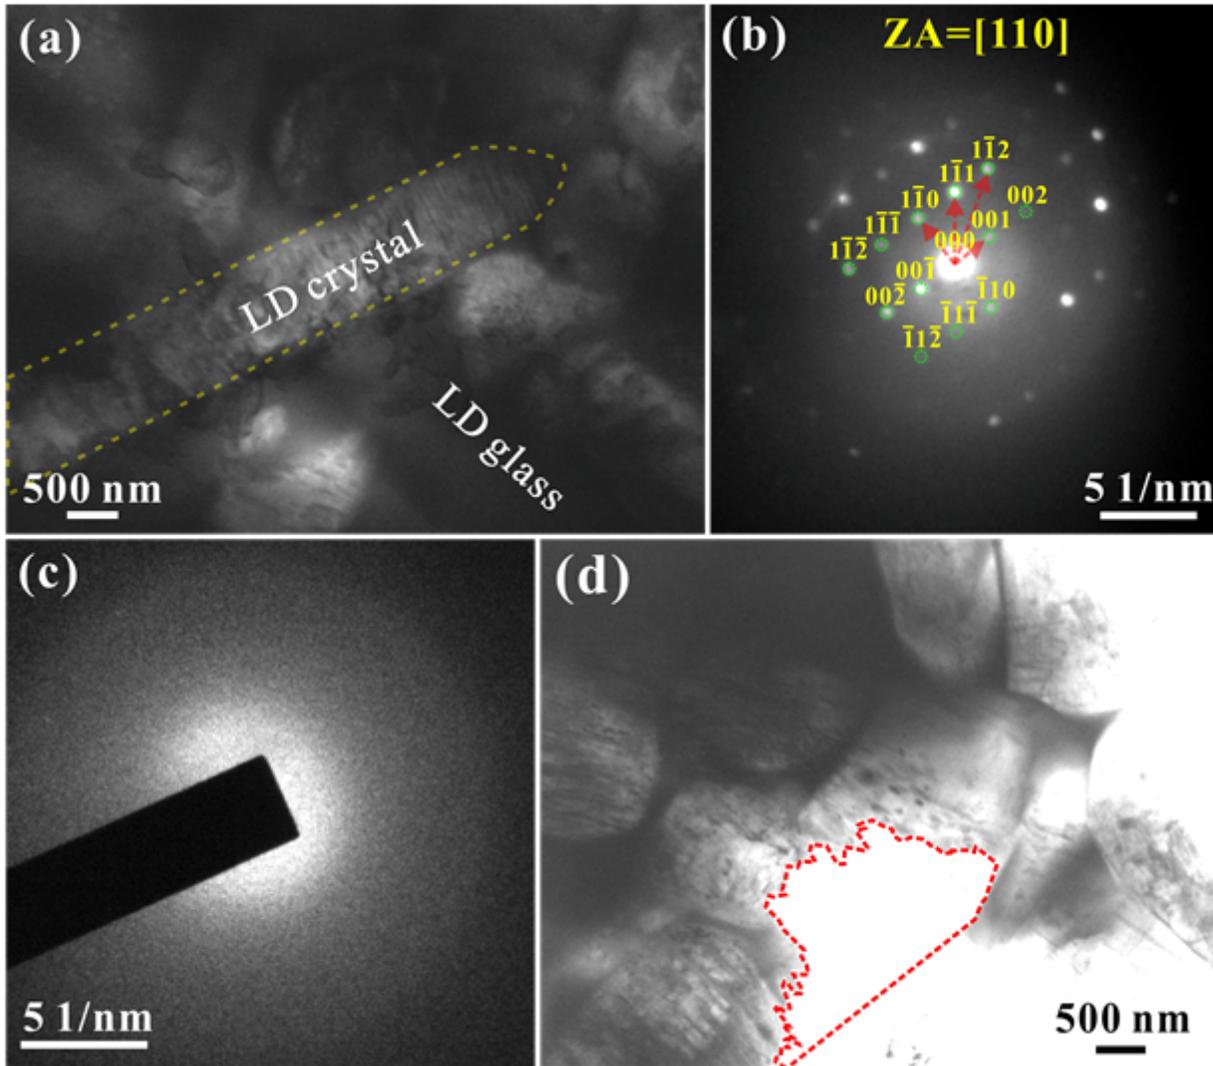


Figure 6

The TEM micrograph of the $\text{Li}_2\text{Si}_2\text{O}_5$ glass-ceramics with 4C5S composition hot-pressed at $850\text{ }^\circ\text{C}$ for 0.5 h. (a), (d) bright field images; (b) corresponding electron diffraction pattern of the LD crystal in (a), indexed as the $\text{Li}_2\text{Si}_2\text{O}_5$ phase in the $[110]$ direction; (c) corresponding electron diffraction pattern of the LD glass in (a).

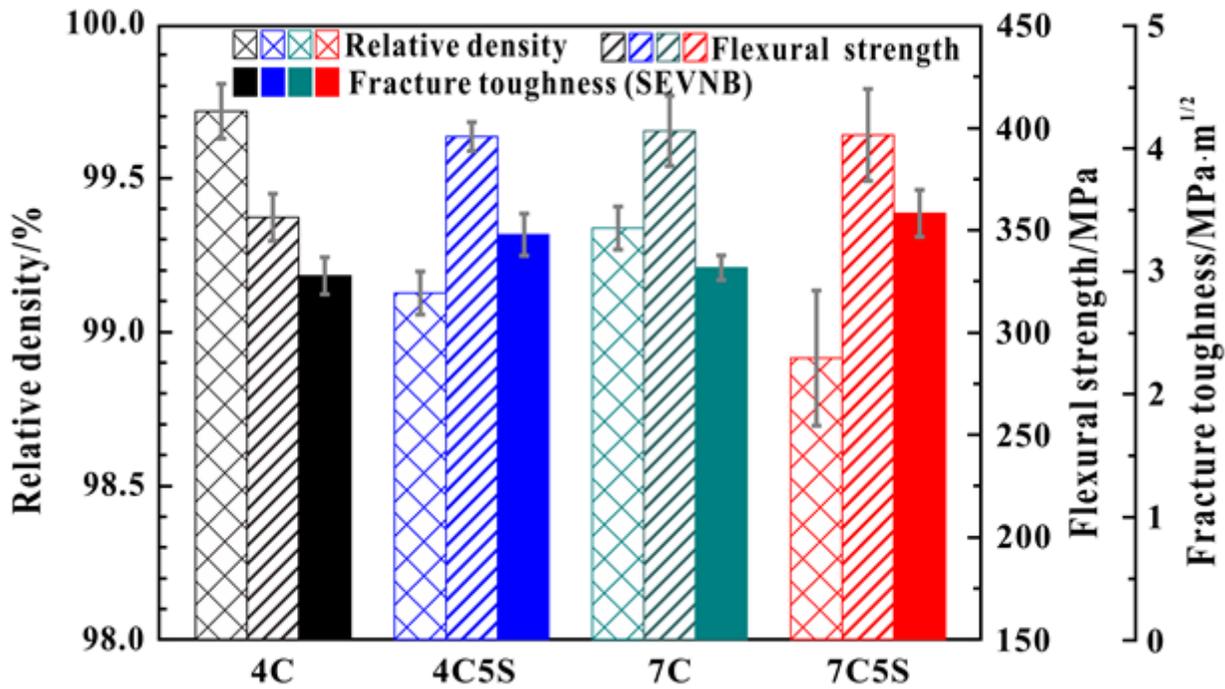


Figure 7

The relative density, three-point flexural strength and fracture toughness of the Li₂Si₂O₅ glass-ceramics with different compositions.

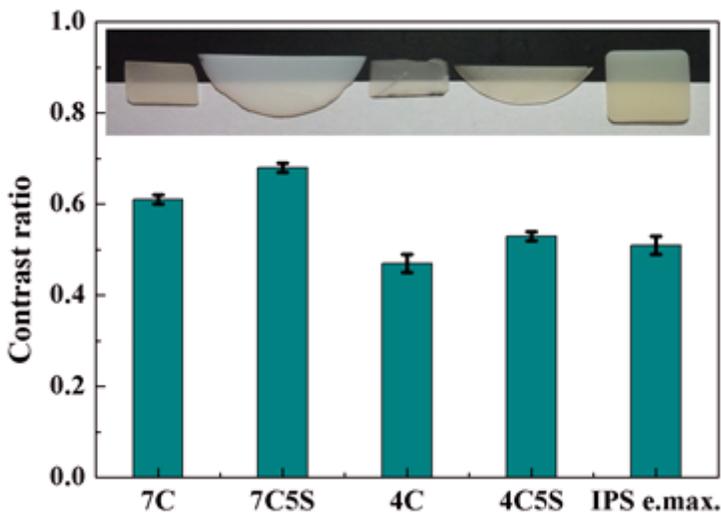


Figure 8

The contrast ratio and appearance of the Li₂Si₂O₅ glass-ceramics with different compositions compared with the IPS e.max specimen on a black-and-white backing with reflected light (the samples with 0.8 mm thickness were placed directly on the backing).