

Influence Of Geometric Attribute On Friction Coefficient In Sheet Metal Stamping

Dewang Zhao (✉ dewangzhao@qq.com)

Dalian University of Technology

Kunmin Zhao

Dalian University of Technology

Huaihao Song

Dalian University of Technology

Daxin Ren

Dalian University of Technology

Ying Chang

Dalian University of Technology

Original Article

Keywords: friction coefficient, geometric attribute, process parameter, sheet metal stamping

Posted Date: June 8th, 2021

DOI: <https://doi.org/10.21203/rs.3.rs-572476/v1>

License:  This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

Influence of Geometric Attribute on Friction Coefficient in Sheet Metal Stamping

Dewang Zhao ^{a,b,*}, Kunmin Zhao ^{a,b,d,*}, Huaihao Song ^c, Daxin Ren ^a, Ying Chang ^a

^a School of Automotive Engineering, Dalian University of Technology, Dalian 116024, China

^b School of Mechanical Engineering, Anhui University of Science and Technology, Huainan 232063, China

^c Institute of Industrial and Equipment Technology, Hefei University of Technology, Hefei 230009, China

^d Zhejiang Hezhong New Energy Automobile Co. Ltd. (Hozon Auto Company), Tongxiang 314500, China

* Corresponding author at 2 Ling Gong Road, Dalian, 116024, China.

E-mail: zhaokunmin@honzonauto.com (Kunmin Zhao)

dewangzhao@qq.com (Dewang Zhao)

Abstract: This paper presents a test device to explore the influence of geometric attribute of the contact surface on friction coefficient along with sliding speed and contact pressure. Friction tests were conducted on a third-generation high strength steel QP980. The friction coefficients for different surface curvatures, contact pressures and sliding speeds were calculated and the influences of these factors were analyzed. The formula for calculating the friction coefficients between curved contact surfaces was derived. The relationship between bending induced surface roughness increase and friction coefficient was established. An enhanced friction coefficient model with pressure, velocity and curvature dependence was proposed. The enhanced friction model was applied to simulate the stamping of an automotive part and a better correlation was achieved.

Keywords: friction coefficient; geometric attribute; process parameter; sheet metal stamping;

1. Introduction

Sheet metal stamping is an efficient and widely used manufacturing process in the automobile industry. Recent years have seen increasing applications of advanced high strength steels and aluminum alloys in automobile bodies for weight reduction. The friction between sheet metal and die during the stamping process has a great impact on formability, surface quality and die wear. The

Coulomb friction model has been commonly used to describe the friction condition in numerical simulations of sheet metal stamping, which in its general form allows the friction coefficient to be defined in terms of sliding speed, contact pressure, temperature at the contact point, and other field variables. The friction coefficient is also influenced by the contact surface's shape and topography, material's hardness, and lubrication condition. However, in conventional stamping operations, the dies are made according to corporate or industry standards with specifications on material hardness and surface roughness, the to-be-stamped sheet metals have pre-determined surface topography, and lubrication oil is not preferred unless otherwise necessitated by severe poor formability. Therefore, this study focused on the influence of a geometric attribute of the contact surface, i.e. the surface curvature, together with two process variables, sliding speed and contact pressure, on the friction coefficient.

Evin et al [1] used a friction simulator (strip drawing test) that has a flat blank holder and a roller to evaluate the friction in different contact areas of bar and lubricated specimens under one drawing speed and various contact pressures. The friction coefficient on curved contact surface (the roller) was found to be lower than the one on flat contact surface (the blank holder) by the simple calculation method but higher by the slope method. It appears that only one size of roller was used in their study and the roller's radius was not mentioned. Lemu et al [2] studied the impact of surface roughness on friction coefficient through bending under tension tests with a fixed roller of 20 mm in diameter. The force to overcome bending and unbending of the specimen over the roller was not explicitly subtracted from the pulling force when calculating the friction coefficient, although it should be. Wang et al [3] evaluated the pressure dependence of friction coefficient via pin-on-disc wear tests, where a bare 0.9 mm thick DP780 steel was used as the pin specimens and a cold-worked DC53 tool steel was machined into the circular disc specimen to prevent material plowing. The results showed a decrease in friction coefficient with an increase in normal contact pressure and a significant improvement in springback prediction using a pressure-dependent friction model. Li et al [4] pointed out that friction coefficient decreases with an increase in sliding speed and contact pressure. Kim et al [5] conducted draw-bend tests on AA5754 sheets applied with Parker lubricant to study the contact pressure and sliding speed dependencies of the friction coefficient, and revealed that the friction coefficient decreases with sliding speed, but increases with contact pressure, contrary to what Wang and Li [3,4] had pointed out, probably because of the different lubrication conditions. The fact that

surface coating and lubrication condition complicate the pressure dependence of friction coefficient has been noticed by Evin et al [1]. Furthermore, the geometric influence of the different sized pins on the friction coefficient was not considered by Kim et al [5]. A one-side-contact friction test device was used by Ma et al [6] to measure the friction coefficients of 0.95 mm thick SUS304L lubricated by press oil. The sliding distance was found to be an influencing factor for the friction coefficient in addition to the sliding speed. Dilmeç et al [7] presented a test apparatus which can determine the friction coefficient for both the flange and the radius contact regions with a single experiment. The effects of die radius, surface roughness of the tools, drawing speed, blank holder force, and lubrication on the dynamic friction coefficient were investigated by using ANOVA analysis. The friction coefficient in the die radius region was found to be significantly different from the one in the flange region, e.g. 0.43 versus 0.25 for dry condition, and much less sensitive to the geometric and process parameters. The contact pressure in the die radius region, although directly related to the blank holder force, was not explicitly calculated; otherwise, a clearer relationship between the friction coefficient and the contact pressure in the curved contact region could be established. The bending and unbending force was not but should be excluded from the total punch force when calculating the friction coefficient. Trzepieciński et al [8] pointed out that the directional topography of sheet metals caused by the rolling process results in diversification of friction coefficient according to the sliding orientation to the rolling direction.

While the influence of contact pressure and sliding speed on friction coefficient has been intensively investigated [1-8], the study on the influence of the contact surface's geometric attribute in terms of curvature is limited. Literature [1,5,7] reported different friction coefficients between flat surfaces and between curved surfaces, but did not analyze the root cause in depth. The main purpose of this study was to investigate how the geometric attribute of the contact surface impacts the friction coefficient. To experimentally determine the friction coefficients, a universal test machine based mechanical driven device that can explore the influence of geometric attribute of the contact surface on friction coefficient along with sliding speed and contact pressure was designed and manufactured. Friction tests were conducted on a third-generation advanced high strength steel QP980 because of its superior strength and formability and its increasing attention in the automotive industry [9]. The friction coefficients between a pair of flat surfaces and three pairs of curved surfaces under three contact pressures and three sliding speeds were calculated and the influences of these factors were

analyzed. Additionally, finite element modeling was performed to verify the theoretical formula derived for calculating the bending/unbending forces. Finally, the impact of surface curvature on friction was correlated to the change of surface roughness caused by bending based on microscopic observation and quantification.

2. Experiment

2.1 Design of friction device

The drawing of a new friction test device is shown in Fig. 1 (front view in Fig. 2). The six bolts fix the base plate on the worktable of a universal test machine. The two vertical plates are inserted into the slots of the base plate. The guides have external threads at one end, matching the internal threads of the holes in vertical plate 3. The other end of the guides protruding from vertical plate 4 are bolted with nuts. The guides not only play a guiding role, but also help prevent the vertical plates from being deformed under screw drive loading. Three sliding plates and four springs are mounted on the guides. The springs are placed between sliding plates 6 and 7. A male die and a female die are installed on sliding plates 5 and 6, respectively. A long rectangle specimen is clamped between the male and female dies. The top end of the specimen is pulled by the head of the universal test machine. The middle round hole in sliding plate 7 is engraved with an internal thread, which matches the thread on the screw rod to form a screw drive. The screw rod is rotated by the handle, pushing sliding plate 7 to compress the springs, which transmit the force to sliding plate 6. The female die on sliding plate 6 transmits the force to the male die on sliding plate 5. The function of the spacer is to adjust the distance between the dies to adapt for specimens of different thicknesses so that they coincide with the center line of the universal test machine to avoid eccentric loading. The spacer is support by the pallet, which is embedded in vertical plate 4.

Four sets of male and female dies with different contact surface shapes were designed and manufactured, as shown in Fig. 3. One set of dies has a flat surface, and the other three sets have curved surfaces with a radius of 15, 20 and 30 mm on the male dies, respectively. The corresponding female dies have a radius of 16, 21 and 31 mm respectively to accommodate the 1 mm thick specimen. The overall dimensions of each set of dies are 100 mm long, 62.5 mm wide and 15 mm high.

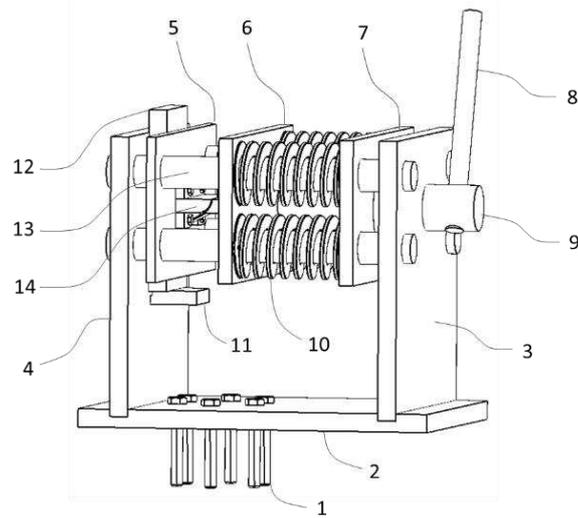


Fig. 1. Drawing of the friction test device

1. Bolts 2. Base plate 3-4. Vertical plates 5-7. Sliding plates 8. Handle 9. Screw rod
 10. Springs (four) 11. Pallet 12. Spacer 13. Guides (four) 14. Specimen

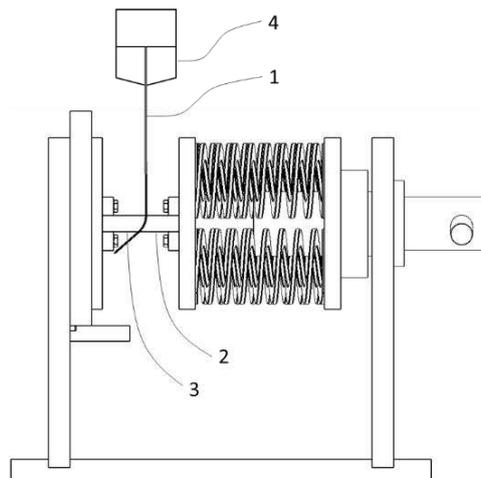


Fig. 2. Front view of the friction test device

1. Specimen 2. Female die 3. Male die 4. Head of the universal test machine

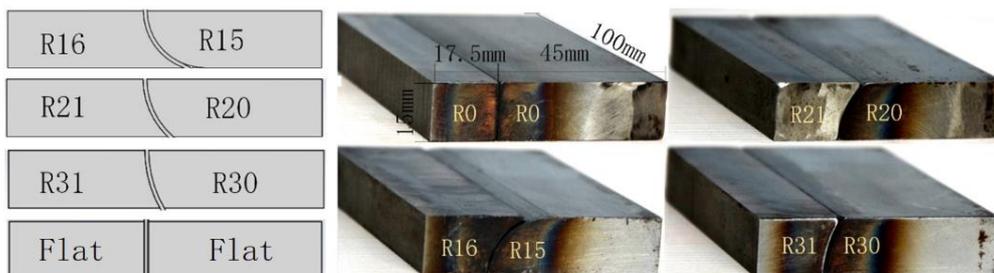


Fig. 3. Geometric attributes of the clamping dies

2.2 Materials

As-received bare 1.0 mm thick QP980 advanced high strength steel produced by Baoshan Iron & Steel Co. Ltd. was used in this experiment. The chemical composition is given in Table 1 and the mechanical properties are given in Table 2. The steel sheet was cut to 180 mm long and 30 mm wide rectangular specimens with the length aligned with the sheet's rolling direction. After the specimens were prepared, the corner burrs were removed and the surface was treated with acetone to maintain surface finish. The treated specimens were properly stored to ensure that the surface was clean and free from contamination.

The dies to clamp the specimens are made of Cr12MoV, a tool steel that has the advantages of high hardness, small heat treatment deformation, good wear resistance and good hardenability. The dies were quenched at 1100 °C for 30 minutes and tempered twice at 200 °C to a surface hardness of 60 HRC. The surface roughness Ra of these dies is approximately 0.6 μm , which meets the standard used in automotive stamping industry.

No lubricant or stamping oil was applied to the specimens and dies; therefore, the effect of lubrication was not evaluated in this experiment.

Table 1 QP980 main chemical compositions (mass %)

C	Si	Mn	P	S	Ti	N	Fe
≤ 0.17	≤ 1.7	≤ 2.1	≤ 0.008	≤ 0.002	≤ 0.006	≤ 0.003	Bal

Table 2 QP980 basic mechanical properties

Material	Yield strength (MPa)	Tensile strength (MPa)	Uniform elongation (%)	Work hardening index (n)	Anisotropic coefficient (r)
QP980	689	1054	17.3	0.179	0.758

2.3 Test procedures and results

The friction tests were carried out on a SANS electronic universal test machine (shown in Fig. 4), which has a rated maximum load of 100 KN and a real-time data acquisition system to collect the force, speed and displacement data. Pulling speeds of 2, 5 and 10 mm/s were applied in the tests.

The clamping force on the specimen is determined through the spring stiffness and the screw rod advancement distance. Although the stiffness of each single spring is known, the stiffness of the screw drive assembly consisting of springs, sliding plates, guides and screw rod needs to be calibrated following this procedure: remove the dies and place a force transducer between the sliding plates (5 and 6 in Fig. 1); turn the screw rod to compress the springs, generating force on plate 6; record the force and the advancement distance to calculate the overall stiffness of the assembly. According to the thread characteristic of the screw rod, the corresponding advancement distance for each turn of the rod, i.e. the amount of spring compression, can be obtained. Thus, the force between the two sliding plates generated by each turn of the screw rod was determined. During the test, the number of turns of the screw rod was counted to calculate the clamping force on the specimen. Clamping forces of 5.55, 6.92 and 8.23 KN were applied in the tests.

There are 36 combinations among the 4 geometric attributes (flat, R30, R20 and R15), 3 clamping forces (5.55, 6.92 and 8.23 KN), and 3 pulling speeds (2, 5 and 10 mm/s). Each case was tested three times to ensure repeatability. The recorded pulling force versus displacement curves for all cases are plotted in Fig. 5-8.

It can be seen that in all cases the pulling force increases initially until the specimen starts to slide, then decreases and remains stable as the specimen continues sliding over the dies. It is not a surprise that the pulling force increases with clamping force, since friction force is positively related to normal force. For a given die radius and clamping force, a higher pulling speed lowers the pulling force because of the negative relationship between sliding speed and friction coefficient as pointed out by the literature. The geometric attribute of the contact surface apparently has a positive impact on the pulling force, i.e. the larger the curvature of the contact surface the greater the pulling force, partially caused by the difference in bending/unbending force and partially by the difference in friction coefficient, which will be examined in detail later.

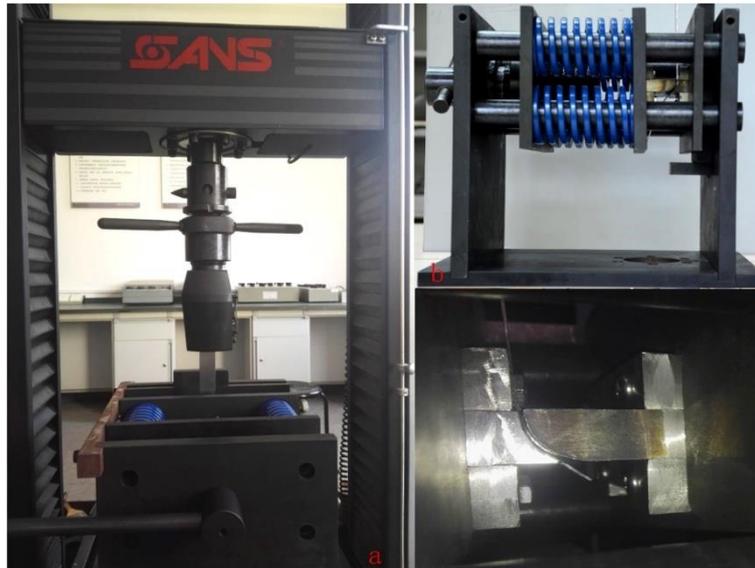


Fig. 4. Friction device set up on a SANS universal test machine

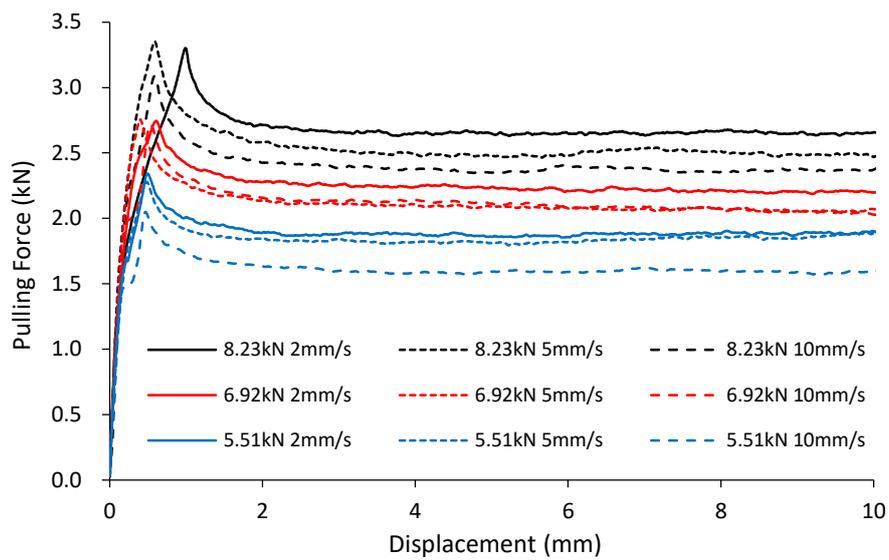


Fig. 5. Pulling force versus displacement curves for flat die

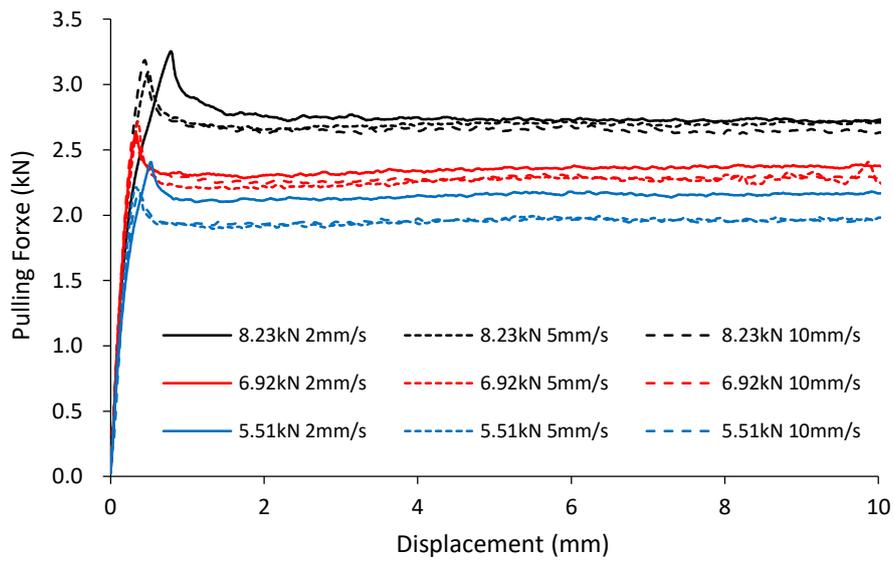


Fig. 6. Pulling force versus displacement curves for R30 die

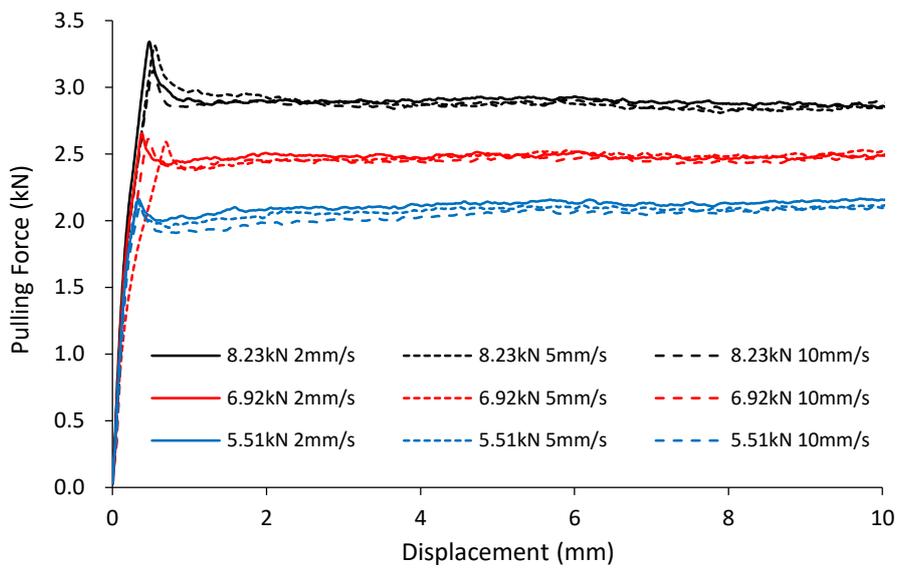


Fig. 7. Pulling force versus displacement curves for R20 die

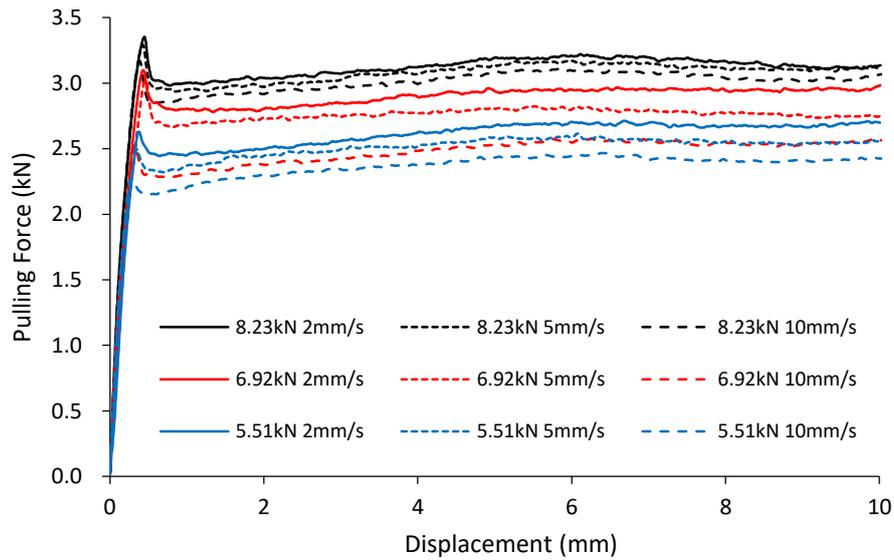


Fig. 8. Pulling force versus displacement curves for R15 die

3. Friction coefficient

The Coulomb friction coefficient is calculated by the normal pressure and sliding friction force on the contact surface, which are determined by the clamping force N and pulling force P in this experiment. The pulling force versus clamping force for all cases are plotted in Fig. 9.

The friction coefficient formula for a flat contact surface is straightforward, i.e. $\mu = P/N/2$, but for a curved contact surface, the pulling force P has two parts: the force to overcome the bending and reverse bending of the specimen when entering and exiting the clamping dies; and the friction force between the specimen and the clamping dies. The formula for calculating the friction coefficient between curved contact surfaces is $\mu = \lambda(P_{\text{total}} - P_{\text{b+ub}})/N/2$, where λ is a correction factor related the curvature and $P_{\text{b+ub}}$ is bending/unbending force that needs to be determined theoretically or via numerical simulation.

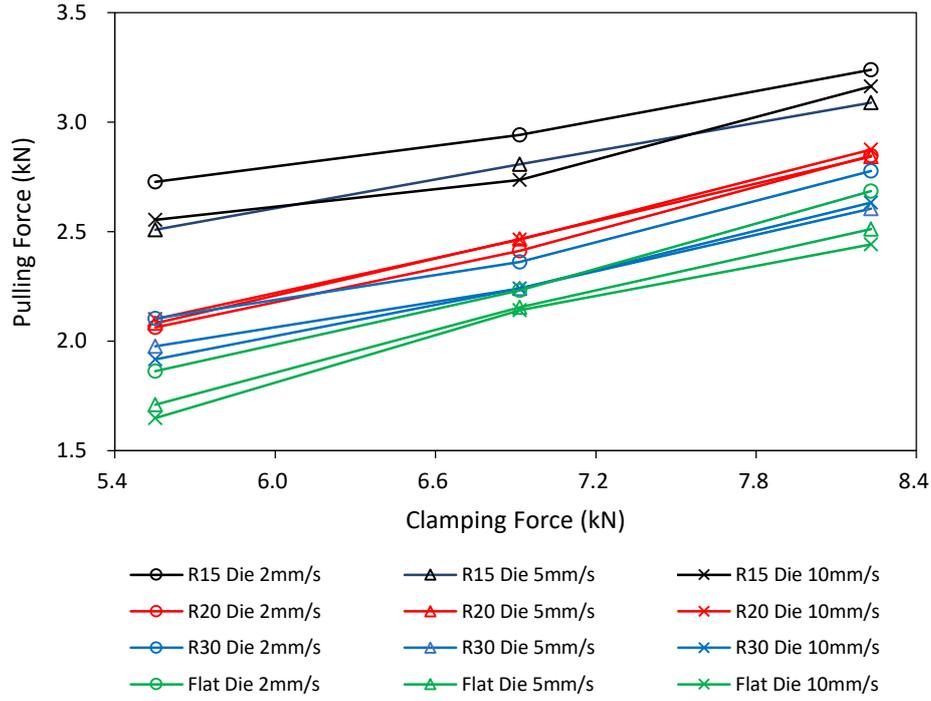


Fig. 9. Pulling forces versus clamping forces for all cases

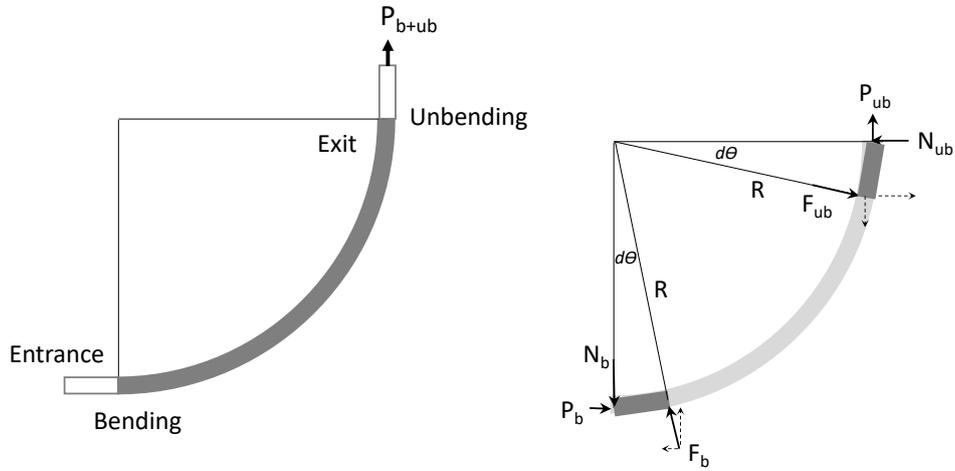


Fig. 10. Force diagram at die entrance point and exit point

According to the force diagram in Fig. 10, the bending/unbending force is given by Eq. (1):

$$P_{b+ub} = \frac{4w}{2R + t} \int_{-0.5t}^{+0.5t} y\sigma_y dy \quad \text{Eq. (1)}$$

where σ_y is the stress in different layers of the specimen, R is the radius of the die, w is the width of the specimen, and t is the thickness of the specimen. The detailed derivations are provided in Appendix A.

Fig. 11 illustrates the stress distribution through the thickness. The middle layer is assumed as the natural layer. The stress distribution can be simplified by a pure plastic model as shown in the right diagram in Fig. 11, which yields an explicit formula for the bending/unbending force given by Eq. (2):

$$P_{b+ub} = \frac{wt^2\sigma_b}{2R+t} \quad \text{Eq. (2)}$$

where σ_b is the stress in the outermost layer, which as a function of strain $\sigma_b = \sigma(\varepsilon_b)$ can be determined from the stress hardening curve of QP980. The strain ε_b is given by Eq. (3):

$$\varepsilon_b = \frac{t}{2R+t} \quad \text{Eq. (3)}$$

The through-thickness stress distributions in the curved specimens with different radii are plotted in Fig. 12.

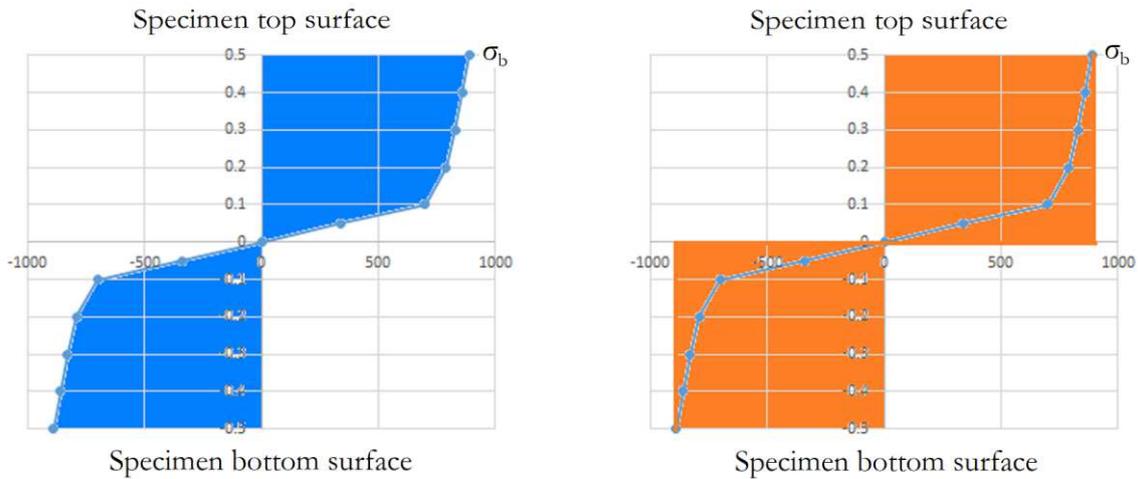


Fig. 11. Illustration of through-thickness stress distribution (left) and their approximation (right)

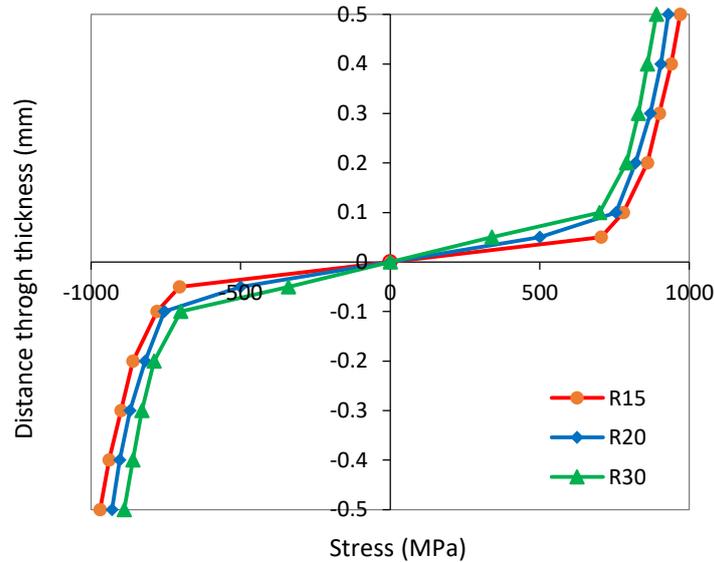


Fig. 12. Through-thickness stress distributions in curved specimens

Finite element simulation is a powerful tool to help investigate complex physical problems. The abovementioned methods to calculate the bending/unbending force are based on some assumptions and approximations. It is worthwhile to obtain the bending/unbending force via finite element modeling. ABAQUS/Standard is used to model this experiment. The specimen is modeled by a mesh of 1x1 mm S4R (4-node doubly curved, reduced integration) thick shell elements with 11 Simpson thickness integration points. The interaction between the specimen and die is defined by the surface-to-surface finite sliding contact algorithm, where the normal behavior is defined by hard contact pressure-overclosure and penalty constraint enforcement method, and the tangential behavior is defined as frictionless. Stationary boundary conditions are assigned to the dies. Since there is no friction force in this numerical model, the simulated pulling force is equal to the bending/unbending force.

The simulated pulling forces versus displacements for the curved specimens are plotted in Fig. 13, where two stable segments and a bump between them are observed. This phenomenon is due to the numerical model setup not exactly mimicking the experimental setup. In the experiment, the specimen is bent by the dies and then pulled sliding over the die, while in the finite element model, a pre-bent specimen is directly modeled for simplification. Therefore, in the first segment of deformation in simulation, the specimen initially does not have stress and just undergoes unbending as it slides through the dies, which does not exactly reflect what happens in the experiment where the

specimen is bent first and then unbent. In the second segment of deformation, the specimen undergoes bending and unbending, which occurs in both the experiment and the simulation. The strain and stress contour plots in Fig. 14 and 15 reveal the difference between the two segments of deformation. The simulated pulling force in the second segment is considered the bending/unbending force since this segment more closely represents the experiment.

The theoretically calculated and numerically simulated bending/unbending forces are presented in Table 3. The overestimation by theoretical calculations is probably due to the assumptions and approximations behind them. It is reasonable that a higher force is required to cause bending and unbending of a specimen over a smaller radius.

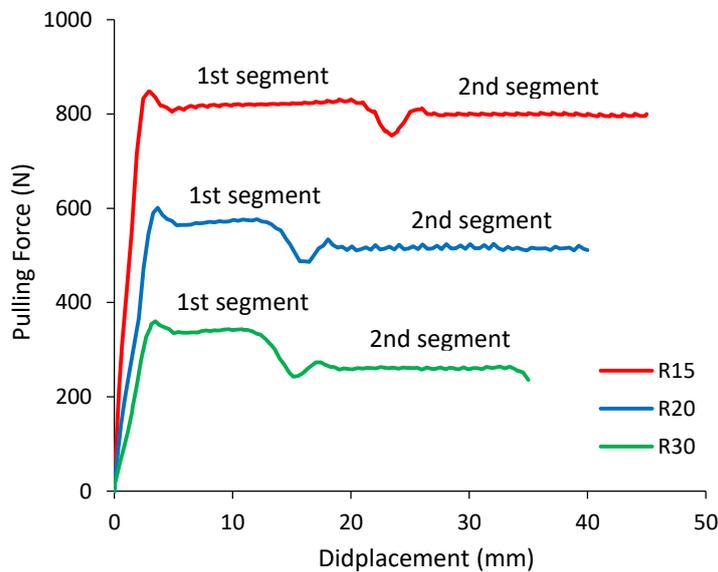


Fig. 13. Simulated bending/unbending forces

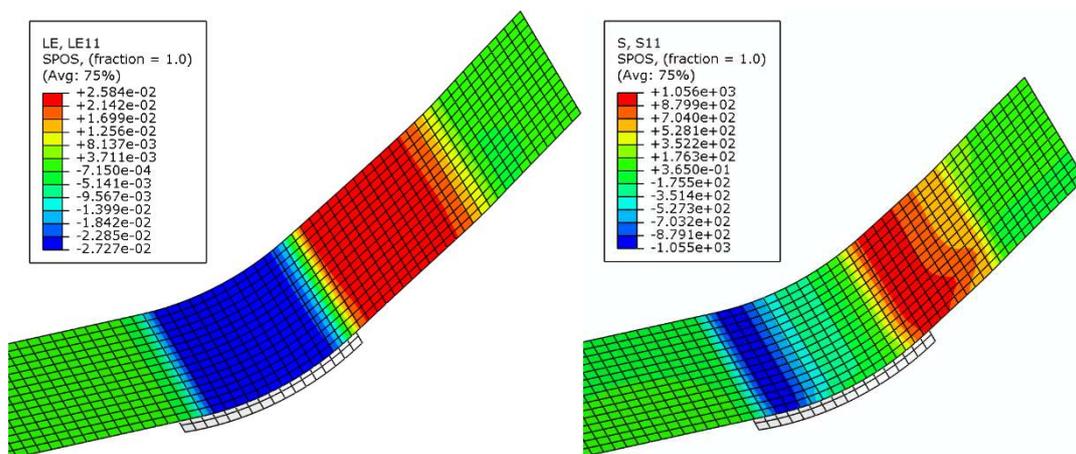


Fig. 14. First principal strain (left) and stress (right) during the 1st segment of deformation

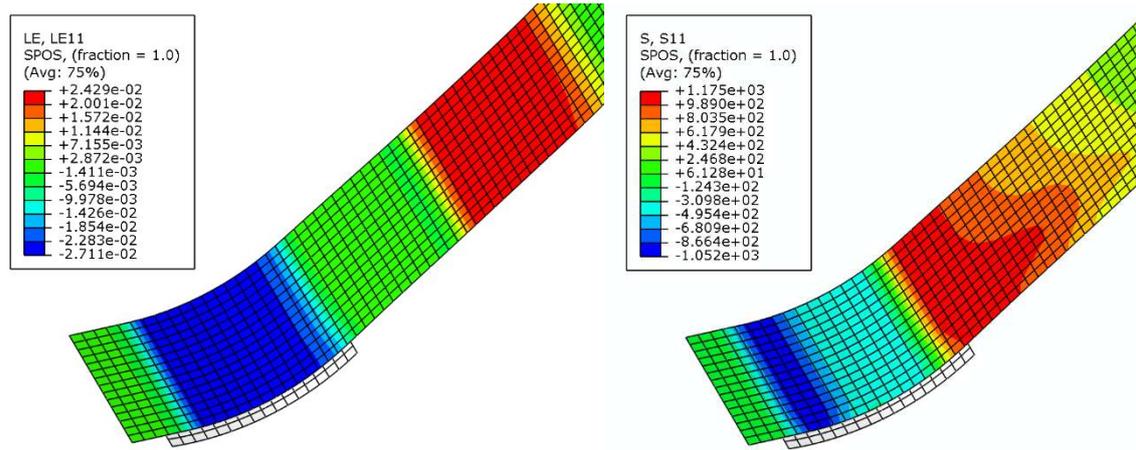


Fig. 15. First principal strain (left) and stress (right) during the 2nd segment of deformation

Table 3 Bending/unbending forces (N) by different methods

Method	R15	R20	R30
Calculation by approximation	939	680	438
Calculation by integration	873	632	403
Simulation first segment	821	572	340
Simulation second segment	799	516	261

The clamping force N is the normal contact force for the flat die, but not for the curved dies. Fig. 16 shows the force diagram of a curved specimen. The formula for calculating the friction coefficient between curved contact surfaces is given by Eq. (4):

$$\mu = \frac{(P_{\text{total}} - P_{\text{b+ub}}) \arcsin\left(\frac{H}{R}\right)}{2N\left(\frac{H}{R}\right)} \quad \text{Eq. (4)}$$

where H is the height of the die (15 mm) and R is the die radius (15, 20 and 30 mm). The detailed derivations are provided in Appendix B. For a flat contact surface, the R is infinite and there is no bending/unbending force, so the $P_{\text{b+ub}}$ and H/R terms in Eq. (4) drop out. The degeneration leads to the formula $\mu=P/N/2$.

The friction coefficients for all combinations among the geometric attributes, pulling speeds and clamping forces are presented in Table 4.

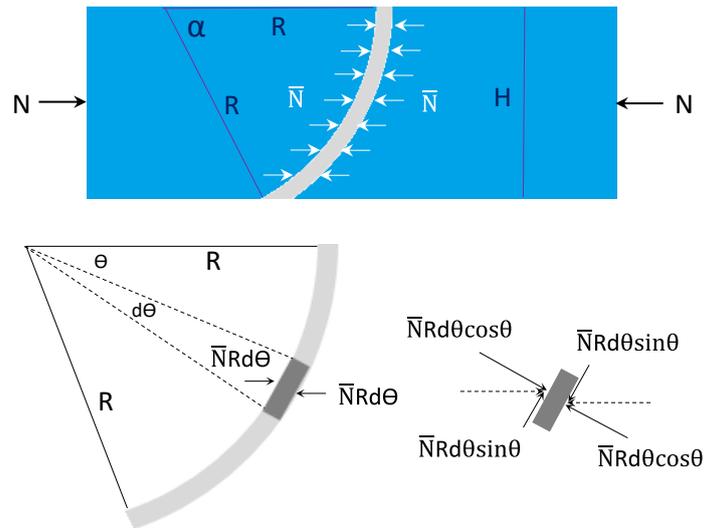


Fig. 16. Force diagram of a curved specimen

Table 4 Friction coefficients

Speed	Force	Flat	R30	R20	R15
2 mm/s	5.51 KN	0.1641	0.1780	0.1911	0.2319
	6.92 KN	0.1614	0.1734	0.1859	0.2068
	8.23 KN	0.1631	0.1734	0.1860	0.1980
5 mm/s	5.51 KN	0.1540	0.1675	0.1781	0.2056
	6.92 KN	0.1557	0.1678	0.1863	0.1939
	8.23 KN	0.1526	0.1671	0.1758	0.1856
10 mm/s	5.51 KN	0.1484	0.1639	0.1775	0.2110
	6.92 KN	0.1548	0.1678	0.1763	0.1869
	8.23 KN	0.1484	0.1584	0.1782	0.1918

4. Influence of curvature on friction coefficient

It can be seen from Table 4 that the friction coefficient in general is negatively related to sliding speed and positively to the curvature of contact surface, consistent with what was found in the literature [2,5,6,7]. However, its sensitivity to contact pressure is not as significant as reported by other researchers [3,4,5,8], probably because the difference in the clamping forces applied in this experiment is not large enough to cause a noticeable influence and the lubrication conditions in these studies are different as well.

The influence of geometric attribute on friction coefficient can be explained by examining the property of the contact surface. Fig. 17 shows the images of the as received sheet and the specimens stamped by flat and curved dies at 8.23 KN clamping force. A small area of each specimen was

observed by a laser confocal microscope LEXT OLS4000 and the surface morphology images were shown in Fig. 18. It can be seen from the microscopic images that the surface of the curved specimens is rougher than the surface of the flat specimen and the degree of roughness is positively related to the curvature. The limitation of this confocal microscope is that it cannot measure the concave surface, i.e. the inner surface of the curved specimens, due to the interference between the lens and the specimen. It is also not convenient to measure a large curved area using this microscope. Therefore, a 3D surface profiling instrument Talysurf CLI 2000 was used to measure the surface roughness of both outer and inner surfaces of each specimen. The probe travelled along three paths in both length and width directions as shown in Fig. 19. The measured roughness along the six paths of each surface were averaged as the surface roughness, which are plotted in Fig. 20.

Comparison between the as received sheet and the stamped flat specimen reveals that pressure changes the surface roughness very little. To further investigate the impact of contact pressure on surface roughness, a group of flat specimens were clamped at 5, 25, 50 and 100 MPa respectively. The measured surface roughness are within 0.8-0.82 μm . It has been reported in literatures [3-4, 10-11] that contact pressure does influence friction coefficient, but since the pressure induced deformation of surface topology is elastic, the measurement of unloaded specimens does not show significant changes in surface roughness. On the other hand, bending does cause a permanent change to surface roughness, and the amount of roughness increase is positively related the curvature. A curve fitting in Fig. 20 shows that the bending induced surface roughness increase can be approximated by a second order polynomial function:

$$\Delta Ra = 5.246K^2 + 1.923K \quad \text{Eq. (5)}$$

where K is the curvature of the specimen.

The influence of surface roughness on friction has been reported in literatures [12-21]. To quantify the relationship between surface roughness and friction coefficient, a curve fitting was performed for the data points in Fig. 21, which yield a linear function:

$$\mu = \mu_0 + 0.284\Delta Ra \quad \text{Eq. (6)}$$

where μ_0 is the friction coefficient of the flat specimen.

Combining Eq. (5) and Eq. (6) and neglecting the linear term of K yields:

$$\mu = \mu_0 + 1.49K^2 + 0.546K \quad \text{Eq. (7)}$$

This leads to the conclusion that the specimen's surface roughness changes as it bends and slides

over the curved dies. Since surface roughness is directly related to friction, the degree of change in surface roughness is reflected by the change in friction coefficient.

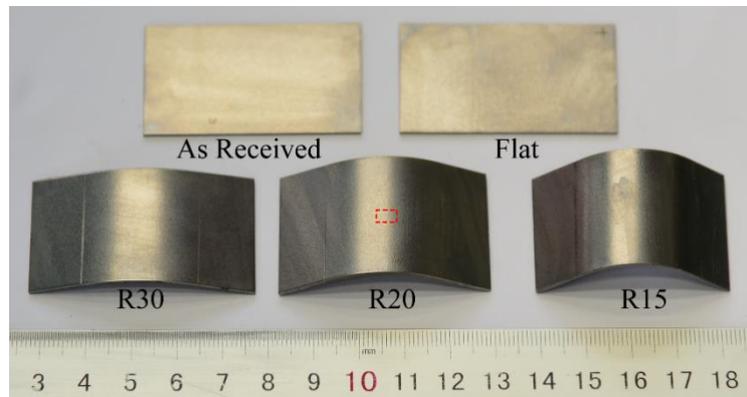


Fig. 17. Image of the as received sheet and the specimens stamped by flat and curved dies (R30, R20, R15)

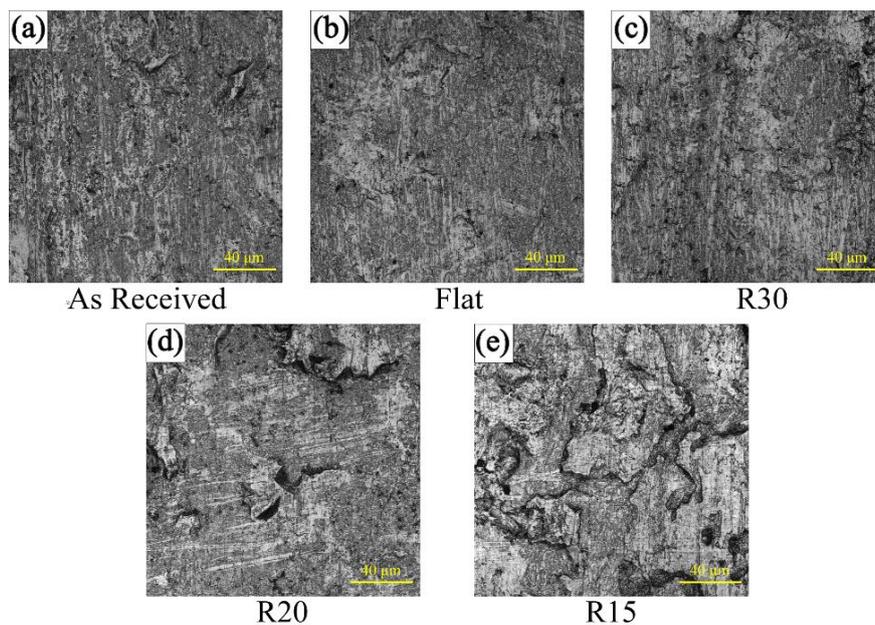


Fig. 18. Surface morphology the as received sheet and the specimens stamped by flat and curved dies (R30, R20, R15)

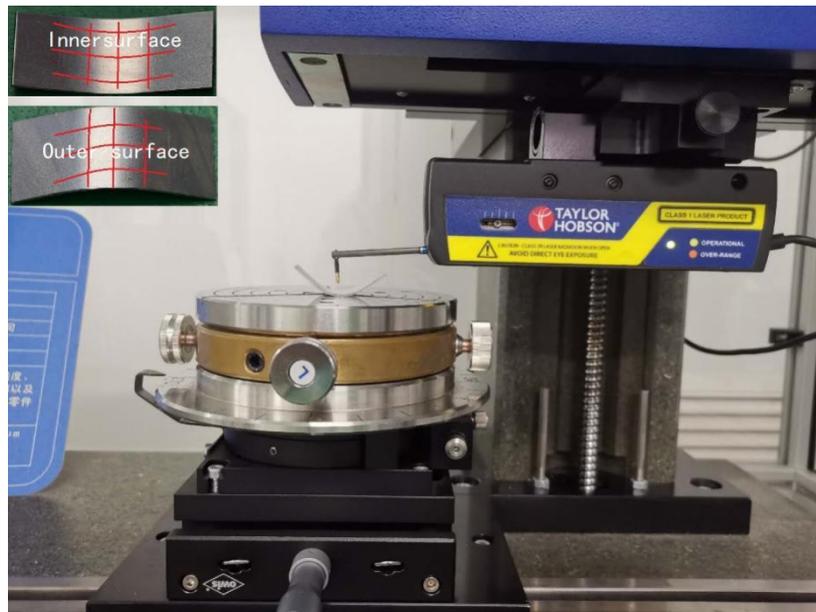


Fig. 19. Surface roughness measurement by 3D surface profiling instrument

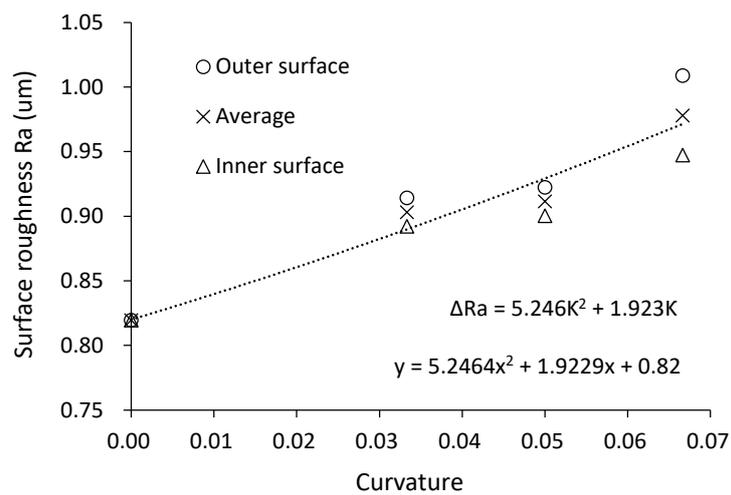


Fig. 20. Surface roughness of the specimens stamped by flat and curved dies (R30, R20, R15)

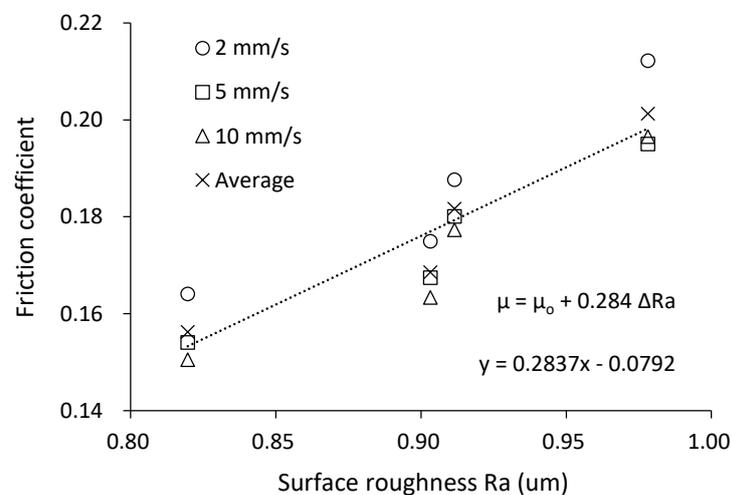


Fig. 21. Relationship between surface roughness and friction coefficient

5. Enhanced friction model

Coulomb friction model with constant friction coefficient is widely used in stamping simulation. However, the friction coefficient is not constant in reality, but depends on multiple factors such contact pressure, sliding speed and geometric attribute. The value of friction is one of the considerable uncertainties in simulation and using an enhanced friction model may lead to improved simulation results.

The theory manual of stamping simulation software AutoForm [22] provides a Coulomb friction model with contact pressure and sliding velocity dependent friction coefficient:

$$\mu = \mu_o \left(\frac{p}{p_o} \right)^{a-1} - b \operatorname{Ln} \frac{\max(v, v_o)}{v_o} \quad \text{Eq. (8)}$$

where μ_o is the base friction coefficient at reference conditions, p_o the reference contact pressure, p the contact pressure, a the pressure exponent, v_o the reference sliding velocity, v the sliding velocity, b the velocity factor.

An enhanced friction coefficient model with geometric attribute dependence taken into account can be constructed by combining Eq. (7) and (8):

$$\mu = (\mu_o + cK^2 + dK) \left(\frac{p}{p_o} \right)^{a-1} - b \operatorname{Ln} \frac{\max(v, v_o)}{v_o} \quad \text{Eq. (9)}$$

where K is the curvature, c and d are the curvature factors which have been determined to be 1.49 and 0.546 in Eq. (8). The parameter a and b can be determined individually by using the data in Table 4. The force of 5.51, 6.92 and 8.23 KN on a 30 by 15 mm² specimen correspond to contact pressure of 12.2, 15.4 and 18.3 MPa. The parameter a and b are determined to be 0.928 and 0.0097, respectively. In summary, the constants and reference values in Eq. (9) are:

$$\mu_o = 0.164, p_o = 12.2, v_o = 2, a = 0.928, b = 0.0097, c = 1.49, d = 0.546$$

6. Example of application

The enhanced friction model was used to simulate an automotive structural part - front load beam. The die setup is shown in Fig. 22. The upper tools consist of a pad and a steel, and the lower tools

consist of a binder and a post. The stamping process is defined as below:

Step 1: a developed blank of QP980 1.0 mm thick is initially placed between the upper tools and the lower tools.

Step 2: the upper pad moves down to press the blank against the post, a constant force of 102 kN is applied to the pad.

Step 3: while the blank is held between the pad and the post, the upper steel moves down until it closes with the lower binder.

Step 4: the upper steel and the lower binder move down together, pulling the blank into the die cavity until they hit home position. A constant force of 246 kN is applied to the binder.

Step 5: the part is removed from the dies followed by a free-state springback analysis.

In order to apply curvature dependent friction coefficients to the die, the radii of the steel and post are defined as separate tools. Thus, the steel is separated into steel-main and steel-radius, and the post into post-main and post-radius. The reference friction coefficient of 0.164 is assigned to steel-main, pad, post-main, and binder. The curvature of the steel-radius and post-radius is $1/6$, which leads to a friction coefficient of 0.296 by using Eq. (7). Each tool's name and its applied initial friction coefficient are labeled in Fig. 22. The friction model in AutoForm software takes into account the pressure and velocity dependence during the simulation.

A major concern of high strength steel parts is springback, therefore the load beam was measured for dimensional quality along 7 sections as shown in Fig. 23. The measurement shows a maximum springback magnitude of 11.6 mm on the sidewall near the bottom radius. The simulated springback values are presented in Fig. 24, where it can be seen that the enhanced friction model predicts 11.9 mm while the conventional friction model predicts 13.1 mm, indicating that the enhanced model improves simulation accuracy.

Another big concern of stamping high strength steel is die wear. Engineers often use simulation to predict the most severe worn areas of the die so that the die's lifetime can be better estimated and a preventive maintenance schedule can be created. Friction plays an important role in die wear, so a more accurate friction model is desired in simulation. Fig. 25 shows the simulated die wear in term of friction work by using the conventional model and the enhanced model. Differences in friction-work distribution and the peak value are observed. The curvature induced increase of friction coefficient yields a higher degree of die wear.

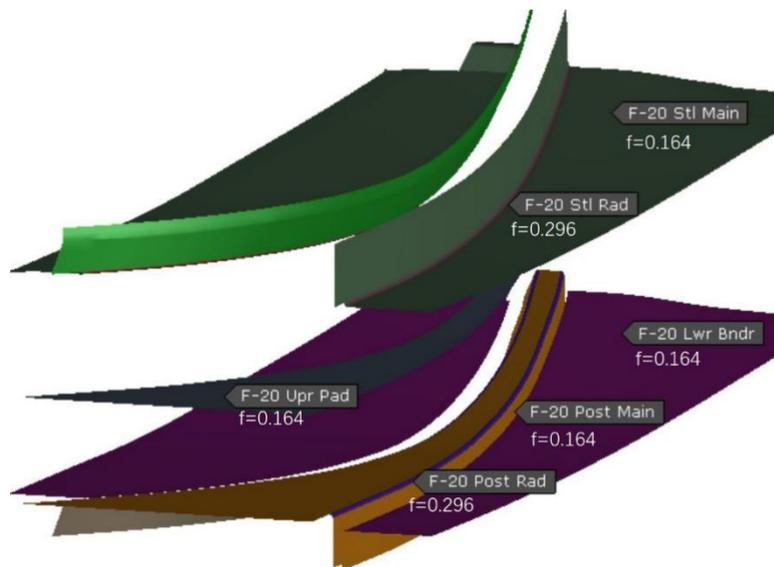


Fig. 22. Die setup for stamping an automotive front load beam

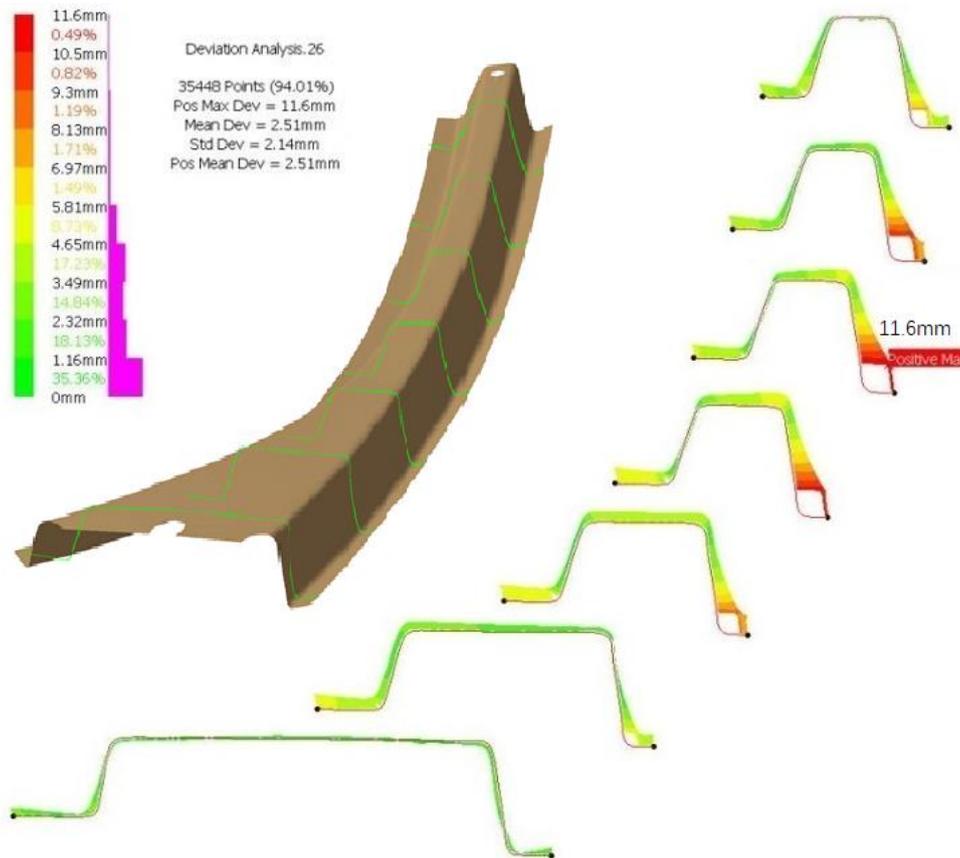


Fig. 23. Measured springback magnitude of the load beam

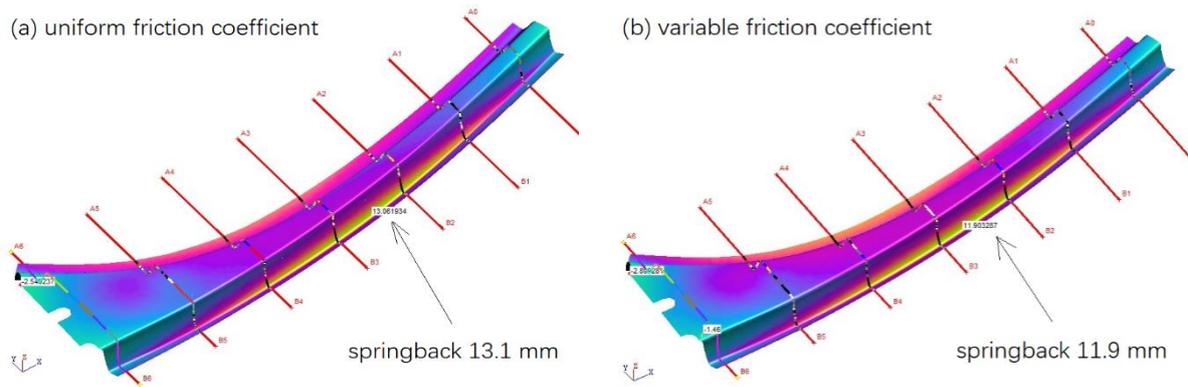


Fig. 24. Simulated springback magnitude of the load beam: (a) conventional uniform friction coefficient model; (b) enhanced variable friction coefficient model

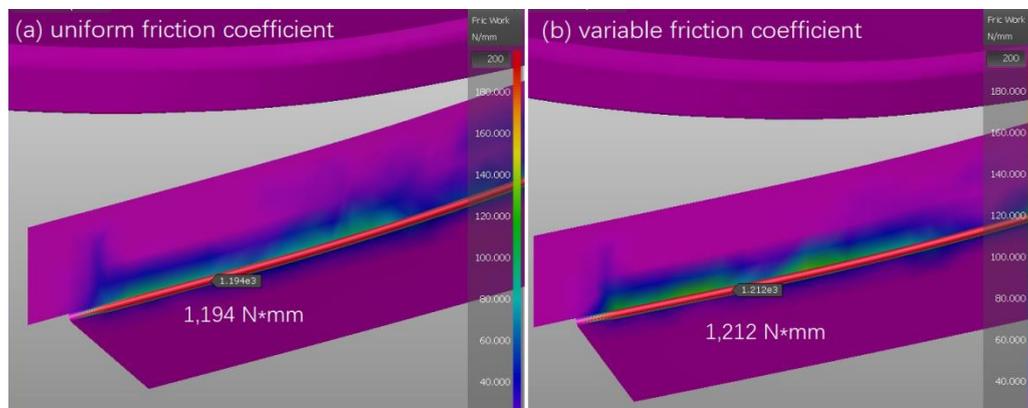


Fig. 25. Simulated die wear in term of friction work: (a) conventional uniform friction coefficient model; (b) enhanced variable friction coefficient model

7. Conclusion

A universal test machine based mechanical driven friction device was designed and manufactured. Friction tests were conducted on a third-generation high strength steel QP980 with flat and curved dies at different pulling speeds and clamping forces. The formula for calculating the friction coefficients between curved contact surfaces was derived. Finite element modeling was performed to find the bending/unbending force when a specimen is pulled over curved dies. The relationship between bending induced surface roughness increase and friction coefficient was established. An enhanced friction coefficient model with contact pressure, sliding velocity and geometric curvature dependence was proposed and the parameters were determined. The enhanced friction model was applied to simulate the stamping of an automotive part and the simulation results were compared with measurement results. The following conclusions can be drawn:

- (1) The friction coefficient between curved contact surfaces is higher than the one between flat surfaces when other geometric and process attributes like die surface roughness, lubrication condition, contact pressure, and sliding speed are the same. The friction coefficient in general is positively related to the curvature of contact surface.
- (2) Sliding speed negatively impacts the friction coefficient between flat and curved surfaces, although the impact on flat surface is more consistent than on curved surface. The friction coefficient is also negatively related to contact pressure. The difference in contact pressure in this experiment is not large enough to generate a significant pressure sensitivity.
- (3) The increase of friction coefficient between curved contact surfaces is because the specimen's surface roughness changes as it bends and slides over a curved die. The degree of change in surface roughness is positively related to the curvature, so is the changes in friction coefficient.
- (4) The curvature induced surface roughness increase can be approximated by a second order polynomial. A linear relationship between the surface roughness and friction coefficient can be established. Thus, the dependence of friction coefficient on curvature can also be modeled by a second order polynomial.
- (5) The enhanced friction coefficient model with contact pressure, sliding velocity and geometric curvature dependence can be implemented in stamping simulation software and the predicted springback and die wear using the enhanced model are more accurate.

Availability of data and materials

The datasets supporting the conclusions of this article are included within the article.

Competing interests

The authors declare no competing financial interests.

CRedit authorship contribution statement

Dewang Zhao: Conceptualization, Methodology, Writing - Review & Editing. **Kunmin Zhao:** Writing - original draft, Project administration, Funding acquisition. **Huaihao Song:** Data curation, Visualization. **Daxin Ren:** Conceptualization, Methodology, Supervision. **Ying Chang:** Supervision, Funding acquisition.

Funding and Acknowledgement

This research is financially supported by the National Natural Science Foundation of China (51775160, 51971050), and the China Postdoctoral Science Foundation(2020M680947). The QP980 high strength steel is provided by Baoshan Iron & Steel Co. Ltd. of China.

Biographical notes

Kun-Min Zhao, born in 1971, is currently a professor at State Key Laboratory of Structural Analysis for Industrial Equipment, Dalian University of Technology, China. “The one-thousand-talents scheme” specially invited Expert. His research interests include advanced manufacturing and metal forming process.

Tel: +86-15509853169; E-mail: kmzhao@dlut.edu.cn



Dewang Zhao, born in 1986, is currently a Postdoctoral at *School of Materials Science and Engineering, Dalian University of Technology, China*. His research interests include advanced manufacturing and welding. Tel: +86-18545051095; E-mail: dewangzhao@qq.com



Appendix

A. Calculation of bending/unbending force

Referring to Fig. 10 and 11.

$$M_b = F_b(R + 0.5t)d\theta$$

$$P_b = F_b \sin(d\theta) \approx F_b d\theta$$

$$P_b = \frac{M_b}{R + 0.5t}$$

$$P_b \approx P_{ub} , \quad M_b \approx M_{ub} , \quad \sigma_b \approx \sigma_{ub}$$

$$P_{b+ub} = P_b + P_{ub} = \frac{4M_b}{2R + t}$$

$$M_b = w \int_{-0.5t}^{+0.5t} y \sigma_y dy$$

$$P_{b+ub} = \frac{4w}{2R + t} \int_{-0.5t}^{+0.5t} y \sigma_y dy$$

For simplified through-thickness stress distribution:

$$M_b = 0.25wt^2 \sigma_b$$

$$\sigma_b = \sigma(\varepsilon_b)$$

$$\varepsilon_b = \frac{t}{2R + t}$$

$$P_b = \frac{wt^2 \sigma_b}{4R + 2t}$$

$$P_{b+ub} = P_b + P_{ub} = \frac{wt^2 \sigma_b}{2R + t}$$

B. Friction coefficient formula for curved surface

Referring to Fig. 16:

$$\bar{N} = \frac{N}{R\alpha}$$

$$\sin\alpha = \frac{H}{R}$$

$$\alpha = \arcsin\left(\frac{H}{R}\right)$$

$$df = 2\mu\bar{N}R\cos\theta d\theta$$

$$f = \int_0^\alpha 2\mu\bar{N}R\cos\theta d\theta = 2\mu\bar{N}R\sin\alpha$$

$$f = P_{\text{total}} - P_{\text{b+ub}}$$

$$\mu = \frac{(P_{\text{total}} - P_{\text{b+ub}}) \arcsin\left(\frac{H}{R}\right)}{2N\left(\frac{H}{R}\right)}$$

References:

- [1] E. Evin, S. Nemeth, M. Vyrostek, Evaluation of friction coefficient of stamping, *Acta Mechanica Slovaca* 18(3-4):20-27, 2014
- [2] H. Lemu, T. Trzepiecinski, Numerical and experimental study of frictional behavior in bending under tension test, *Journal of Mechanical Engineering* 59(2013)1, 41-49
- [3] W. Wang, Y. Zhao, Z. Wang, M. Hua, X. Wei, A study on variable friction model in sheet metal forming with advanced high strength steels, *Tribology International* 93 (2016) 17-28
- [4] G. Li, X. Long, P. Yang, Z. Liang, Advance on friction of stamping forming, *International Journal of Advanced Manufacturing Technology* (2018) 96:21-28
- [5] Y.S. Kim, M.K. Jain, D.R. Metzger, Determination of pressure-dependent friction coefficient from draw-bend test and its application to cup drawing, *International Journal of Machine Tools & Manufacture* 56 (2012) 69-78
- [6] N. Ma, N. Sugitomo, Development and application of non-linear friction models for metal forming simulation, *AIP Conference Proceedings* 1383, 382 (2011)
- [7] M. Dilmeç, M. Arap, Effect of geometrical and process parameters on coefficient of friction in deep drawing process at the flange and the radius regions, *International Journal of Advanced Manufacturing Technology* (2016) 86:747-759

- [8] T. Trzepiecinski, A. Bazan, H.G. Lemu, Frictional characteristics of steel sheets used in automotive industry, *International Journal of Automotive Technology*, Vol. 16, No. 5, pp. 849-863 (2015)
- [9] X. Chen, C. Niu, C. Lian, J. Lin, et al. The evaluation of formability of the 3rd generation advanced high strength steels QP980 based on digital image correlation method, *Procedia Engineering* 207 (2017) 556-561
- [10] M. Stembalskin, P. Pres, W. Skoczynski. Determination of the friction coefficient as a function of sliding speed and normal pressure for steel C45 and steel 40HM. *Archives of Civil and Mechanical Engineering* 13 (2013) 444–448
- [11] Yoshikiyo Tamai, Toru Inazumi, Ken-ichi Manabe. FE forming analysis with nonlinear friction coefficient model considering contact pressure, sliding velocity and sliding length. *Journal of Materials Processing Technology* 227 (2016) 161–168
- [12] Daw-Kwei Leu. Modeling of surface roughness effect on dry contact friction in metal forming. *Int J Adv Manuf Technol* (2011) 57:575–584
- [13] Guoxing Liang, Siegfried Schmauder, Ming Lyu, et al. An investigation of the influence of initial roughness on the friction and wear behavior of ground surfaces. *Materials* 2018, 11, 237
- [14] Ruimin Shi, Bukang Wang, Zhiwei Yan, et al. Effect of surface topography parameters on friction and wear of random rough surface. *Materials* 2019, 12, 2762
- [15] Mats Sigvanta, Johan Pilthammara, Johan Hol, et al. Friction in sheet metal forming: influence of surface roughness and strain rate on sheet metal forming simulation results. *Procedia Manufacturing* 29 (2019) 512–519
- [16] L. Xiao, S. Bjorklund, B.G. Rosen. The influence of surface roughness and the contact pressure distribution on friction in rolling/sliding contacts. *Tribology International* 40 (2007) 694–698
- [17] B. Ivkovic, M. Djukdjanovic, D. Stamenkovi. The Influence of the Contact Surface Roughness on the Static Friction Coefficient. *Tribology in industry*, Volume22, No. 3&4, 200
- [18] Tomasz Trzepiecinski, Romuald Fejkiel. On the influence of deformation of deep drawing quality steel sheet on surface topography and friction. *Tribology International* 115 (2017) 78–88
- [19] Mumin Sahin, Cem S. Cetinarslan, H. Erol Akata. Effect of surface roughness on friction coefficients during upsetting processes for different materials. *Materials and Design* 28 (2007) 633–640

- [20] T. Trzepiecinski. A Study of the Coefficient of Friction in Steel Sheets Forming. *Metals* 2019, 9, 988
- [21] L. Folle, Lírío Schaeffer. New Proposal to Calculate the Friction in Sheet Metal Forming Through Bending Under Tension Test. *Materials Research*. 2019; 22(6)
- [22] AutoForm R7 Software Manual 2016. AutoForm Engineering GmbH.

Figures

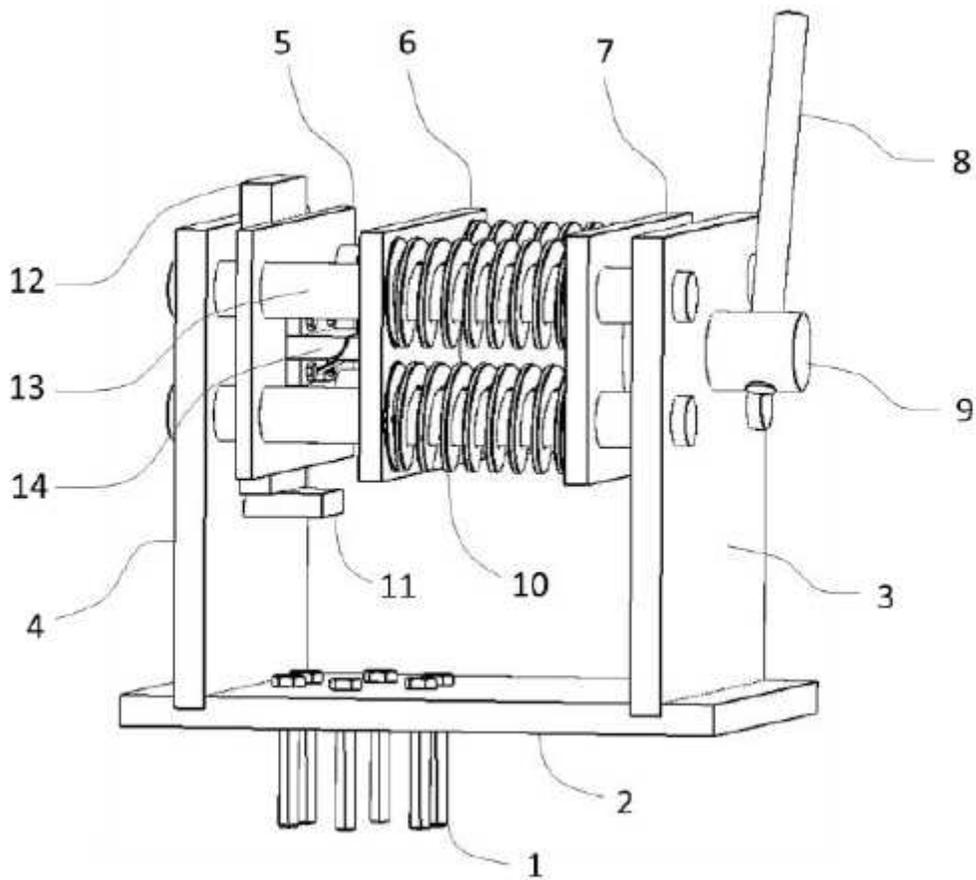


Figure 1

Drawing of the friction test device 1. Bolts 2. Base plate 3-4. Vertical plates 5-7. Sliding plates 8. Handle 9. Screw rod 10. Springs (four) 11. Pallet 12. Spacer 13. Guides (four) 14. Specimen

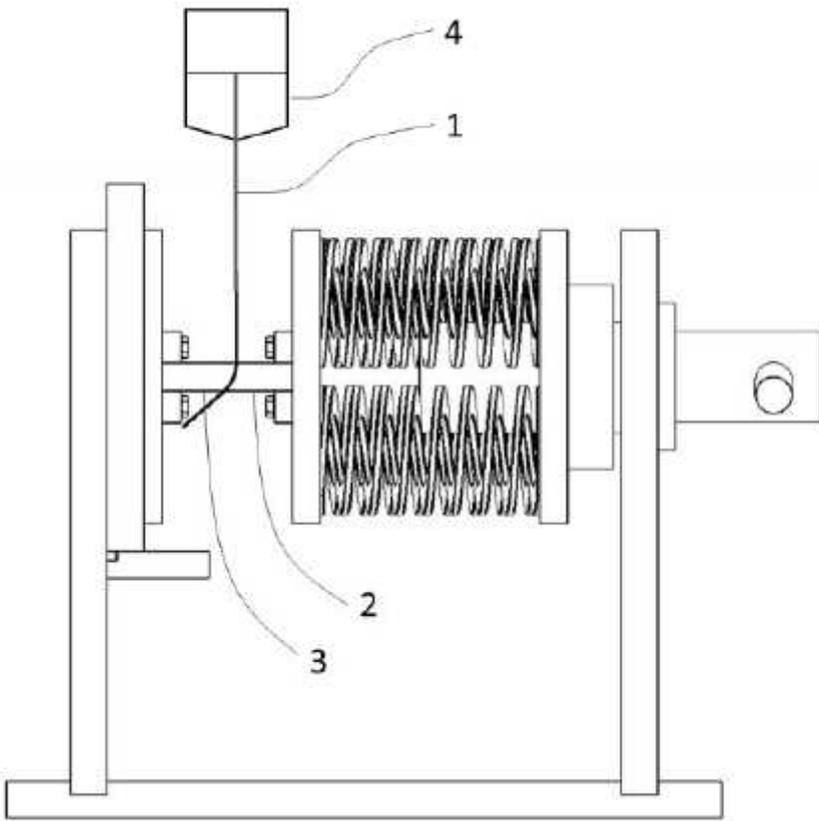


Figure 2

Front view of the friction test device 1. Specimen 2. Female die 3. Male die 4. Head of the universal test machine

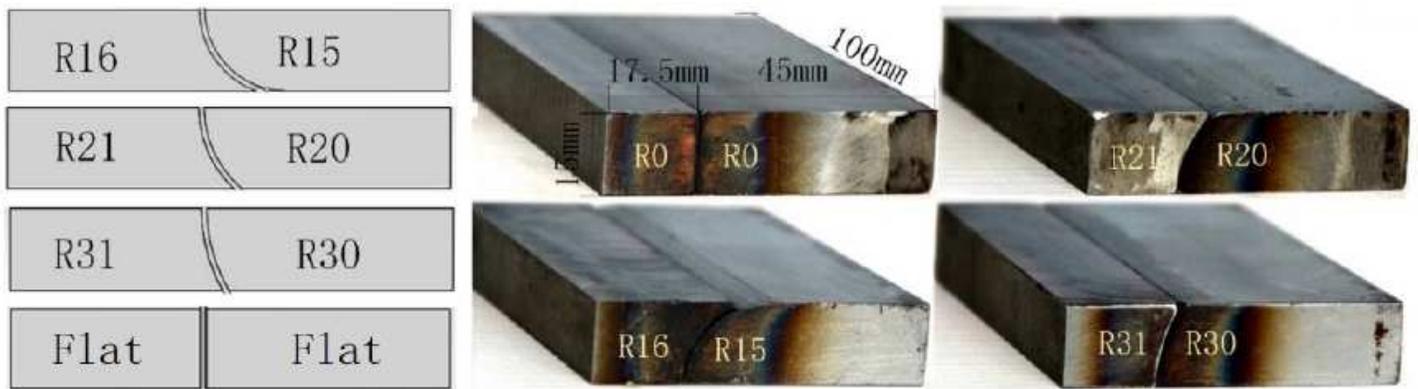


Figure 3

Geometric attributes of the clamping dies

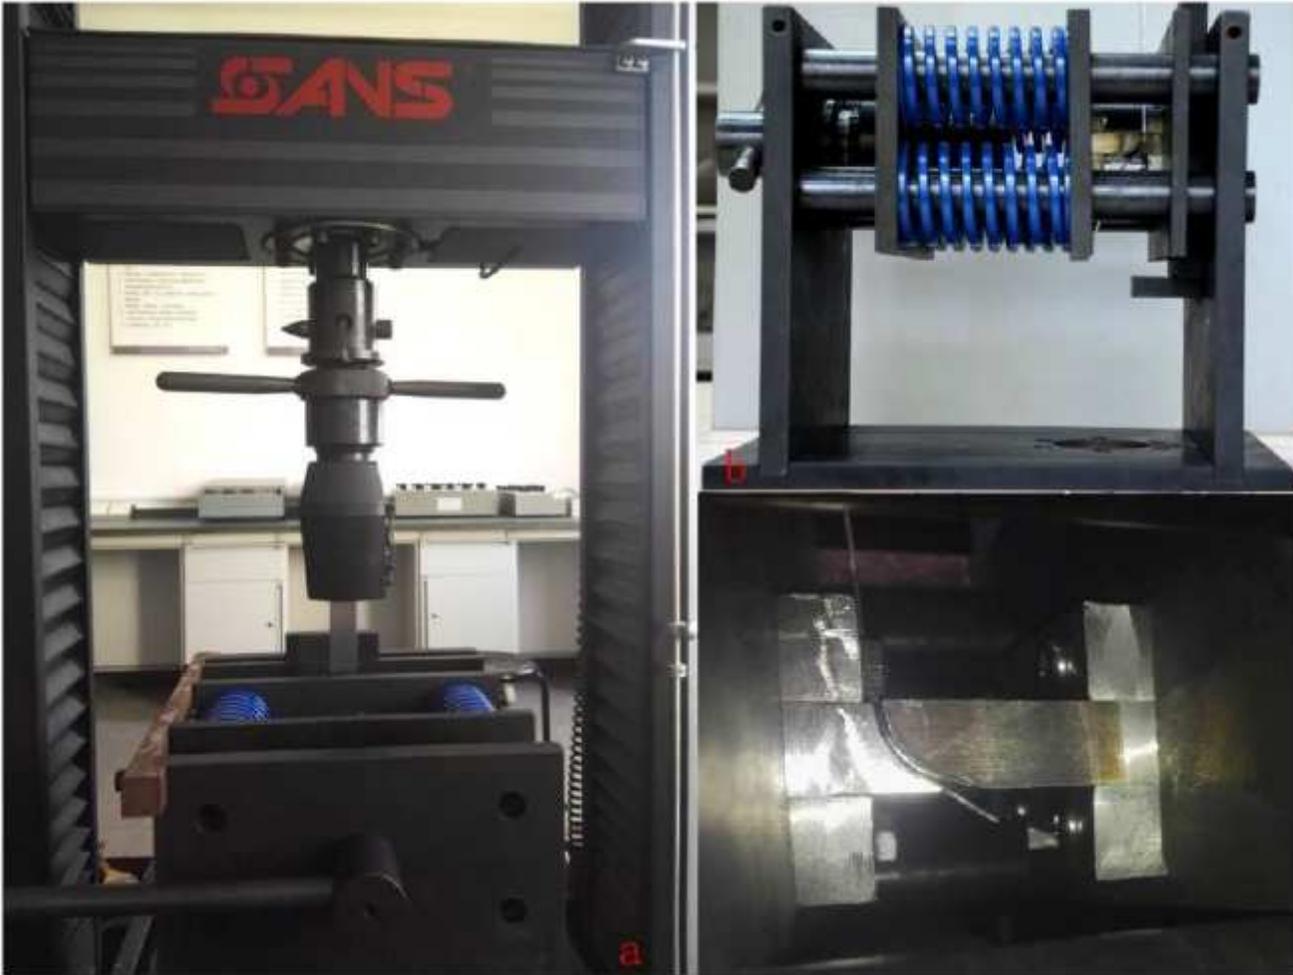


Figure 4

Friction device set up on a SANS universal test machine

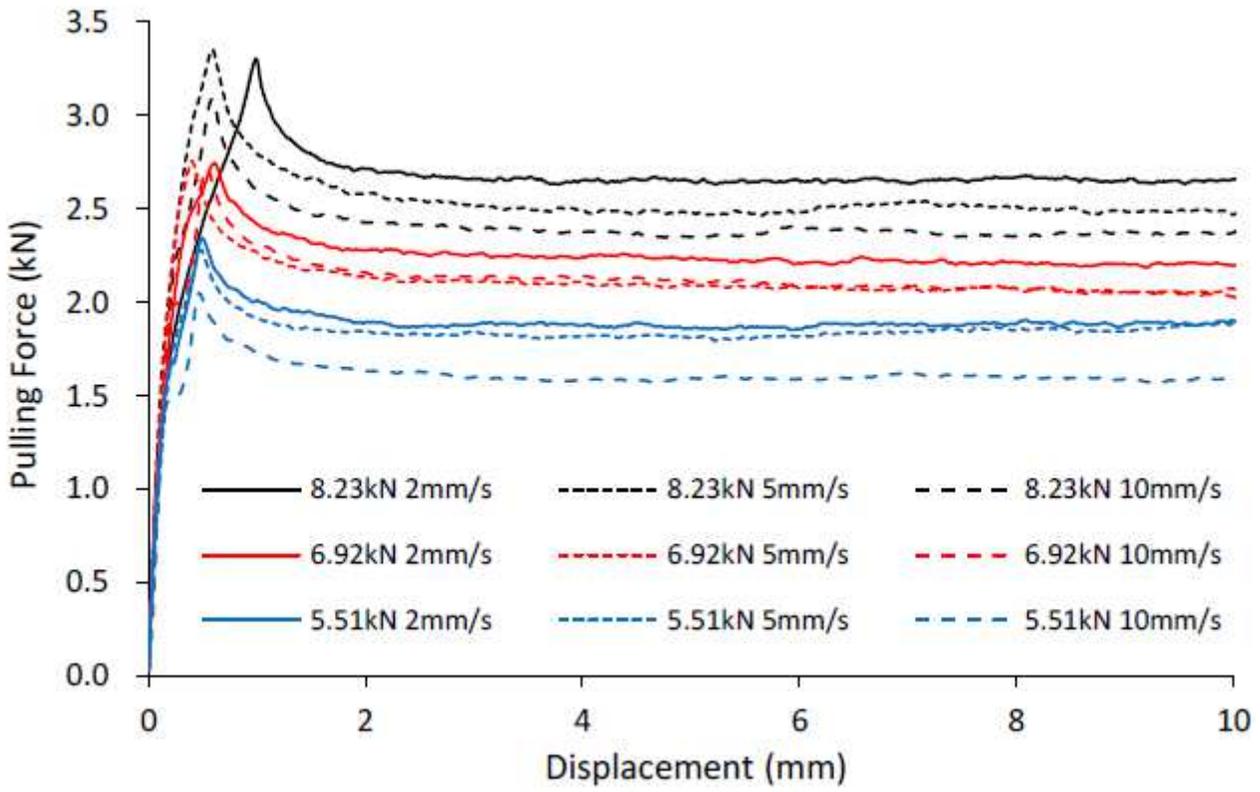


Figure 5

Pulling force versus displacement curves for flat die

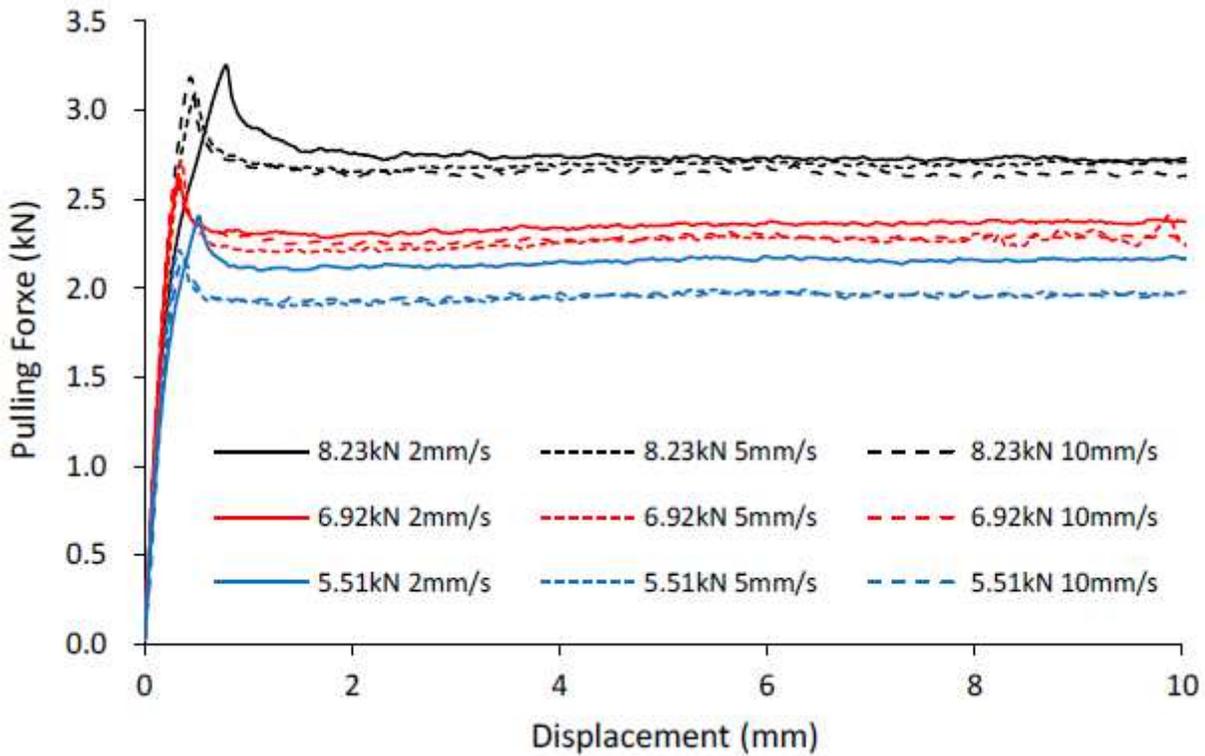


Figure 6

Pulling force versus displacement curves for R30 die

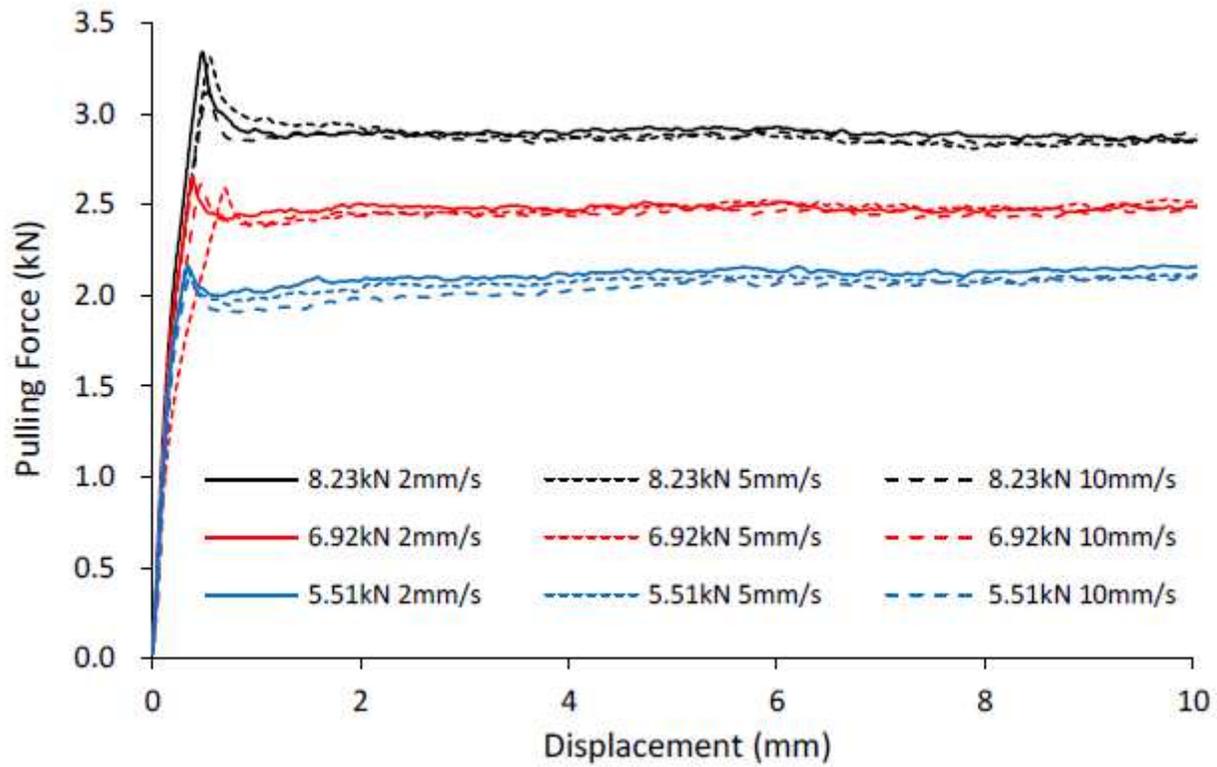


Figure 7

Pulling force versus displacement curves for R20 die

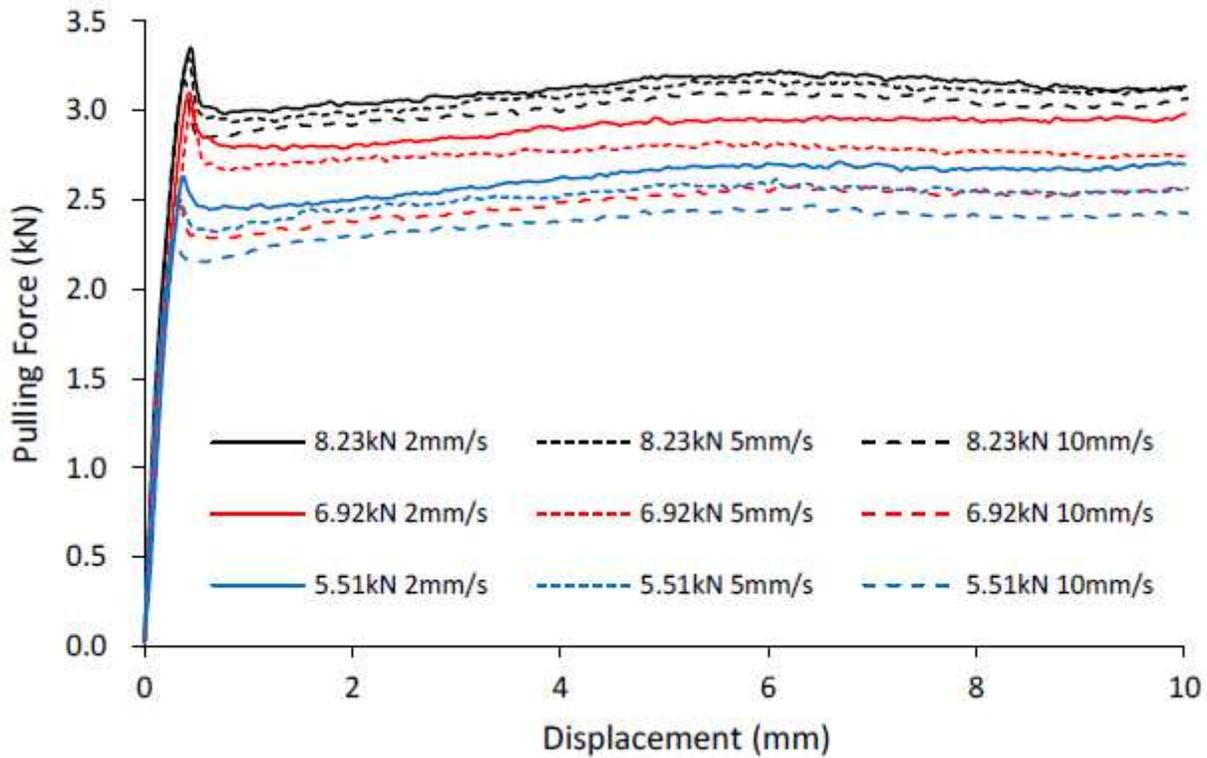


Figure 8

Pulling force versus displacement curves for R15 die

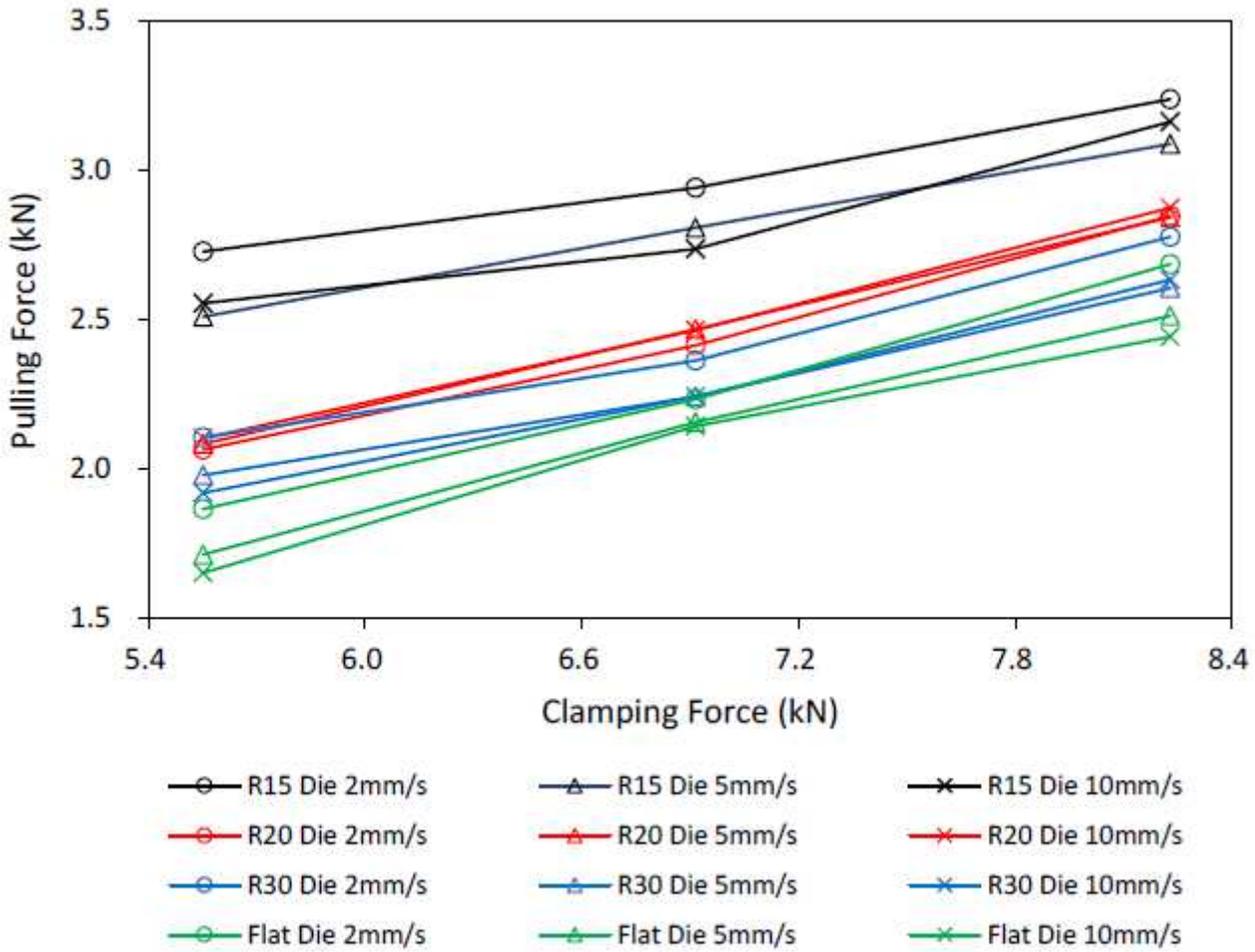


Figure 9

Pulling forces versus clamping forces for all cases

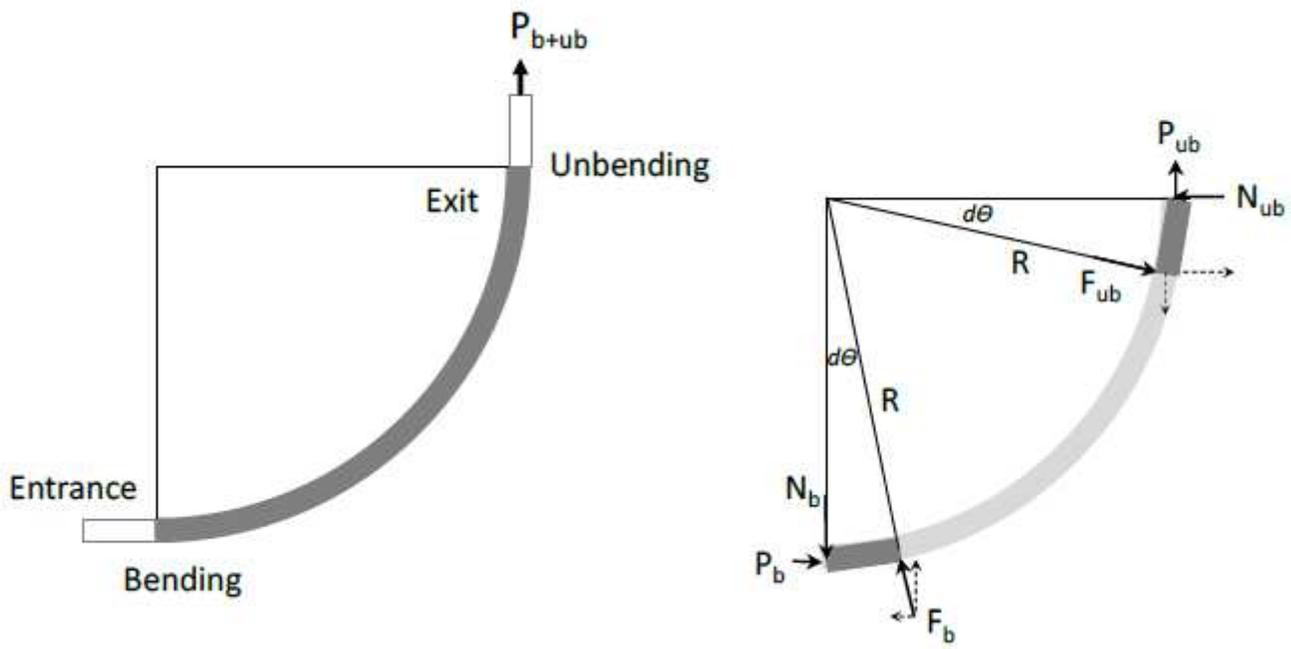


Figure 10

Force diagram at die entrance point and exit point

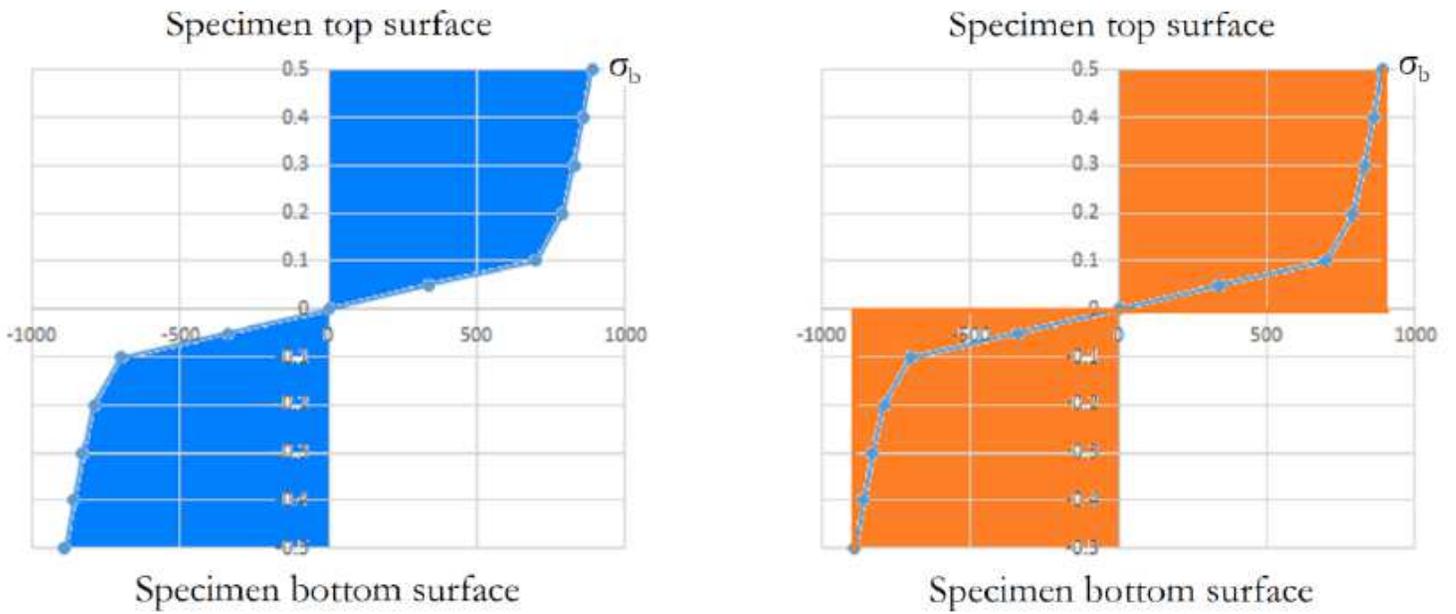


Figure 11

Illustration of through-thickness stress distribution (left) and their approximation (right)

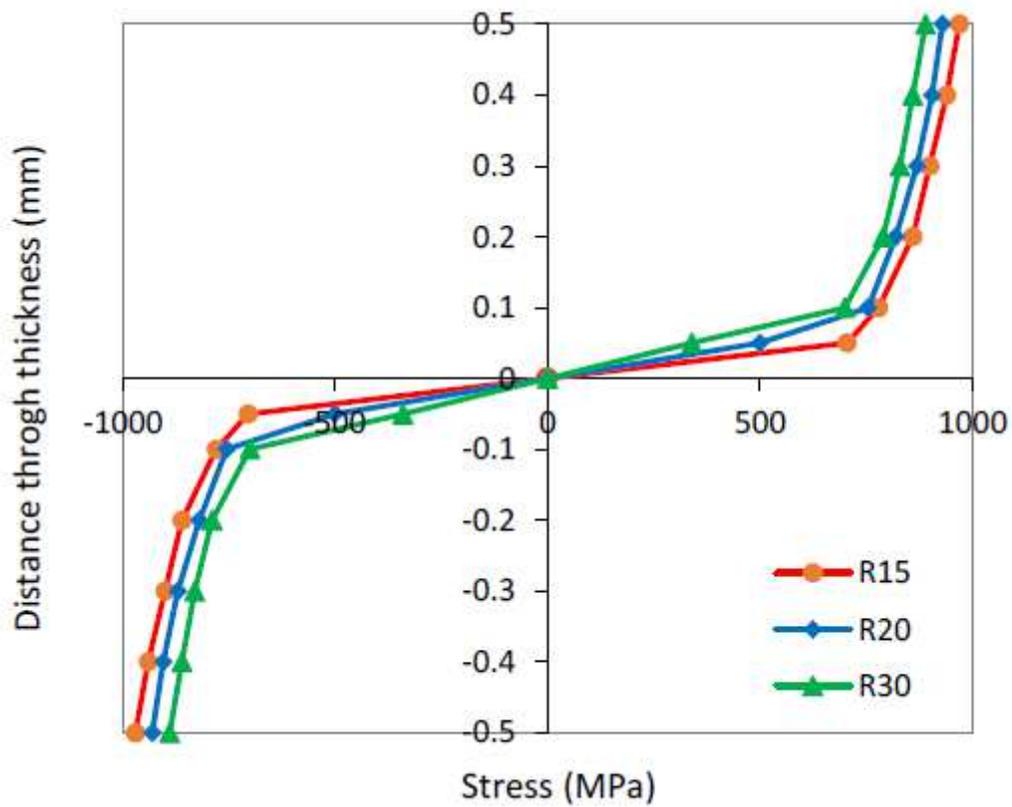


Figure 12

Through-thickness stress distributions in curved specimens

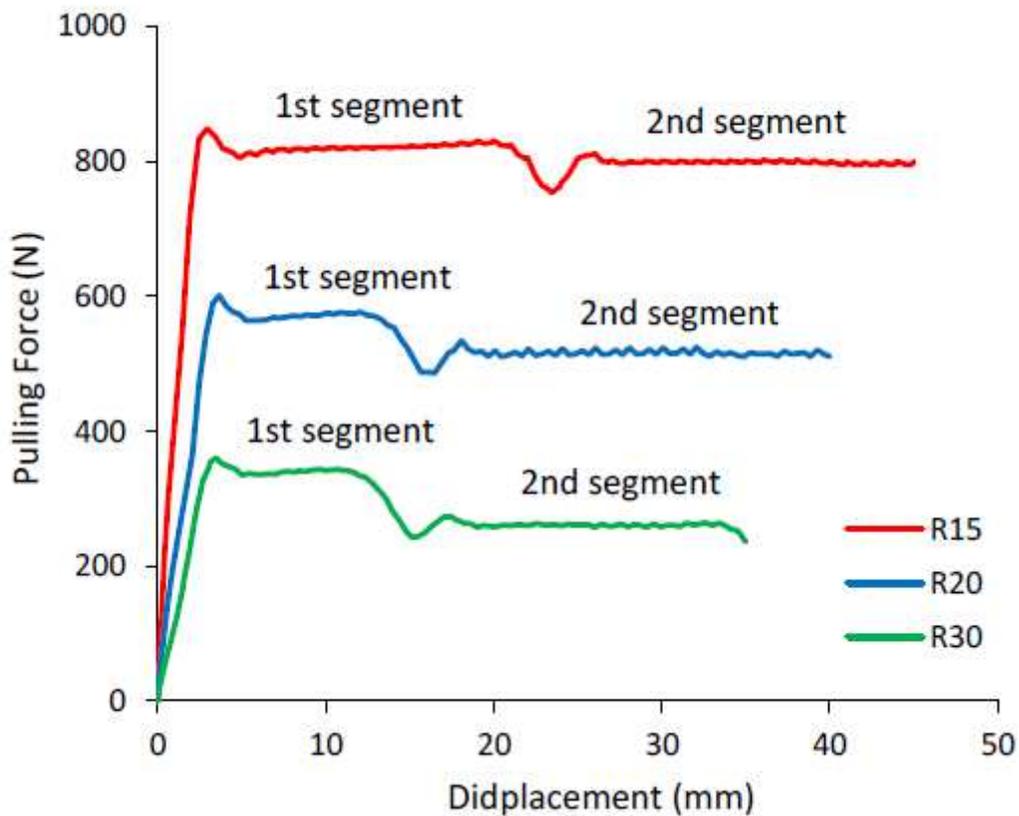


Figure 13

Simulated bending/unbending forces

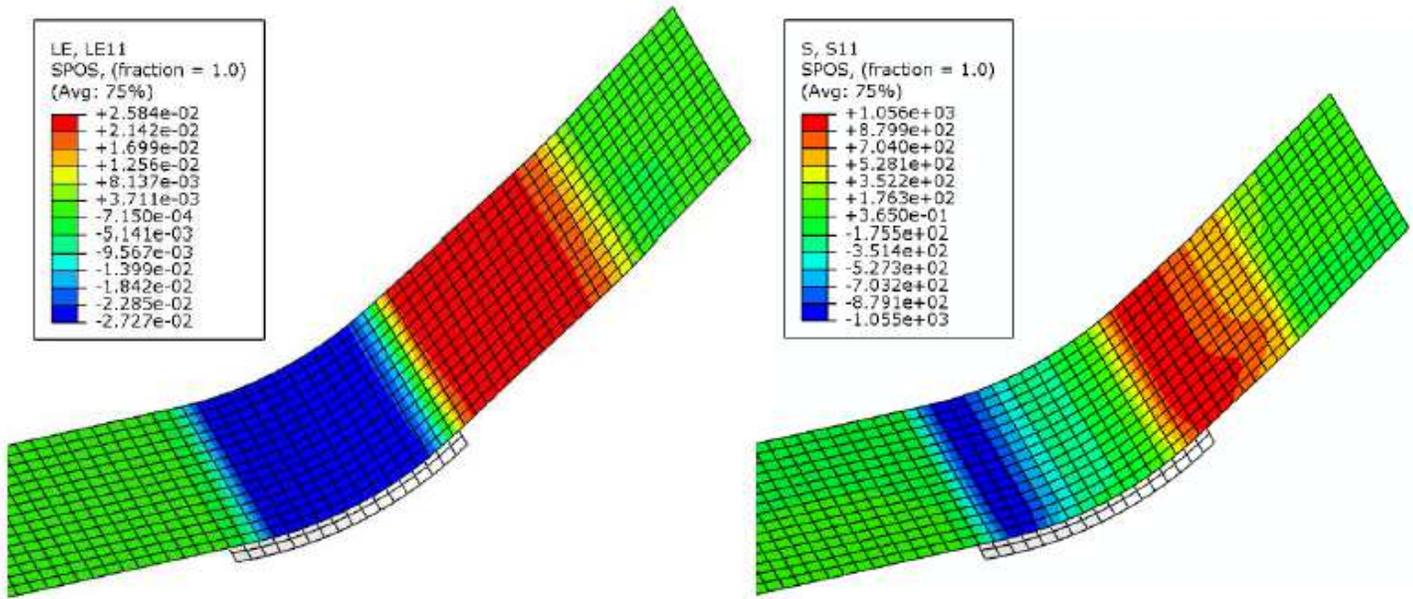


Figure 14

First principal strain (left) and stress (right) during the 1st segment of deformation

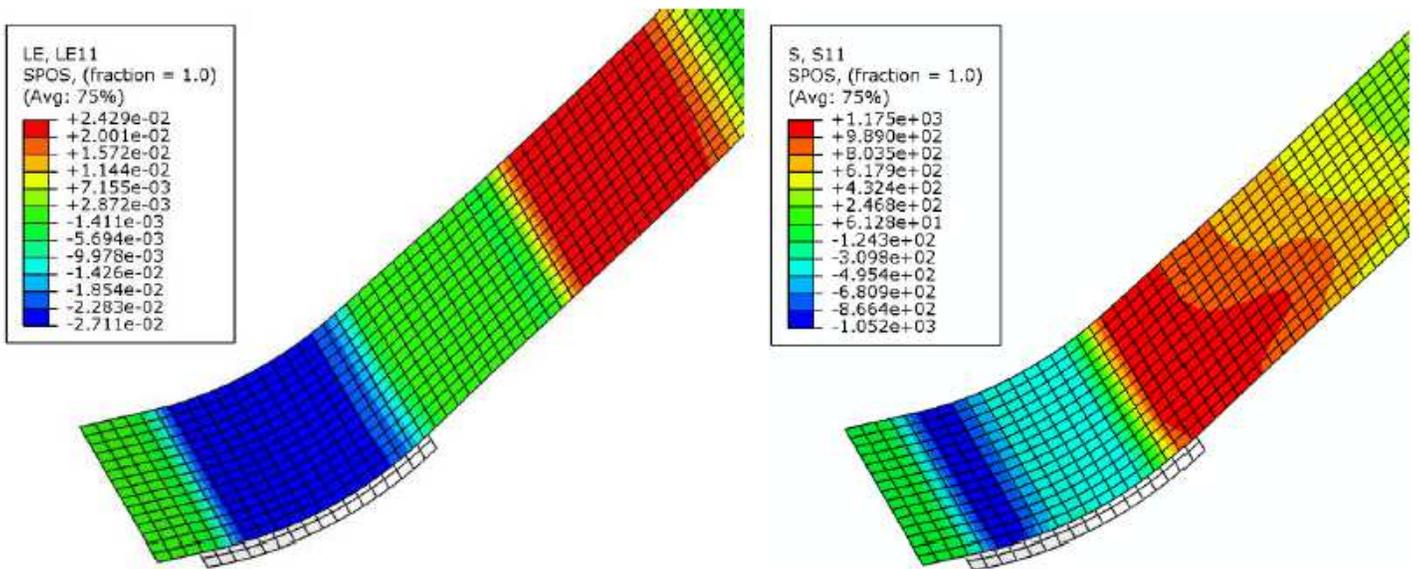


Figure 15

First principal strain (left) and stress (right) during the 2nd segment of deformation

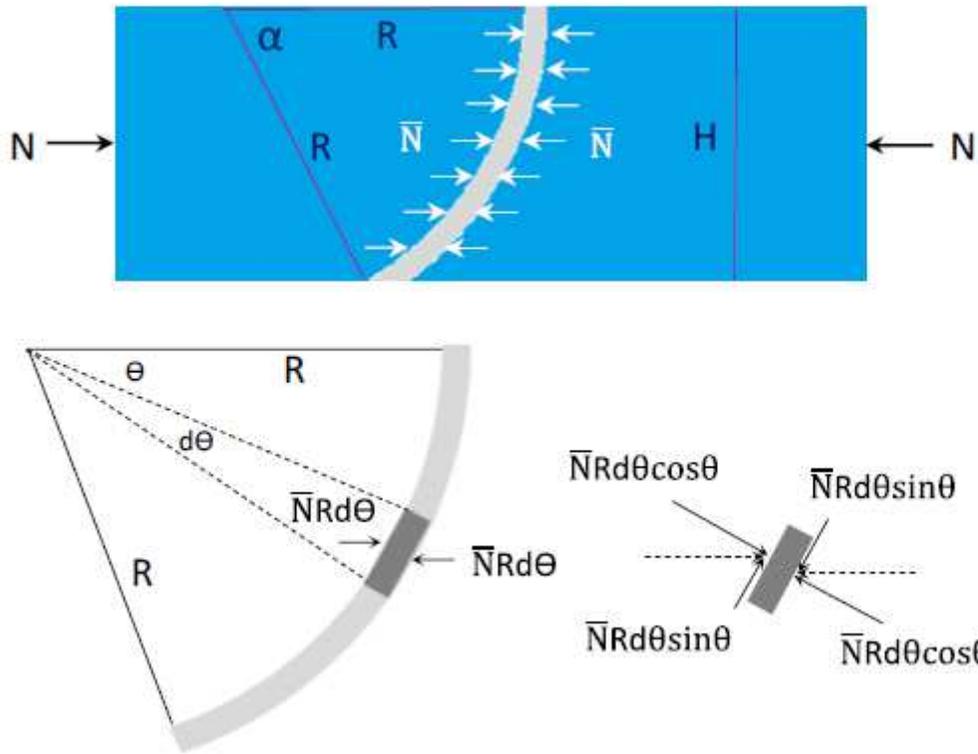


Figure 16

Force diagram of a curved specimen

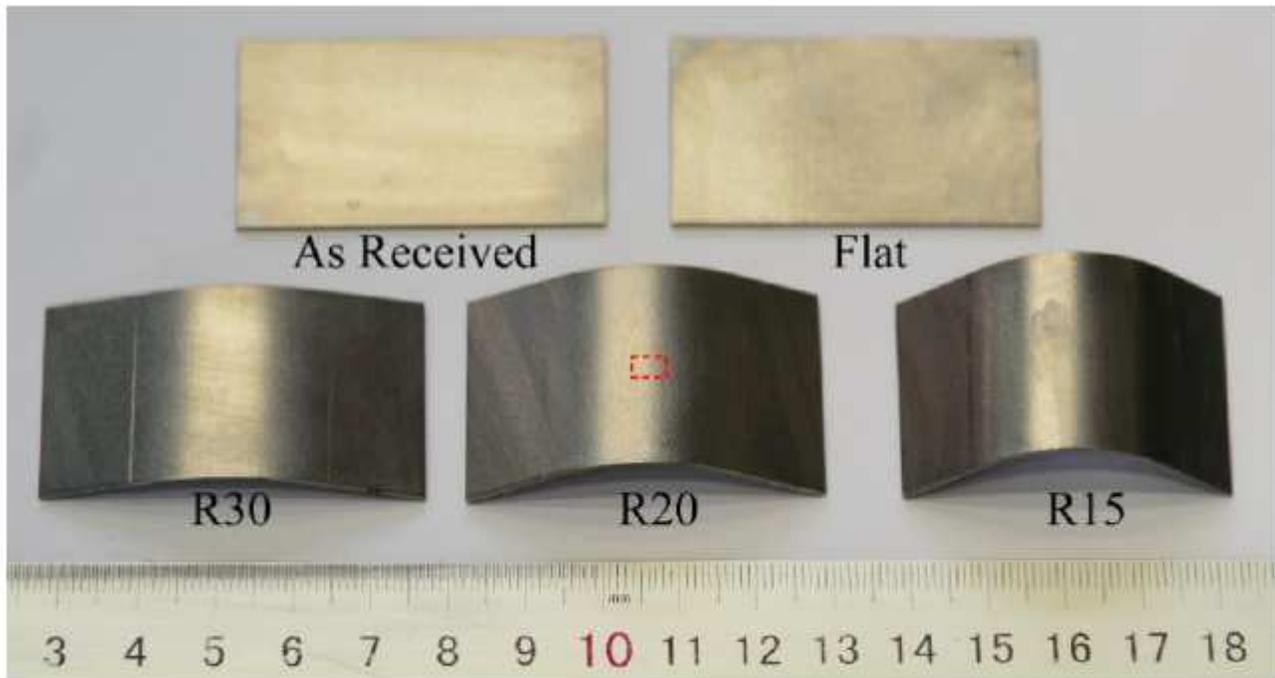


Figure 17

Image of the as received sheet and the specimens stamped by flat and curved dies (R30, R20, R15)

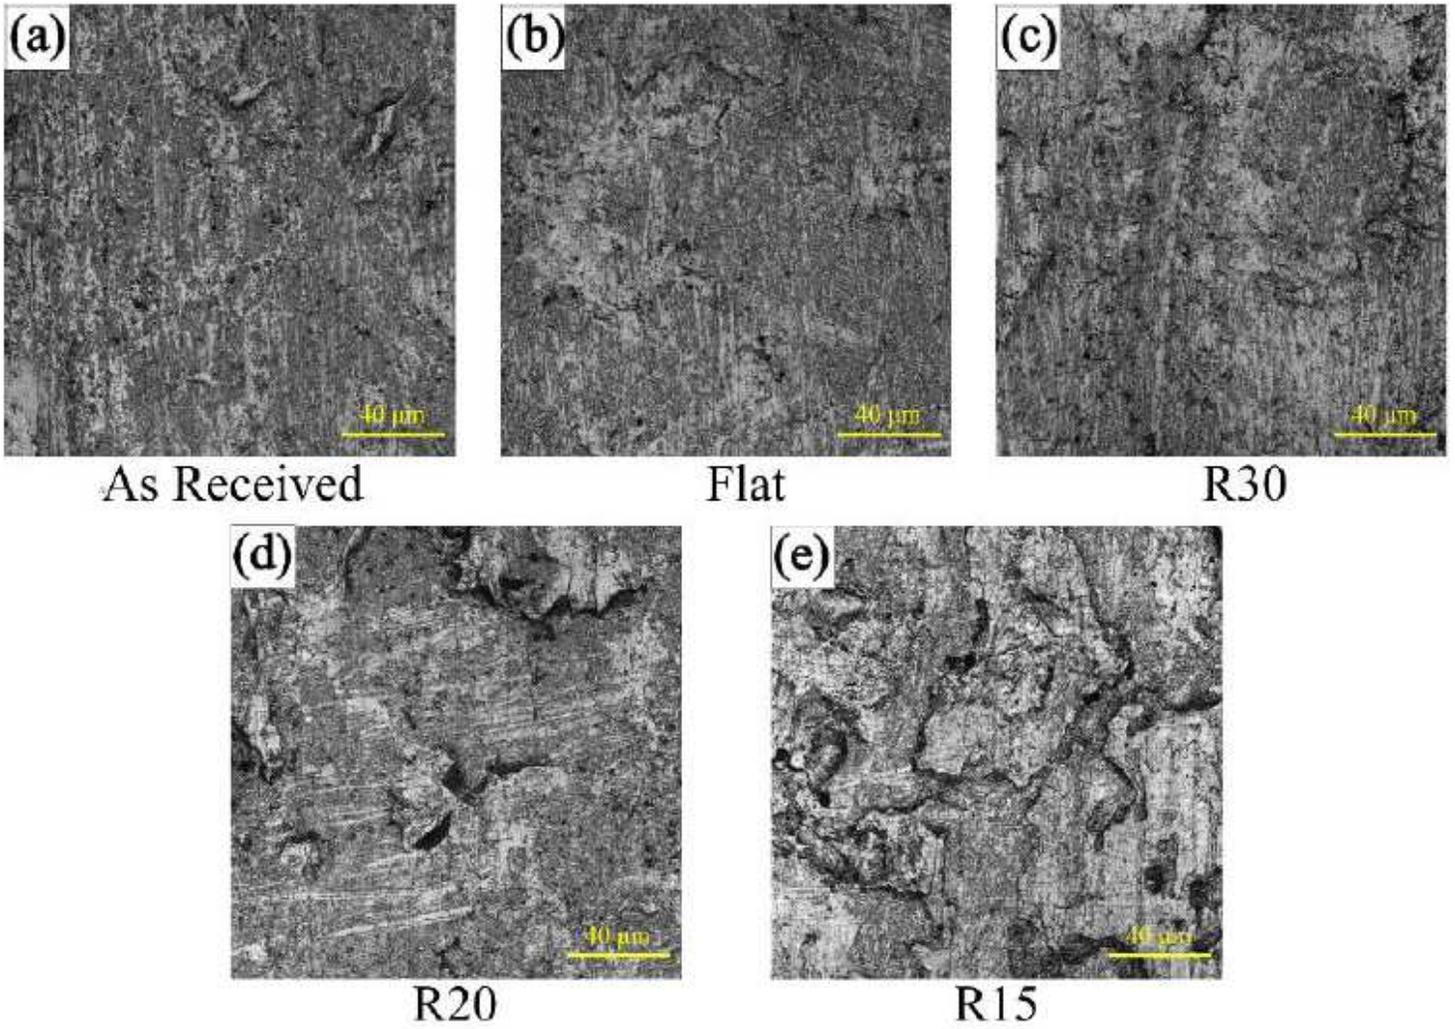


Figure 18

Surface morphology the as received sheet and the specimens stamped by flat and curved dies (R30, R20, R15)

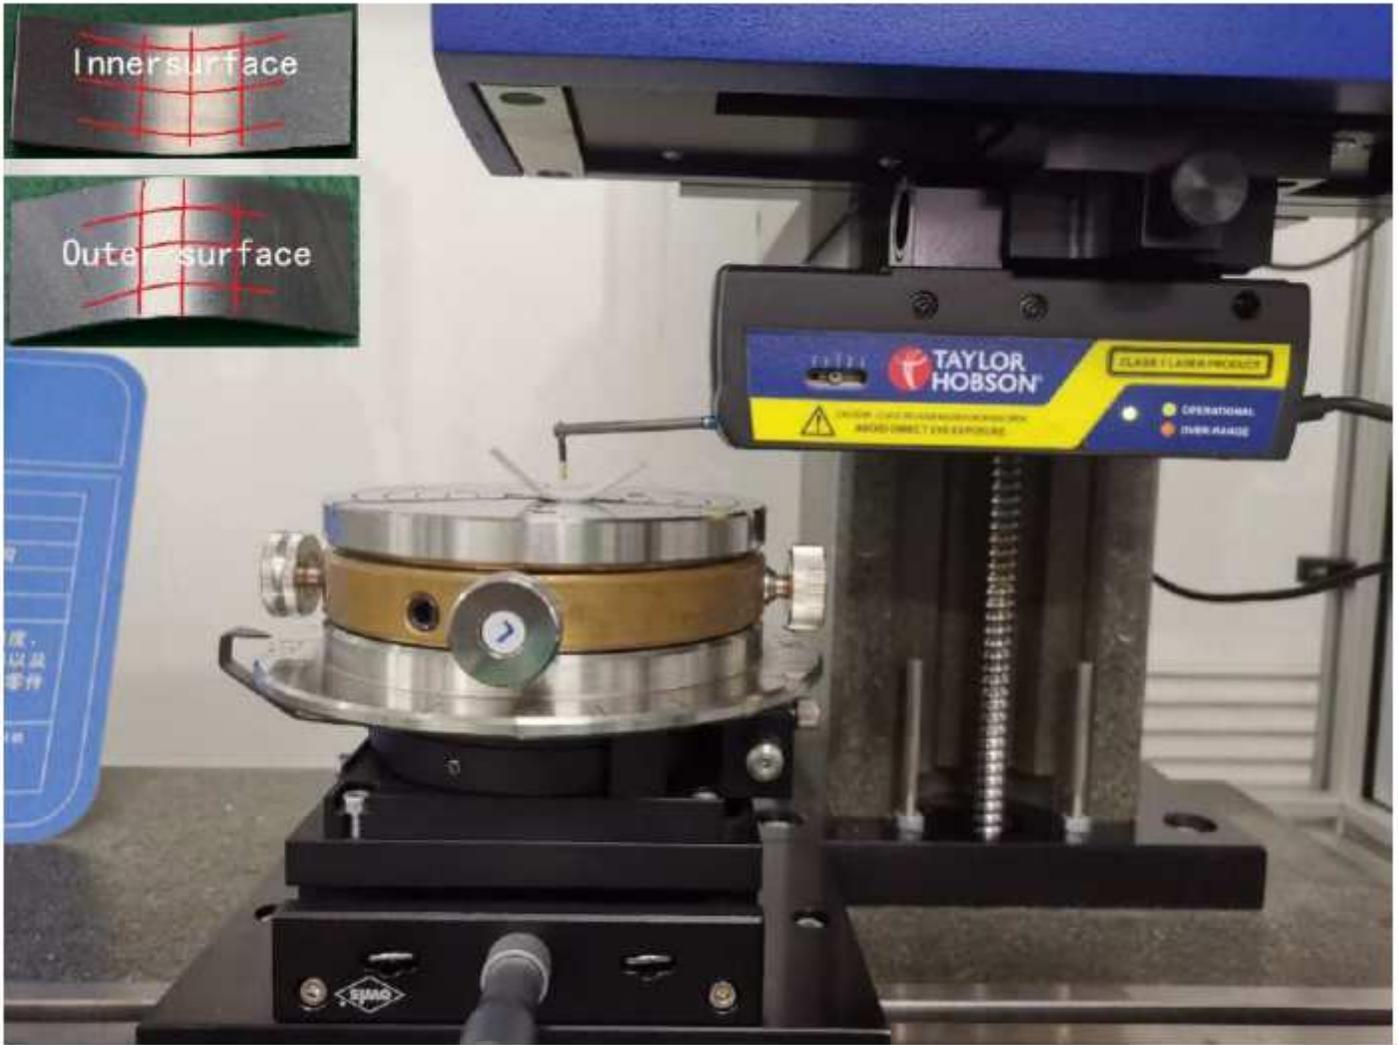


Figure 19

Surface roughness measurement by 3D surface profiling instrument

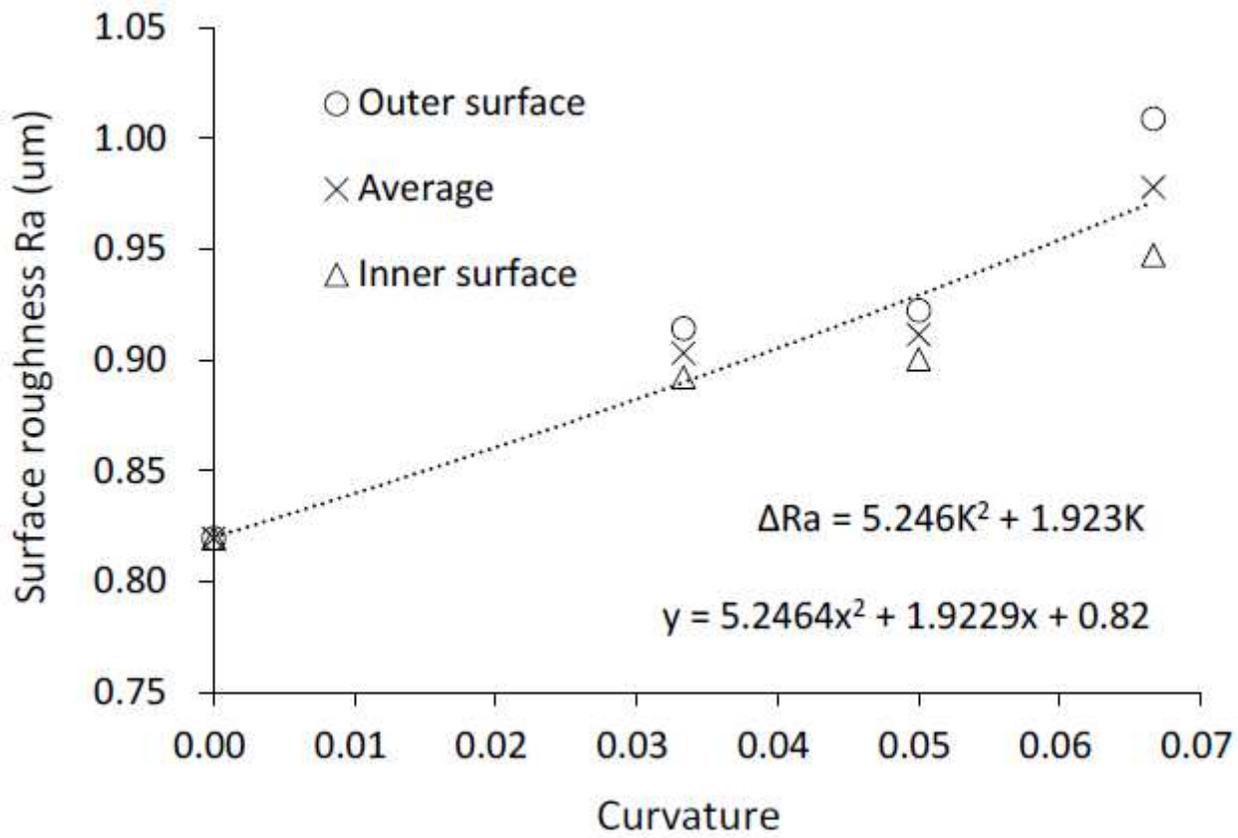


Figure 20

Surface roughness of the specimens stamped by flat and curved dies (R30, R20, R15)

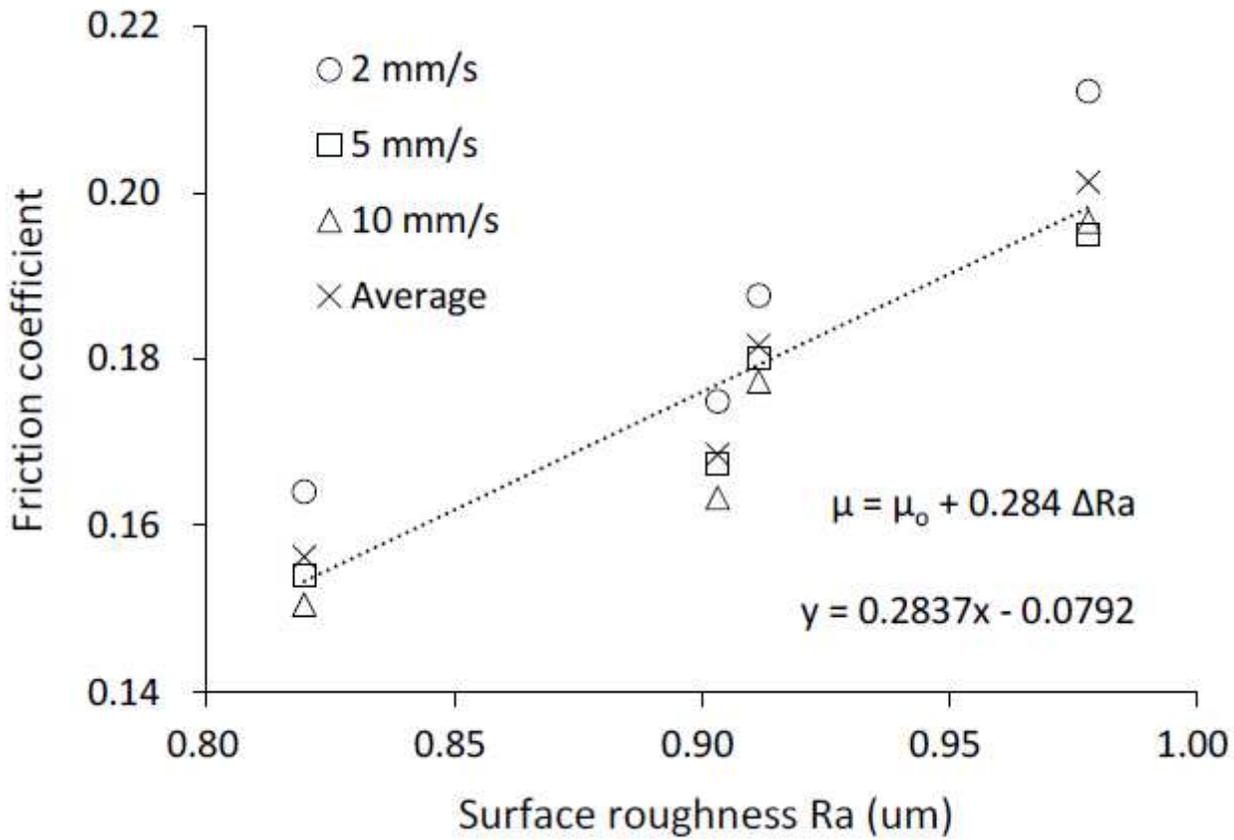


Figure 21

Relationship between surface roughness and friction coefficient

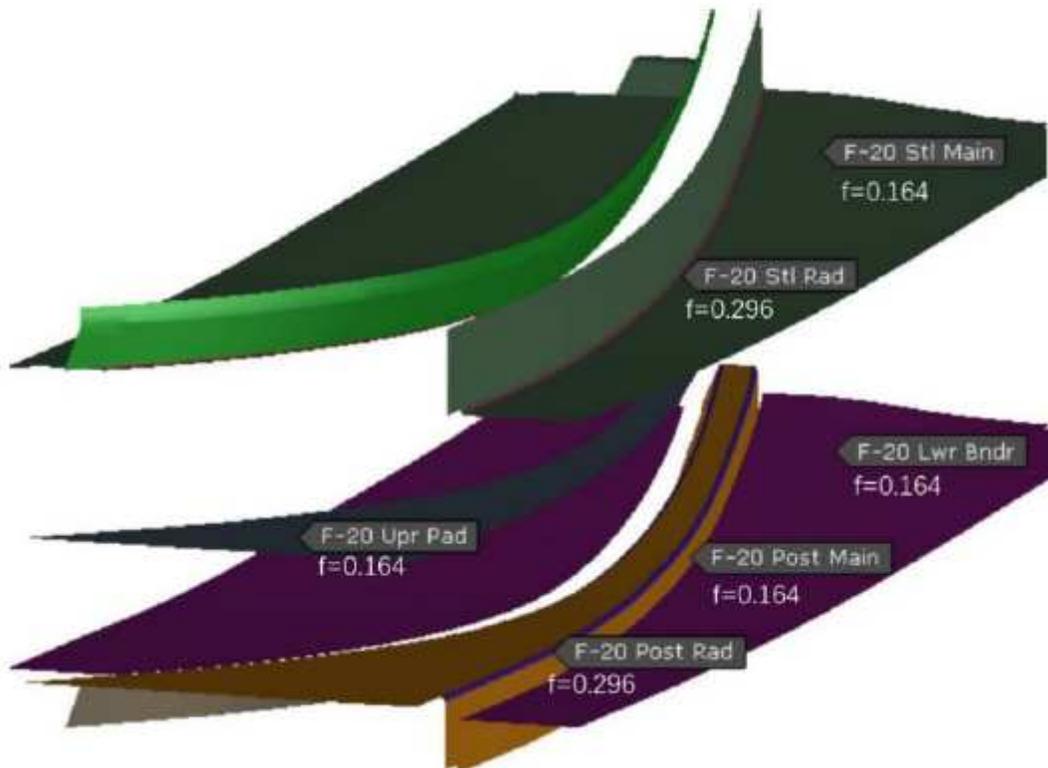


Figure 22

Die setup for stamping an automotive front load beam

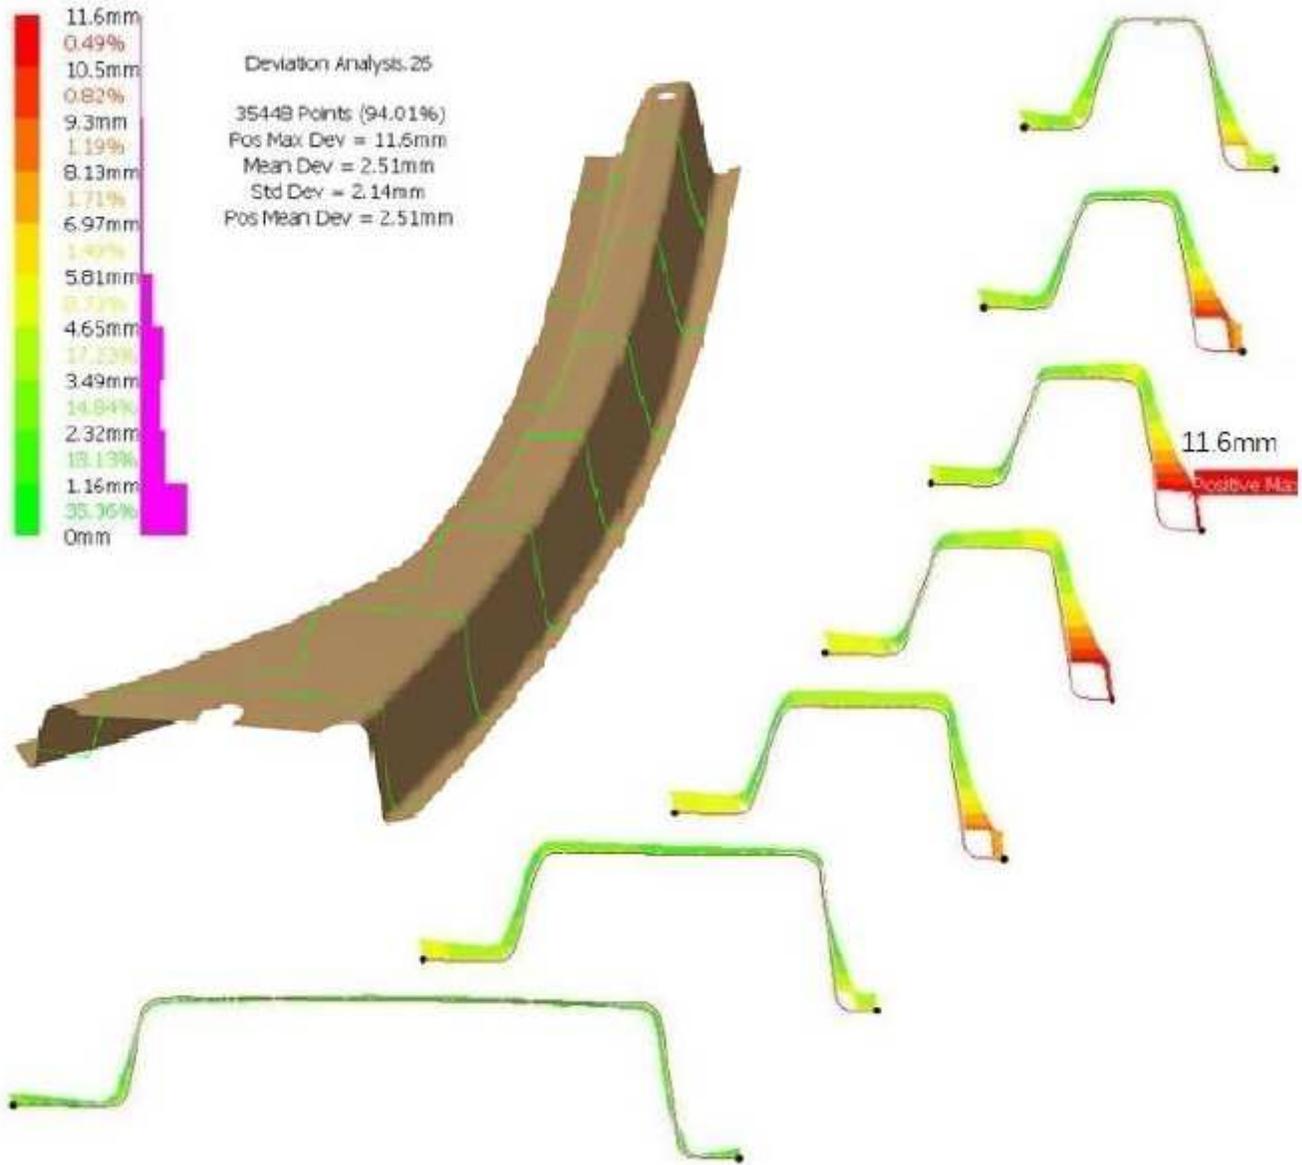


Figure 23

Measured springback magnitude of the load beam

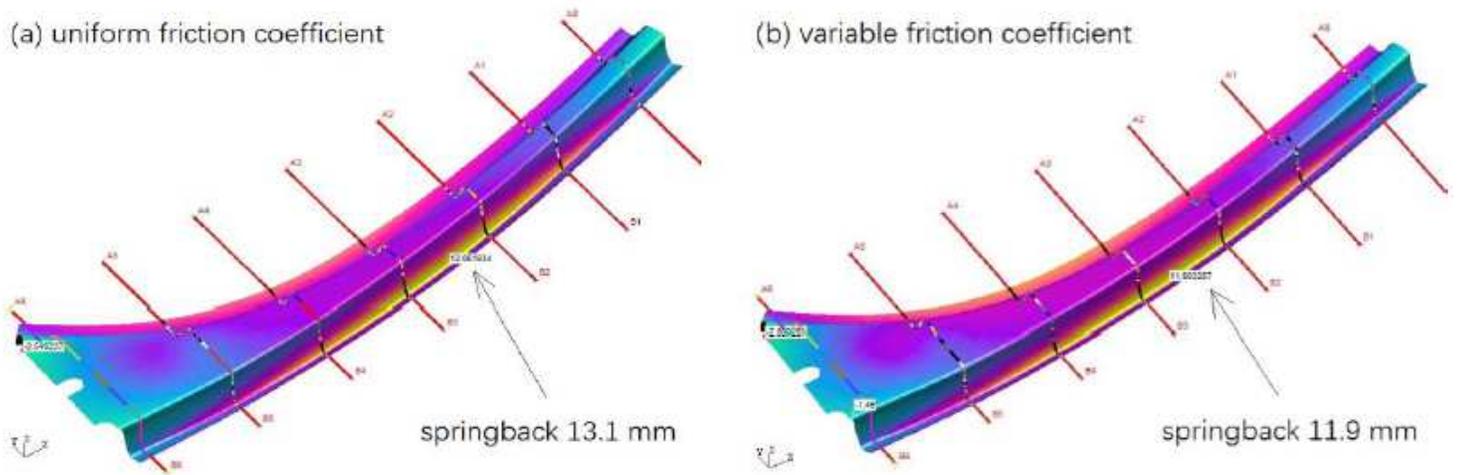


Figure 24

Simulated springback magnitude of the load beam: (a) conventional uniform friction coefficient model; (b) enhanced variable friction coefficient model

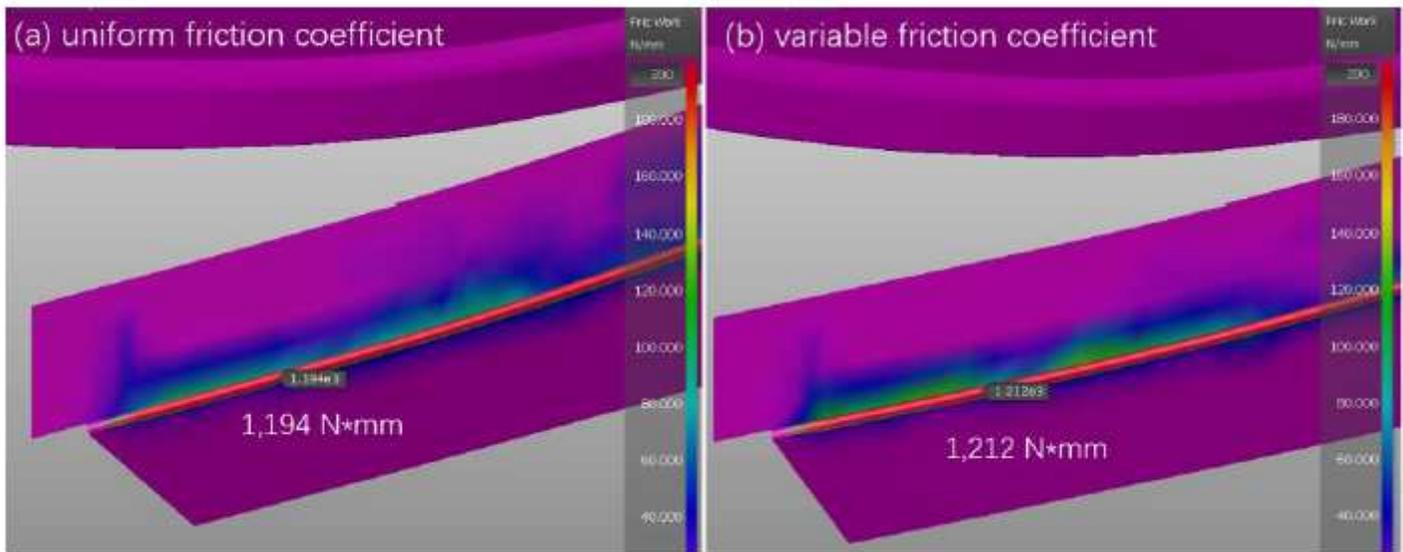


Figure 25

Simulated die wear in term of friction work: (a) conventional uniform friction coefficient model; (b) enhanced variable friction coefficient model