

Efficient Oil-Water Separation Coating With Robust Superhydrophobicity and High Transparency

Baiyi Chen (✉ baiyi0112@163.com)

Xiamen University

Rongrong Zhang

Xiamen University

Hexuan Fu

Xiamen University

Jiada Xu

Xiamen University

Yuan Jing

Xiamen University

Guohe Xu

Hebei Agricultural University

Xu Hou

Xiamen University

Research Article

Keywords: oil-water separation, coating, robust, superhydrophobicity, high transparency, coating, phenomenon

Posted Date: September 28th, 2021

DOI: <https://doi.org/10.21203/rs.3.rs-930057/v1>

License:  This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

Version of Record: A version of this preprint was published at Scientific Reports on February 9th, 2022. See the published version at <https://doi.org/10.1038/s41598-022-06220-9>.

Abstract

There has been a growing interest in oil-water separation due to the massive economic and energy loss caused by world-wide oil spill. In the past decades, a new type of superhydrophobic surface has been developed for the efficient oil-water separation, but its large-scale use is significantly limited by its expensive, sophisticated, and fragile roughness structure. Meanwhile, to handle complex operating conditions, the transparency of the superhydrophobic surface has been more attractive due to its potential visual oil-water separation and optical applications. Herein, we showed a simple and versatile strategy to fabricate superhydrophobic coating with robustness and high transparency. Subsequently, this multifunctional superhydrophobic coating was utilized for oil-water separation and indicated excellent separation efficiency. In this strategy, candle soot composed of carbon nanoparticles was deposited onto the substrate and used as a rough surface template. Then, a filmy and hard silica shell was modified onto this template via chemical vapor deposition to reinforce the roughness structure. Following, this soot-silica coated substrate was calcined in air to remove the candle soot template. Finally, based on a rational surface design, this robust silica coating achieved excellent superhydrophobicity thereby showing inherently oil-water separation benefits. This reinforced superhydrophobic coating presented robust superhydrophobicity even after 410 s sand impacting with the height of 40 cm. Also, it retained excellent oil-water separation efficiency even after reuses.

Introduction

Superhydrophobicity refers to the phenomenon with the contact angle between water and the corresponding surface greater than 150° and the rolling angle less than 10° ^{1,2}. From ancient cave paintings to modern microfluidic devices³, numerous researches and practical applications have been devoted to deepening the understanding of the superhydrophobic surface. The inherently merits of superhydrophobic surface, such as its self-cleaning, drag reduction, condensation-heat transfer, anti-fouling and anti-icing,⁴⁻⁹ have shown great potentials for broad applications in industry, biomedicine, military, and many other fields¹⁰⁻¹⁴. However, limited on the precise micro-nano hierarchical structure which normally relies on the sophisticated micro- and nano-particles physical accumulation¹⁵⁻¹⁸, the improvement of the superhydrophobic surface remains challenging, especially its functional integration and durability in practical application scenarios.

To handle these problems, many efforts have been devoted to developing robust and multi-functional superhydrophobic surfaces to adapt to the complex and harsh environments.¹⁹⁻²¹ Recently, Seeger et al.²² has created a hierarchical architecture combining micro- and nano-scale structure to protect the superhydrophobic surface with precise roughness from the mechanical damage. Glass beads (75 μm) were partially embedded in the low-density polyethylene matrix, followed by coating with nanoscale silicone filaments. Furtherly, TiO_2 nanoparticles were synthesized in situ on the silicone nanofilaments as photocatalyst. Consequently, it has been demonstrated this hierarchical composite surface possessed self-cleaning property and enhanced mechanical durability. Additionally, Deng et al.²³ developed a robust

superhydrophobic surface by structuring it with a hierarchical micro-nano system. The interconnected micro-structured surface frame acted as an 'armour' to provide the robustness, and the fluorinated nano-structured silica clusters housed in the micro-structured frame ensured its water repellency. Especially, this strategy can be applied to various substrates and showing strong superhydrophobicity even after abrasion by sandpaper or sharp steel blade. However, the robust function-integrated superhydrophobic coating is still in its early stage, and there are many challenges to be done for its development, such as the complex and cumbersome preparation²⁴, high-cost²⁵ and poor functional stability²⁶, which have severely limited its large-scale application. Thus, the exploitation of a durable and function-integrated superhydrophobic coating with simple and versatile preparation is essential to make up for the lack of the conventional superhydrophobic coating.

In this work, we have shown a simple and versatile strategy to develop a new type of robust superhydrophobic coating with high transparency. Firstly, candle soot was physically accumulated onto the quartz wafer surface forming a template. Then, a silicon dioxide layer was deposited on the template by chemical vapor deposition of SiCl_4 to create a hard and rough coating. Based on a rational surface design, this robust coating achieved excellent superhydrophobicity thereby showing inherently oil-water separation benefits and broke the limitations of conventional superhydrophobic surface. This robust superhydrophobic coating fabricated in this way not only greatly improved its abrasion resistance, but also had low cost and simple operation, and could be mass-produced and popularized. Moreover, this highly transparent superhydrophobic coating possessed excellent optical transmittance to facilitate the real-time observation of the separation process in the oil-water separation device and make target adjustments. It is believed that this transparent superhydrophobic coating has potential applications in various aspects such as isolation film, protective glasses, lens coating and touch screen.

Materials And Methods

Materials. Candle (Kameyama Co., Ltd., Japan), Oil blue 35 (Askul Co., Ltd., Japan), stainless steel mesh with the average pore size of 800 μm (Huirui wire mesh Co., Ltd, China), Scarlet 4GE (Askul Co., Ltd., Japan), gasoline (Komeri Co., Ltd., Japan) and sea sands. The laboratory solvents and Trichloro (1H, 1H, 2H, 2H-perfluorooctyl) silane were purchased from Nacalai tesque.

Fabrication of the transparent, robust and superhydrophobic coating. To achieve a robust, transparent and superhydrophobic coating, the substrate (quartz wafer or stainless-steel mesh) was first thoroughly washed with ethanol and deionized water thoroughly, and dried in an oven at 60°C. The cleaned substrate was then placed over the candle flame until a few microns thick layer of soot was deposited. Subsequently, the soot coated substrate together with SiCl_4 were placed in a drier for chemical vapor deposition about 2 h. As a result, like the Stöber reaction²⁷, a porous silica shell was formed on the soot coated substrate by hydrolysis and condensation of SiCl_4 . Then, through calcination at 600°C for half an hour in air, the candle soot composed of carbon nanoparticles thermally degraded and diffused through the silica shell gradually. Consequently, a superhydrophilic and hollow silica shell was produced on the substrate. To modify the surface into superhydrophobic, the silica shell was performed chemical vapor deposition in a drier together with about 1 mL of trichloro (1H, 1H, 2H, 2H-perfluorooctyl) silane for 2 h at 60°C. Finally, a superhydrophobic coating was obtained on substrate caused by stable oxane bonds formed between abundant hydroxide radical on silica shell and silane.

Furthermore, in order to investigate the oil-water separation application of this transparent, robust and superhydrophobic coating, a rounded stainless-steel mesh was utilized as substrate to perform the modification. In particular, both sides of the mesh were modified to ensure its superhydrophobicity entirely.

Robustness tests. To study the mechanical properties of the superhydrophobic coating, sea sands with the average particle size of 300 to 500 μm were employed to impact the multifunctional superhydrophobic coating surface from a height of 40 cm, while the substrate was held at 30° to the horizontal surface. After a certain time of impact, this coating was observed and its water contact angle was measured.

Oil-water separation. To investigate the oil-water separation application of the multifunctional superhydrophobic coating, the oil-water mixture was formed by mixing dichloromethane (5 mL) dyed with Solvent Blue 35 and water (5 mL) dyed with Scarlet 4GE. The oil-water separation device was prepared by placing a round modified stainless steel mesh between the split type funnel, and then placed it on the top of a flask. During the oil-water separation, the dichloromethane-water mixture was used as a representative and quickly poured into the separation device, the oil phase was allowed to permeate through the modified stainless-steel mesh while the water phase was blocked. Finally, the oil-water separation efficiency was studied by measuring the water content in the separated oil phase.

Characterization. Surface morphologies of samples were carried out on a Hitachi s-4800 (Hitachi, Japan) Field-emission Scanning Electron Microscope (SEM) at 15.0 kV. Moisture in oil phase was analyzed by Karl Fischer Moisture Titrator (MKC-60 Kyotoelectronics) Manufacturing Co. LTD., Japan). The contact angle (CA) was characterized on an OCA100 instrument (Dataphysics, Germany) in air. Water droplets around 4 μL in volume were placed on multiple areas on the surface of samples. Photographic images were taken with a Nikon camera (D 5000).

Results And Discussion

According to the illustration shown in Fig. 1, the cheap and accessible candle soot were utilized as a rough surface template to directly deposit onto the substrate. The candle soot was composed of carbon nanoparticles forming by incompletely burned paraffin, which loosely accumulated on the substrate and formed a rough surface. Following, a hard and porous silica shell was deposited on the candle soot template through chemical vapor deposition of SiCl_4 like Stöber reaction, which completely replicate the roughness of the template and formed a robust rough surface. Because the thickness of the silica shell was much smaller than the wavelength of visible light (420 ~ 700 nm), it showed good transparency. After removal of the carbon nanoparticles template by calcination in air, the hard and transparent silica shell was reserved on substrate. Due to the abundant hydroxyl on this silica shell, it can be easily modified into superhydrophobicity through grafting trichloro (1H, 1H, 2H, 2H-perfluorooctyl) silane. As a result, a transparent silica coating with robust superhydrophobicity was obtained by rational surface design.

Surface modification and characterization. During preparation of this transparent and robust superhydrophobic coating, the surface wettability has changed significantly. Taking the quartz wafer sample as representative, its surface modifications have been successfully demonstrated (Fig. 2). As shown in Fig. 2a, the bare quartz wafer was washed carefully with dry ethanol, ethanol-deionized water (v/v 1:1) and deionized water in turn, and then characterized by SEM, CA and EDS. The SEM images

indicated that the surface morphology of bare quartz wafer was homogeneous and smooth, and the EDS analysis only detected the signals of Si and O, the main elements that constituted quartz wafer, indicating a thoroughly clean surface. Meanwhile, the bare quartz wafer showed a hydrophilic surface with the water droplet contact angle of 58.4° , which was mainly due to the presence of hydroxyl on its surface.

Following, to prepare the candle soot template, the abluent quartz wafer was held above the flame of a candle for 3–5 s until a black soot layer with a few micrometers thickness was deposited. As can be seen in Fig. 2b, the SEM and EDS analysis indicated that the candle soot had formed a loose and porous layer, which consisted entirely of carbon nanoparticles with the diameter of 30 to 40 nm. Meanwhile, a rough surface formed by accumulating candle soot nanoparticles can be observed on the quartz wafer. As is well recognized, the surface chemical composition and morphology are considered to be the key factors for obtaining superhydrophobicity on solid surface.²⁸ The surface chemical composition with low surface energy ensures its hydrophobicity, and the rough surface morphology with micro-nano hierarchical structure amplifies hydrophobicity into superhydrophobicity furtherly.²⁹ For instance, the surface of an abluent plastic sheet is only naturally hydrophobic, but not superhydrophobic (CA above 150°). However, it is interesting to note that a rough surface accumulated by hydrophobic nanoparticles can be amplified into superhydrophobicity. Therefore, the rough surface formed by accumulating candle soot nanoparticles showed a significant superhydrophobicity with water contact angle of 154.4° . Due to the weak physical interaction between the soot nanoparticles, this soot deposition layer was fragile. As water droplets rolled down from it, the soot nanoparticles were easily taken off by the droplets until nearly all of the deposits were removed, causing a wettability transition of the surface. Inspired by the promising morphology and super-wettability of candle soot deposits, a novel method to replicate and enhance the roughness structure was adopted³⁰. In this method, a silica shell was prepared to cover the candle soot layer by chemical vapor deposition of SiCl_4 , as shown in Fig. 1. As can be seen from Fig. 2c obviously, the average particle diameter of the candle soot increased slightly after the silica deposition, but its original morphology has been completely replicated. This has demonstrated that the roughness structure of the candle soot layer was not destroyed by chemical vapor deposition of SiCl_4 . Thus, the silica shell obtained superhydrophilicity (CA about 0°) due to the hydrophilicity of the silica and the roughness structure of candle soot layer. The SEM image and EDS analysis of the silica shell after calcination was shown in Fig. 2d. As can be seen from this figure, the candle soot template composed by carbon nanoparticles has been removed during calcination in air, but its rough and porous surface morphology was completely reserved by the hard silica shell. After surface modification by grafting with trichloro (1H, 1H, 2H, 2H-perfluorooctyl) silane, the silica shell surface showed a static contact angle of 153.0° . Because of the extremely low adhesion interaction between water and this superhydrophobic surface, the water droplets would be difficult to deposit and immediately roll off. In some special application scenarios, such as goggles or touch screens, the superhydrophobic coating would require transparency, heat stability and mechanical robustness. Since the thickness of the hollow silica shell was smaller than the wavelength of visible light, this shell was highly transparent. By calcination, the candle soot carbon nanoparticles disappeared and cavities were formed. The visible light transmittance of the quartz wafers before and after modification with transparent superhydrophobic coating were measured and shown in Fig. 2e top,

the transparent superhydrophobic coating modified quartz wafer showed almost the same transparency with the bare quartz wafer. Moreover, this transparent superhydrophobic coating also showed excellent thermal stability, which remained superhydrophobicity even after 1 h calcination under high temperature up to 300°C (Fig. 2e bottom).

Robustness. When exposed to the natural environment, the superhydrophobic coating should be endowed mechanical robustness against the harsh application scenarios. Therefore, sand abrasion test was performed on this superhydrophobic coating to characterize its mechanical durability. Sand particles with an average diameter of 300 to 500 μm were used to impact the superhydrophobic coating directly from a height of 40 cm (Fig. 3a), and the corresponding impact energy was 1.1×10^{-4} J/particle. As shown in Fig. 3b and c, the superhydrophobic silica shell were strong enough to fully withstand the impact of sand particles in 410 s. As the impact time increases, holes were eventually formed in the impacted area, and the silica shells were partially destroyed (Fig. 3d). In spite of this, the SEM image of the partially destroyed superhydrophobic coating indicated that the microscopic morphology of the cavities had hardly changed (Fig. 3d). Due to the self-similarity of the silica shell, this coating remained superhydrophobicity (CA = 151.8°) until the silica shell was completely removed from the substrate after continuous impact. The mechanical durability of the superhydrophobic coating mainly depended on the sand grains size, the sand impinging amount per time unit, the thickness of the silica shell, and the height of fall. And it would increase with the thickness of the silica shell, but at the expense of the coating's transparency.

Oil-water separation. This superhydrophobic coating can be also used for oil-water separation due to its durable superhydrophobicity under oil. Thus, we utilized the strategy mentioned above to prepare an oil-water separation device with the stainless-steel mesh as substrate. Dichloromethane-water mixture was used as the representative to study the oil-water separation efficiency and oil flow rate, the results were shown in Figs. 4 and 5.

Both sides of the stainless-steel mesh were coated by the superhydrophobic silica shell as the oil-water separation mesh, and then the as-prepared mesh was imbedded into a split type filter. The filter was finally placed on a flask as shown in Fig. 4a. Following, the same volume (5 mL) of blue-dyed oil and red-dyed water was uniformly mixed and poured into the filter rapidly. Driven by gravity only, blue-dyed oil penetrated through the mesh immediately and red-dyed water was prevented (Fig. 4b and c). The oil-water mixture was completely separated; this was because the durable superhydrophobicity of the silica shell coated mesh even immersed under oil. The hydrophobic-oleophilic shell held a stable oil layer on its roughness surface, which constructed a 3-phase interface with water and prevented water from penetrating through the separation mesh (Fig. 4d). In addition, after oil-water separation course, the superhydrophobicity of the modified mesh was tested again. Water droplets did not wet or even contaminate the surface, demonstrating the reusability of the superhydrophilic surface.

According to the Cassie and Baxter theory³¹, the three-phase interface is necessary for forming superhydrophobic surface. During the oil-water separation, the water-oil-solid system also constructed a three-phase interface and repelled water off, which only allowed the oil through. Ultimately, the oil-water

mixture was successfully separated only dependent on gravity by utilizing the feature of this superhydrophobic coating, indicating the low energy consumption and easy operation of this strategy.

Due to the frequent offshore oil spills, it is very necessary to spread the oil-water separation application to different oil-water mixtures. We chose chloroform, toluene, gasoline and dichloromethane as the oil phase to blend with water. The separation efficiency was investigated to quantitatively evaluate separation property of our device, which was defined as the water content in oil after separation and measured by Karl Fischer moisture titrator. There were large differences of the separation efficiencies between different oil-water mixtures, this was mainly because water showed different solubility in different oil. The water contents in oil after separation were tested and shown in Fig. 5a, the separated gasoline, toluene, chloroform and dichloromethane presented water contents of 133 ppm, 262 ppm, 148 ppm and 77 ppm, respectively. Additionally, we also calculated the flow rate of different oil during separation through measuring its passing time, the results have been shown in Fig. 5b. The toluene-water and gasoline-water mixtures showed the peak flow rates of 0.991 and $1.4 \text{ m}^3 \cdot \text{m}^{-2} \cdot \text{h}^{-1}$, which indicated the oil kinds influenced the penetrating rate significantly. For chloroform, its mixture needed longer time for stratification after mixing thoroughly. Therefore, it showed a relatively low flow rate of $0.586 \text{ m}^3 \cdot \text{m}^{-2} \cdot \text{h}^{-1}$. After that, the gasoline-water mixture was used as a representative and continuously separated for 6 times to investigate the cycle stability of this separation device, and the separation efficiencies and flow rates were studied (Fig. 5b). For each separation cycle, the water content of the separated gasoline was below 300 ppm. In addition, the flow rate stabilized at about $1.0 \text{ m}^3 \cdot \text{m}^{-2} \cdot \text{h}^{-1}$, which verified the availability of this separation device. To sum up, the results indicated that this superhydrophobic coating has exhibited excellent comprehensive performance, not only in robustness and transparency, but also in oil-water separation applications.

Conclusion

In summary, we have designed a highly transparent, robust and superhydrophobic coating using a versatile and simple straightforward template method, and its oil-water separation application has been demonstrated. In this work, the cheap and accessible candle soot composed of carbon nanoparticles was utilized as a rough template to obtain the hard and transparent silica shell with roughness. Following, the candle soot rough template was removed by calcining in air, thus a hollow and transparent silica shell was obtained. Furtherly, this silica shell with abundant hydroxyl was modified into superhydrophobic by grafting low surface energy substance, and ultimately used for oil-water separation. At the same time, the transparency, robustness and oil-water separation properties of this superhydrophobic coating were investigated. The results showed this transparent and robust superhydrophobic coating was successfully prepared and its water contact angle was 153.0° . The reinforced coating presented a mechanical robustness withstanding of 410 s sand impact. Additionally, the superhydrophobic coating revealed excellent separation efficiency and cycle stability in oil-water separation application. It remained good oil flow rate and oil-water separation efficiency even after 6 times reuses.

It can be believed that this transparent and robust superhydrophobic coating could be potentially used in optical and visual application scenarios where suffer from harsh and oily environments, such as the goggles, building facade, visual oil-water separation device and touch screen.

Declarations

Acknowledgements

This work was supported by the National Key R&D Program of China (2018YFA0209500), Science and Technology Research Project of Higher Education in Hebei Province of China (supported by Education Department of Hebei Province NO. BJ2017026), the National Natural Science Foundation of China (52025132, 21975209, 12075191, 22005255), the Fundamental Research Funds for the Central Universities of China (20720190037), and CAS Key Laboratory of Bio-inspired Materials and Interfacial Science, Technical Institute of Physics and Chemistry, Chinese Academy of Sciences.

Author contributions

B.C. and R.Z. performed the experimental procedures, B.C. and G.X. established the main idea and wrote the manuscript text, X.H., H.F., J.X. and Y.J. edited the manuscript text and helped perform the experiments.

Competing interests

The authors declare no competing interests.

Additional information

Correspondence and requests for materials should be addressed to B.C. or G.X.

Reprints and permissions information is available at www.nature.com/reprints.

Publisher's note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

References

1. Feng, L. *et al.* Super-hydrophobic surfaces: from natural to artificial. *Adv. Mater*, **14**, 1857–1860 <https://doi.org/10.1002/adma.200290020> (2002).
2. Barthlott, W. & Neinhuis, C. Purity of the sacred lotus, or escape from contamination in biological surfaces. *Planta*, **202**, 1–8 <https://doi.org/10.1007/s004250050096> (1997).
3. Wang, S., Liu, K., Yao, X. & Jiang, L. Bioinspired surfaces with super wettability: new insight on theory, design, and applications. *Chem. Rev*, **115**, 8230–8293 <https://doi.org/10.1021/cr400083y> (2015).

4. Gao, X. *et al.* The dry-style antifogging properties of mosquito compound eyes and artificial analogues prepared by soft lithography. *Adv. Mater*, **19**, 2213–2217 <https://doi.org/10.1002/adma.200601946> (2007).
5. Milijkovic, N., Enright, R. & Wang, E. N. Effect of droplet morphology on growth dynamics and heat transfer during condensation on superhydrophobic nanostructured surfaces. *ACS Nano*, **6**, 1776–1785 <https://doi.org/10.1021/nn205052a> (2012).
6. Xiao, Z. *et al.* Highly efficient oil/water separation and trace organic contaminants removal based on superhydrophobic conjugated microporous polymer coated devices. *Chem. Eng. J*, **326**, 640–646 <https://doi.org/10.1016/j.cej.2017.06.023> (2017).
7. Ye, C. *et al.* Highly reflective superhydrophobic white coating inspired by poplar leaf hairs toward an effective “cool roof”. *Energy Environ. Sci*, **4**, 3364–3367 <https://doi.org/10.1039/C0EE00686F> (2011).
8. Jung, S., Tiwari, M. K., Doan, N. V. & Poulikakos, D. Mechanism of supercooled droplet freezing on surfaces. *Nat. Commun*, **3**, 615 <https://doi.org/10.1038/ncomms1630> (2012).
9. Mishchenko, L. *et al.* Design of ice-free nanostructured surfaces based on repulsion of impacting water droplets. *ACS Nano*, **4**, 7699–7707 <https://doi.org/10.1021/nn102557p> (2010).
10. Maguire-Boyle, S. J. & Barron, A. R. A new functionalization strategy for oil/water separation membranes. *J. Memb. Sci*, **382**, 107–115 <https://doi.org/10.1016/j.memsci.2011.07.046> (2011).
11. Alexander, S., Eastoe, J., Lord, A. M., Guittard, F. & Barron, A. R. Branched hydrocarbon low surface energy materials for superhydrophobic nanoparticle derived surfaces. *ACS Appl. Mater. Interfaces*, **8**, 660–666 <https://doi.org/10.1021/acsami.5b09784> (2016).
12. Vazirinasab, E. & Momen, R. J. G. Application of superhydrophobic coatings as a corrosion barrier: a review. *Surf. Coat. Technol*, **341**, 40–56 <https://doi.org/10.1016/j.surfcoat.2017.11.053> (2018).
13. Qi, H. *et al.* Bioinspired multifunctional protein coating for antifogging, self-cleaning, and antimicrobial properties. *ACS Appl. Mater. Interfaces*, **11**, 24504–24511 <https://doi.org/10.1021/acsami.9b03522> (2019).
14. Long, S. *et al.* An ultralight, super compressible, superhydrophobic and multifunctional carbon aerogel with a specially designed structure., **158**, 137–145 <https://doi.org/10.1016/j.carbon.2019.11.065> (2020).
15. Ju, G., Cheng, M. & Shi, F. A pH-responsive smart surface for the continuous separation of oil/water/oil ternary mixtures. *NPG Asia Mater*, **6**, e111 <https://doi.org/10.1038/am.2014.44> (2014).
16. Kin, J. Y., Kim, E. K. & Kim, S. S. Micro-nano hierarchical superhydrophobic electro-spray-synthesized silica layer. *J. Colloid. Interf. Sci*, **392**, 376–381 <https://doi.org/10.1016/j.jcis.2012.09.075> (2013).
17. Chu, F. & Wu, X. Fabrication and condensation characteristics of metallic superhydrophobic surface with hierarchical micro-nano structures. *Appl. Surf. Sci*, **371**, 322–328 <https://doi.org/10.1016/j.apsusc.2016.02.208> (2016).
18. Ju, G., Li, D. & Zhang, Y. Magnetically driven functionally integrated device for continuous and efficient collection of oil droplets from water. *RSC Adv*, **6**, 20559–20564

- <https://doi.org/10.1039/C5RA27908A> (2016).
19. Jin, H., Tian, X., Ikkala, O. & Ras, R. H. A. Preservation of superhydrophobic and superoleophobic properties upon wear damage. *ACS Appl. Mater. Interfaces*, **5**, 485–488 <https://doi.org/10.1021/am302541f> (2013).
 20. Zhu, L. *et al.* Superhydrophobic stability of nanotube array surfaces under impact and static forces. *ACS Appl. Mater. Interfaces*, **6**, 8073–8079 <https://doi.org/10.1021/am500261c> (2014).
 21. Li, X., Guan, T., Xu, F. & Sun, J. Durable, highly electrically conductive cotton fabrics with healable superamphiphobicity. *ACS Appl. Mater. Interfaces*, **10**, 10242–12050 <https://doi.org/10.1021/acsami.8b01279> (2018).
 22. Zhang, X. *et al.* Hierarchical structured multifunctional self-cleaning material with durable superhydrophobicity and photocatalytic functionalities. *Small*, **15**, 1901822 <https://doi.org/10.1002/sml.201901822> (2019).
 23. Wang, D. *et al.* Design of robust superhydrophobic surfaces. *Nature*, **582**, 56–59 <https://doi.org/10.1038/s41586-020-2331-8> (2020).
 24. Deng, B. *et al.* Laundering durability of superhydrophobic cotton fabric. *Adv. Mater*, **22**, 5473–5477 <https://doi.org/10.1002/adma.201002614> (2010).
 25. Song, J., Wang, D., Hu, L., Huang, X. & Chen, Y. Superhydrophobic surface fabricated by nanosecond laser and perhydropolysilazane. *Appl. Surf. Sci*, **455**, 771–779 <https://doi.org/10.1016/j.apsusc.2018.05.227> (2018).
 26. Mertaniemi, H. *et al.* Superhydrophobic tracks for low-friction, guided transport of water droplets. *Adv. Mater*, **23**, 2911–2914 <https://doi.org/10.1002/adma.201100461> (2011).
 27. Stöber, W. & Fink, A. Controlled growth of monodisperse silica spheres in the micron size range. *J. Colloid Interface Sci*, **26**, 62–69 [https://doi.org/10.1016/0021-9797\(68\)90272-5](https://doi.org/10.1016/0021-9797(68)90272-5) (1968).
 28. Chen, B. *et al.* Light-responsive and corrosion-resistant gas valve with non-thermal effective liquid-gating positional flow control. *Light Sci. Appl*, **10**, 127 <https://doi.org/10.1038/s41377-021-00568-9> (2021).
 29. Liu, T. & Kim, C. J. Turning a surface super repellent even to completely wetting liquids., **346**, 1096–1100 <https://doi.org/10.1126/science.1254787> (2014).
 30. Deng, X. *et al.* Candle soot as a template for a transparent robust superamphiphobic coating., **335**, 67–70 <https://doi.org/10.1126/science.1207115> (2012).
 31. Cassie, A. B. D. & Baxter, S. Wettability of porous surfaces. *Trans. Faraday Soc*, **40**, 546–551 <https://doi.org/10.1039/tf94444000546> (1944).

Figures

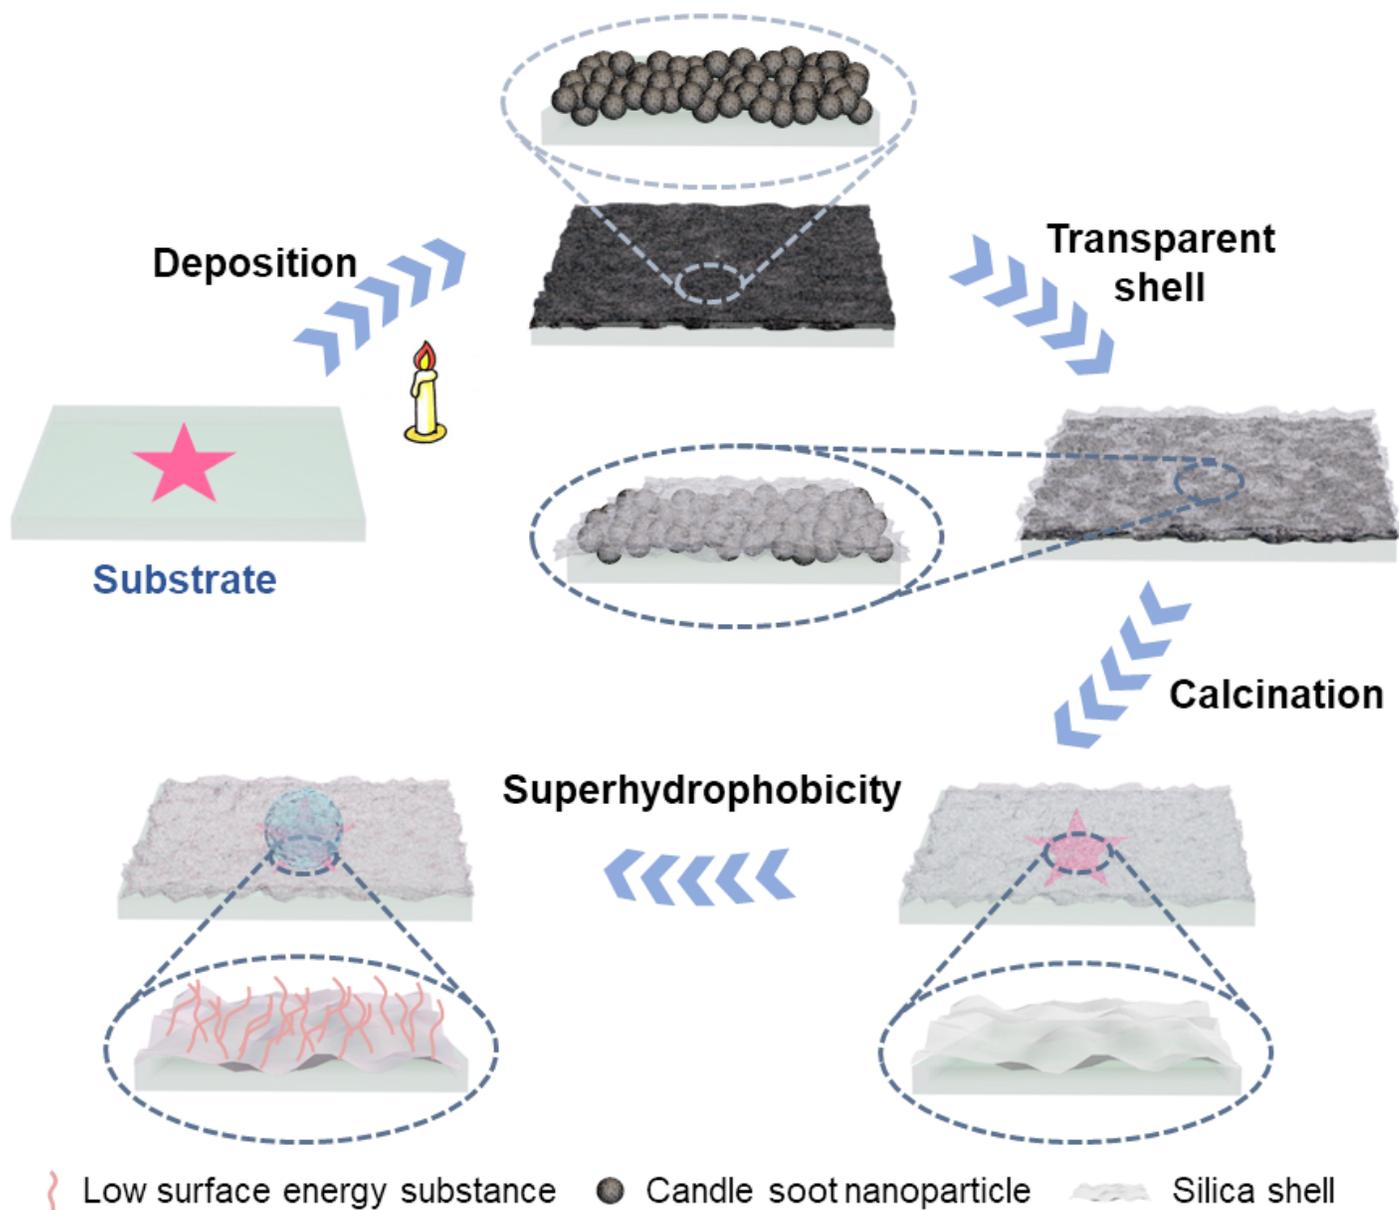


Figure 1

Schematic illustration of preparation and properties of the transparent and robust superhydrophobic coating.

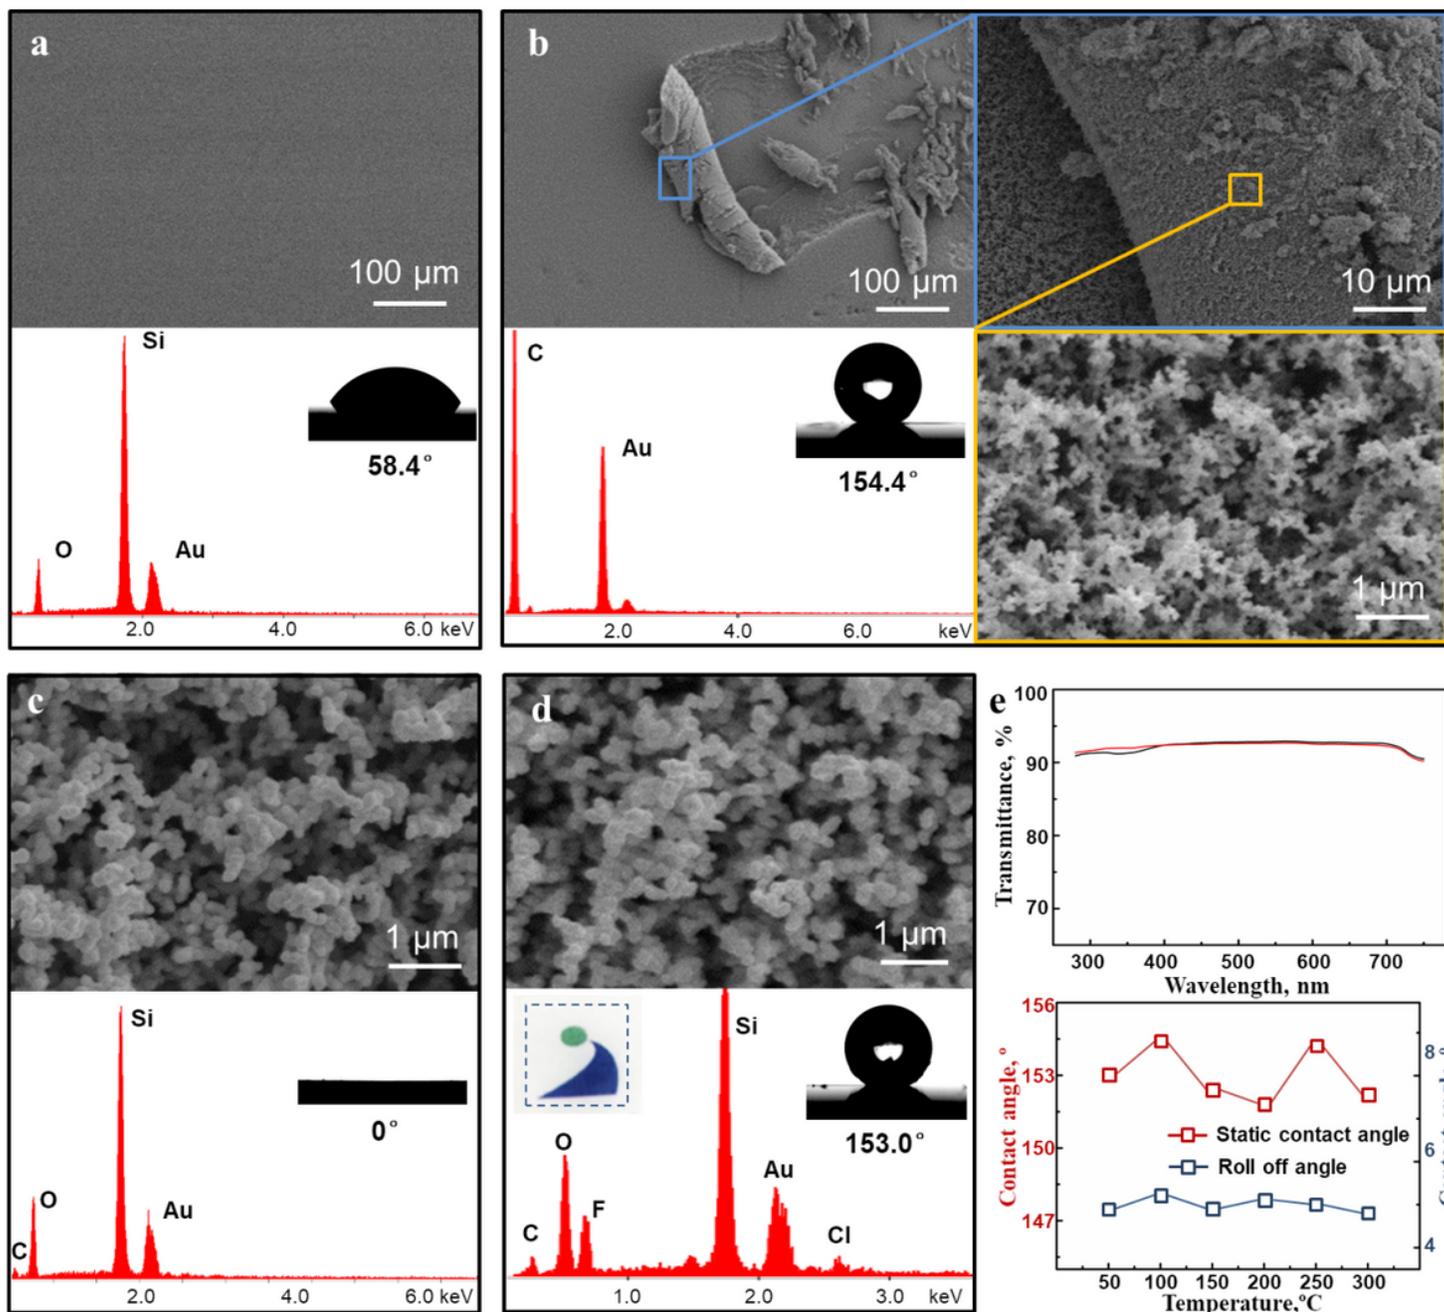


Figure 2

The SEM images, CA and EDX measurements of different quartz wafer samples: (a) the bare quartz wafer, (b) the quartz wafer with the candle soot rough template, (c) the quartz wafer with the silica shell reinforced rough template, (d) the quartz wafer with the hollow and superhydrophobic silica shell. (e) The visible light transmittance and thermal stability of the superhydrophobic coating.

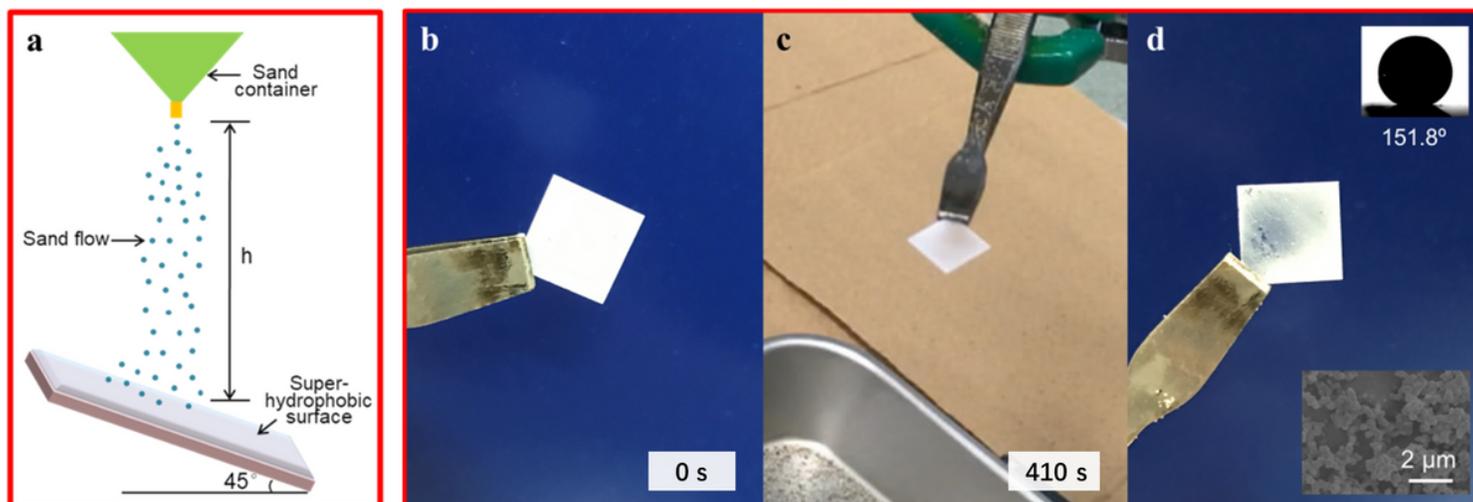


Figure 3

Sand abrasion test of the superhydrophobic coating: (a) schematic diagram of the sand abrasion test, (b) the superhydrophobic coating before sand abrasion, (c) the superhydrophobic coating during sand abrasion, (d) the superhydrophobic coating after sand abrasion, and its CA and SEM images were shown in the insets.

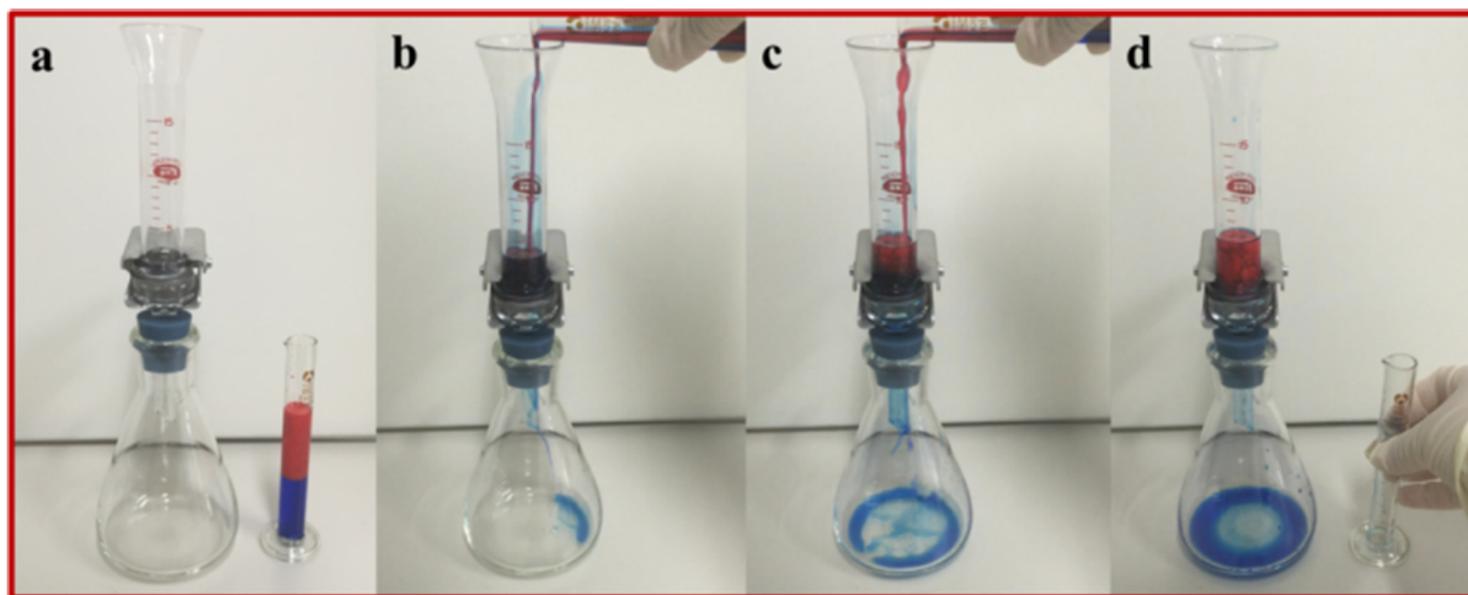


Figure 4

The oil-water separation application of the superhydrophobic coating: (a) Color-dyed oil-water mixture was prepared to be separated by the separation device. (b) The oil-water mixture was mixed uniformly and poured into the device. (c and d) The oil-water mixture was successfully separated.

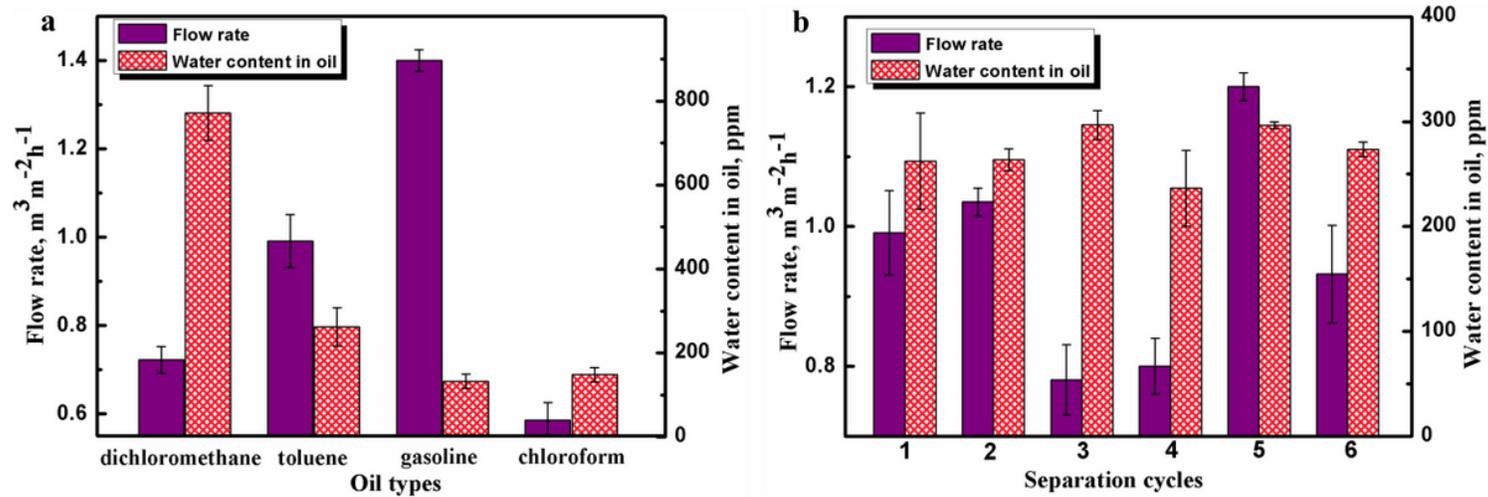


Figure 5

Oil-water separation application. (a) Separation efficiencies and flow rates with different oil-water mixtures. (b) Cycle stability of the separation device.